



Designation: D 6013 – 00

## Standard Test Method for Determination of Area Stability of Leather to Laundering<sup>1</sup>

This standard is issued under the fixed designation D 6013; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last approval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope

1.1 This test method<sup>2</sup> covers the determination of launderability of dyed leathers with or without a pigment finish. This test method does not apply to wet blue.

1.2 The values stated in inch-pound units are to be regarded as the standard. The values given in parentheses are for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

### 2. Referenced Documents

#### 2.1 ASTM Standards:

D 1610 Practice for Conditioning Leather and Leather Products for Testing<sup>3</sup>

### 3. Significance and Use

3.1 The procedure is primarily intended to evaluate the ability of a leather specimen to withstand fixed, and rather strenuous, laundering conditions. This test method is not intended as a recommended washing procedure, neither household nor commercial. The resulting area stability is determined.

### 4. Apparatus<sup>4</sup>

4.1 *Washing Machine*—A Launder-Ometer,<sup>5</sup> or an assembly of apparatus capable of similar test conditions (see Note). In

either machine, 1-pt (500-mL) specimen containers are held with their bases toward a horizontal shaft and 2 in. (50 mm) out from its center of rotation. Speed of rotation shall be 40 to 45 rpm. Provision shall be made for maintaining the initial temperature of the specimen containers throughout the test. Additional agitation shall be provided by ¼-in. (6.4-mm) stainless steel balls in the specimen containers. Apparatus is illustrated in Figs. 1-3.

NOTE 1—A motor-driven assembly, designed to hold 1-pt (500-mL) specimen containers so that they are relative to the axis of the motor shaft in the same way as in the Launder-Ometer, can be used.<sup>5</sup> The entire assembly, fitted with specimen containers, shall be turned at 40 to 45 rpm inside a simple boxlike container which is heated at 120°F (49°C) with thermostatic control. Thus, heat loss from the preheated contents of the specimen containers is held at a minimum during the 30-min washing periods. Such an apparatus is illustrated in Figs. 4 and 5.

4.2 *Stainless Steel Balls*, type 316, ¼ in. (6 mm) diameter.

4.3 *Steel or Glass Jar*, 1 pt (0.5 L), with washer and cap.

4.4 *Circulating-air Oven*, capable of maintaining the required temperature of  $120 \pm 2^\circ\text{F}$  ( $49 \pm 1^\circ\text{C}$ ).

4.5 *Blotting Paper*,<sup>6</sup> (laboratory) (see 7.2).

4.6 *Metal Die*, for cutting the specimen to the required dimensions.

4.7 *Soap Solution*,<sup>7</sup> prepared by dissolving 5 g of standard neutral chip soap in 1 L of distilled water (see 7.3).

### 5. Test Specimen

5.1 The specimen shall be a square of leather 2.0 by 2.0 in. (51 by 51 mm) cut from the sample unit of leather. Three specimens from each sample unit shall be tested.

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D31 on Leather and is the direct responsibility of Subcommittee D31.04 on Apparel and Upholstery. Current edition approved Sept. 10, 2000. Published October 2000. Originally published as D 6013 - 96. Last previous edition D 6013 - 96.

<sup>2</sup> This test method was developed from Federal Test Method Standard No. 311 Method 3041.1 in cooperation with the U.S. Army Natick Research Development and Engineering Center, Natick, MA, and the Defense Personnel Support Center Directorate of Clothing and Textiles, Philadelphia, PA.

<sup>3</sup> *Annual Book of ASTM Standards*, Vol 15.04.

<sup>4</sup> The leather washing apparatus drawing is available from ASTM Headquarters, 100 Barr Harbor Drive, W. Conshohocken, PA 19428-2959. Request Adjunct ADJD6013.

<sup>5</sup> The sole source of supply of the apparatus known to the committee at this time is Atlas Electric Devices Co., 4114 N. Ravenswood Ave., Chicago, IL 60613. If you are aware of alternative suppliers, please provide this information to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend.

<sup>6</sup> The sole source of supply of the apparatus known to the committee at this time is Standard Paper Manufacturing Co., P.O. Box 1554, Richmond, VA 23212. If you are aware of alternative suppliers, please provide this information to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend.

<sup>7</sup> The sole source of supply of the apparatus known to the committee at this time is AATCC National Headquarters, P.O. Box 12215, Research Triangle Park, NC 22709. If you are aware of alternative suppliers, please provide this information to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend.

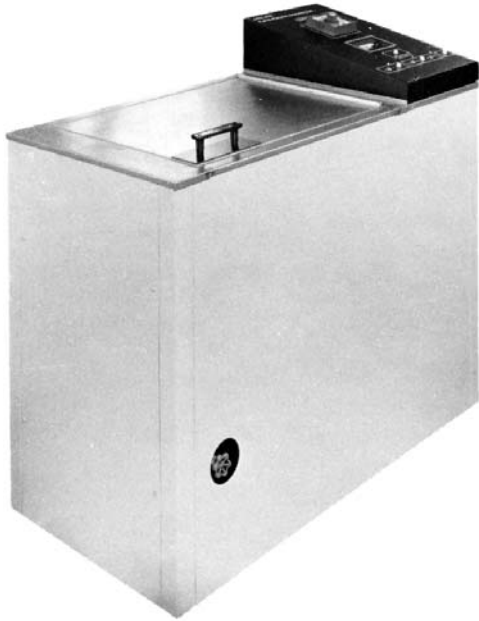


FIG. 1 Launder-Ometer



FIG. 2 Launder-Ometer Stainless Steel Specimen Containers

**6. Procedure**

6.1 Unless otherwise specified, perform this test in accordance with standard atmospheric conditions (see Practice D 1610). Weigh the conditioned samples to the nearest 0.1 g.

6.2 Make two measurements of each dimension of the specimen and average them. Make the measurements 13 mm from the edges of the specimen. Indelibly mark the grain surface of the specimen to indicate the points of measurement. Use the average measurement to determine the original area of the specimen, and record this area as A. (The known dimensions of the die may be used instead of actually measuring the specimen. When this option is taken, the specimen shall still be indelibly marked at the points of measurement indicated above.)

6.3 Add three specimens and twenty stainless steel balls to a 1-pt jar together with 150 mL of a soap solution that has been preheated to 120 ± 2°F (49 ± 1°C).

6.4 Seal the jars and clamp them into the rotor of a washing machine. Run the apparatus at 40 to 45 rpm for 30 min at 120 ± 2°F (49 ± 1°C).

6.5 Remove the jars and pour the soap solution from the jars through a sieve to avoid losing the steel balls and specimens. Then place the specimens flesh side down on a pad consisting of two 10 by 10-in. (25.4 by 25.4-cm) blotting papers, and cover them with a pad of two additional blotting papers of the same type. Place a non-absorbent flat rigid plate large enough to cover the blotters on the cover blotter. If necessary, place a weight on the plate so as to subject the specimens to a 10 g/cm<sup>2</sup> load for 5 min. At the end of this period, remove the load and transfer the specimens to the pint container previously filled with water preheated to 120 ± 2°F (49 ± 1°C). The volume of water in millilitres shall be approximately 20 times the initial weight of the conditioned specimens in grams.

6.6 Seal, clamp, and rotate jars for 30 min in washing machine. Remove the water and squeeze the specimens by hand and spread next to each other on a flat noncorrosive rigid plate. No specimen shall be closer than ½ in. (12.7 mm) to the others.

6.7 Place the plate with specimens in a pre-heated circulating air oven for 30 min at 120 ± 2°F (49 ± 1°C). At the end of 30 min, return the dried specimens to the pint jars, 3 specimens per jar, together with the steel balls and 100 mL of the soap solution preheated to 120 ± 2°F (49 ± 1°C). Repeat the entire procedure again. After the specimens have been removed from the oven the second time, return them to the pint jars, 3 specimens per jar, together with the steel balls and 50 mL of the soap solution preheated to 120 ± 2°F (49 ± 1°C). Repeat the entire procedure a third time, except do not squeeze the specimens by hand or dried in the oven, after being tumbled in the pre-heated water. Instead, the specimens shall be placed grain side up on a flat noncorrosive rigid surface and allowed to dry under standard conditions for 48 h.

6.8 Take two measurements in one dimension, average them, and record the average as B. Take two measurements in the other dimension, average them, and record the average as C. The measurements will be made at the indelibly marked points of measurement described in 6.2. The averages shall be calculated to the nearest 0.02 in. (0.1 mm). Calculate the average area change as follows:

$$\text{Percent area change} = \frac{A - (B \times C) \times 100}{A} \tag{1}$$

where:

- A = original area of the specimen (can be calculated from the known dimensions of the die),
- B = average of two measurements in one dimension of the specimen, and
- C = average of two measurements in the other dimension of test specimen.

6.8.1 In the event of increase in area of the test specimen, the calculations shall be made as follows:

$$\text{Percent area change} = \frac{(B \times C) - A \times 100}{A} \tag{2}$$

**7. Report**

7.1 Report area change to the nearest 0.1 %.