



Designation: F2731 – 18

Standard Test Method for Measuring the Transmitted and Stored Energy of Firefighter Protective Clothing Systems¹

This standard is issued under the fixed designation F2731; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method uses one of two procedures to measure: (1) heat energy, which can be directly transmitted through the multilayer structure without compressive force, that can result in predicted burn injury, or (2) heat energy directly transmitted through the multilayer structure, followed by applying a compressive force, which rapidly releases stored heat energy in the multilayer structure that can result in a predicted burn injury.

1.1.1 This test method is applicable only to protective clothing systems that are suitable for exposure to heat and flames.

1.1.2 Flame resistance of the material system shall be determined prior to testing according to the applicable performance or specification standard, or both, for the material's end use.

1.2 This test method establishes procedures for moisture preconditioning of firefighter protective clothing material systems.

1.3 The second-degree burn injury prediction used in this standard is based on a limited number of experiments on forearms of human subjects.

1.3.1 The length of exposures needed to generate a second-degree burn injury in this test method exceeds the exposure times found in the limited number of experiments on human forearms.

1.4 The values stated in SI units are to be regarded as the standard. The values given in parentheses are mathematical conversions to English units or other units commonly used for thermal testing.

1.5 *This standard is used to measure and describe the properties of materials, products, or assemblies in response to radiant heat under controlled laboratory conditions but does*

not by itself incorporate all factors required for fire hazard or fire risk assessment of the materials, products, or assemblies under actual fire conditions.

1.6 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use. Specific precautionary information is found in Section 7.*

1.7 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 ASTM Standards:²

[D123 Terminology Relating to Textiles](#)

[D1777 Test Method for Thickness of Textile Materials](#)

[D3776/D3776M Test Methods for Mass Per Unit Area \(Weight\) of Fabric](#)

[E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method](#)

[F1494 Terminology Relating to Protective Clothing](#)

[F1930–17 Test Method for Evaluation of Flame-Resistant Clothing for Protection Against Fire Simulations Using an Instrumented Manikin](#)

2.2 AATCC Test Methods:³

[AATCC 70 Test Method for Water Repellency: Tumble Jar Dynamic Absorption Test](#)

[AATCC 135 Dimensional Changes in Automatic Home Laundering of Durable Press Woven or Knit Fabrics](#)

¹ This test method is under the jurisdiction of ASTM Committee F23 on Personal Protective Clothing and Equipment and is the direct responsibility of Subcommittee F23.80 on Flame and Thermal.

Current edition approved June 1, 2018. Published June 2018. Originally approved in 2010. Last previous edition approved in 2011 as F2731 – 11. DOI: 10.1520/F2731-18.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Available from American Association of Textile Chemists and Colorists (AATCC), P.O. Box 12215, Research Triangle Park, NC 27709, <http://www.aatcc.org>.

2.3 *NFPA Standard*:⁴

NFPA 1971 Standard on Protective Ensembles for Structural Fire Fighting and Proximity Fire Fighting

3. Terminology

3.1 *Definitions*:

3.1.1 *break-open, n*—in testing thermal protective materials, a material response evidenced by the formation of a hole in the test specimen.

3.1.1.1 *Discussion*—The specimen is considered to exhibit break-open when a hole is produced as a result of the thermal exposure that is at least 3.2 cm² (0.25 in.²) in area or at least 2.5 cm (1.0 in.) in any dimension. Single threads across the opening or hole do not reduce the size of the hole for purposes of this test method.

3.1.2 *charring, n*—the formation a carbonaceous residue as the result of pyrolysis or incomplete combustion.

3.1.3 *dripping, n*—a material response evidenced by flowing of the polymer.

3.1.4 *embrittlement, n*—the formation of brittle residue as a result of pyrolysis or incomplete combustion.

3.1.5 *heat flux, n*—the thermal intensity indicated by the amount of energy transmitted per unit area and per unit time; kW/m² (cal/cm²-s).

3.1.6 *ignition, n*—the initiation of combustion.

3.1.7 *melting, n*—in testing thermal protective materials, a response evidenced by softening of the polymer.

3.1.8 *response to heat exposure, n*—in testing for the transmitted and stored energy of thermal protective materials, the observable response of the textile to the energy exposure, as indicated by break-open, melting, dripping, charring, embrittlement, shrinkage, sticking, and ignition.

3.1.8.1 *Discussion*—For the purposes of this test method, response to heat exposure also includes any non-textile reinforcement material used as part of the protective clothing material system that is tested.

3.1.9 *second-degree burn injury, n*—reversible burn damage in the epidermis and upper layers of the dermis, resulting in blistering, severe pain, reddening, and swelling.

3.1.10 *shrinkage, n*—a decrease in one or more dimensions of an object or material.

3.1.11 *sticking, n*—a response evidenced by softening and adherence of the material to other material.

3.1.11.1 *Discussion*—For the purpose of this test method, the observation of sticking applies to any material layer in the protective clothing material system.

3.1.12 *stored energy, n*—in testing thermal protective materials, thermal energy that remains in a fabric/composite after the heating source is removed.

3.1.12.1 *Discussion*—The stored energy measured by this standard only accounts for the energy released to the sensor after compressing. Stored energy is also lost to the compressor block and the surrounding environment.

3.1.13 *thermal protective clothing system, n*—any combination of materials which, when used as a composite, can limit the rate of heat transfer to or from the wearer of the clothing.

3.1.13.1 *Discussion*—The rate at which this heat transfer occurs can vary depending on the materials.

3.2 For definitions of other terms used in this test method, refer to Terminologies **D123** and **F1494**.

4. Summary of Test Method

4.1 A vertically positioned test specimen, representative of the lay-up in firefighter protective clothing, is exposed to a relatively low level of radiant heat flux at 8.5 ± 0.5 kW/m² (0.2 ± 0.012 cal/cm²-s) for a fixed period of time.

4.2 During the time of radiant heat exposure, a data collection sensor, positioned 6.4 ± 0.1 mm (0.25 ± 0.004 in.) behind and parallel to the innermost surface of the test specimen, measures the heat energy transmitted through the test specimen.

4.3 Using the same test apparatus, the test specimen is permitted to be compressed against the data collection sensor at a pressure of 13.8 ± 0.7 kPa (2.0 psi ± 0.1 psi) for a fixed period of time.

4.3.1 This compressive force is intended to simulate a firefighter leaning against a wall, squatting, or sitting down in a manner that expels the insulating air layers from the composite while drawing the clothing materials taut against the skin, and then causes the transfer of the heat energy from the garment layers to the skin.

4.4 During the time of compression against the data collection sensor, the data collection sensor continues to measure the heat energy transferred from the test specimen for a fixed duration of time.

4.5 The total energy transmitted and stored by the test specimen is used to predict whether a second-degree burn injury can be predicted. If a second-degree burn injury is predicted, the time to a second-degree burn injury is reported.

4.6 This method uses two distinct procedures.

4.6.1 Procedure A uses a low-level radiant heat exposure, without compression, to predict the time to second-degree burn.

4.6.2 Procedure B uses a low-level radiant heat exposure and a 60-s compression period to predict the time to second-degree burn.

4.6.3 The report indicates the predicted time to second-degree burn.

4.6.3.1 If a second-degree burn injury is not predicted, the result is indicated as “no predicted burn.”

4.7 Test Method **F1930-17** contains a general description of human burn injury, its calculation, and historical notes.

5. Significance and Use

5.1 Firefighters are routinely exposed to radiant heat in the course of their fireground activities. In some cases, firefighters have reported burn injuries under clothing where there is no evidence of damage to the exterior or interior layers of the

⁴ Available from National Fire Protection Association (NFPA), 1 Batterymarch Park, Quincy, MA 02169-7471, <http://www.nfpa.org>.

firefighter protective clothing.⁵ Low levels of transmitted radiant energy alone, or a combination of the transmitted radiant energy and stored energy released through compression, can be sufficient to cause these types of injuries. This test method was designed to measure both the transmitted and stored energy in firefighter protective clothing material systems under a specific set of laboratory exposure conditions.

5.2 The intensity of radiant heat exposure used in this test method was chosen to be an approximate midpoint representative of ordinary fireground conditions as defined for structural firefighting (1, 2).⁶ The specific radiant heat exposure was selected at $8.5 \pm 0.5 \text{ kW/m}^2$ ($0.20 \pm 0.012 \text{ cal/cm}^2\text{-s}$), since this level of radiant heat can be maintained by the test equipment and produces little or no damage to most NFPA 1971-compliant protective clothing systems.

5.2.1 Utech (2) defined ordinary fireground conditions as having air temperatures ranging from 60 to 300 °C and having heat flux values ranging from 2.1 to 21.0 kW/m² (0.05 to 0.5 cal/cm²-s).

5.3 Protective clothing systems include the materials used in the composite structure. These include the outer shell, moisture barrier, and thermal barrier. It is possible that they will also include other materials used on firefighter protective clothing such as reinforcement layers, seams, pockets, flaps, hook and loop, straps, or reflective trim.

5.4 The transmission and storage of heat energy in firefighter protective clothing is affected by several factors. These include the effects of wear and use conditions of the protective clothing system. In this test method, conditioning procedures are provided for the laundering of composite samples prior to testing, and also composite sample moisture preconditioning. The amount of moisture added during preconditioning typically falls into a worst-case amount in terms of predicted heat transfer, as suggested by Barker (3).

5.5 Two different procedures for conducting the test are provided in this test method. Procedure A measures only the transmitted energy that passes through the composite, without compression, during the exposure time. In this approach, the length of the radiant exposure is likely to be sufficient in the prediction of a second-degree burn injury. Procedure B involves using a fixed radiant heat exposure time to determine if a second-degree burn injury will or will not be predicted. If a second-degree burn injury is predicted, the time to a second-degree burn injury is reported. If a second-degree burn injury is not predicted, the result is indicated as “no predicted burn.” This procedure includes recommended fixed radiant exposure times.

6. Apparatus and Materials

6.1 General Arrangement—The transmitted and stored energy testing apparatus shall consist of a specimen holder, sensor assembly, transfer tray, data collection sensor, compressor assembly, heating source, and a data acquisition/controls/burn damage analysis system. An overhead view of these components, minus the data acquisition/controls/burn damage analysis system, is illustrated in Fig. 1.

6.2 Specimen Holder—The specimen holder shall consist of upper and lower mounting plates made of stainless steel. Each plate shall be 170 by 170 ± 1 mm (6.6 by 6.6 ± 0.04 in.) and the thickness shall be 6.4 ± 0.1 mm (0.25 ± 0.004 in.), with a centered 100 by 100 ± 1-mm (3.9 by 3.9 ± 0.04-in.) hole. The lower plate shall have an attached handle that is at least 75 mm (3 in.) in length. The lower specimen mounting plate shall have a minimum of two alignment posts attached perpendicularly to the plane of the plate. The upper sample mounting plate shall have corresponding holes on each side so that the upper specimen mounting plate fits over the lower specimen mounting plate. The specimen holder components are shown in Fig. 2.

6.2.1 The handle of the sample holder shall be made of or surrounded by a material with a low thermal conductivity.

6.2.2 The alignment posts shall be positioned such that they do not interfere with the test specimen.

6.3 Sensor Assembly—The sensor assembly shall be composed of a water-cooled plate and a sensor holder.

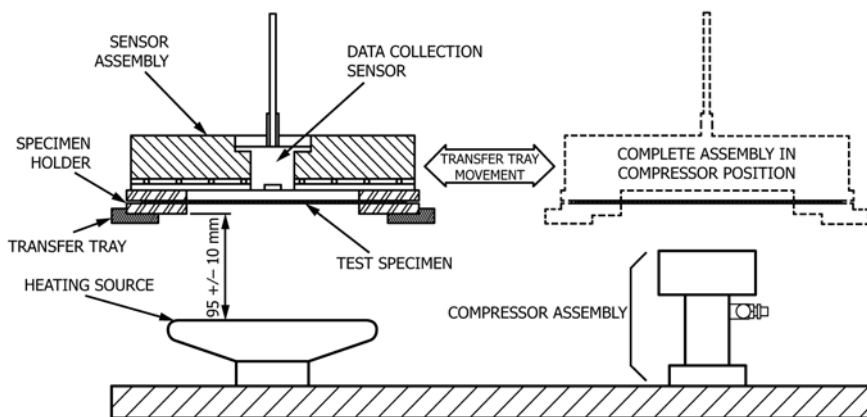


FIG. 1 Overhead View of Major Apparatus Components

⁵ “Development of a Test Method for Measuring Transmitted Heat and Stored Thermal Energy in Firefighter Turnouts,” final report presented to National Institute for Occupational Safety and Health (NIOSH) National Personal Protective Technology Laboratory (NPPTL) under Contract No. 200-2005-12411, April 29, 2008.

⁶ The boldface numbers in parentheses refer to a list of references at the end of this standard.

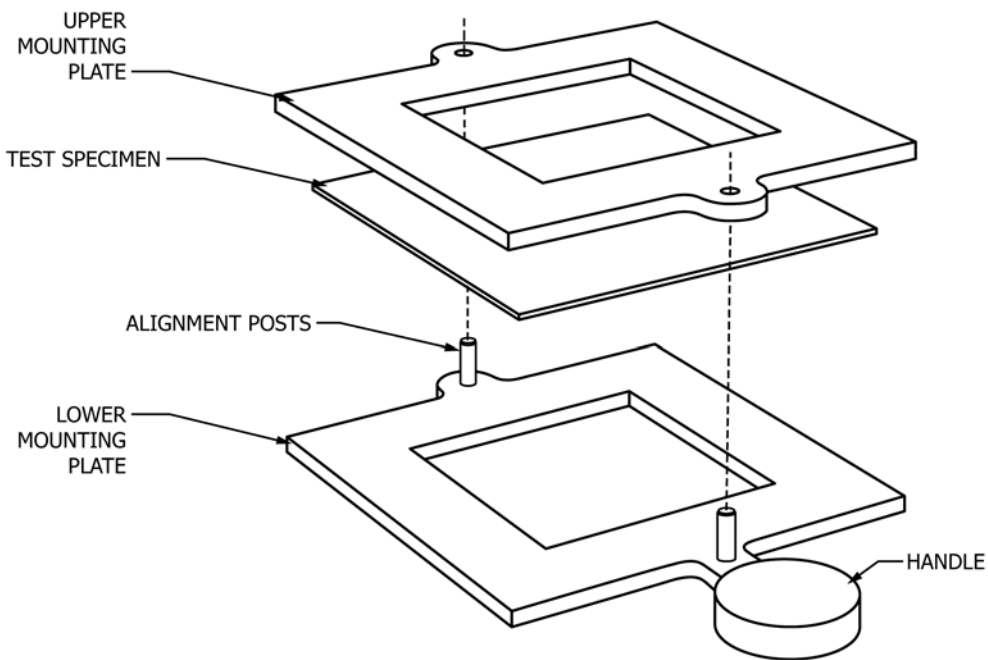


FIG. 2 Specimen Holder

6.3.1 Construct the water-cooled plate from a copper sheet with a thickness of no less than 3.1 mm and no more than 6.6 mm, with a water cooling system applied to the back side. The copper plate shall be machined at its center line to accept the data collection sensor with a tolerance of +0.3 mm. The four corners of the plate shall be drilled to accept a countersunk screw.

6.3.1.1 Construct the water-cooled plate assembly such that water flows through it and provides a uniform temperature across the surface of the copper plate.

6.3.1.2 Water shall flow through the copper tubing at a rate of no less than 100 mL/min, and the water shall have a temperature of 32.5 ± 1 °C.

NOTE 1—The 32.5 °C temperature was set based on the average surface temperature of the forearms of volunteers as measured by Pennes (4).

6.3.2 The exposed surface of the water-cooled plate shall be painted with a thin coating of flat, black, high-temperature spray paint with an emissivity of 0.9 or greater. The painted water-cooled plate shall be dried before use and shall present a uniformly applied coating (no visual thick spots or surface irregularities).

6.3.2.1 For information about paints that can meet the emissivity requirement, please refer to 6.5.2.

6.3.3 The sensor holder shall be a 166 ± 2 -mm (6.54 ± 0.8 -in.) aluminum block. The thickness of the block shall be no less than 25.4 mm (1 in.). The four corners of the block shall be drilled and tapped such that they align with the holes found in the water-cooled plate. After the sensor holder and water-cooled plate are attached with the flathead countersunk screws, the sensor holder shall be machined at its

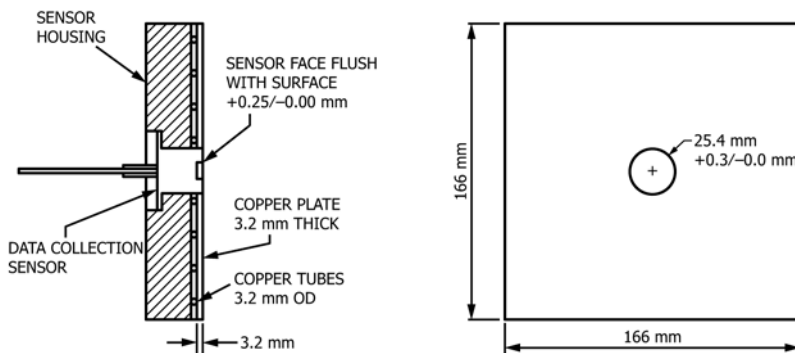


FIG. 3 Specification for Sensor Assembly