



Designation: **C1273—15 C1273 – 18**

Standard Test Method for Tensile Strength of Monolithic Advanced Ceramics at Ambient Temperatures¹

This standard is issued under the fixed designation C1273; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the determination of tensile strength under uniaxial loading of monolithic advanced ceramics at ambient temperatures. This test method addresses, but is not restricted to, various suggested test specimen geometries as listed in the ~~appendix~~ appendixes. In addition, test specimen fabrication methods, testing modes (force, displacement, or strain control), testing rates (force rate, stress rate, displacement rate, or strain rate), allowable bending, and data collection and reporting procedures are addressed. Note that tensile strength as used in this test method refers to the tensile strength obtained under uniaxial loading.

1.2 This test method applies primarily to advanced ceramics that macroscopically exhibit isotropic, homogeneous, continuous behavior. While this test method applies primarily to monolithic advanced ceramics, certain whisker- or particle-reinforced composite ceramics as well as certain discontinuous fiber-reinforced composite ceramics may also meet these macroscopic behavior assumptions. Generally, continuous fiber ceramic composites (CFCCs) do not macroscopically exhibit isotropic, homogeneous, continuous behavior and application of this practice to these materials is not recommended.

1.3 Values expressed in this test method are in accordance with the International System of Units (SI) and ~~SH0-02-IEEE/ASTM~~ **SI 10**.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and ~~health~~ environmental practices and determine the applicability of regulatory limitations prior to use.* Specific precautionary statements are given in Section 7.

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 ASTM Standards:²

[C1145 Terminology of Advanced Ceramics](#)

[C1161 Test Method for Flexural Strength of Advanced Ceramics at Ambient Temperature](#)

[C1239 Practice for Reporting Uniaxial Strength Data and Estimating Weibull Distribution Parameters for Advanced Ceramics](#)

[C1322 Practice for Fractography and Characterization of Fracture Origins in Advanced Ceramics](#)

[D3379 Test Method for Tensile Strength and Young's Modulus for High-Modulus Single-Filament Materials](#)

[E4 Practices for Force Verification of Testing Machines](#)

[E6 Terminology Relating to Methods of Mechanical Testing](#)

[E83 Practice for Verification and Classification of Extensometer Systems](#)

[E337 Test Method for Measuring Humidity with a Psychrometer \(the Measurement of Wet- and Dry-Bulb Temperatures\)](#)

[E1012 Practice for Verification of Testing Frame and Specimen Alignment Under Tensile and Compressive Axial Force Application](#)

[SH0-02-IEEE/ASTM SI 10 American National Standard for Use of the International System of Units \(SI\): The Modern Metric System Metric Practice](#)

¹ This test method is under the jurisdiction of ASTM Committee C28 on Advanced Ceramics and is the direct responsibility of Subcommittee C28.01 on Mechanical Properties and Performance.

Current edition approved July 1, 2015/July 1, 2018. Published September 2015/July 2018. Originally approved in 1994. Last previous edition approved in 2010/2015 as C1273 – 05 (2010):C1273 – 15. DOI: 10.1520/C1273-15.10.1520/C1273-18.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

3. Terminology

3.1 Definitions:

3.1.1 The definitions of terms relating to tensile testing appearing in Terminology E6 apply to the terms used in this test method on tensile testing. The definitions of terms relating to advanced ceramics testing appearing in Terminology C1145 apply to the terms used in this test method. Pertinent definitions as listed in Practice C1239, Practice E1012, Terminology C1145, and Terminology E6 are shown in the following with the appropriate source given in parentheses. Additional terms used in conjunction with this test method are defined in the following:

3.1.2 *advanced ceramic*—a highly engineered, ~~high performance~~ high-performance, predominately nonmetallic, inorganic, ceramic material having specific functional attributes. **C1145**

3.1.3 *axial strain*—~~strain~~ $[LL^{-1}]$, n —the average of longitudinal strains measured at the surface on opposite sides of the longitudinal axis of symmetry of the specimen by two ~~strain-sensing~~ strain sensing devices located at the mid length of the reduced section. **E1012**

3.1.4 *bending strain*—~~strain~~ $[LL^{-1}]$, n —the difference between the strain at the surface and the axial strain. In general, the bending strain varies from point to point around and along the reduced section of the specimen. **E1012**

3.1.5 *breaking force*—~~force~~ $[F]$, n —the force at which fracture occurs. **E6**

3.1.6 *fractography*—means and methods for characterizing a fractured specimen or component. **C1145**

3.1.7 *fracture origin*—the source from which brittle fracture commences. **C1145**

3.1.8 *percent bending*—the bending strain times 100 divided by the axial strain. **E1012**

3.1.9 *slow crack growth (SCG)*—subcritical crack growth (extension) which may result from, but is not restricted to, such mechanisms as ~~environmentally-assisted~~ environmentally assisted stress corrosion or diffusive crack growth. **C1145**

3.1.10 *tensile strength*,—~~strength~~, $S_u [FL^{-2}]$, n —~~the~~ the maximum tensile stress which a material is capable of sustaining. Tensile strength is calculated from the maximum force during a tension test carried to rupture and the original cross-sectional area of the specimen. **E6**

4. Significance and Use

4.1 This test method may be used for material development, material comparison, quality assurance, characterization, and design data generation.

4.2 ~~High strength~~, High-strength, monolithic advanced ceramic materials generally characterized by small grain sizes (<50 μm) and bulk densities near the theoretical density are candidates for load-bearing structural applications requiring high degrees of wear and corrosion ~~resistance~~, resistance and high temperature strength. Although flexural test methods are commonly used to evaluate strength of advanced ceramics, the ~~non-uniform~~ nonuniform stress distribution of the flexure test specimen limits the volume of material subjected to the maximum applied stress at fracture. ~~Uniaxially-loaded~~ Uniaxially loaded tensile strength tests provide information on strength-limiting flaws from a greater volume of uniformly stressed material.

4.3 Although the volume or surface area of material subjected to a uniform tensile stress for a single ~~uniaxially-loaded~~ uniaxially loaded tensile test may be several times that of a single flexure test specimen, the need to test a statistically significant number of tensile test specimens is not obviated. Therefore, because of the probabilistic strength distributions of brittle materials such as advanced ceramics, a sufficient number of test specimens at each testing condition is required for statistical analysis and eventual design, with guidelines for sufficient numbers provided in this test method. Note that size-scaling effects as discussed in Practice C1239 will affect the strength values. Therefore, strengths obtained using different recommended tensile test specimens with different volumes or surface areas of material in the gage sections will be different due to these size differences. Resulting strength values can be scaled to an effective volume or surface area of unity as discussed in Practice C1239.

4.4 Tensile tests provide information on the strength and deformation of materials under uniaxial tensile stresses. Uniform stress states are required to effectively evaluate any ~~non-linear~~ nonlinear stress-strain behavior which may develop as the result of testing mode, testing rate, processing or alloying effects, or environmental influences. These effects may be consequences of stress corrosion or subcritical (slow) crack growth, which can be minimized by testing at appropriately rapid rates as outlined in this test method.

4.5 The results of tensile tests of test specimens fabricated to standardized dimensions from a particular material or selected portions, or both, of a part may not totally represent the strength and deformation properties of the entire, full-size end product or its in-service behavior in different environments.

4.6 For quality control purposes, results derived from standardized tensile test specimens can be considered to be indicative of the response of the material from which they were taken for given primary processing conditions and post-processing heat treatments.

4.7 The tensile strength of a ceramic material is dependent on both its inherent resistance to fracture and the presence of flaws. Analysis of fracture surfaces and fractography, though beyond the scope of this test method, is highly recommended for all purposes, especially for design data.

5. Interferences

5.1 Test environment (vacuum, inert gas, ambient air, etc.) etc.), including moisture content (for example, relative humidity) humidity), may have an influence on the measured tensile strength. In particular, the behavior of materials susceptible to slow crack growth fracture will be strongly influenced by test environment and testing rate. Testing to evaluate the maximum strength potential of a material should be conducted in inert environments or at sufficiently rapid testing rates, or both, so as to minimize slow crack growth effects. Conversely, testing can be conducted in environments and testing modes and rates representative of service conditions to evaluate material performance under use conditions. When testing is conducted in uncontrolled ambient air with the intent of evaluating maximum strength potential, relative humidity and temperature must be monitored and reported. Testing at humidity levels >65 % relative humidity (RH) is not recommended, and any deviations from this recommendation must be reported.

5.2 Surface preparation of test specimens can introduce fabrication flaws that may have pronounced effects on tensile strength. Machining damage introduced during test specimen preparation can be either a random interfering factor in the determination of ultimate strength of pristine material (that is, increase increased frequency of surface initiated fractures compared to volume initiated fractures), or an inherent part of the strength characteristics to be measured. Surface preparation can also lead to the introduction of residual stresses. Universal or standardized test methods of surface preparation do not exist. It should be understood that final machining steps may or may not negate machining damage introduced during the early coarse or intermediate machining. Thus, test specimen fabrication history may play an important role in the measured strength distributions and should be reported.

5.3 Bending in uniaxial tensile tests can cause or promote non-uniform nonuniform stress distributions with maximum stresses occurring at the test specimen surface leading to non-representative fractures originating at surfaces or near geometrical transitions. In addition, if strains or deformations are measured at surfaces where maximum or minimum stresses occur, bending may introduce over or under measurement of strains. Similarly, fracture from surface flaws may be accentuated or muted by the presence of the non-uniform nonuniform stresses caused by bending.

6. Apparatus

6.1 Testing Machines—Machines used for tensile testing shall conform to the requirements of Practices E4. The forces used in determining tensile strength shall be accurate to within ±1 % at any force within the selected force range of the testing machine as defined in Practices E4. A schematic showing pertinent features of the tensile testing apparatus is shown in Fig. 1.

6.2 Gripping Devices:

6.2.1 General—Various types of gripping devices may be used to transmit the measured force applied by the testing machine to the test specimens. The brittle nature of advanced ceramics requires a uniform interface between the grip components and the

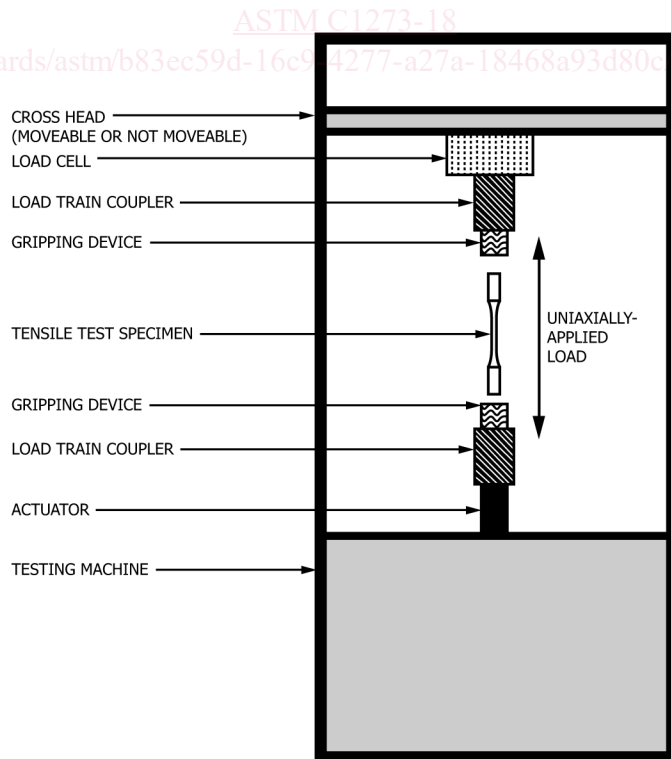


FIG. 1 Schematic Diagram of One Possible Apparatus for Conducting a Uniaxially-Loaded-Uniaxially Loaded Tensile Test