



Designation: ~~D5147/D5147M~~ – 14 D5147/D5147M – 18

## Standard Test Methods for Sampling and Testing Modified Bituminous Sheet Material<sup>1</sup>

This standard is issued under the fixed designation D5147/D5147M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reappraisal.

### 1. Scope

1.1 These test methods cover procedures for sampling and testing prefabricated, reinforced, polymer-modified bituminous sheet materials designed for single- or multiple-ply application in roofing and waterproofing membranes. These products may use various surfacing materials on one side.

1.2 These test methods cover a number of different products. Not all tests are required for every product. Only those called out in the Product Standard are required.

1.3 These test methods appear in the following order:

	Section
Sampling	4
Conditioning	5
Thickness	6
Load Strain Properties	7
Tear Strength	8
Moisture Content	9
Water Absorption	10
Dimensional Stability	11
Low-Temperature Flexibility	12
Heat Conditioning	13
Accelerated Weathering	14
Granule Embedment	15
Compound Stability	16
Coating Thickness	17
Low Temperature Unrolling	18
Precision and Bias	19

1.4 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.6 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

### 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

[D95 Test Method for Water in Petroleum Products and Bituminous Materials by Distillation](#)

[D146/D146M Test Methods for Sampling and Testing Bitumen-Saturated Felts and Woven Fabrics for Roofing and Waterproofing](#)

[D1204 Test Method for Linear Dimensional Changes of Nonrigid Thermoplastic Sheeting or Film at Elevated Temperature](#)

<sup>1</sup> These test methods are under the jurisdiction of ASTM Committee D08 on Roofing and Waterproofing and are the direct responsibility of Subcommittee D08.04 on Felts, Fabrics and Bituminous Sheet Materials.

Current edition approved Jan. 1, 2014; July 1, 2018. Published January 2014; August 2018. Originally approved in 1991. Last previous edition approved in 2014 as ~~D5147/D5147M – 14~~ D5147/D5147M – 14. DOI: ~~10.1520/D5147-D5147M-14~~ 10.1520/D5147\_D5147M-18.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.



D4073 Test Method for Tensile-Tear Strength of Bituminous Roofing Membranes

~~D4798~~D4798/D4798M Practice for Accelerated Weathering Test Conditions and Procedures for Bituminous Materials (Xenon-Arc Method)

~~D4977~~D4977/D4977M Test Method for Granule Adhesion to Mineral Surfaced Roofing by Abrasion

~~D5636~~D5636/D5636M Test Method for Low Temperature Unrolling of Felt or Sheet Roofing and Waterproofing Materials

~~D5869~~D5869/D5869M Practice for Dark Oven Heat Exposure of Roofing and Waterproofing Materials

~~D6162~~D6162/D6162M Specification for Styrene Butadiene Styrene (SBS) Modified Bituminous Sheet Materials Using a Combination of Polyester and Glass Fiber Reinforcements

~~D6163~~D6163/D6163M Specification for Styrene Butadiene Styrene (SBS) Modified Bituminous Sheet Materials Using Glass Fiber Reinforcements

~~D6164~~D6164/D6164M Specification for Styrene Butadiene Styrene (SBS) Modified Bituminous Sheet Materials Using Polyester Reinforcements

~~D6222~~D6222/D6222M Specification for Atactic Polypropylene (APP) Modified Bituminous Sheet Materials Using Polyester Reinforcements

~~D6223~~D6223/D6223M Specification for Atactic Polypropylene (APP) Modified Bituminous Sheet Materials Using a Combination of Polyester and Glass Fiber Reinforcements

~~D6298~~D6298/D6298M Specification for Fiberglass Reinforced Styrene-Butadiene-Styrene (SBS) Modified Bituminous Sheets with a Factory Applied Metal Surface

~~D6509~~D6509/D6509M Specification for Atactic Polypropylene (APP) Modified Bituminous Base Sheet Materials Using Glass Fiber Reinforcement

E177 Practice for Use of the Terms Precision and Bias in ASTM Test Methods

E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method

### 3. Significance and Use

3.1 These test methods are used for sampling and testing modified bitumen sheet materials. Property requirements, determined by these test methods, are found in the following product standards: Specifications ~~D6162~~D6162/D6162M, ~~D6163~~D6163/D6163M, ~~D6164~~D6164/D6164M, ~~D6222~~D6222/D6222M, ~~D6223~~D6223/D6223M, ~~D6298~~D6298/D6298M, and ~~D6509~~D6509/D6509M.

### 4. Sampling

4.1 From each shipment or fraction thereof, select at random a number of rolls equal to one half the cube root of the total number of rolls in the lot. If the calculated number is fractional, express it as the next highest whole number. For convenience, a table showing the number of rolls to be selected from the lots of various sizes is given in Test Method ~~D146~~D146/D146M. When mutually agreed upon by the concerned parties, other sampling frequencies may be used and reported within the framework of these procedures. The minimum sample shall consist of five rolls. The rolls so selected constitute the representative sample used for all subsequent observations and tests pertaining to the lot of material being examined.

### 5. Conditioning

5.1 Unless otherwise specified, condition test specimens for a minimum of 4 h at  $23 \pm 2^\circ\text{C}$  [ $73.4 \pm 3.6^\circ\text{F}$ ] and  $50 \pm 5\%$  relative humidity before testing.

### 6. Thickness

6.1 The thickness measuring device shall be a micrometer of the dial or digital-electronic type capable of measuring dimensions to an accuracy of 0.1 mm [0.004 in.]. The micrometer shall be equipped with a flat, circular presser foot with a diameter greater or equal to 9.5 mm [0.375 in.] and less than 32 mm [1.25 in.]. During operation, contact between the presser foot and the specimen shall be maintained either by a spring inside the micrometer or by the weight of the presser foot and attached parts.

6.2 One specimen shall be obtained from each of the rolls selected in accordance with the Sampling section of these test methods. Each specimen shall be at least 700 mm [27½ in.] in length by the manufactured width of the roll. Five measurements of sheet thickness and five measurements of selvage thickness shall be taken on each specimen. All measurements shall be taken in a manner that requires the presser foot to contact the side of the sheet that is intended to be exposed when applied in accordance with the manufacturer's instructions.

NOTE 1—When measuring products with particulate surfaces, wiping particles from the presser foot between measurements is recommended to prevent buildup of particles that may result in inaccurate measurements.

6.2.1 Take five measurements of the sheet thickness along a line parallel to cross-machine direction. Two of the five measurements shall be taken  $150 \pm 15$  mm [ $6 \pm 0.5$  in.] from each edge of the specimen. The remaining three measurements shall be taken at three points approximately equally spaced ( $\pm 15$  mm [0.5 in.]) between these two points. Refer to Fig. 1 for an illustration of the sheet thickness measurement locations.

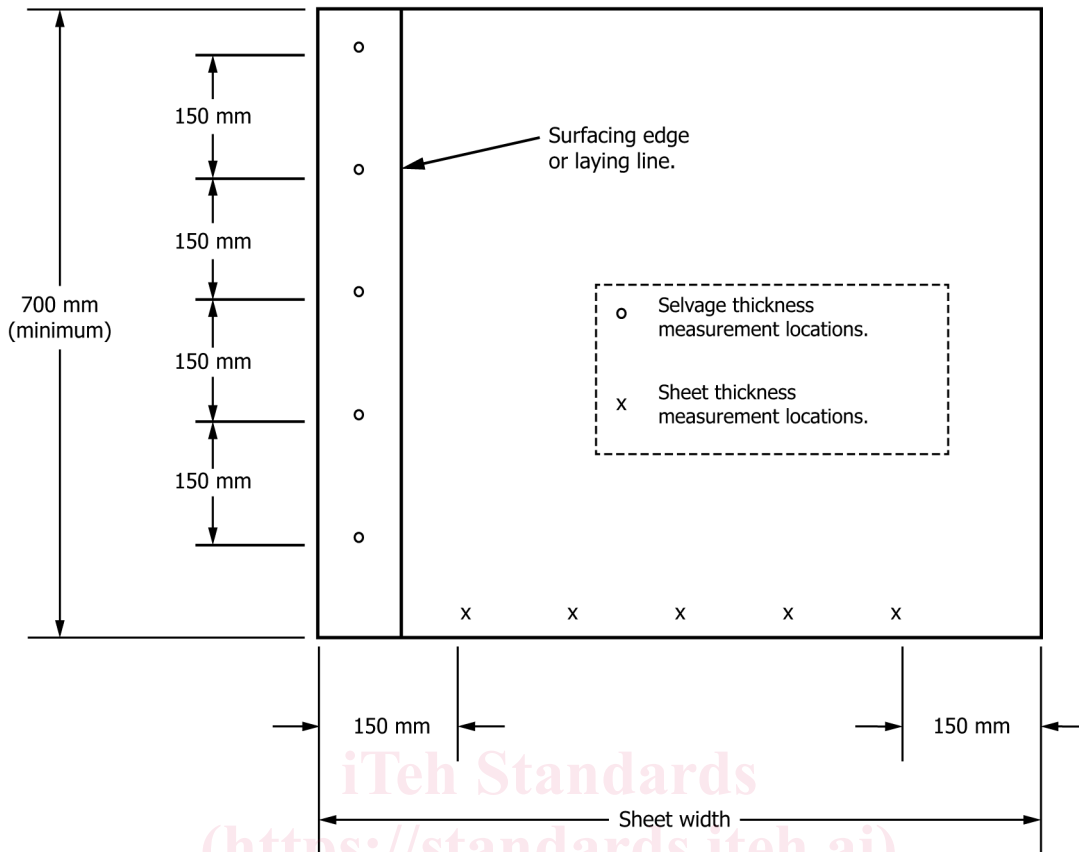


FIG. 1 Location of Thickness Measurements

## ASTM D5147/D5147M-18

6.2.2 Take five measurements of the selvage thickness along a line parallel to machine direction. The measurements are to be taken midway between the surfacing edge and the sheet edge or, in the case of smooth products, midway between the laying line and the sheet edge, and spaced  $150 \pm 15$  mm [ $6 \pm 0.5$  in.] apart. Refer to Fig. 1 for an illustration of the selvage thickness measurement locations.

6.3 For each specimen, report the individual point measurements, mean, and standard deviation for both the sheet thickness and selvage thickness measurements.

6.4 Calculate the mean of the specimen sheet thickness means and report this value as sample sheet thickness. Calculate the mean of the specimen selvage thickness means and report this value as sample selvage thickness. Unless otherwise required by the standard product specification that references these test methods, sample sheet thickness and sample selvage thickness are the values used for comparison with the product specification requirements.

#### 6.5 Precision and Bias:

6.5.1 *Interlaboratory Test Program*—Interlaboratory studies were run in which randomly drawn test specimens of three materials (sand-surfaced SBS-modified base sheet, fiberglass-reinforced SBS-modified cap sheet, and polyester-reinforced APP-modified cap sheet) were tested for sample sheet thickness and sample selvage thickness in each of eleven laboratories. Each laboratory tested two sets of five specimens of each material. Practice E691 was followed for the experimental design and analysis of the data. Details of the experiment are available in ASTM Research Reports RR:D08-1010 and RR:D08-1011.<sup>3,4</sup>

6.5.2 *Test Result*—The precision information given below for sheet thickness and selvage thickness in the units of measurement (millimetres) is for the comparison of two test results, each of which is the average of five test determinations.

#### 6.5.3 Precision:

<sup>3</sup> Supporting data have been filed at ASTM International Headquarters and may be obtained by requesting Research Report RR:D08-1010.

<sup>4</sup> Supporting data have been filed at ASTM International Headquarters and may be obtained by requesting Research Report RR:D08-1011.

Test range	Selvage Thickness	Sheet Thickness
	1.952 to 2.706 mm	1.959 to 3.824 mm
r, 95 % repeatability limit (within a laboratory)	0.088 mm (0.040 to 0.157 mm)	0.048 mm (0.039 to 0.054 mm)
R, 95 % reproducibility limit (between laboratories)	0.281 mm (0.148 to 0.366 mm)	0.252 mm (0.239 to 0.277 mm)
<u>R, 95 % reproducibility limit (between laboratories)</u>	<u>0.281 mm (0.148 to 0.366 mm)</u>	<u>0.252 mm (0.239 to 0.277 mm)</u>

The above terms (repeatability limit and reproducibility limit) are used as specified in Practice E177. The respective standard deviations among test results may be obtained by dividing the above limit values by 2.8.

6.5.4 *Bias*—Since there is no accepted reference material suitable for determining the bias for the procedure in this test method for measuring sheet thickness and selvage thickness, no statement on bias is being made.

### 7. Load Strain Properties

7.1 This test method covers the determination of the load strain (tensile elongation and strain energy) properties of polymer-modified bituminous sheets.

7.1.1 *Specimens*—Prepare five specimens from each sample roll in both the longitudinal and transverse directions for each temperature to be tested. Specimens shall be 25 mm [1.0 in.] wide by a minimum of 150 mm [6.0 in.] long for sheet materials having an ultimate elongation of 75 % or less at  $-18^{\circ}\text{C}$  [ $0^{\circ}\text{F}$ ]. Specimens shall be 12.5 mm [0.5 in.] wide by a minimum of 100 mm [4.0 in.] long for materials having an ultimate elongation of greater than 75 % at  $-18^{\circ}\text{C}$  [ $0^{\circ}\text{F}$ ].

#### 7.1.2 Procedure:

7.1.2.1 Condition each specimen at least 2 h at the selected test temperature. If conditioning is done outside the machine clamps, allow the specimen to equilibrate at the testing temperature for at least 15 min before the testing force is applied.

7.1.2.2 Test specimens at both  $23 \pm 2^{\circ}\text{C}$  [ $73.4 \pm 3.6^{\circ}\text{F}$ ] [ $4^{\circ}\text{F}$ ] and  $-18 \pm 3^{\circ}\text{C}$  [ $0 \pm 3.6^{\circ}\text{F}$ ] [ $4^{\circ}\text{F}$ ].

7.1.2.3 Use a constant rate of elongation (CRE) tension testing machine, preferably with automatic load and strain recording equipment, and clamps that permit a uniform clamping pressure on the specimen without slipping. The initial clamp separation shall be  $75 \pm 2$  mm [ $3.0 \pm 0.1$  in.] for sheet materials having an ultimate elongation of 75 % or less at  $-18^{\circ}\text{C}$  [ $0^{\circ}\text{F}$ ], and  $50 \pm 2$  mm [ $2.0 \pm 0.1$  in.] for sheet materials having an ultimate elongation greater than 75 % at  $-18^{\circ}\text{C}$  [ $0^{\circ}\text{F}$ ].

7.1.2.4 Maintain a rate of separation of 50 mm/min  $\pm 3$  % [ $2.0$  in./min  $\pm 3$  %] for specimens tested at  $23 \pm 2^{\circ}\text{C}$  [ $73.4 \pm 3.6^{\circ}\text{F}$ ] [ $4^{\circ}\text{F}$ ] and a rate of separation of 2.0 mm/min  $\pm 3$  % [ $0.08$  in./min  $\pm 3$  %] for specimens tested at  $-18 \pm 3^{\circ}\text{C}$  [ $0 \pm 3.6^{\circ}\text{F}$ ] [ $4^{\circ}\text{F}$ ].

7.1.2.5 An alternative clamping method can be used for high tensile materials that slip in conventional jaws. Clamp the specimen in the jaws so that the length or width is aligned with the axis of the jaws.

7.1.2.6 Use a cylindrical stop in each jaw such as shown in Fig. 2 for membranes difficult to clamp.

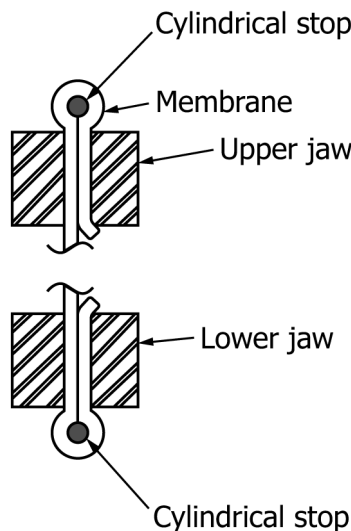


FIG. 2 Alternative Clamping Method