



Designation: D4510 – 18

# Standard Test Method for Counting Partial Cleavages in Wool and Other Animal Fibers<sup>1</sup>

This standard is issued under the fixed designation D4510; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 This test method covers a procedure, using the microprojector, for the counting of partial cleavages in wool and other animal fibers.

1.2 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.4 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

## 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

- D123 Terminology Relating to Textiles
- D2258 Practice for Sampling Yarn for Testing
- D2525 Practice for Sampling Wool for Moisture
- D4845 Terminology Relating to Wool

2.2 *Other Document:*

- Wool Products Labeling Act of 1939<sup>3</sup>

## 3. Terminology

3.1 For all terminology relating to D13.13, Wool and Wool Felt, refer to Terminology D4845.

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D13 on Textiles and is the direct responsibility of Subcommittee D13.13 on Wool and Felt.

Current edition approved July 1, 2018. Published August 2018. Originally approved in 1991. Last previous edition approved in 2009 as D4510 – 05(2009) which was withdrawn January 2018 and reinstated in July 2018. DOI: 10.1520/D4510-18.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> Act of Congress, "Wool Products Labeling Act of 1939," 76th Congress, Third Session, approved October 14, 1939.

3.1.1 The following terms are relevant to this standard: cashmere, coarse hair, cashmere coarse hair content, cashmere down, cashmere hair.

3.2 For all other terminology related to textiles, see Terminology D123.

## 4. Summary of Test Method

4.1 This test method describes a procedure:

4.1.1 The segmenting of various test specimens in preparation for testing.

4.1.2 The projection on a screen of magnified images of the randomly sampled short segments of fiber from the small test specimens, and



4.1.3 The measurement of the number of partially cleaved fibers.

## 5. Significance and Use


5.1 Test Method D4510 for the counting of partial cleavages, may be used for the acceptance testing of commercial shipments of wool and other animal fibers, but caution is advised, since information on between-laboratory precision is limited. Comparative tests as directed in 5.1.1 may be advisable.

5.1.1 In case of a dispute arising from differences in reported test results when using this test method for acceptance testing of commercial shipments, the purchaser and the supplier should conduct comparative tests to determine if there is a statistical bias between their laboratories. Competent statistical assistance is recommended for the investigation of bias. As a minimum, the two parties should take a group of test specimens that are as homogeneous as possible and that are from a lot of material of the type in question. The test specimens should then be randomly assigned in equal numbers to each laboratory for testing. The average results from the two laboratories should be compared using Student's t-test for unpaired data and an acceptable probability level chosen by the two parties before the testing is begun. If a bias is found, either its cause must be found and corrected or the purchaser and the supplier must agree to interpret future test results in the light of the known bias.


5.2 Chemically damaged or tendered fibers are recognizable microscopically by qualified operators and should not be

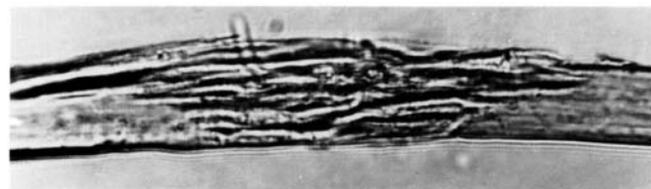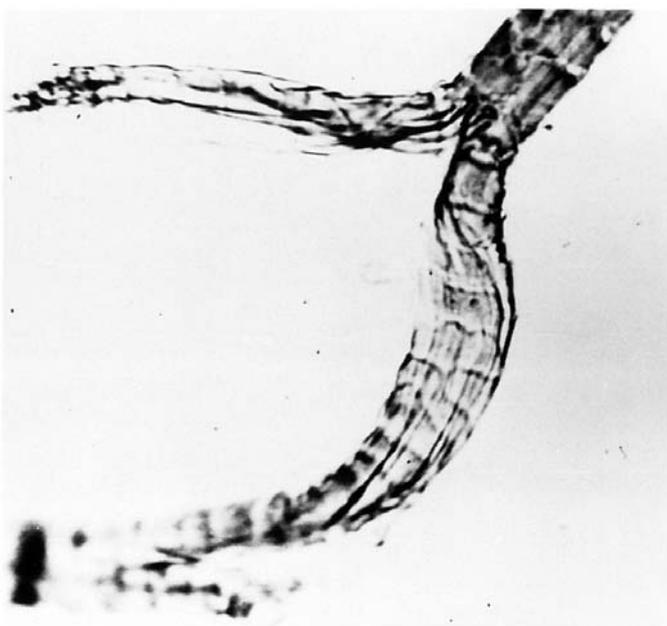

SPLIT FIBER

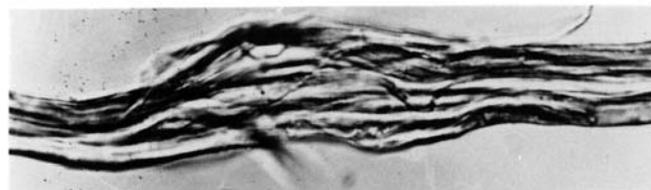

SPLIT FIBER

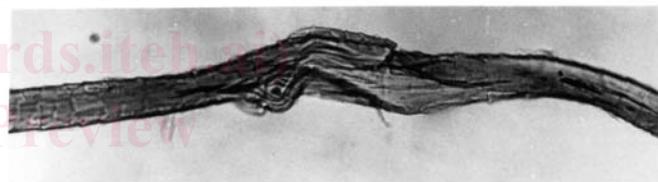

SPLIT FIBER

FIG. 1 (A) Partial Cleavage—But do not count if it is at the end of a fiber. The split may have been caused by other means

counted as partial cleavages. Such fibers exhibit total loss of cuticle, severe surface erosion, tenderizing cracks, longitudinal fibrillation, or a combination of these features (see Figs. 1 and 2). In a study of deliberately over-carbonized wool at one laboratory, it was found that when more than 24 tendered fibers were seen in 1 m, partial cleavage counts were significantly higher than on similar fibers that were not overcarbonized.

## 6. Apparatus and Material

6.1 *Microprojector*<sup>4</sup>—The microscope shall be equipped with a fixed body tube, a focusable stage responsive to coarse and fine adjustments, a focusable substage with condenser and iris diaphragm, and a vertically installed adequate light source to give a precise magnification of 500×, that is, a 12.5 × eyepiece and a 21 × 0.50 numerical aperture objective.

6.2 *Stage Micrometer*<sup>5</sup>—calibrated in intervals of 0.01 mm for accurate setting and control of the magnification.

### 6.3 Fiber-Sectioning Apparatus:

6.3.1 *Heavy-Duty Sectioning Device*<sup>6,7</sup>— An instrument comprised of a metal plate with a slot and compressing key and equipped with a propulsion mechanism by which the fiber

<sup>4</sup> The sole source of supply of the apparatus known to the committee at this time is R&B Instruments, Leeds Wortly Low Mills, 318 Whitehall Road, Leeds LS12 4RJ England. If you are aware of alternative suppliers, please provide this information to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee,<sup>1</sup> which you may attend.

<sup>5</sup> Available from most scientific laboratory instrument supply companies.

<sup>6</sup> The sole source of supply of the apparatus known to the committee at this time is Joe Opherken, 426 Adams, Ogden, UT 84403. If you are aware of alternative suppliers, please provide this information to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee,<sup>1</sup> which you may attend.

FIG. 1 (B–D) Split Fiber (continued)


bundle may be extruded for sectioning. The instrument is designed to hold a sliver of top or equivalent bulk of fibers, or yarn. (Fig. 3)

6.3.2 *Safety Razor Blades*—Single-edge or double-edge blades (if used with blade holder).


6.3.3 *FRL Fiber Cutter*<sup>8</sup>—A device comprised of two razor blades, a threaded pin and an assemblage that will hold the blades rigidly in position. The device, which is operated by applying pressure vertically downward, cuts fibers approximately 250 μm in length (Fig. 3).

<sup>7</sup> The sole source of supply of the Shirley Fibre Microtome known to the committee at this time is Crosroe, Inc., P.O. Box 6408, Tower Drive, Greenville, SC 29606. If you are aware of alternative suppliers, please provide this information to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee,<sup>1</sup> which you may attend.

<sup>8</sup> The sole source of supply of the apparatus known to the committee at this time is Albany International Research Co., 777 West St., P.O. Box 9114, Mansfield, MA 02048-9114. If you are aware of alternative suppliers, please provide this information to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee,<sup>1</sup> which you may attend.

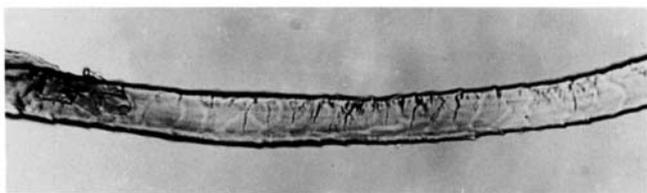

FIBER WITH TRANSVERSE CRACKS

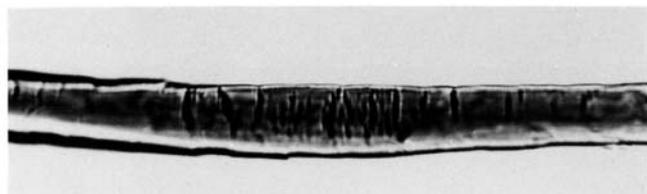

FIBER WITH TRANSVERSE CRACKS

FIG. 2 Fiber With Transverse Cracks



FIG. 3 Heavy Duty Cross-Section Device

6.4 *Microscope Slides*, 25 by 75 mm (1 by 3 in.).

6.5 *Cover Glasses*, No. 1 thickness, 22 by 50 mm (7/8 by 2 in.).

6.6 *Mounting Medium*<sup>9</sup>—Colorless immersion oil with a refractive index of  $1.480 \pm 0.005$  at 20°C (68°F), and a viscosity of 78.81 SUS at 37.8°C (100°F).

6.7 *Length Gage*, made of stiff, white paper 155 mm long, and having thin transverse lines inscribed on it 10 mm from each end, so that the distance between the lines shall be  $135.0 \pm 2.5$  mm. The length gage shall be of convenient width (for example, 30 mm). A satisfactory length gage may also be

<sup>9</sup> The sole source of supply of the apparatus known to the committee at this time is Yocom-McColl Testing Laboratories, Inc. If you are aware of alternative suppliers, please provide this information to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee,<sup>1</sup> which you may attend.

constructed of cardboard by inscribing thereon concentric circles having diameters of 135 mm and 155 mm. This length gage has been found most suitable for the projected field of vision of the microprojector recommended with this length gage.

#### 6.8 *Dissecting Needle*.

### 7. Sampling Bulk Wool

7.1 *Lot Sample for Bulk Wool*—As a lot sample for the acceptance testing of bulk wool, such as wool top, intermediate products, and rovings, take at random the number of shipping containers directed in an applicable material specification or in an agreement between the purchaser and supplier, such as an agreement to use Practice D2525. Consider shipping containers to be the primary sampling unit.

NOTE 1—An adequate specification or other agreement between the purchaser and the supplier requires taking into account the variability between shipping containers, within shipping containers, and between test specimens taken from a single laboratory sample so as to provide a sampling plan with a meaningful producers' risk, consumers' risk, acceptable quality level, and limiting quality level.

7.2 *Laboratory Sample for Bulk Wool*— Consider each unit in the lot sample as a unit in the laboratory sample.

7.3 *Test Specimens for Bulk Wool*—Take two test specimens from each unit in the laboratory sample as described in Practice D2525.

### 8. Sampling

#### 8.1 *Wool Yarns*:

8.1.1 *Lot Sample for Wool Yarn*—As a lot sample for acceptance testing, take at random the number of shipping cases directed in an applicable material specification or other agreement between the purchaser and the supplier, such as an agreement to use Practice D2258. Consider shipping cases to be the primary sampling units. (Note 1)

8.1.2 *Laboratory Sample for Wool Yarn*— As a laboratory sample for acceptance testing, take at random from each shipping case in the lot sample the number of packages directed in an applicable material specification or other agreement to use Practice D2258. Preferably, the same number of packages should be taken from each shipping case in the sample. If differing numbers of packages are to be taken from shipping cases in the lot sample, determine at random which shipping cases are to have each number of packages drawn.

8.1.3 *Test Specimens for Wool Yarn*—From each package in the laboratory sample, take two test specimens as follows. Inspect each package after withdrawing at least five layers of yarn from the outside of the package. If there is visible evidence of damage to the package, continue to withdraw units of five layers and reinspect. Take specimens of about 1 m (1 yd.) long. Discard specimen lengths that are damaged. Discard at least 2 m (2 yds) of strand between specimens from a single package.

#### 8.2 *Wool Fabric*:

8.2.1 *Lot Sample for Wool Fabric*—As a lot sample for acceptance testing, take at random the number of rolls of fabric