

INTERNATIONAL STANDARD

NORME INTERNATIONALE

Environmental testing –
Part 2-20: Tests – Tests Ta and Tb: Test methods for solderability and
resistance to soldering heat of devices with leads

Essais d'environnement –
Partie 2-20: Essais – Essais Ta et Tb: Méthodes d'essai de la brasabilité
et de la résistance à la chaleur de brasage des dispositifs à broches



THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2021 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de l'IEC ou du Comité national de l'IEC du pays du demandeur. Si vous avez des questions sur le copyright de l'IEC ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de l'IEC de votre pays de résidence.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, ...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

IEC online collection - oc.iec.ch

Discover our powerful search engine and read freely all the publications previews. With a subscription you will always have access to up to date content tailored to your needs.

Electropedia - www.electropedia.org

The world's leading online dictionary on electrotechnology, containing more than 22 000 terminological entries in English and French, with equivalent terms in 18 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

A propos de l'IEC

La Commission Electrotechnique Internationale (IEC) est la première organisation mondiale qui élabore et publie des Normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications IEC

Le contenu technique des publications IEC est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

Recherche de publications IEC -

webstore.iec.ch/advsearchform

La recherche avancée permet de trouver des publications IEC en utilisant différents critères (numéro de référence, texte, comité d'études, ...). Elle donne aussi des informations sur les projets et les publications remplacées ou retirées.

IEC Just Published - webstore.iec.ch/justpublished

Restez informé sur les nouvelles publications IEC. Just Published détaille les nouvelles publications parues. Disponible en ligne et une fois par mois par email.

Service Clients - webstore.iec.ch/csc

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions contactez-nous: sales@iec.ch.

IEC online collection - oc.iec.ch

Découvrez notre puissant moteur de recherche et consultez gratuitement tous les aperçus des publications. Avec un abonnement, vous aurez toujours accès à un contenu à jour adapté à vos besoins.

Electropedia - www.electropedia.org

Le premier dictionnaire d'électrotechnologie en ligne au monde, avec plus de 22 000 articles terminologiques en anglais et en français, ainsi que les termes équivalents dans 16 langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International (IEV) en ligne.



IEC 60068-2-20

Edition 6.0 2021-03

INTERNATIONAL STANDARD

NORME INTERNATIONALE

**Environmental testing –
Part 2-20: Tests – Tests Ta and Tb: Test methods for solderability and
resistance to soldering heat of devices with leads**

**Essais d'environnement –
Partie 2-20: Essais – Essais Ta et Tb: Méthodes d'essai de la brasabilité
et de la résistance à la chaleur de brasage des dispositifs à broches**

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

COMMISSION
ELECTROTECHNIQUE
INTERNATIONALE

ICS 19.040

ISBN 978-2-8322-9585-4

**Warning! Make sure that you obtained this publication from an authorized distributor.
Attention! Veuillez vous assurer que vous avez obtenu cette publication via un distributeur agréé.**

CONTENTS

FOREWORD	4
1 Scope	6
2 Normative references	6
3 Terms and definitions	6
4 Test Ta: Solderability of wire and tag terminations	8
4.1 Objective and general description of the test	8
4.1.1 Test methods	8
4.1.2 Specimen preparation	8
4.1.3 Initial measurements	9
4.1.4 Preconditioning	9
4.2 Method 1: Solder bath	10
4.2.1 General	10
4.2.2 Description of the solder bath	10
4.2.3 Flux	10
4.2.4 Procedure	10
4.2.5 Test conditions	11
4.2.6 Final measurements and requirements	11
4.3 Method 2: Soldering iron at 350 °C	11
4.3.1 General	11
4.3.2 Description of soldering irons	11
4.3.3 Solder and flux	12
4.3.4 Procedure	12
4.3.5 Final measurements and requirements	13
4.4 Information to be given in the relevant specification	13
5 Test Tb: Resistance to soldering heat	14
5.1 Objective and general description of the test	14
5.1.1 Test methods	14
5.1.2 Initial measurements	14
5.2 Method 1: Solder bath	14
5.2.1 Description of the solder bath	14
5.2.2 Flux	14
5.2.3 Procedure	14
5.2.4 Test conditions	15
5.2.5 De-wetting	15
5.3 Method 2: Soldering iron	16
5.3.1 Description of soldering iron	16
5.3.2 Solder and flux	16
5.3.3 Procedure	16
5.4 Recovery	16
5.5 Final measurements and requirements	16
5.6 De-wetting (if required)	16
5.7 Information to be given in the relevant specification	17
Annex A (informative) Example of apparatus for steam conditioning process	18
Annex B (normative) Specification for flux constituents	19
B.1 Colophony	19
B.2 2-propanol (isopropyl alcohol)	19

B.3	Ethyl alcohol	19
B.4	Flux composition	19
Bibliography		21
Figure 1 – Diagram of contact angle		7
Figure 2 – Position of soldering iron		12
Figure A.1 – Example of apparatus		18
Table 1 – Solderability, solder bath method: Test severities (duration and temperature)		11
Table 2 – Resistance to soldering heat, solder bath method: Test severities (duration and temperature)		15
Table B.1 – Colophony based flux compositions		20

iTeh STANDARD PREVIEW (standards.iteh.ai)

[IEC 60068-2-20:2021](https://standards.iteh.ai/catalog/standards/sist/238224f3-bdfb-4017-a263-52dc4f10a2e4/iec-60068-2-20-2021)

<https://standards.iteh.ai/catalog/standards/sist/238224f3-bdfb-4017-a263-52dc4f10a2e4/iec-60068-2-20-2021>

INTERNATIONAL ELECTROTECHNICAL COMMISSION

ENVIRONMENTAL TESTING –

**Part 2-20: Tests –
Tests Ta and Tb: Test methods for solderability
and resistance to soldering heat of devices with leads**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

IEC 60068-2-20 has been prepared by IEC technical committee 91: Electronics assembly technology. It is an International Standard.

This sixth edition cancels and replaces the fifth edition published in 2008. This sixth edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) update of and clarification of pre-conditioning (former "aging") and its relation to natural aging.

The text of this International Standard is based on the following documents:

Draft	Report on voting
91/1701/FDIS	91/1711/RVD

Full information on the voting for its approval can be found in the report on voting indicated in the above table.

The language used for the development of this International Standard is English.

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at www.iec.ch/members_experts/refdocs. The main document types developed by IEC are described in greater detail at www.iec.ch/standardsdev/publications.

A list of all the parts in the IEC 60068 series, under the general title *Environmental testing*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under "<http://webstore.iec.ch>" in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/sist/238224f3-bdfb-4017-a263-52dc4f10a2e4/iec-60068-2-20-2021>

ENVIRONMENTAL TESTING –

Part 2-20: Tests – Tests Ta and Tb: Test methods for solderability and resistance to soldering heat of devices with leads

1 Scope

This part of IEC 60068 outlines Tests Ta and Tb, applicable to devices with leads and leads themselves. Soldering tests for surface mounting devices (SMD) are described in IEC 60068-2-58.

This document provides procedures for determining the solderability and resistance to soldering heat of devices in applications using solder alloys, which are eutectic or near eutectic tin lead (Pb), or lead-free alloys.

The procedures in this document include the solder bath method and soldering iron method.

The objective of this document is to ensure that component lead or termination solderability meets the applicable solder joint requirements of IEC 61191-3 and IEC 61191-4. In addition, test methods are provided to ensure that the component body can be resistant to the heat load to which it is exposed during soldering.

NOTE Information about wetting time and wetting force can be obtained by test methods using a wetting balance. IEC 60068-2-69 (solder bath and solder globule method) can be consulted.

<https://standards.iteh.ai/catalog/standards/sist/238224f3-bdfb-4017-a263-52dc4f10a2e4/iec-60068-2-20-2021>

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60068-1, *Environmental testing – Part 1: General and guidance*

IEC 60068-2-2, *Environmental testing – Part 2-2: Tests – Test B: Dry heat*

IEC 60068-2-66, *Environmental testing – Part 2: Test methods – Test Cx: Damp heat, steady state (unsaturated pressurized vapour)*

IEC 60068-2-78, *Environmental testing – Part 2-78: Tests – Test Cab: Damp heat, steady state*

IEC 61191-3, *Printed board assemblies – Part 3: Sectional specification – Requirements for through-hole mount soldered assemblies*

IEC 61191-4, *Printed board assemblies – Part 4: Sectional specification – Requirements for terminal soldered assemblies*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1

colophony

natural resin obtained as the residue after removal of turpentine from the oleo-resin of the pine tree, consisting mainly of abietic acid and related resin acids, the remainder being resin acid esters

Note 1 to entry: "Rosin" is a synonym for colophony, and is deprecated because of the common confusion with the generic term "resin".

3.2

contact angle

in general, the angle enclosed between two planes, tangent to a liquid surface and a solid/liquid interface at their intersection (see Figure 1); in particular, the contact angle of liquid solder in contact with a solid metal surface

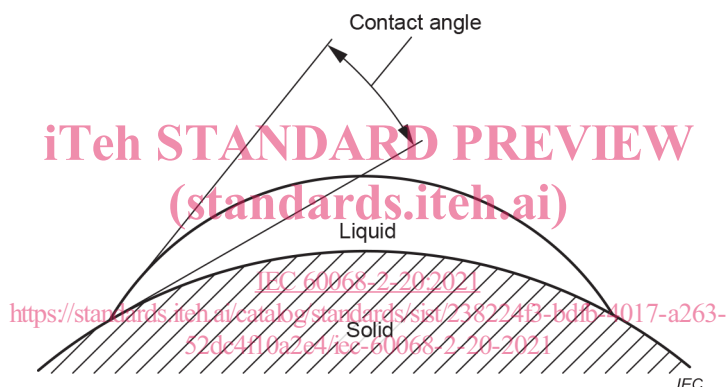


Figure 1 – Diagram of contact angle

3.3

wetting

formation of an adherent coating of solder on a surface

Note 1 to entry: A small contact angle is indicative of wetting.

3.4

non-wetting

inability to form an adherent coating of solder on a surface

Note 1 to entry: In this case the contact angle is greater than 90°.

3.5

de-wetting

retraction of molten solder on a solid area that it has initially wetted

Note 1 to entry: In some cases, an extremely thin film of solder may remain. As the solder retracts the contact angle increases.

3.6

solderability

ability of the lead, termination or electrode of a component to be wetted by solder at the temperature of the termination or electrode, which is assumed to be the lowest temperature in the soldering process within the applicable temperature range of the solder alloy

3.7

soldering time

time required for a defined surface area to be wetted under specific conditions

3.8

resistance to soldering heat

ability of the component to withstand the highest temperature stress in terms of temperature gradient, peak temperature and duration of the soldering process, where the temperature of the component body is within the applicable temperature range of the solder alloy

3.9

lead-free solder

alloy that does not contain more than 0,1 % lead (Pb) by weight as its constituent and is used for joining components to substrates or for coating surfaces

[SOURCE: IEC 60194-2:2017, 3.12.5, modified – The words "as its constituent" have been added.]

4 Test Ta: Solderability of wire and tag terminations

4.1 Objective and general description of the test

4.1.1 Test methods

Test Ta provides two different test methods to determine the solderability of areas on wire and tag terminations that are required to be wetted by solder during the assembly operation.

- Method 1: solder bath;
- Method 2: soldering iron.

The test method to be used shall be indicated in the relevant specification. The solder bath method is the one which most closely simulates the soldering procedures of flow soldering and similar soldering processes.

The soldering iron method may be used in cases where Method 1 is impracticable.

If required by the relevant specification, the test specimen shall be preconditioned according to 4.1.4. The following are typical methods for preconditioning:

- Type 1a: 1 h steam
- Type 1b: 4 h steam
- Type 2: 10 days damp heat, steady state condition (40 ± 2) °C; (93 ± 3) % RH (Test Cab)
- Type 3a: 4 h at 155 °C dry heat (Test Bb)
- Type 3b: 16 h at 155 °C dry heat (Test Bb).
- Type 4: 4 h unsaturated pressurized vapour (Test Cx)

NOTE 1 In general, the acceleration for ageing prior to solderability testing is estimated by simulating the degradation in storage environment. However, the steam ageing condition does not correspond with storage conditions because the failure mode derived from steam ageing is clearly different from that derived from storage conditions. Therefore, an accelerated correlation between steam ageing and natural ageing in storage condition is impossible and steam ageing conditions such as type 1a and type 1b are inappropriate as accelerated ageing.

NOTE 2 For Ni/Au surface, Type 2 or Type 4 is appropriate as preconditioning.

4.1.2 Specimen preparation

The surface to be tested shall be in the "as received" condition and shall not be subsequently touched by the fingers or otherwise contaminated.

The specimen shall not be cleaned prior to the application of a solderability test. If required by the relevant specification, the specimen may be degreased by immersion in a neutral organic solvent at room temperature.

4.1.3 Initial measurements

The specimens shall be visually examined and, if required by the relevant specification, electrically and mechanically checked.

4.1.4 Preconditioning

4.1.4.1 General

If preconditioning is required by the relevant specification, one of the following procedures may be adopted. At the end of the conditioning, the specimen shall be subjected to standard atmospheric conditions for testing for not less than 2 h and not more than 24 h.

Terminations may be detached if the conditioning temperature is higher than the component's maximum operating or storage temperature, or if the component is likely to degrade considerably at 100 °C in steam and thus affect the solderability in a manner which would not normally occur in natural ageing.

4.1.4.2 Type 1

The relevant specification shall indicate whether type 1a (1 h in steam) or type 1b (4 h in steam) is to be used. For these procedures the specimen is suspended, preferably with the termination vertical, with the area to be tested positioned 25 mm to 30 mm above the surface of boiling distilled water which is contained in a borosilicate glass or stainless steel vessel of suitable size (e.g., a 2 liter beaker). The termination shall be at least 10 mm from the walls of the vessel.

<https://standards.iteh.ai/catalog/standards/sist/238224f7-bdfb-4017-a263-52dc4810a2e4/iec-60068-2-20-2021>

The vessel shall be provided with a cover of similar material, consisting of one or more plates which are capable of covering approximately seven-eighths of the opening. A suitable method of suspending the specimens shall be devised; perforations or slots in the cover are permitted for this purpose. The specimen holder shall be non-metallic.

The level of water shall be maintained by the addition of hot distilled water, added gradually in small quantities, so that the water will continue to boil vigorously; alternatively a reflux condenser may be used if desired. (See Figure A.1).

NOTE There are many problems for steam conditioning. For example, dew always condenses on the terminations and liquid water directly drops onto specimens in some cases.

4.1.4.3 Type 2

Specimens are subjected to 10 days damp heat, steady state, according to IEC 60068-2-78, Test Cab: Damp heat, steady state.

4.1.4.4 Type 3

Specimens are subjected to 4 h (Type 3a) or 16 h (Type 3b) dry heat at 155 °C according to IEC 60068-2-2, Test B: Dry heat.

The test specimens may be introduced into the chamber at any temperature from laboratory ambient to the specified temperature.

4.1.4.5 Type 4

Specimens are subjected to 4 h at 120 °C and 85 % RH according to IEC 60068-2-66, Test Cx: Damp heat, steady state (unsaturated pressurized vapour).

4.2 Method 1: Solder bath

4.2.1 General

This method provides a procedure for assessing the solderability of wires, tags, and terminations of irregular form.

4.2.2 Description of the solder bath

The solder bath shall be of adequate dimensions to accommodate the specimens and contain sufficient solder to maintain the solder temperature during testing, and to prevent exceeding the contamination levels applicable to the type of solder used for testing. If not otherwise defined by the relevant specification, the solder bath shall be not less than 40 mm in depth and not less than 300 ml in volume. The bath shall contain solder as specified in Table 1.

NOTE 1 When the specimens are of a small size and heat capacity, a solder bath with dimensions less than described above can be appropriate.

NOTE 2 Clause A.2 of IEC 60068-2-69:2017 can be consulted as an example of the solder bath corresponding to NOTE 1.

4.2.3 Flux

A colophony based flux as described in Annex B shall be used. The flux shall be non-activated (see Table B.1).

If non-activated flux is inappropriate, the relevant specification may require the use of a low activated flux (see Table B.1).

4.2.4 Procedure

The dross on the surface of the molten solder shall be removed with a piece of suitable thermally resistant material, immediately before each test, to ensure a clean and bright surface.

The termination to be tested shall be immersed first in the flux (described in 4.2.3) at ambient temperature, and excess flux shall be eliminated either by draining off for a suitable time, or by using any other procedure likely to produce a similar result. In case of dispute, drainage shall be carried out for (60 ± 5) s.

NOTE It sometimes happen that excessive remaining flux boil when coming into contact with the liquid solder and gas bubbles stick to the surface of terminations and prevent wetting of the termination in such areas.

The termination is then immersed immediately in the solder bath in the direction of its longitudinal axis. The point of immersion of the termination shall be at a distance not less than 10 mm from the walls of the bath.

The speed of immersion shall be determined at 25 mm/s or less. and the termination shall remain immersed for the time selected from Table 1 with the body of the component at the distance above the solder prescribed in the relevant specification. The specimen shall then be withdrawn at $(25 \pm 2,5)$ mm/s.

For components having a high thermal capacity, an immersion time of $(5,0 \pm 0,5)$ s or (10 ± 1) s may be selected from Table 1.

If required by the relevant specification, a screen of thermally insulating material of $(1,5 \pm 0,5)$ mm thickness with clearance holes appropriate to the size of the termination, may be placed between the body of the component and solder.

Any flux residues shall be removed with 2-propanol (isopropyl alcohol) or ethanol (ethyl alcohol) after testing.

4.2.5 Test conditions

The duration and temperature of immersion shall be selected from Table 1, unless otherwise prescribed by the relevant specification.

Table 1 – Solderability, solder bath method: Test severities (duration and temperature)

Alloy composition	Severity					
	(215 ± 3) °C (3 ± 0,3) s	(10 ± 1) s	(235 ± 3) °C (2 ± 0,2) s	(5 ± 0,5) s	(245 ± 3) °C (3 ± 0,3) s	(250± 3) °C (3 ± 0,3) s
SnPb	X	X	X	X		
Sn96,5Ag3Cu,5					X	
Sn99,3Cu,7						X
<p>The alloy compositions are given for test reference purposes only.</p> <p>SnPb: The solder alloys consisting of a mass fraction of 37 % or 40 % Pb, and the remainder of Sn may be used; Sn96,5Ag3Cu,5: The solder alloys consisting of a mass fraction of 3,0 % to 4,0 % Ag, 0,5 % to 1,0 % Cu, and the remainder of Sn may be used; Sn99,3Cu,7: The solder alloys consisting of a mass fraction of 0,45 % to 0,9 % Cu and the remainder of Sn may be used.</p> <p>The basic lead-free solder alloys listed in this table represent compositions that are currently preferred for lead-free soldering processes. If solder alloys other than those listed here are used, it needs to be verified that the given severities are applicable.</p>						
iTech STANDARD PREVIEW (standards.itech.ai)						
NOTE 1 "X" denotes 'applicable'.						
NOTE 2 Annex B of IEC 61190-1-3:2017 can be consulted to identify alloy compositions.						

IEC 60068-2-20:2021

4.2.6 Final measurements and requirements

The visual inspection shall be carried out under adequate light with a binocular microscope of magnification in a range of 4x to 100x.

The specimens shall be visually examined and, if required by the relevant specification, electrically and mechanically checked.

The dipped surface relevant for soldering shall be covered with solder coating with no more than small amounts of scattered imperfections such as pin-holes or un-wetted or de-wetted areas. All leads shall exhibit a continuous solder coating free from defects for a minimum of 95 % of the critical area of any individual lead. For solder alloys containing lead (Pb), solder shall be smooth and bright.

4.3 Method 2: Soldering iron at 350 °C

4.3.1 General

This method provides a procedure for assessing the solderability of terminations in cases where the solder bath method is impracticable. It applies to lead containing and lead-free solder alloys.

4.3.2 Description of soldering iron

To keep the tip temperature during test within the specified limits, usage of a temperature controlled soldering iron is recommended.