

INTERNATIONAL STANDARD



**Measurement procedures for materials used in photovoltaic modules –
Part 7-3: Accelerated stress tests – Methods of abrasion of PV module external
Surfaces**

(<https://standards.iteh.ai>)

Document Preview

[IEC 62788-7-3:2022](#)

<https://standards.iteh.ai/catalog/standards/iec/3f6a523c-0ba3-4fe0-ac97-f3a52eb7bd7c/iec-62788-7-3-2022>





THIS PUBLICATION IS COPYRIGHT PROTECTED
Copyright © 2024 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Secretariat
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, ...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

IEC Products & Services Portal - products.iec.ch

Discover our powerful search engine and read freely all the publications previews, graphical symbols and the glossary. With a subscription you will always have access to up to date content tailored to your needs.

Electropedia - www.electropedia.org

The world's leading online dictionary on electrotechnology, containing more than 22 500 terminological entries in English and French, with equivalent terms in 25 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

International Standards
Document Preview

[IEC 62788-7-3:2022](https://standards.iteh.ai/catalog/standards/iec/3f6a523c-0ba3-4fe0-ac97-f3a52eb7bd7c/iec-62788-7-3-2022)

<https://standards.iteh.ai/catalog/standards/iec/3f6a523c-0ba3-4fe0-ac97-f3a52eb7bd7c/iec-62788-7-3-2022>



IEC 62788-7-3

Edition 1.1 2024-07
CONSOLIDATED VERSION

INTERNATIONAL STANDARD



Measurement procedures for materials used in photovoltaic modules –
Part 7-3: Accelerated stress tests – Methods of abrasion of PV module external
Surfaces

Document Preview

[IEC 62788-7-3:2022](https://standards.iteh.ai/standards/iec/3f6a523c-0ba3-4fe0-ac97-f3a52eb7bd7c/iec-62788-7-3-2022)

<https://standards.iteh.ai/catalog/standards/iec/3f6a523c-0ba3-4fe0-ac97-f3a52eb7bd7c/iec-62788-7-3-2022>

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 27.160

ISBN 978-2-8322-9506-9

Warning! Make sure that you obtained this publication from an authorized distributor.

CONTENTS

FOREWORD.....	4
INTRODUCTION.....	6
1 Scope.....	7
2 Normative references	7
3 Terms and definitions	8
4 Artificial linear machine abrasion test (SAT01).....	8
4.1 Principle	8
4.2 Apparatus	8
4.2.1 Artificial linear machine abrasion apparatus.....	8
4.2.2 Brush.....	9
4.2.3 Abrasive medium (dry).....	10
4.2.4 Abrasive medium (wet slurry).....	11
4.3 Test specimens.....	11
4.3.1 Materials and geometry	11
4.3.2 Number of replicate specimens.....	12
4.3.3 Reference material	12
4.4 Test procedure.....	13
4.4.1 Setting up the apparatus and specimen.....	13
4.4.2 Performing the abrasion test.....	13
4.5 Specimen preparation for examination after testing.....	14
5 Artificial rotary machine abrasion test (SAT02).....	14
5.1 General.....	14
5.2 Apparatus	14
5.2.1 Artificial rotary machine abrasion apparatus	14
5.2.2 Brush.....	15
5.2.3 Abrasive medium (dry).....	16
5.2.4 Abrasive medium (wet/slurry).....	16
5.3 Test specimens.....	16
5.4 Test procedure.....	16
5.5 Specimen preparation for examination after testing.....	16
6 Falling sand test (SAT03).....	16
6.1 Principle	16
6.2 Apparatus	17
6.2.1 Falling sand apparatus	17
6.2.2 Abrasive medium	17
6.3 Test specimens.....	17
6.3.1 General	17
6.3.2 Number of replicate specimens.....	17
6.4 Test procedure.....	18
6.5 Specimen preparation for examination after testing.....	18
7 Forced sand impingement test (SAT04).....	18
7.1 Principle	18
7.2 Apparatus	18
7.2.1 Forced sand impingement apparatus	18
7.2.2 Abrasive medium	19
7.3 Test specimens.....	19

7.4	Procedure	19
7.5	Specimen preparation for examination after testing	20
8	Test report	20
Annex A (informative) References describing the durability of materials to linear abrasion		21
Bibliography		22
Figure 1 – Schematics showing the arrangement of bristle tufts on the linear brush		10
Figure 4.2 – Schematic showing the arrangement of bristle tufts on the rotary brush		16
Table 1 – Examples of suitable reference materials		13

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[IEC 62788-7-3:2022](https://standards.iteh.ai/catalog/standards/iec/3f6a523c-0ba3-4fe0-ac97-f3a52eb7bd7c/iec-62788-7-3-2022)

<https://standards.iteh.ai/catalog/standards/iec/3f6a523c-0ba3-4fe0-ac97-f3a52eb7bd7c/iec-62788-7-3-2022>

INTERNATIONAL ELECTROTECHNICAL COMMISSION

**MEASUREMENT PROCEDURES FOR MATERIALS
USED IN PHOTOVOLTAIC MODULES –****Part 7-3: Accelerated stress tests –
Methods of abrasion of PV module external surfaces**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as “IEC Publication(s)”). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) IEC draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). IEC takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, IEC had not received notice of (a) patent(s), which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at <https://patents.iec.ch>. IEC shall not be held responsible for identifying any or all such patent rights.

This consolidated version of the official IEC Standard and its amendment has been prepared for user convenience.

IEC 62788-7-3 edition 1.1 contains the first edition (2022-02) [documents 82/1987/FDIS and 82/2009/RVD] and its amendment 1 (2024-07) [documents 82/2259/FDIS and 82/2277/RVD].

In this Redline version, a vertical line in the margin shows where the technical content is modified by amendment 1. Additions are in green text, deletions are in strikethrough red text. A separate Final version with all changes accepted is available in this publication.

IEC 62788-7-3 has been prepared by IEC technical committee 82: Solar photovoltaic energy systems. It is an International Standard.

The language used for the development of this International Standard is English.

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at www.iec.ch/members_experts/refdocs. The main document types developed by IEC are described in greater detail at www.iec.ch/standardsdev/publications.

A list of all parts in the IEC 62788 series, published under the general title *Measurement procedures for materials used in photovoltaic modules*, can be found on the IEC website.

The committee has decided that the contents of this document and its amendment will remain unchanged until the stability date indicated on the IEC website under webstore.iec.ch in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn, or
- revised.

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

Document Preview

[IEC 62788-7-3:2022](https://standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/iec/3f6a523c-0ba3-4fe0-ac97-f3a52eb7bd7c/iec-62788-7-3-2022>

INTRODUCTION

There is a need for abrasion test methods in the PV industry, particularly for the front and back surfaces of PV modules. This document defines a set of test methods to be used for evaluating the abrasion of materials and coatings in photovoltaic modules or other solar devices. Linear and rotary machine abrasion methods are specified that can be used to address durability to abrasion with respect to the cleaning of solar devices. Linear abrasion is intended to emulate traditional manual methods of cleaning, where the cleaning equipment typically acts perpendicular to the surface, giving a scratching motion. Rotary abrasion is intended to emulate popular robotic methods of cleaning, where the cleaning element often may act along the surface in a swiping motion. Relative to DIN 53778-2 and ASTM D2486, application specific modifications for the machine abrasion tests include the longer bristle length, use of abrasive (test dust) of the size encountered in PV, the use of dry or wet abrasive as may be encountered during cleaning modules, and the number of test cycles relative to the maintenance of PV systems. A falling sand method is specified that can be used to address durability to abrasion with respect to damage from ordinary use in the application environment, i.e., typically meteorological events. Relative to DIN 52348, modifications include the quantity of test sand, which is intended for examination of PV surfaces and coatings. A forced sand impingement method is specified that can be used to address durability to abrasion from severe weather events and/or the most challenging locations of use. Relative to IEC 60068-2-68, modifications include the composition of test sand that may be compared to the PV application and the falling sand test in this document as well as the specified carrier velocities based on the PV application. The methods in this document can be used to aid performance analysis and/or for the purpose of material design/selection. Comparing the linear brush, rotary brush, falling sand, and forced impingement methods, different rates of abrasion and/or damage morphology can occur between the different test methods – they are not expected to produce the same result.

Formal working reference materials are identified in this document. The purpose of the working reference is to verify the apparatus is installed and working correctly. The characteristic(s) of interest can be verified on a regular basis (monthly, weekly, etc.). The characteristic(s) of interest and their values (with acceptance limits for precision) will be given in a referencing document or future version of this document, based on the results of an interlaboratory precision study.

<https://standards.iteh.ai/standards/iec/3f6a523c-0ba3-4fe0-ac97-f3a52eb7bd7c/iec-62788-7-3-2022>

<https://standards.iteh.ai/catalog/standards/iec/3f6a523c-0ba3-4fe0-ac97-f3a52eb7bd7c/iec-62788-7-3-2022>

MEASUREMENT PROCEDURES FOR MATERIALS USED IN PHOTOVOLTAIC MODULES –

Part 7-3: Accelerated stress tests – Methods of abrasion of PV module external surfaces

1 Scope

This part of IEC 62788 defines the test methods that can be used for evaluating the abrasion of materials and coatings in photovoltaic modules or other solar devices. This document may be applied to components on the incident surface (including coatings, frontsheet, and glass) as well as the back surface (including backsheets or back glass). This document is intended to address abrasion of PV module surfaces and any coatings present using representative specimens (e.g. which can be centimetres in size); the methods and apparatus used here can also be used on PV module specimens (e.g. meters in size). A suite of tests and their methods are identified in this document, including falling sand, forced sand impingement, and machine (brush) abrasion. Materials and coatings can have different intended design purposes and design lifetimes and therefore no specific pass/fail criteria are defined in this document. The results of the testing can, however, be used to identify relative durability of coatings for various outdoor environments and cleaning practices. The methods can be used for the purpose of relative comparison, e.g. for the purpose of material or coating selection. The quantitative correlation between artificial abrasion and field erosion (which will depend on factors including climate or location of use as well as application, e.g., use of a tracker, rack-mount, roof-mount, building integrated, or vehicle integrated PV) can be established for each specific material or coating, which is beyond the scope of this document.

The correlation between the rates of degradation from the different test methods (linear brush, rotary brush, falling sand, and forced impingement) is beyond the scope of this document and may be covered in referencing documents. The correlation between the rates of degradation for unaged and aged specimens is also beyond the scope of this document and may be covered in referencing documents.

The methods related to the characterization of abraded specimens (which might include optical transmittance, optical reflectance, surface roughness, and surface energy) are not defined in this document; characterization methods from other standards (including optical transmittance, optical reflectance, electrical performance, surface roughness, and surface energy) can be applied to specimens abraded using the methods defined in this document. Methods for examining the contamination of specimens, including artificial soiling, are not examined in this document. Additional specimen conditioning can be applied prior to the methods in this document. The abrasion tests in this document can be referenced and/or applied in conjunction with an accelerated test or test sequence in other standards.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60068-2-68, *Environmental testing – Part 2-68: Tests – Test L: Dust and sand*

IEC TS 61836, *Solar photovoltaic energy systems – Terms, definitions and symbols*

ISO 291, *Plastics – Standard atmospheres for conditioning and testing*

ISO 12103-1, *Road vehicles – Test contaminants for filter evaluation – Part 1: Arizona test dust*

ASTM D2486, *Standard test methods for scrub resistance of wall paints*

DIN 52348:1985-02, *Testing of glass and plastics; abrasion test; sand trickling method*

DIN 53778-2:1983-08, *Emulsion paints for interior use; evaluation of cleanability and of wash and scrub resistance of coatings*

MIL-STD-810G, *Environmental engineering considerations and laboratory tests*

VDI 3956, *Evaluation of the soiling properties of surfaces – Test method for the dust soiling behaviour of solar energy systems*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in IEC TS 61836 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1

artificial abrasion

wear resulting from the cleaning of a PV device, including manual or robotic cleaning

3.2

natural erosion

wear resulting from the ordinary terrestrial use of a PV device

Note 1 to entry: Sources of erosion may include particulate impingement, particulate transport (from wind or water), or autonomous scraping (from snow or ice by gravity).

4 Artificial linear machine abrasion test (SAT01)

4.1 Principle

The machine abrasion methods are specified that can be used to address durability to abrasion with respect to the cleaning of solar devices. Linear abrasion is intended to emulate traditional manual methods of cleaning, where the cleaning equipment typically acts perpendicular to the surface, giving a scratching motion. The test is typically applied to the irradiance incident surface of a PV module. Because either dry or wet cleaning may be used to clean a PV module, both dry and wet (slurry) abrasives may be used in this test. The test may simulate the cleaning of fixed, tracked, or vehicle integrated PV.

4.2 Apparatus

4.2.1 Artificial linear machine abrasion apparatus

A linear abrasion apparatus fulfilling the requirements of ASTM D2486 or DIN 53778-2 shall be used. Essential components of the apparatus include: a linear abrasion mechanism, a brush, an abrasive dispenser (slurry or dry abrasive), and an enclosure (if applicable). An enclosure is recommended for the apparatus to prevent spilling or spraying of abrasive (dry or wet slurry abrasives) or the possibility of silicosis (with ventilation, for dry abrasive). Additional equipment and containers for the management of waste abrasive and its disposal after the test is advised.

The abrasion mechanism shall provide a brush stroke length of at least 14,5 cm. The brush may operate at either a constant or varied velocity through each stroke. The brush velocity of $30 \pm 3 \text{ cm}\cdot\text{s}^{-1}$ shall be used for the through the central 7,5 cm test region on the specimen during machine abrasion testing. Other test rates may be used for the purposes of research and development.

NOTE For example, the brush velocity of $30 \text{ cm}\cdot\text{s}^{-1}$, when used with a stroke length of 25,4 cm corresponds to a test rate of 37 ± 1 cycles per minute.

Specimens shall be rigidly mounted relative to the apparatus using mechanical springs or clamps, tape or other means.

To ensure repeatability of results (i.e., avoid temperature-related effects related to the abrasion process or abrasive) the apparatus shall be maintained, in a laboratory maintained at $(23 \pm 2) \text{ }^\circ\text{C}$, $(50 \pm 10) \%$ RH, as specified per Class 2 in ISO 291.

The dispenser for dry dust shall be separated from the specimen surface by at least 10 cm to provide clearance for the motion of the brush (in both linear and rotary configurations) and also aid dispensing to the designated test area of the specimen.

The dispenser for wet slurry shall be separated from the specimen surface by at least 5 cm to aid dispensing to the designated test area of the specimen.

4.2.2 Brush

The brush block shall be $(3538 \pm 1) \text{ mm} \times (8589 \pm 1) \text{ mm}$ in area and $(13 \pm 1) \text{ mm}$ in thickness.

The brush bristles shall consist of polyamide 612, poly(hexamethylene dodecanediamide) with a 50:50 molar ratio of monomer types, $(0,23 \pm 0,03) \text{ mm}$ in diameter that extend $(38 \pm 2) \text{ mm}$ from the brush block. Brushes with bristles shorter than 35 mm in length shall be replaced. The bristle profile shall be round, with no taper or other change in geometry along their length. The lateral repeat space of 6,4 mm shall be used for the bristle tuft rows across the width of the brush and 12,7 mm shall be used for the bristle tuft columns along the length of the brush, with a. For the staggered bristles, an offset space of 3,2 mm between adjacent rows and lateral offset space of 6,4 mm between adjacent bristle columns. The bristle tufts shall be staggered in a 5-4-5-4-... pattern along the brush, with total of 59 tufts. The bristle count shall be $(158 \pm 6) \text{ tips}\cdot\text{tuft}^{-1}$. See Figure 1.

~~A 325 g external weight shall be used with the brush, as in ASTM D2486. The nominal brush weight of 125 g includes the dry weight of brush block and bristles. The nominal brush net weight (including 5 g attachment bolt) shall be $455 \pm 10 \text{ g}$, including the dry weight of brush block, bristles, external weight, fasteners, and holder. The nominal contact force of 4,46 N shall result from the self-weight of the components; no spring or other external force shall be used.~~

Dimensions in millimetres

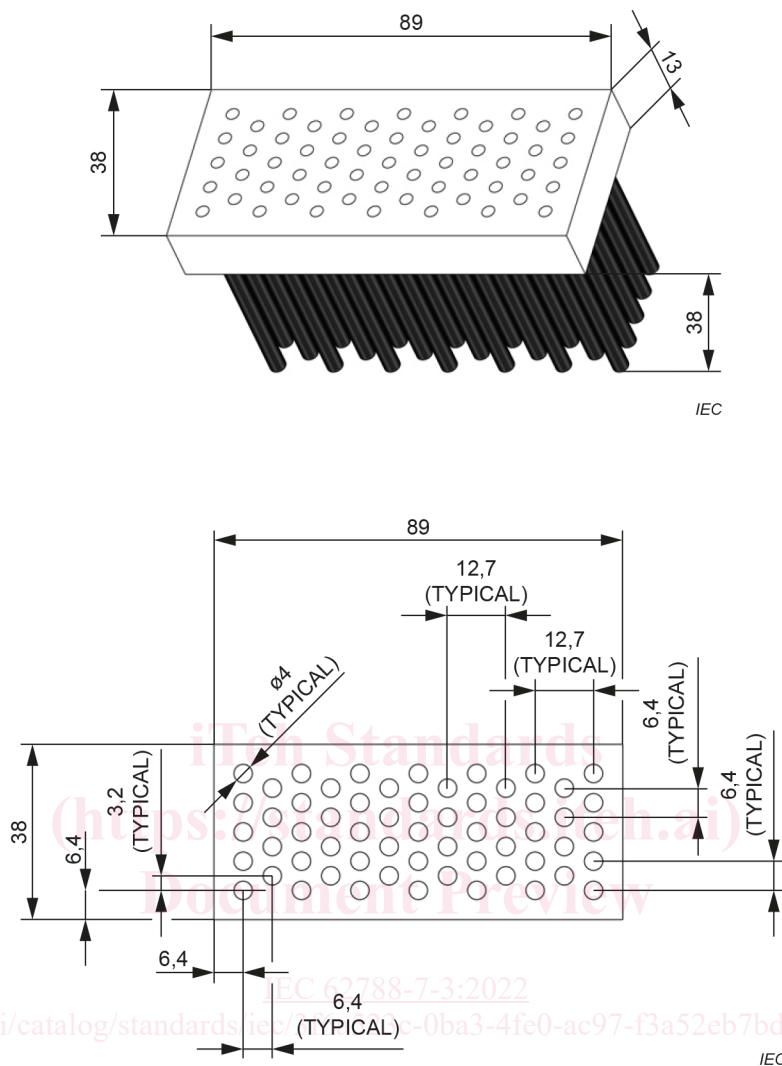


Figure 1 – Schematics showing the arrangement of bristle tufts on the linear brush

4.2.3 Abrasive medium (dry)

The dry abrasive medium shall consist of A3 (medium) AZ test dust, as specified in ISO 12103-1. The nominal abrasive concentration of $(0,7) \text{ mg}\cdot\text{cm}^{-2}\cdot\text{cycle}^{-1}$ shall be used during the test. To ensure repeatability, the test dust shall not be reused after testing. Other abrasive materials or quantities of abrasive may be used for the purposes of research and development.

NOTE The abrasive concentration of $(20 \pm 5) \text{ mg}\cdot\text{cycle}^{-1}$ when applied to the nominal area of the linear brush $(29,75) \text{ cm}^{-2}$ provides the nominal abrasive concentration of $(0,7) \text{ mg}\cdot\text{cm}^{-2}\cdot\text{cycle}^{-1}$.

Dry abrasive shall be maintained at $(23 \pm 2) ^\circ\text{C}$ and $(50 \pm 10) \% \text{ RH}$ for at least 24 h, as specified per Class 2 in ISO 291, prior to use in the linear abrasion test.

For the dry abrasive test, the brush bristles shall be maintained at $(23 \pm 2) ^\circ\text{C}$ and $(50 \pm 10) \% \text{ RH}$ for at least 24 h, as specified per Class 2 in ISO 291, prior to use in the linear abrasion test.