



SLOVENSKI STANDARD SIST ISO 4299:2001

01-junij-2001

A Ub[Ubcj Yfi XY!`8 c`c Yj Ub`Yj`Uj Y

Manganese ores -- Determination of moisture content

Minerais de manganèse -- Détermination de l'humidité

Ta slovenski standard je istoveten z: **ISO 4299:1989**

[SIST ISO 4299:2001](https://standards.iteh.ai/catalog/standards/sist/c06e5caf-66a2-4c80-87f6-683a1e2081fd/sist-iso-4299-2001)

<https://standards.iteh.ai/catalog/standards/sist/c06e5caf-66a2-4c80-87f6-683a1e2081fd/sist-iso-4299-2001>

ICS:

73.060.20 Manganove rude Manganese ores

SIST ISO 4299:2001

en

iTeh STANDARD PREVIEW **(standards.iteh.ai)**

SIST ISO 4299:2001

<https://standards.iteh.ai/catalog/standards/sist/c06e5caf-66a2-4c80-87f6-683a1e2081fd/sist-iso-4299-2001>

INTERNATIONAL STANDARD

**ISO
4299**

Second edition
1989-07-01

Manganese ores — Determination of moisture content

Minerais de manganèse — Détermination de l'humidité

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST ISO 4299:2001

<https://standards.iteh.ai/catalog/standards/sist/c06e5caf-66a2-4c80-87f6-683a1e2081fd/sist-iso-4299-2001>



Reference number
ISO 4299 : 1989 (E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council. They are approved in accordance with ISO procedures requiring at least 75 % approval by the member bodies voting.

International Standard ISO 4299 was prepared by Technical Committee ISO/TC 65, *Manganese and chromium ores*.

This second edition cancels and replaces the first edition (ISO 4299:1980) of which it constitutes a minor revision.

Annexes A and B form an integral part of this International Standard.

© ISO 1989

All rights reserved. No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Manganese ores — Determination of moisture content

1 Scope

This International Standard specifies a method for determining the mean value of the moisture content of a consignment (lot) of manganese ores, whether natural or processed, including concentrates, pellets and agglomerates.

The method is intended to be applied at the places of dispatch and/or acceptance of the ore.

Annex A specifies a method to be used in the case of adhesive or wet manganese ores. Annex B specifies methods of correction for sprinkled water and/or rain-water.

3.3 test portion : A representative part of a test sample subjected to moisture measurement.

If the entire quantity of a test sample is subjected to moisture measurement, the test sample may also be called "test portion".

4 Principle

Drying of the test portion in an oven at 105 °C and determination of the moisture content, as a percentage by mass, from the initial and dried masses.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards listed below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 4296-1 : 1984, *Manganese ores — Sampling — Part 1: Increment sampling*.

ISO 4296-2 : 1983, *Manganese ores — Sampling — Part 2: Preparation of samples*.

3 Definitions

For the purposes of this International Standard, the following definitions apply.

3.1 moisture sample : The sample taken for the determination of moisture content of the consignment or part of the consignment.

3.2 test sample : A sample prepared for moisture determination from each increment, from each sub-sample, or from the gross sample, in accordance with the method specified for the moisture sample.

5 Apparatus

5.1 Drying pans, made of stainless material (for example, stainless steel or brass), having a smooth surface, free from contamination and capable of accommodating the specified quantity of moisture sample in a layer of thickness less than 30 mm.

5.2 Drying oven, equipped with a temperature-controlling device capable of regulating the temperature at all points in the oven to within ± 5 °C of the desired temperature.

5.3 Weighing device, accurate to at least 0,05 % of the initial mass of a sample.

6 Sampling and samples

Test samples which have been taken in accordance with ISO 4296-1 and prepared in accordance with ISO 4296-2 shall be used. The mass of a test portion in relation to its whole-through sieve size is specified in table 1.

Table 1 — Minimum mass of test portion

Whole-through sieve size of test portion (mm)	Minimum mass of test portion (kg)
22,4	5
10	1

7 Procedure

7.1 Number of moisture measurements

7.1.1 If one gross sample is obtained from the consignment, four test portions shall be prepared. Two of these shall be submitted for the determination of moisture content and the other two test portions shall be reserved as duplicates in case a check determination is required.

7.1.2 If sub-samples or increments from a consignment are not combined into one gross sample, one test portion shall be prepared from each sub-sample or increment and each of these shall be submitted for the determination of moisture content.

NOTE — Samples which have been sieved in water for size determination are not to be used for determination of moisture content.

7.2 Measurement

7.2.1 Weigh a drying pan (5.1) and record its mass.

7.2.2 Spread the test portion (6) to a thickness of less than 30 mm in the tared drying pan (5.1) and weigh. Record the total mass and the initial mass of the test portion.

7.2.3 Place the drying pan with the test portion in the drying oven (5.2) set at 105 °C and maintain at this temperature for not less than 4 h.

7.2.4 Remove the drying pan with the test portion from the oven and weigh immediately while still hot.

NOTE — The weighing device (5.3) should be protected from the effects of the hot material by a suitable heat-resisting material.

7.2.5 Replace the drying pan with the test portion in the drying oven, heat for a further 1 h, and repeat the weighing.

7.2.6 Repeat the procedure described in 7.2.5 until the difference in mass between subsequent measurements becomes 0,05 % or less of the initial mass of the test portion. If, after repeated drying, the mass increases, the mass measured before the last weighing shall be used.

7.2.7 The moisture content of adhesive or wet ores shall be determined by the method specified in annex A unless the mass of the sample is small, in which case the entire mass of the sample may be dried to determine the moisture content using the procedure described above.

8 Calculation and expression of results

8.1 Moisture content of each test portion

The moisture content, w_i , expressed as a percentage by mass, shall be calculated from equation (1) and reported to the second decimal place :

$$w_i = \frac{m_1 - m_2}{m_1} \times 100 \quad \dots (1)$$

where

m_1 is the initial mass, in grams, of the test portion;

m_2 is the mass, in grams, of the test portion after drying.

8.2 Moisture content of the consignment

The moisture content of the consignment, \bar{w} , expressed as a percentage by mass, shall be calculated from one of the equations (2) to (5), as appropriate, and reported to the second decimal place.

8.2.1 When the moisture determination is conducted on a gross sample from the consignment, the moisture content, as a percentage by mass, shall be calculated from the arithmetic mean of the two results obtained from the two test portions as given by the equation

$$w = \frac{w_1 + w_2}{2} \quad \dots (2)$$

where

w_1 and w_2 are the moisture contents, as a percentage by mass, of test portions 1 and 2 respectively.

8.2.2 When the moisture determination is conducted on each sub-sample, the moisture content, as a percentage by mass, shall be calculated from the weighted mean of the results for all sub-samples considering the number of increments in each sub-sample as given by the equation

$$\bar{w} = \frac{\sum_{i=1}^k N_i w_i}{\sum_{i=1}^k N_i} \quad \dots (3)$$

where

k is the number of sub-samples;

N_i is the number of increments in the i th sub-sample;

w_i is the result of moisture determination, as a percentage by mass, of the i th sub-sample (test portion).

NOTE — If it is impracticable to sample the consignment as a whole or desirable to sample a consignment in separate parts of unequal mass as in the case of time-basis sampling, the moisture content of each part should be determined independently and the weighted mean of moisture content of the consignment calculated from the individual results as given by the equation

$$\bar{w} = \frac{\sum_{i=1}^k m_i w_i}{\sum_{i=1}^k m_i} \quad \dots (4)$$

where

k is the number of parts in the consignment;

m_i is the mass, in grams, of the i th part;

w_i is the result of moisture determination, as a percentage by mass, of the i th part.

8.2.3 When the moisture determination is conducted on each increment, the moisture content, as a percentage by mass, shall be calculated from the arithmetic mean of the results obtained as described in 8.2.1 for all the increments, as given by the equation

$$\bar{w} = \frac{\sum_{i=1}^n w_i}{n} \quad \dots (5)$$

where

n is the number of increments;

w_i is the result of moisture determination, as a percentage by mass, of the i th increment.

9 Precision

The following precision requirements relate to the precision in determining the values of moisture content in a moisture sample when moisture determinations are made in the same laboratory. The method is designed so as to obtain the values of precision, with 95 % probability, shown in table 2.

Table 2 — Precision and maximum permissible tolerances between results of duplicate determinations

Moisture content % (m/m)		Precision (absolute %)	Maximum permissible tolerance (absolute %)
>	≤		
—	5	±0,4	0,5
5	10	±0,5	0,7
10	15	±0,7	0,9
15	—	±0,8	1,1

If the values of precision and maximum tolerance obtained exceed those given in the table, the moisture determination shall be repeated.


When two duplicate determinations are carried out, the final results shall be obtained as shown in the flow chart (see figure 1).

10 Test report

The test report shall include the following information :

- reference to this International Standard;
- details necessary for the identification of the sample;
- result of the test;
- any characteristics noticed during the determination and any operations not specified in this International Standard which may have had an influence on the results.

Examples of suitable test reports are given in tables 3, 4 and 5.

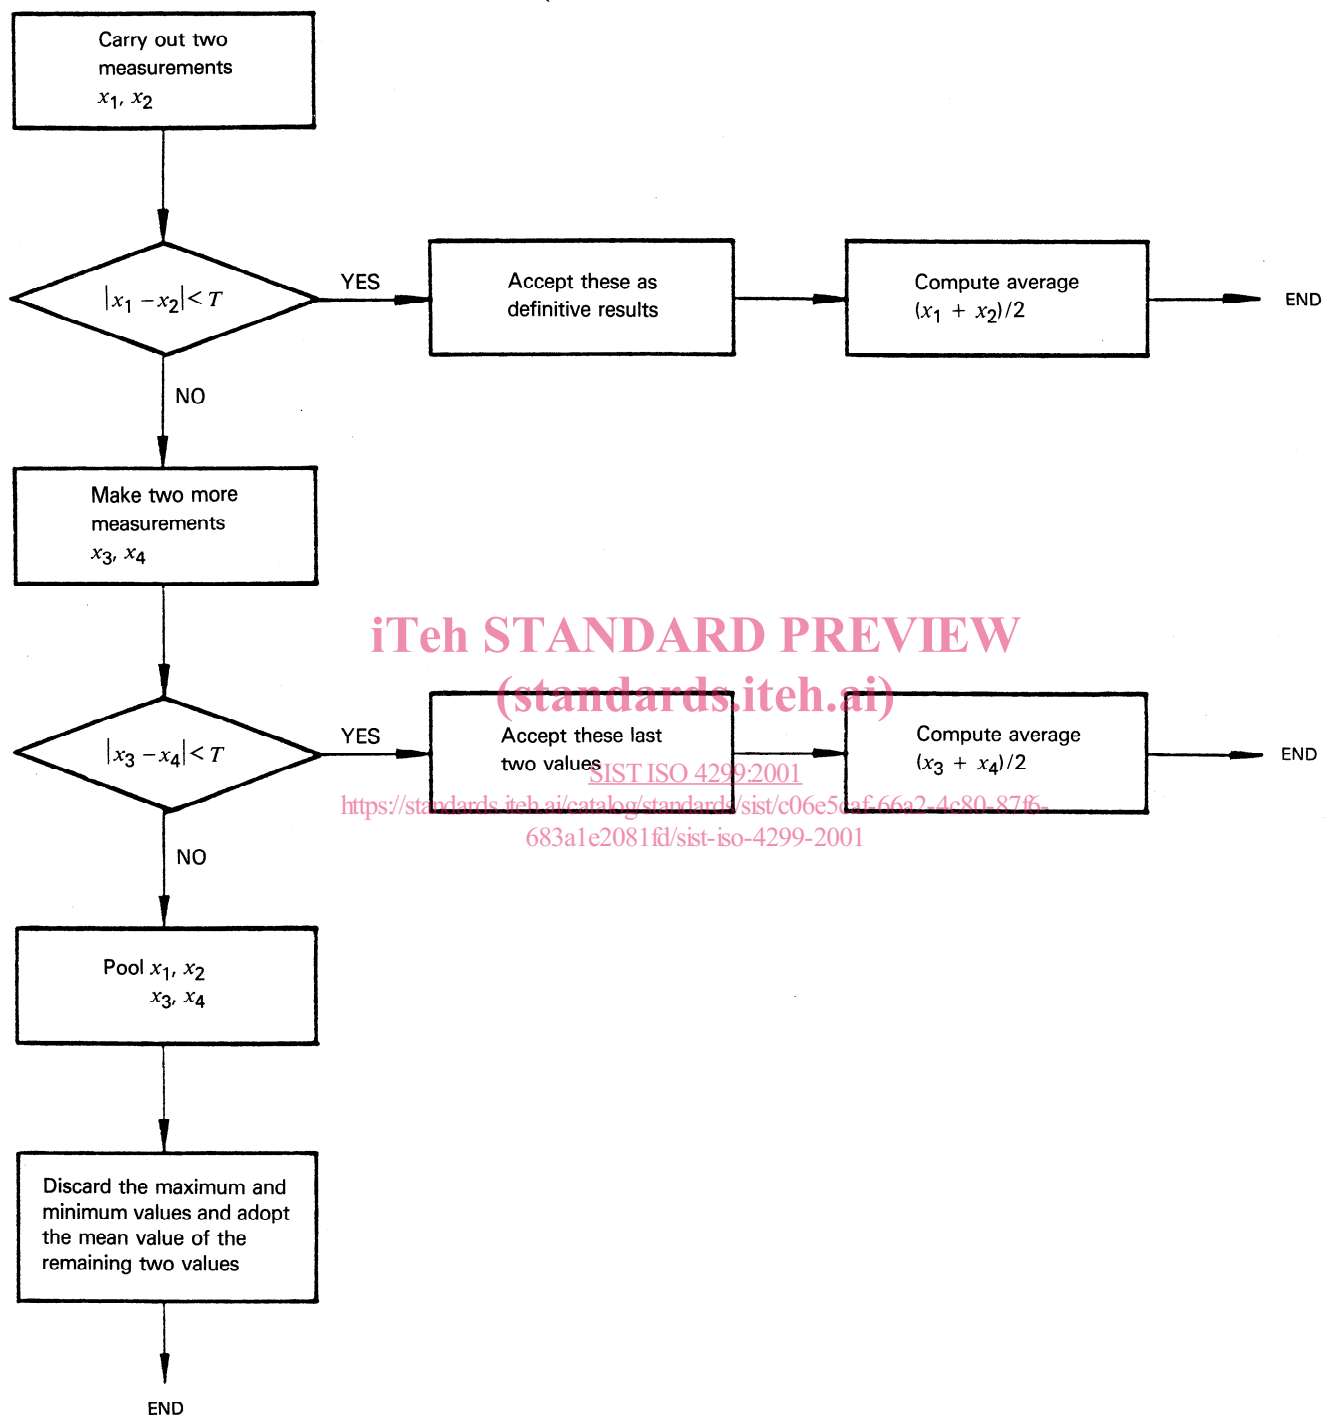

NOTE — T is the maximum permissible tolerance given in table 2.

Figure 1 — Flow chart — Procedures for processing the results of moisture determinations

Table 3 — Example of a test report for values of moisture measurement on a test portion

Type and grade of manganese ore :			
Identity and quality of consignment :			
Sample No. :	Minimum mass of sample : 5 kg	Particle size of sample : – 22,4 mm	Date :
Total mass before drying (g)	(1)		6 021
Mass of drying pan (g)	(2)		896
Initial mass of sample (g)	3 = (1) – (2)		5 125
Value of 0,05 % of initial mass of sample (g)	(4) = $\frac{(3)}{2\,000}$		2,56
Total mass after 4 h drying (g)	(5)	mass	5 592
Total mass after further 1 h drying (g)	(6)		5 583
Total mass after another 1 h drying (g)	(7)		5 581
Final loss on drying (g)	(8) = (1) – (7)		440
Moisture content, w_i (%)	(9) = $\frac{(8)}{(3)} \times 100$		8,59
Remarks :			
Assayer :			
* The difference (5) – (6) was 9 g and exceeded (4); so another 1 h drying was conducted. The difference (6) – (7) became 2 g and was less than (4). Therefore, the drying of this sample was terminated.			

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Table 4 — Example of a test report for determination of the moisture content of a gross sample

(Duplicate determinations)
<https://standards.iteh.ai/catalog/standards/sist/c0665ca1-66a2-4c80-87f6-683a1c2081fd/sist-iso-4299-2001>

Type and grade of manganese ore :			
Identity and quality of consignment :			
Sample No. :	Minimum mass of sample : 1 kg	Particle size of sample : – 10 mm	Date :
Total mass before drying (g)	(1)	1 228,4	1 220,9
Mass of drying pan (g)	(2)	204,1	196,0
Initial mass of sample (g)	(3) = (1) – (2)	1 024,3	1 024,9
Value of 0,05 % of initial mass of sample (g)	(4) = $\frac{(3)}{2\,000}$	0,51	0,51
Total mass after 4 h drying (g)	(5)	mass	1 169,6
Total mass after further 1 h drying (g)	(6)	difference	1 167,0
Total mass after another 1 h drying (g)	(7)	mass	1 161,9
Final loss on drying (g)	(8) = (1) – (7)	difference	1 158,6
Moisture content of each sample (%)	(9) = $\frac{(8)}{(3)} \times 100$	mass	1 161,7
Difference between two determinations (%)		difference	1 158,3
Maximum permissible tolerance (%)			66,7
Moisture content (%)			62,6
Remarks :			
Assayer :			