



Designation: G60 – 01 (Reapproved 2018)

Standard Practice for Conducting Cyclic Humidity Exposures¹

This standard is issued under the fixed designation G60; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This practice covers procedures for conducting cyclic humidity exposures with a corrosive dip.² It sets forth the conditions required in cyclic humidity testing.

1.2 This practice does not prescribe the type of exposure specimen or exposure periods nor the interpretation to be given to the results.

1.3 The values stated in SI units are to be regarded as standard. The values given in parentheses are for information only.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to consult and establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 *ASTM Standards:*³

[D1193 Specification for Reagent Water](#)

[G1 Practice for Preparing, Cleaning, and Evaluating Corrosion Test Specimens](#)

¹ This practice is under the jurisdiction of ASTM Committee G01 on Corrosion of Metals and is the direct responsibility of Subcommittee G01.05 on Laboratory Corrosion Tests.

Current edition approved Oct. 1, 2018. Published November 2018. Originally approved in 1979. Last previous edition approved in 2013 as G60 – 01 (2013). DOI: 10.1520/G0060-01R18.

² Opinsky, A. J., Thomson, R. F., and Boegehold, A. L., "A Cyclic Humidity Accelerated Corrosion Test for Sheet Steel," *ASTM Bulletin*, January 1953.

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

3. Significance and Use

3.1 The procedure described is used to observe the behavior of steels under exposure conditions that retard the formation of a protective type of rust. It is also used to evaluate seal coat on insulation.

3.2 This practice should not be used to rank steels that form a protective type of rust under atmospheric exposure conditions.

4. Apparatus

4.1 The apparatus required for cyclic humidity exposures consists of a test chamber, provisions for heating the chamber, a humidifying tower, a drying train, a dip mechanism, provisions for introducing and draining the solution, a supply of compressed air, specimen supports, and necessary means of control.

4.2 The size and detailed construction of the apparatus are optional, provided the conditions obtained meet the requirements of this practice.

4.3 A schematic diagram of the apparatus is shown in [Fig. 1](#).

4.4 The apparatus should be capable of providing an 8-h humidity cycle three times per day, as shown in [Fig. 2](#), and a dip cycle once a day.

4.4.1 The cyclic variation of humidity can be obtained by variation of the temperature of the water in the humidifying tower. The temperature of the water is cycled thermostatically such that the relative humidity of air bubbling through the water at a minimum rate of 1 L/min (0.04 ft³/min) will vary between 100 and 50 % when the temperature of the air in the test chamber is brought to $52 \pm 1^\circ\text{C}$ ($125 \pm 2^\circ\text{F}$).

4.4.2 The range of relative humidity can be extended by adding a drying period to the humidity cycle described above. The minimum relative humidity shall be $\leq 20\%$ and the maximum relative humidity shall be $\geq 95\%$ for each cycle.

4.4.3 Drops of solution which accumulate on the ceiling or cover of the chamber shall not be permitted to fall on the specimens being exposed.

NOTE 1—Instruments to continuously record temperature and humidity are not mandatory, but these provide the most reliable and economical

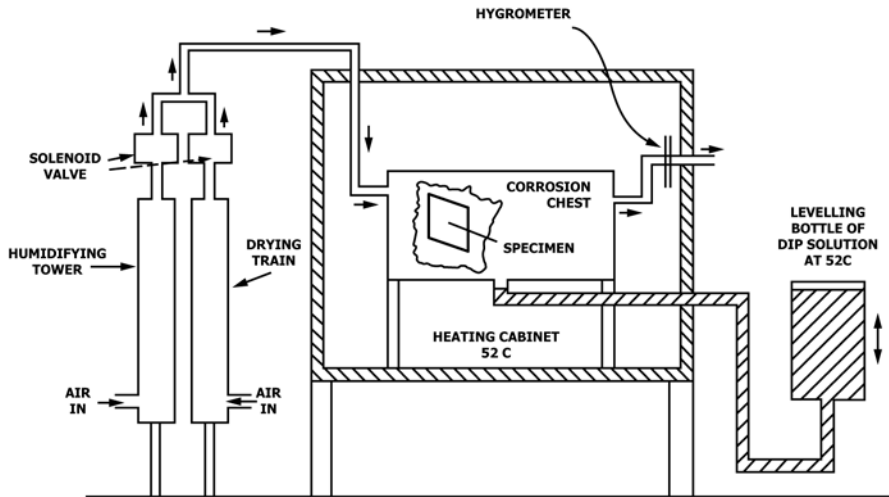


FIG. 1 Main Parts of the Cyclic Humidity Corrosion Exposure Apparatus (Schematic)

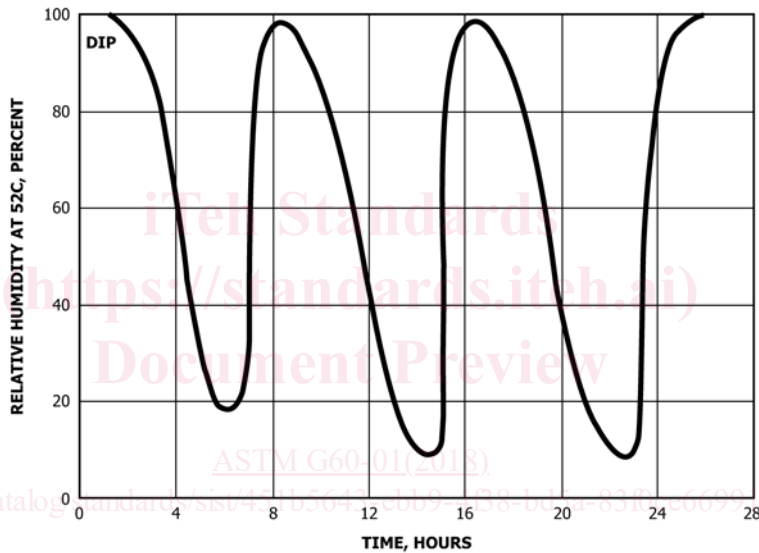


FIG. 2 Humidity Cycle (Schematic)

way of recording such information. In the absence of such instrumentation, temperature and humidity measurement shall be made, at least twice a day, at the maximum and minimum humidity in a cycle.

4.5 *Materials of Construction:*

4.5.1 The test chamber should be made of inert materials such as plastics, glass, or metals lined with impervious plastics, rubber or epoxy-type materials, or materials exhibiting equivalent corrosion resistance. Material of construction shall be such that it will not affect the corrosiveness of the exposure atmosphere.

4.5.2 The dip solution container should not be affected by or cause contamination of the dip solution.

4.6 *Specimen Supports:*

4.6.1 The specimen-supporting device should not be affected by or cause contamination of the dip solution. See **Note 2**.

4.6.2 The method of supporting specimens will vary with the apparatus used for conducting the tests, but should be designed to insulate the specimens from each other physically and electrically and to insulate the specimens from any metallic container or supporting device used within the apparatus. The specimens shall not contact any material capable of acting as a wick.

NOTE 2—Suitable materials for the construction or coating of racks and supports are glass, rubber, plastic, or suitably coated wood. Bare metal shall not be used. Specimens shall preferably be supported from the