

INTERNATIONAL STANDARD

NORME INTERNATIONALE



**Dielectric and resistive properties of solid insulating materials –
Part 3-2: Determination of resistive properties (DC methods) – Surface
resistance and surface resistivity**

**Propriétés diélectriques et résistives des matériaux isolants solides –
Partie 3-2: Détermination des propriétés résistives (méthodes en courant
continu) – Résistance superficielle et résistivité superficielle**

<https://standards.iteh.ai/catalog/standards/sist/1a57877c-ec4b-448a-ae25-2ef9e24dd786/iec-62631-3-2-2023>





THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2023 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de l'IEC ou du Comité national de l'IEC du pays du demandeur. Si vous avez des questions sur le copyright de l'IEC ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de l'IEC de votre pays de résidence.

IEC Secretariat
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, ...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

IEC Products & Services Portal - products.iec.ch

Discover our powerful search engine and read freely all the publications previews. With a subscription you will always have access to up to date content tailored to your needs.

Electropedia - www.electropedia.org

The world's leading online dictionary on electrotechnology, containing more than 22 300 terminological entries in English and French, with equivalent terms in 19 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

A propos de l'IEC

La Commission Electrotechnique Internationale (IEC) est la première organisation mondiale qui élabore et publie des Normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications IEC

Le contenu technique des publications IEC est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

Recherche de publications IEC -

webstore.iec.ch/advsearchform

La recherche avancée permet de trouver des publications IEC en utilisant différents critères (numéro de référence, texte, comité d'études, ...). Elle donne aussi des informations sur les projets et les publications remplacées ou retirées.

IEC Just Published - webstore.iec.ch/justpublished

Restez informé sur les nouvelles publications IEC. Just Published détaille les nouvelles publications parues. Disponible en ligne et une fois par mois par email.

Service Clients - webstore.iec.ch/csc

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions contactez-nous: sales@iec.ch.

IEC Products & Services Portal - products.iec.ch

Découvrez notre puissant moteur de recherche et consultez gratuitement tous les aperçus des publications. Avec un abonnement, vous aurez toujours accès à un contenu à jour adapté à vos besoins.

Electropedia - www.electropedia.org

Le premier dictionnaire d'électrotechnologie en ligne au monde, avec plus de 22 300 articles terminologiques en anglais et en français, ainsi que les termes équivalents dans 19 langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International (IEV) en ligne.

INTERNATIONAL STANDARD

NORME INTERNATIONALE



**Dielectric and resistive properties of solid insulating materials –
Part 3-2: Determination of resistive properties (DC methods) – Surface
resistance and surface resistivity**

**Propriétés diélectriques et résistives des matériaux isolants solides –
Partie 3-2: Détermination des propriétés résistives (méthodes en courant
continu) – Résistance superficielle et résistivité superficielle**

<https://standards.iteh.ai/catalog/standards/sist/1a57877c-ec4b-448a-ae25-2ef9e24dd786/iec-62631-3-2-2023>

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

COMMISSION
ELECTROTECHNIQUE
INTERNATIONALE

ICS 17.220.99, 29.035.01

ISBN 978-2-8322-7549-8

**Warning! Make sure that you obtained this publication from an authorized distributor.
Attention! Veuillez vous assurer que vous avez obtenu cette publication via un distributeur agréé.**

CONTENTS

FOREWORD.....	4
1 Scope.....	6
2 Normative references	6
3 Terms and definitions	6
4 Significance.....	8
5 Method of test	8
5.1 General.....	8
5.2 Voltage	9
5.3 Equipment	9
5.3.1 General	9
5.3.2 Accuracy	9
5.3.3 Voltage source	10
5.3.4 Electrode arrangements.....	10
5.4 Test circuit.....	14
5.5 Calibration	15
5.6 Test specimen	15
5.6.1 Recommended dimensions of test specimen and electrode arrangements	15
5.6.2 Manufacturing of test specimen	15
5.6.3 Number of test specimens	16
5.6.4 Application of conductive means.....	16
5.6.5 Conditioning and pre-treatment of test specimen	16
5.7 Test procedure.....	17
6 Calculation of surface resistivity	17
6.1 For electrode arrangements A, B, D and E.....	17
6.2 For electrode arrangement C	17
7 Test report.....	18
8 Repeatability and reproducibility	18
Annex A (informative) Specimen dimensions and electrode arrangements	19
Annex B (informative) Comparative verification study on surface resistivities using different electrode arrangements (type C and type E)	20
B.1 General.....	20
B.2 Inter-laboratory trial conditions.....	20
B.2.1 General	20
B.2.2 Test specimens	20
B.2.3 Electrode types, conductive materials and test voltage	20
B.2.4 Test conditions	21
B.3 Summary of the test results	21
B.4 Inter-laboratory trial outcomes and suggestions for IEC 62631-3-2	22
B.5 Detailed inter-laboratory results	22
B.5.1 General	22
B.5.2 Laboratories results by different groups of electrode types and conductive materials for the different test specimens	23
B.5.3 Laboratory 2 results comparing different electrode types and conductive materials	29
B.5.4 Laboratory 3 results – Electrode type C with and without use of conductive silver paint	31

Bibliography.....	33
Figure 1 – Electrode arrangement A (example)	11
Figure 2 – Electrode arrangement B (example)	12
Figure 3 – Electrode arrangement C (example)	13
Figure 4 – Connection diagram of measurement with two- and three-terminal electrode arrangements.....	15
Figure B.1 – Surface resistivity equations for the used electrodes.....	21
Table 1 – Typical electrode dimensions for electrode arrangement C	13
Table A.1 – Recommended test specimen dimensions and electrode arrangements for specific products	19
Table B.1 – Test specimens characteristics	20
Table B.2 – Test conditions per specific participant.....	21
Table B.3 – Summary of the test results.....	22
Table B.4 – Polybutylene terephthalate (PBT) test specimen results – Electrode type C with conductive rubber	23
Table B.5 – Polyamide 66 (PA66) test specimen results – Electrode type C with conductive rubber	24
Table B.6 – Polybutylene terephthalate (PBT) test specimen results – Electrode type C with conductive silver paint	25
Table B.7 – Polyamide 66 (PA66) test specimen results – Electrode type C with conductive silver paint	26
Table B.8 – Polybutylene terephthalate (PBT) test specimen results – Electrode type E with conductive silver paint	27
Table B.9 – Polyamide 66 (PA66) test specimen results – Electrode type E with conductive silver paint	28
Table B.10 – Laboratory 2 results – Polybutylene terephthalate (PBT) – Different electrodes and conductive materials	29
Table B.11 – Laboratory 2 results – Polyamide 66 (PA66) – Different electrodes and conductive materials	30
Table B.12 – Laboratory 3 results – Polybutylene terephthalate (PBT) – Electrode type C with and without conductive silver paint.....	31
Table B.13 – Laboratory 3 results – Polyamide 66 (PA66) – Electrode type C with and without conductive silver paint	32

INTERNATIONAL ELECTROTECHNICAL COMMISSION

**DIELECTRIC AND RESISTIVE PROPERTIES
OF SOLID INSULATING MATERIALS –****Part 3-2: Determination of resistive properties (DC methods) –
Surface resistance and surface resistivity**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as “IEC Publication(s)”). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) IEC draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). IEC takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, IEC had not received notice of (a) patent(s), which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at <https://patents.iec.ch>. IEC shall not be held responsible for identifying any or all such patent rights.

IEC 62631-3-2 has been prepared by IEC technical committee 112: Evaluation and qualification of electrical insulating materials and systems. It is an International Standard.

This second edition cancels and replaces the first edition published in 2015. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) descriptions of the electrode arrangements have been clarified;
- b) new descriptions of the conductive means have been added;

- c) a new informative Annex B summarizing the results of the comparative verification study on surface resistivities using different electrode arrangements has been added.

The text of this International Standard is based on the following documents:

Draft	Report on voting
112/612/FDIS	112/619/RVD

Full information on the voting for its approval can be found in the report on voting indicated in the above table.

The language used for the development of this International Standard is English.

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at www.iec.ch/members_experts/refdocs. The main document types developed by IEC are described in greater detail at www.iec.ch/publications.

A list of all parts in the IEC 62631 series, published under the general title *Dielectric and resistive properties of solid insulating materials*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under webstore.iec.ch in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn, or
- revised.

IEC 62631-3-2:2023

IMPORTANT – The "colour inside" logo on the cover page of this document indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

DIELECTRIC AND RESISTIVE PROPERTIES OF SOLID INSULATING MATERIALS –

Part 3-2: Determination of resistive properties (DC methods) – Surface resistance and surface resistivity

1 Scope

This part of IEC 62631 describes methods of test for the determination of surface resistance and surface resistivity of electrical insulation materials by applying DC voltage.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60212, *Standard conditions for use prior to and during the testing of solid electrical insulating materials*

IEC 62631-3-1, *Dielectric and resistive properties of solid insulating materials – Part 3-1: Determination of resistive properties (DC methods) – Volume resistance and volume resistivity – General method*

IEC 62631-3-3, *Dielectric and resistive properties of solid insulating materials – Part 3-3: Determination of resistive properties (DC methods) – Insulation resistance*

<https://standards.iteh.ai/catalog/standards/sist/1a57877c-ec4b-448a-ae25-2ef9e24dd786/iec-62631-3-2-2023>

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- IEC Electropedia: available at <https://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp>

3.1

electrode arrangement

electrical conductive bodies on the surface of a test specimen

Note 1 to entry: The arrangement of electrodes should include procedures to ascertain sufficient contact to the surface (e.g. by means of conducting paint) or the use of adequate mechanical system applying the necessary contact force to the test specimen's surface or both.

3.1.1

annular electrode

central circular planar electrode with a surrounding ring electrode separated by a gap

SEE: Figure 3.

Note 1 to entry: Guard electrode systems as described in IEC 62321-3-1 are of similar shape. In the case of surface resistance, the ring electrode does not have the function of a guard; guard functionality, however, is provided by the opposite electrode.

3.1.2

line electrode

electrode arrangement provided by two parallel lines, separated by a gap, applied to the test specimen's surface using a conductive material

SEE: Figure 2.

3.1.3

spring loaded electrode

line electrode system using two parallel lines of conducting spring tongues with sharp edges, separated by a gap

SEE: Figure 1.

3.2

measured resistance

ratio of a DC voltage applied to an electrode arrangement in contact with a test specimen to the current between them measured with sufficient precision

Note 1 to entry: A three-terminal electrode arrangement can be used to exclude undesired volume currents from the determination of the measured resistance.

Note 2 to entry: A Wheatstone bridge can also be used to compare the measured resistance with a standard resistor. However, Wheatstone bridges are not commonly used anymore.

Note 3 to entry: According to IEC 60050-121: Electromagnetism, "conductivity" (IEV 121-12-03) is defined as "the scalar or tensor quantity, the product of which by the electric field strength in a medium is equal to the electric current density" and "resistivity" (IEV 121-12-04) as "the inverse of the conductivity when this inverse exists". Measured in this way, the surface resistivity integrates different electrical conduction pathways at the surface of the material or in its nearby volume, with the possible presence of heterogeneities; it includes the effect of possible polarization phenomena at the electrodes. Therefore, it is considered as an averaged value.

3.3

surface resistance

R_S

measured resistance between any electrode arrangement defined in IEC 62361-3-2

Note 1 to entry: Depending on the electrode arrangement used, it is designated as R_{SA} , R_{SB} , R_{SC} , R_{SD} or R_{SE} with surface resistance, R_S expressed in Ω .

Note 2 to entry: An indeterminable part of the resistance inside the material is also included in surface resistance during the measurement of this resistance.

3.4

R_{SC}

surface resistance between annular electrodes

measured resistance between the inner circular area of an annular electrode system and the outer circular ring electrode

3.5

R_{SD}

surface resistance between line electrodes

measured resistance between line electrodes

3.6 R_{SE}

surface resistance between line electrodes for small plates
 measured resistance between line electrodes for small plates

3.7 R_{SB}

surface resistance between small line electrodes
 measured resistance between small line electrodes

3.8 R_{SA}

surface resistance between spring load electrodes
 measured resistance between spring loaded electrodes

3.9**surface resistivity** σ /square

surface resistance reduced to a square

Note 1 to entry: The numerical value of surface resistivity is independent of the size of the square.

Note 2 to entry: Surface resistance R_{SA} , R_{SB} , R_{SC} , R_{SD} and R_{SE} referred to a square, are expressed as σ_A , σ_B , σ_C , σ_D and σ_E respectively.

Note 3 to entry: Surface resistivity is often expressed by the non-standardized unit Ω per square, to show that the electrode dimension has been taken into account by calculating the specific value.

Note 4 to entry: The surface resistivity is often used to compare one kind of surface characteristic of a sample material with those of other materials. It can be compared for materials only if identical standardized dimensions of the electrodes are used. Recommended dimensions are given in 5.3.

4 Significance

Insulating materials are used in general to electrically isolate components of an electrical system from each other and from the earth. Solid insulating materials can also provide mechanical support. For this purpose, it is generally desirable to have the insulation resistance as high as possible, consistent with acceptable mechanical, chemical and heat resistance properties.

Surface resistance is, as volume resistance, a part of the insulating resistance.

Insulating resistance shall be determined according to IEC 62631-3-3 and volume resistance according to IEC 62631-3-1.

Surface resistance supplies information on the electrical resistances of the surface of materials and products. Surface resistance, however, for its major part is not a materials' property. Surface resistance depends mainly on processing parameters, environmental conditions, surface ageing phenomena and pollution, etc.

NOTE Depending on the specific application, different electrode arrangements can be preferable.

5 Method of test**5.1 General**

This general method describes common values for general measurements. If a method for a specific type of material is described in this document, the specific method shall be used.

Different types of electrodes can be used, depending on the specific measurement or product demands. For instance, on surfaces with a curved shape, a small line electrode can be advantageous. Spring loaded electrodes provide measurements with low effort on products and are optimal for materials which have to be conditioned before the test. If not already stipulated by a product standard, the choice of the electrode arrangement shall be made considering the typical application.

If test specimens are made from materials (e.g. soft rubber) whose dimensions will change significantly as a result of the force applied by the electrodes on them, these electrodes are not applicable and an alternative arrangement shall be used.

If no information about the application is available, small line electrodes (R_{SB}) are recommended.

5.2 Voltage

The measuring voltage should preferably be 10 V, 100 V, 500 V, 1 000 V, 10 000 V.

If not otherwise specified by the relevant product standard, a voltage of 100 V shall be used.

Technical committees shall specify the preferred test voltage when referring to this document.

NOTE 1 Partial discharge can lead to erroneous measurements when a specific inception voltage is exceeded. In air, below 340 V, no partial discharges will occur.

NOTE 2 The ripple of the voltage source is important. A typical value for 100 V is $< 5 \times 10^{-5}$ peak to peak.

5.3 Equipment

5.3.1 General

Care should be taken that the surface resistance is not negatively influenced by parasitic resistances parallel to the electrode arrangement, such as the resistance of test supports or cable isolation.

To prevent measuring errors for measured resistances higher than $10^{10} \Omega$, shielded cables and shielded measuring cabinets shall be used.

For the determination of surface resistance and surface resistivity, different electrode arrangements can be used. The evaluation of surface resistivity is dependent on the selected electrode arrangement.

NOTE Comparison between measurement results can be done only between measurements performed using the same electrode arrangements and conductive means.

5.3.2 Accuracy

Any suitable equipment can be used. The measuring device shall be capable of determining the unknown resistance with an overall accuracy of at least

- ± 10 % for resistances less than $10^{10} \Omega$;
- ± 20 % for resistances between $10^{10} \Omega$ and $10^{14} \Omega$; and
- ± 50 % for resistances higher than $10^{14} \Omega$.

NOTE The provided accuracies have been confirmed through the round robin test results reported in Annex B.

5.3.3 Voltage source

A source of steady direct voltage is required. This can be provided either by batteries or by rectified and stabilized power supply. The degree of stability required is such that the change in current due to any change in voltage is negligible compared with the current to be measured.

5.3.4 Electrode arrangements

5.3.4.1 General

Electrode arrangements consist of the combination of electrodes and conductive means. The conductive means shall be applied to the test specimen before performing the measurements. Electrodes are then placed in contact with the conductive means applied on the test specimen in order to perform measurements.

NOTE Annex B contains the results of the comparative verification study on surface resistivities using different electrode arrangements.

5.3.4.2 Electrode arrangement A – Spring loaded electrodes


The electrode arrangement A shall consist of two flexible metal knife-edges with a length of 100 mm and a gap distance of 10 mm as shown in Figure 1.

No guard electrode is used. The metal knife-edges shall consist of individual spring tongues arranged next to each other about 0,3 mm apart and each with a length not exceeding 5,0 mm and 0,3 mm thick. The contact force shall be high enough so that all tongues or segments rest against the surface of the test specimen, but without damaging the surface.

A piece of metal exerting the contact force shall be applied with high-grade insulation where in contact with the specimen.

<https://standards.iteh.ai/standards/sist/1a57877c-ec4b-448a-ae25-2ef9e24dd786/iec-62631-3-2-2023>

<https://standards.iteh.ai/catalog/standards/sist/1a57877c-ec4b-448a-ae25-2ef9e24dd786/iec-62631-3-2-2023>

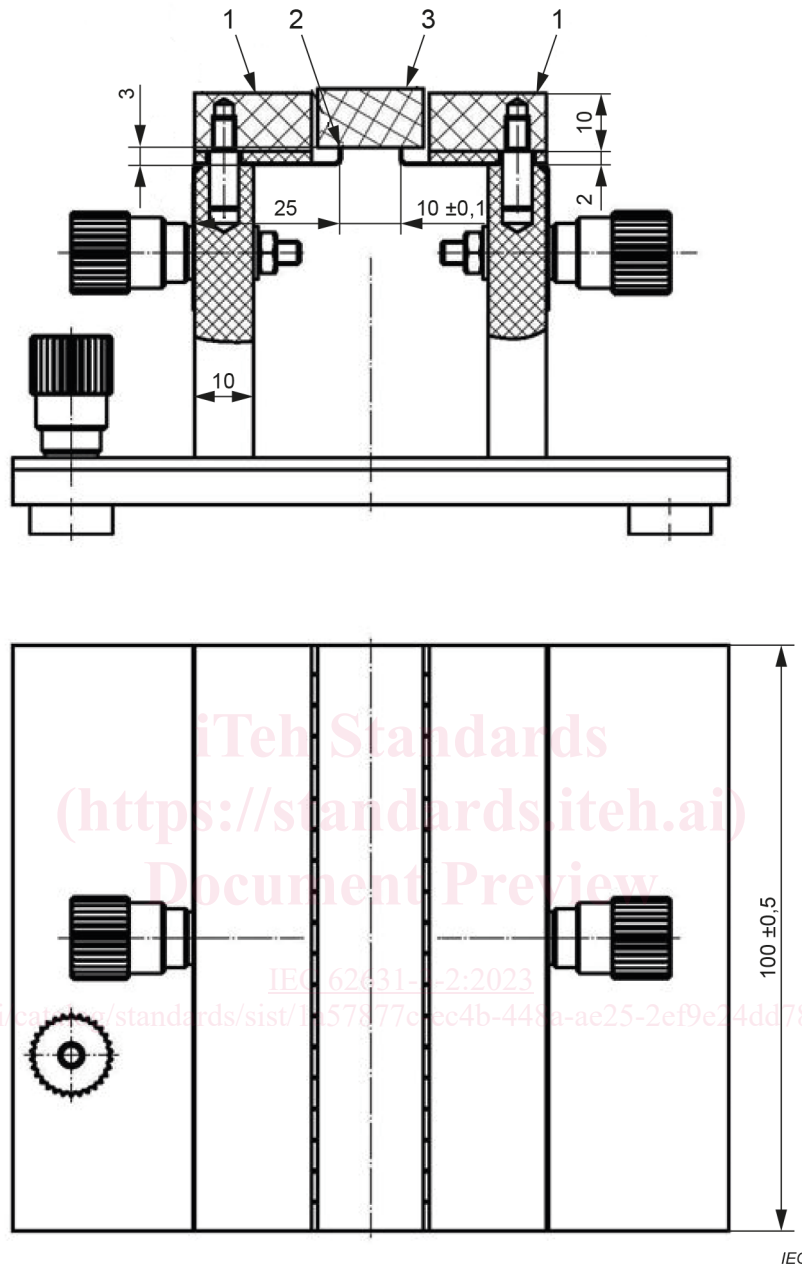**Key**


- 1 guide bar (detachable)
- 2 metal knife-edges
- 3 specimen

Figure 1 – Electrode arrangement A (example)**5.3.4.3 Electrode arrangement B – Small line electrodes**

Electrode arrangement B shall consist of a two-terminal collector with conductive blades being in contact with the conductive means on the test specimen, as shown in Figure 2. No guard electrode is used.

For the purpose of electrode arrangement B, conductive means shall be applied as two 1,5 mm wide lines with a length of 25,0 mm and a gap distance of 2,0 mm. Lines shall be applied before conditioning.

Types of conductive means and the related applications are described in 5.6.4.

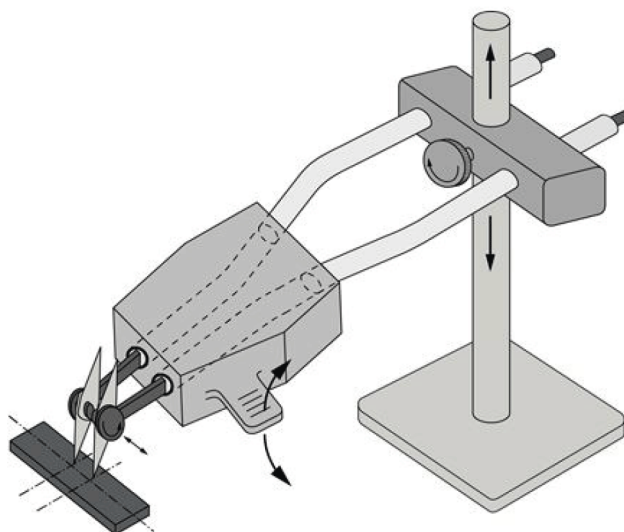

IEC

Figure 2 – Electrode arrangement B (example)

5.3.4.4 Electrode arrangement C – Annular electrodes

Electrode arrangement C is a three-terminal electrode system, as shown in Figure 3. On one side of the test specimen, annular electrodes are applied. The opposite surface of the test specimen shall be covered by a guard electrode, not smaller than the area covered by the corresponding electrodes.

[IEC 62631-3-2:2023](https://standards.iteh.ai/catalog/standards/sist/1a57877c-ec4b-448a-ae25-2ef9e24dd786/iec-62631-3-2-2023)

<https://standards.iteh.ai/catalog/standards/sist/1a57877c-ec4b-448a-ae25-2ef9e24dd786/iec-62631-3-2-2023>