

INTERNATIONAL STANDARD

NORME INTERNATIONALE



HORIZONTAL PUBLICATION
PUBLICATION HORIZONTALE

Fire hazard testing – Part 2-11: Glowing/hot-wire based test methods – Glow-wire flammability test method for end products (GWEPT)

Essais relatifs aux risques du feu – Partie 2-11: Essais au fil incandescent/chauffant – Méthode d'essai d'inflammabilité pour produits finis (GWEPT)



THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2021 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de l'IEC ou du Comité national de l'IEC du pays du demandeur. Si vous avez des questions sur le copyright de l'IEC ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de l'IEC de votre pays de résidence.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, ...). It also gives information on projects, replaced and withdrawn publications.

IEC online collection - oc.iec.ch

Discover our powerful search engine and read freely all the publications previews. With a subscription you will always have access to up to date content tailored to your needs.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

Electropedia - www.electropedia.org

The world's leading online dictionary on electrotechnology, containing more than 22 000 terminological entries in English and French, with equivalent terms in 18 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

A propos de l'IEC

La Commission Electrotechnique Internationale (IEC) est la première organisation mondiale qui élabore et publie des Normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications IEC

Le contenu technique des publications IEC est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

Recherche de publications IEC -

webstore.iec.ch/advsearchform

La recherche avancée permet de trouver des publications IEC en utilisant différents critères (numéro de référence, texte, comité d'études, ...). Elle donne aussi des informations sur les projets et les publications remplacées ou retirées.

IEC online collection - oc.iec.ch

Découvrez notre puissant moteur de recherche et consultez gratuitement tous les aperçus des publications. Avec un abonnement, vous aurez toujours accès à un contenu à jour adapté à vos besoins.

IEC Just Published - webstore.iec.ch/justpublished

Restez informé sur les nouvelles publications IEC. Just Published détaille les nouvelles publications parues. Disponible en ligne et une fois par mois par email.

Electropedia - www.electropedia.org

Le premier dictionnaire d'électrotechnologie en ligne au monde, avec plus de 22 000 articles terminologiques en anglais et en français, ainsi que les termes équivalents dans 16 langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International (IEV) en ligne.

Service Clients - webstore.iec.ch/csc

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions contactez-nous: sales@iec.ch.

INTERNATIONAL STANDARD

NORME INTERNATIONALE



HORIZONTAL PUBLICATION
PUBLICATION HORIZONTALE

Fire hazard testing – Part 2-11: Glowing/hot-wire based test methods – Glow-wire flammability test method for end products (GWEPT)

Essais relatifs aux risques du feu – Partie 2-11: Essais au fil incandescent/chauffant – Méthode d'essai d'inflammabilité pour produits finis (GWEPT)

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

COMMISSION
ELECTROTECHNIQUE
INTERNATIONALE

ICS 13.220.40; 29.020

ISBN 978-2-8322-1011-0

**Warning! Make sure that you obtained this publication from an authorized distributor.
Attention! Veuillez vous assurer que vous avez obtenu cette publication via un distributeur agréé.**

CONTENTS

| | |
|--|----|
| FOREWORD | 3 |
| INTRODUCTION | 5 |
| 1 Scope | 6 |
| 2 Normative references | 6 |
| 3 Terms and definitions | 6 |
| 4 Test specimens | 8 |
| 4.1 General | 8 |
| 4.2 Complete end product | 8 |
| 4.3 Partial end product (alternative) | 9 |
| 4.4 Test considerations and limitations associated with the specimen configuration | 9 |
| 5 Test apparatus | 10 |
| 6 Verification of the temperature measuring system | 10 |
| 7 Conditioning | 10 |
| 7.1 Conditioning of test specimens | 10 |
| 7.2 Conditioning of specified layers | 11 |
| 7.3 Testing conditions | 11 |
| 8 Test procedure | 11 |
| 8.1 General | 11 |
| 8.2 Test temperatures | 11 |
| 8.3 Number of test specimens | 12 |
| 9 Observations and measurements | 12 |
| 10 Evaluation of test results | 12 |
| 11 Test report | 12 |
| 12 Information to be given in the relevant product standard | 13 |
| Annex A (informative) Suggested GWEPT temperatures | 14 |
| Bibliography | 16 |
| | |
| Figure 1 – Small parts | 10 |
| Figure A.1 – Suggested GWEPT temperatures | 15 |
| | |
| Table 1 – Test temperatures | 11 |

iTech STANDARD PREVIEW
(standards.itech.ai)

IEC 60695-2-11:2021
<https://standards.itech.ai/catalog/standards/sist/17b5056b-b0dc-4e55-95b4-536ab552c56b/iec-60695-2-11-2021>

INTERNATIONAL ELECTROTECHNICAL COMMISSION

FIRE HAZARD TESTING –**Part 2-11: Glowing/hot-wire based test methods –
Glow-wire flammability test method for end products (GWEPT)**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

IEC 60695-2-11 has been prepared by IEC technical committee 89: Fire hazard testing. It is an International Standard.

This third edition cancels and replaces the second edition published in 2014. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) Numerous terms and definitions relevant to this document have been added to Clause 3.

The text of this International Standard is based on the following documents:

| FDIS | Report on voting |
|--------------|------------------|
| 89/1536/FDIS | 89/1544/RVD |

Full information on the voting for its approval can be found in the report on voting indicated in the above table.

The language used for the development of this International Standard is English.

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at www.iec.ch/members_experts/refdocs. The main document types developed by IEC are described in greater detail at www.iec.ch/standardsdev/publications.

It has the status of a basic safety publication in accordance with IEC Guide 104.

This standard is to be used in conjunction with IEC 60695-2-10.

A list of all the parts in the IEC 60695 series, under the general title *Fire hazard testing*, can be found on the IEC web site.

In this standard, the following print types are used:

- terms defined in Clause 3: in **bold type**

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under webstore.iec.ch in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

INTRODUCTION

In the design of any electrotechnical product, the risk of fire and the potential hazards associated with fire need to be considered. In this respect the objective within the design of component, circuit, and product design, as well as the choice of the materials, is to reduce to acceptable levels the potential risks of fire during normal operating conditions, reasonable foreseeable abnormal use, malfunction, and/or failure. IEC 60695-1-10 [1]¹, together with its companion IEC 60695-1-11 [2], has been developed to provide guidance on how this is to be accomplished.

The primary aims of IEC 60695-1-10 and IEC 60695-1-11 are to provide guidance on how to:

- a) prevent ignition caused by an electrically energized component part, and
- b) confine any resulting fire within the bounds of the enclosure of the electrotechnical product in the event of ignition.

Secondary aims of IEC 60695-1-10 and IEC 60695-1-11 include the minimization of any flame spread beyond the product's enclosure and the minimization of harmful effects of fire effluents such as heat, smoke, toxicity and/or corrosivity.

Fires involving electrotechnical products can also be initiated from external non-electrical sources. Considerations of this nature are normally dealt with in the overall fire hazard assessment.

In electrotechnical equipment, overheated metal parts can act as ignition sources. In glow-wire tests, a glowing wire is used to simulate such an ignition source.

IEC 60695-2-10 describes a glow-wire test apparatus and common test procedure, IEC 60695-2-12 [3] describes a glow-wire flammability index (GWFI) test method for materials, and IEC 60695-2-13 [4] describes a glow-wire ignition temperature (GWIT) test method for materials.

This document is used to assess the reaction of end products to heat caused by contact with an electrically heated wire under controlled laboratory conditions. This may be useful for the evaluation of end products that may be exposed to excess thermal stress such as a fault current flowing through a wire, overloading of components, and/or bad connections. It should not be used to solely describe or appraise the fire hazard or fire risk of products, or assemblies under actual fire conditions. However, results of this test can be used as elements of a fire hazard assessment which takes into account all of the factors which are pertinent to a particular end use.

This document may involve hazardous materials, operations, and equipment. It does not purport to address all of the safety problems associated with its use. It is the responsibility of the user of this document to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

¹ Numbers in square brackets refer to the bibliography.

FIRE HAZARD TESTING –

Part 2-11: Glowing/hot-wire based test methods – Glow-wire flammability test method for end products (GWEPT)

1 Scope

This part of IEC 60695 specifies a test method on an end product. It is intended to simulate the effects of thermal stresses produced by an electrically heated source to represent a fire hazard.

This test method is used to check that, under defined test conditions, an end product exposed to an electrically heated source has either a limited ability to ignite or, if it ignites, a limited ability to propagate flame. However, the fire hazard analysis, the flammability aspects and the flame spreading to other products are not covered by this document.

This basic safety publication focusing on safety test method(s) is primarily intended for use by technical committees in the preparation of safety publications in accordance with the principles laid down in IEC Guide 104 and ISO/IEC Guide 51.

One of the responsibilities of a technical committee is, wherever applicable, to make use of basic safety publications in the preparation of its publications.

2 Normative references

[IEC 60695-2-11:2021](#)

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60695-2-10, *Fire hazard testing – Part 2-10: Glowing/hot-wire based test methods – Glow-wire apparatus and common test procedure*

IEC 60695-4:2012, *Fire hazard testing – Part 4: Terminology concerning fire tests for electrotechnical products*

ISO 13943:2017, *Fire safety – Vocabulary*

3 Terms and definitions

For the purpose of this document, the terms and definitions given in ISO 13943:2017 and IEC 60695-4:2012, some of which are reproduced below for the user's convenience, and in IEC 60695-2-10 regarding times and durations, and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1

burn, intransitive verb
undergo combustion

[SOURCE: ISO 13943:2017, 3.34]

3.2

combustible, adjective

capable of being ignited and burned

[SOURCE: ISO 13943:2017, 3.52]

3.3

combustion

exothermic reaction of a substance with an oxidizing agent

Note 1 to entry: Combustion generally emits fire effluent accompanied by flames and/or glowing.

[SOURCE: ISO 13943:2017, 3.55]

3.4

enclosure

<electrotechnical> external casing protecting the electrical and mechanical parts of apparatus

Note 1 to entry: The term excludes cables.

[SOURCE: ISO 13943:2017, 3.93]

3.5

end product

product that is ready for use without modification

Note 1 to entry: An end product can be a component of another end product.

[SOURCE: IEC 60695-4:2012, 3.2.7]

3.6

fire hazard

potential for harm associated with fire

Note 1 to entry: Alternatively, fire hazard can be a physical object or condition with a potential for an undesirable consequence from fire.

[SOURCE: ISO 13943:2017, 3.131]

3.7

fire hazard assessment

evaluation of the possible causes of fire, the possibility and nature of subsequent fire growth, and the possible consequences of fire

[SOURCE: IEC 60695-4:2012, 3.2.10]

3.8

fire risk

estimation of expected fire loss that combines the potential for harm in various fire scenarios that can occur with the probabilities of occurrence of those scenarios

Note 1 to entry: An alternative definition of fire risk is, "combination of the probability of a fire and a quantified measure of its consequence".

Note 2 to entry: Fire risk is often calculated as the product of probability and consequence.

[SOURCE: ISO 13943:2017, 3.145]

**3.9
flame**

rapid, self-sustaining, sub-sonic propagation of combustion in a gaseous medium, usually with emission of light

[SOURCE: ISO 13943:2017, 3.159]

**3.10
flame spread**

propagation of a flame front

[SOURCE: ISO 13943:2017, 3.168]

**3.11
flammability**

ability of a material or product to burn with a flame under specified conditions

[SOURCE: ISO 13943:2017, 3.178]

**3.12
glowing**, adjective

emitting light without flame from the combustion of a material in the solid phase

**3.13
ignition**

DEPRECATED: sustained ignition
<general> initiation of combustion

[SOURCE: ISO 13943:2017, 3.217]

iTeh STANDARD PREVIEW
(standards.iteh.ai)
<https://standards.iteh.ai/catalog/standards/sist/17b5056b-b0dc-4e55-95b4-536ab552c56b/iec-60695-2-11-2021>
IEC 60695-2-11:2021

**3.14
insignificant mass**

insufficient combustible material to constitute a fire hazard

Note 1 to entry: A default value is 2 g, but product TCs may assign a different value appropriate to the product type and scale.

[SOURCE: IEC 60695-4:2012, 3.2.16]

**3.15
small part**

part with a dimension less than the minimum specified for the relevant test method

[SOURCE: IEC 60695-4:2012, 3.2.25]

4 Test specimens**4.1 General**

It is not necessary to test **end products** or parts of **end products** which have **insignificant mass**. Additionally, this test method is not suitable for testing **small parts** (see 4.4).

4.2 Complete end product

Whenever possible, the test specimen should be a complete **end product** as opposed to a partial **end product** (see 4.3). The test specimen shall be chosen so that the conditions of the test will not be significantly different from those occurring in normal use with regard to shape,

ventilation, effect of thermal stresses, and eventually, the effects of burning or **glowing** particles falling from the test specimen.

4.3 Partial end product (alternative)

If the test cannot be made on a complete **end product** then, unless otherwise specified by the relevant product standard, it is acceptable to

- a) cut a piece containing the part under examination from a complete and assembled **end product**, or
- b) cut an aperture in the complete **end product** to allow the glow-wire access, or
- c) remove the part under examination in its entirety and test it separately.

Technical committees should define in their relevant product standards what may be removed to achieve access. So far as possible, these product standards should strive to replicate actual service locations and conditions.

4.4 Test considerations and limitations associated with the specimen configuration

When cutting an opening for access purposes, a small aperture may affect the results by leading to the **ignition** of the surroundings and/or reducing the temperature of the tip of the glow-wire. The opening should be large enough to allow an adequate supply of air for **combustion**.

If, during the test, any part of the end product containing the test specimen is ignited by extraneous heat from the glow-wire which in turn influences the thermal conditions at the test specimen, the test is invalid.

The glow-wire **flammability** test method for **end products** shall not be used for testing **small parts**. This is because such parts cannot be effectively supported to avoid heat losses (see IEC 60695-2-10), and they are not able to accommodate the penetration of the glow-wire.


The following are considered to be **small parts**:

- a) where each surface lies completely within a circle of 15 mm in diameter; or
- b) where it is not possible to fit a circle of 8 mm in diameter completely on at least one of the surfaces while, at least one part dimension is > 15 mm.

See Figure 1.

When checking a surface,

- 1) projections on the surface are disregarded, and
- 2) holes or recesses which are not greater than 2 mm in any dimension are disregarded.

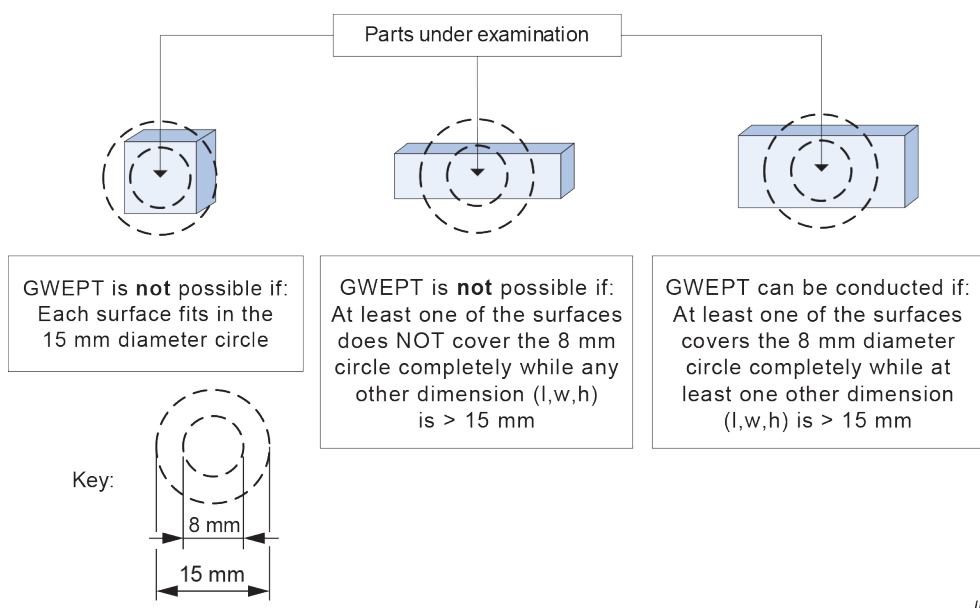

IEC

Figure 1 – Small parts

5 Test apparatus iTech STANDARD PREVIEW (standards.iteh.ai)

The test apparatus of IEC 60695-2-10 shall be used except that the reference to a specified layer may not apply.

[IEC 60695-2-11:2021](https://standards.iteh.ai/catalog/standards/sist/17b5056b-b0dc-4e55-95b4-536ab752c56b/iec-60695-2-11-2021)

To evaluate the possibility of the spread of fire, for example by burning or **glowing** particles falling from the test specimen, a specified layer as described in IEC 60695-2-10, or the material or components normally surrounding or situated underneath the test specimen, are placed underneath the test specimen. The distance between the test specimen and the specified layer representing the surrounding material or components shall be equal to that which occurs in end use. If the test specimen is a component such that surrounding materials and distances are unknown, then the specified layer described in IEC 60695-2-10 shall be placed 200 mm ± 5 mm below the glow-wire point of contact.

If the test specimen is a complete free-standing equipment, it is placed in its normal position of use on the specified layer as described in IEC 60695-2-10 extending for at least 100 mm outside the base of the equipment in all directions.

If the test specimen is a complete wall-mounted equipment, it is fixed in its normal position of use 200 mm ± 5 mm above the specified layer as described in IEC 60695-2-10.

6 Verification of the temperature measuring system

The temperature measuring system shall be verified as specified in IEC 60695-2-10.

7 Conditioning

7.1 Conditioning of test specimens

Unless otherwise specified in the relevant product standard, the test specimens shall be conditioned for 24 h in an atmosphere having a temperature between 15 °C and 35 °C and a relative humidity between 45 % and 75 %.