



Designation: D6295/D6295M – 98 (Reapproved 2019)

Standard Test Method for Dispensability of Light–Duty Pressure–Sensitive Film Tape¹

This standard is issued under the fixed designation D6295/D6295M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the measurement of the force and elongation required to dispense pressure-sensitive film tape on a 1-in. core intended for office and stationery applications from a desk-top dispenser.

1.2 The values stated in either SI or inch-pound units are to be regarded separately as standard. The values stated in each system are not exact equivalents; therefore, each system must be used independently of the other.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.4 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 *ASTM Standards:*²

[D996 Terminology of Packaging and Distribution Environments](#)

[D3715/D3715M Practice for Quality Assurance of Pressure-Sensitive Tapes](#)

[D4332 Practice for Conditioning Containers, Packages, or Packaging Components for Testing](#)

[E122 Practice for Calculating Sample Size to Estimate, With Specified Precision, the Average for a Characteristic of a Lot or Process](#)

¹ This test method is under the jurisdiction of ASTM Committee D10 on Packaging and is the direct responsibility of Subcommittee D10.14 on Tape and Labels.

Current edition approved Aug. 1, 2019. Published August 2019. Originally approved in 1998. Last previous edition approved in 2011 as D6295/D6295M – 98 (2011). DOI: 10.1520/D6295_D6295M-98R19.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

2.2 *Commercial Item Description (CID):*

[A-A-113 Tape, Pressure-Sensitive Adhesive](#)³

3. Terminology

3.1 *Definitions*—Terminology found in Terminology D996 shall apply.

3.2 *Definitions of Terms Specific to This Standard:*

3.2.1 *dispensability*—the initial force and elongation required to sever or cut off a strip of pressure-sensitive film tape from a roll using specific test conditions and specific blade described in this test method.

4. Significance and Use

4.1 Pressure-sensitive film tapes are supplied in roll form. For such a tape to be useful a strip of the tape must be easily dispensed or severed from the roll by means of a cutter found on most dispensers. This test method is a means of measuring the ease of this severing or dispensing of the tape.

4.2 This test method provides information that can be used in material specifications for product design and quality assurance applications. It can be used in comparing different tape products on specific dispensing blades.

4.3 This test method may be suited for office and stationery and tapes with acetate, cellophane, or light-duty plastic backings. Some tapes may be shown to be difficult to dispense under these conditions yet are readily dispensable with other dispensing systems.

NOTE 1—Backings described in CID A-A-113 are typical backings.

5. Apparatus

5.1 *Tension Tester*—A constant-rate-of-extension (CRE) type with load cell capacity such that the maximum expected dispensing force does not exceed 90 % of its normal limit. A means of moving the stressing clamp at a uniform rate of 250 mm/min or 10 in./min. Test information should be displayed graphically with a sampling rate of at least 100 data points per second.

³ Available from General Services Administration, Federal Supply Service Specifications Section (3FP-E), Suite 8100, 470 East L'Enfant Plaza, SW, Washington, DC 20407.

5.2 *Blade*—Manufactured in accordance with information given in Fig. 1.

NOTE 2—The blade used in models C-15, C-38, C-40, and C-41 dispensers⁴ meets these requirements. This blade has been found to be suitable for this testing.

5.3 *Blade Support Fixture*—The test fixture, as shown in Figs. 2 and 3, shall have a means of rigidly mounting the blade in the tensile tester so that the land portion faces at 30° down from the vertical and rotates the blade 10° from the horizontal.

5.4 *Blade Change*—In the normal course of events the blade should be changed at least every 1000 uses or when there is evidence of damage or wear. A new blade should be used for referee testing.

6. Sampling

6.1 *Acceptance Sampling*—Acceptance sampling shall be in accordance with Practice D3715/D3715M.

⁴ Available from Chemsultants International, 9349 Hamilton Dr., Mentor, OH 44061-1118.

6.2 *Sampling for Other Purposes*—The sampling and the number of test specimens depends on the purpose of the testing. Practice E122 is recommended. It is common to test at least five rolls of a particular tape, and wherever possible, among several production runs of tape. Strong conclusions about a specific property of a tape cannot be based on test of a single roll of product.

7. Test Specimen

7.1 The specimens shall be 18 mm or ¾ in. wide. A tolerance of ±0.8 mm or 1/32 in. shall be allowed. The length shall be approximately 150 mm or 6 in.

7.2 Discard at least three but not more than six outer wraps of tape from the sample roll before taking the specimen for testing. Take at least 10 specimens per roll.

8. Conditioning

8.1 Condition the sample rolls of tape in the standard conditioning atmosphere as described in Practice D4332 for a period of not less than 24 h. Test at these conditions.

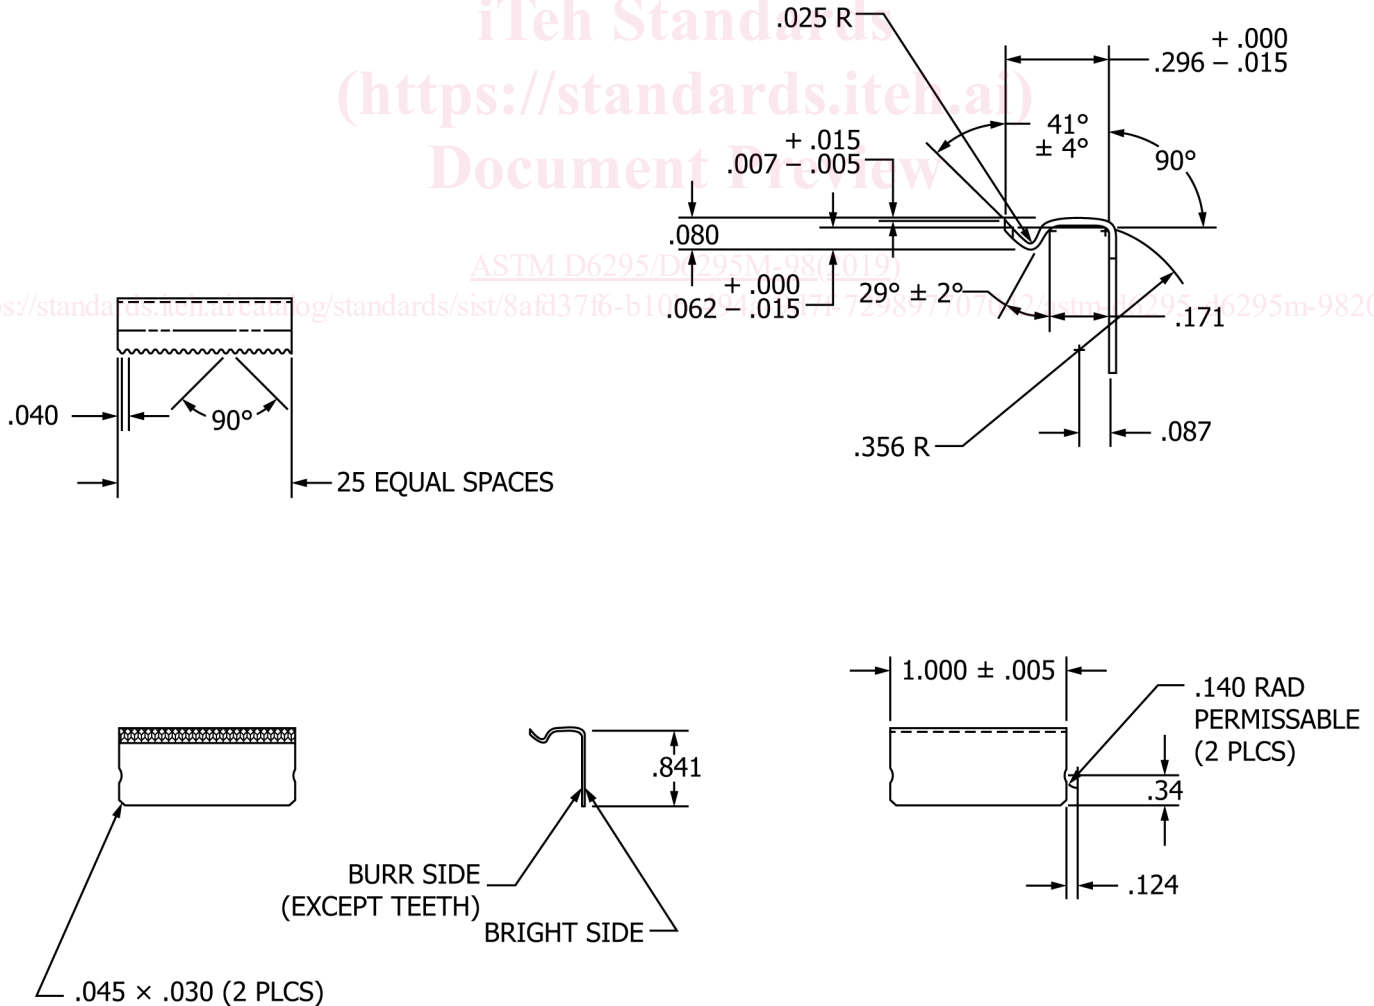


FIG. 1 Blade