

Designation: E571 - 12 E571 - 19

Standard Practice for Electromagnetic (Eddy-Current) Examination of Nickel and Nickel Alloy Tubular Products¹

This standard is issued under the fixed designation E571; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

1. Scope*

- 1.1 This practice² covers the procedures for eddy-current examination of nickel and nickel alloy tubes. These procedures are applicable for tubes with outside diameters up to 2 in. (50.8 mm), 2 in. (50.8 mm), incl, and wall thicknesses from 0.035 to 0.120 in. 0.120 in. (0.889 to 3.04 mm), incl. 3.04 mm), incl. This standard applies to procedures where the sensor is placed on the outside surface of the tube. These procedures may be used for tubes beyond the size range recommended, by contractual agreement between the purchaser and the producer.
 - 1.2 The procedures described in this practice make use of fixed encircling test coils or probe systems.
- 1.3 *Units*—The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.

Note 1-For convenience, the term "tube" or "tubular product" will hereinafter be used to refer to both pipe and tubing.

- 1.4 This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety safety, health, and health environmental practices and determine the applicability of regulatory limitations prior to use.
- 1.5 This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.

2. Referenced Documents

2.1 ASTM Standards:³

E309 Practice for Eddy Current Examination of Steel Tubular Products Using Magnetic Saturation

E543 Specification for Agencies Performing Nondestructive Testing

E1316 Terminology for Nondestructive Examinations

2.2 Other Documents:

SNT-TC-1A Recommended Practice for Personnel Qualification and Certification in Nondestructive Testing⁴ ANSI/ASNT-CP-189 ASNT Standard for Qualification and Certification of Nondestructive Testing Personnel⁴ NAS-410 Certification and Qualification of Nondestructive Personnel (Quality Assurance Committee)⁵ ISO-9712 Non-destructive testing -- Qualification and certification of NDT personnel⁶

3. Terminology

3.1 Standard terminology relating to electromagnetic testing may be found in Terminology E1316, Section C, Electromagnetic Testing.

¹ This practice is under the jurisdiction of ASTM Committee E07 on Nondestructive Testing and is the direct responsibility of Subcommittee E07.07 on Electromagnetic

Current edition approved $\frac{\text{Aug. 1, 2012} \text{July 1, 2019}}{\text{Last previous edition approved in 2007}}$. Published $\frac{\text{September 2012} \text{September 2019}}{\text{September 2019}}$. Originally approved in 1976. Last previous edition approved in $\frac{20072012}{\text{September 2019}}$ as $\frac{\text{E571 - 98E571 - 12,(2007)}}{\text{E571 - 12,(2007)}}$. DOI: $\frac{10.1520/\text{E0571-12,(10.1520/E0571-19,(10.1520/E05$

² For ASME Boiler and Pressure Vessel Code applications see related Practice SE-571 in Section II of that Code.

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

⁴ Available from American Society for Nondestructive Testing (ASNT), P.O. Box 28518, 1711 Arlingate Ln., Columbus, OH 43228-0518, http://www.asnt.org.

⁵ Available from Aerospace Industries Association of America, Inc. (AIA), 1000 Wilson Blvd., Suite 1700, Arlington, VA 22209-3928, http://www.aia-aerospace.org.

⁶ Available from International Organization for Standardization (ISO), 1, ch. de la Voie-Creuse, CP 56, CH-1211 Geneva 20, Switzerland, http://www.iso.org.

4. Summary of Practice

- 4.1 Examination is usually performed by the use of one of two general techniques:
- 4.1.1 *Encircling Coil Technique*—Examination is performed by passing the tube lengthwise through a coil energized with alternating current at one or more frequencies. See Fig. 1. The electrical impedance of the coil is modified by the proximity of the tube, the tube dimensions, electrical conductivity, saturating magnetic field, magnetic permeability, and metallurgical or mechanical discontinuities in the tube. As the tube passes through the coil, the changes in electromagnetic response caused by these variables in the tube change the coil impedance, which activates an audible or visual signaling device or a mechanical marker.
- 4.1.2 *Probe Coil Technique*—Probe coils are positioned in close proximity to the outside diameter or to the inside diameter, or to both diameter surfaces, of the tubular product being examined as shown in Fig. 1. Since the probe is generally small and does not encircle the tube, it examines only a limited area in the vicinity of the probe. When required to examine the entire volume of the tubular product, it is common practice to rotate either the tubular product or the probe around the tube. Frequently, in the case of welded tubular products, only the weld is examined by scanning along the weld zone. In the case where the tubular products are joined by welding and the probe is rotated, the probe is orbited about the central axis of the tube such that a circumferential examination of the tube and/or weld may be made. The depth of penetration of the interrogating magnetic fields into the tubular product may be smaller for this type of probe coil compared to the encircling coil.
- 4.2 The magnetic permeability of magnetic materials severely limits the depth of penetration of induced eddy currents. Furthermore, the permeability variations inherent in magnetic tubular products can cause spurious test results. A useful solution to this problem involves the application of a strong external magnetic field in the region of the examining coil or probe. This technique, known as magnetic saturation, causes a magnetic material to exhibit sufficiently small magnetic characteristics of permeability, hysteresis, etc.,and so forth, so that the material under examination is effectively rendered nonmagnetic. When achieved, this condition allows an eddy-current system to measure and detect electrical resistivity and geometrical variations (including defects) independent of concurrent variations in magnetic properties.

Note 2—Practice E309 may be used for strongly magnetic materials.

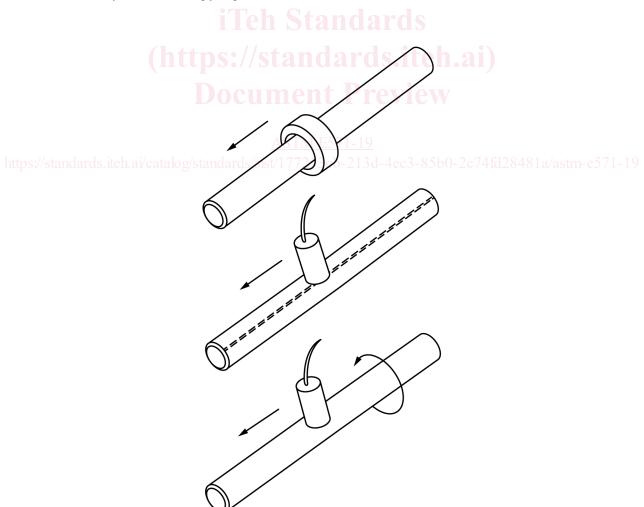


FIG. 1 Encircling-Coil and Probe-Coil Techniques for Electromagnetic Examination of Tubular Products

4.2.1 During the examination of slightly magnetic tubing the signals resulting from the variation of magnetic permeability can mask the signals resulting from small imperfections. A magnetic saturation technique can be used to reduce this interference to an acceptable level.

5. Significance and Use

- 5.1 Eddy-current testing is a nondestructive method of locating discontinuities in metallic materials. Signals can be produced by discontinuities originating on either the external or internal surfaces of the tube or by discontinuities totally contained within the wall. Since the density of eddy currents decreases nearly exponentially with increasing distance from the surface nearest the coil, the response to deep-seated defects decreases correspondingly. Phase changes are also associated with changes in depth, allowing the use of phase analysis techniques.
- 5.2 The response from natural discontinuities can be significantly different than that from artificial discontinuities, such as drilled holes or notches. For this reason, sufficient work should be done to establish the sensitivity level and setup required to detect natural discontinuities of consequence to the end use of the product.
- 5.3 Some indications obtained by this method may not be relevant to product quality; for example, an irrelevant indication may be caused by minute dents or tool chatter marks, which are not detrimental to the end use of the product. Irrelevant indications can mask unacceptable discontinuities. Relevant indications are those which result from discontinuities. Any indication that exceeds the rejection level shall be treated as a relevant indication until it can be demonstrated that it is irrelevant.
 - 5.4 Generally, eddy-current examination systems are not sensitive to discontinuities adjacent to the ends of the tube (end effect).
- 5.5 Discontinuities such as scratches or seams that are continuous and uniform over the full length of the tube may not always be detected with differential encircling coils or probes scanned along the tube length.
- 5.6 For material that is magnetic, a strong magnetic field shall be placed in the region of the examining coil. A magnetic field may also be used to improve the signal-to-noise ratio in tubing that exhibits slight residual magnetism.

6. Basis of Application

- 6.1 The following criteria may be specified in the purchase specification contractual agreement, or elsewhere, and may require agreement between the purchaser and the supplier.
 - 6.1.1 Acceptance criteria.
 - 6.1.2 Type, dimensions, and number of artificial discontinuities to be placed in the reference standard.
 - 6.1.3 Extent of examination; that is, full circumference of outside or inside diameter, or both, or weld only, if welded.
 - 6.1.4 Operator qualifications, if required (see 6.1.66.2 below).
 - 6.1.5 Standardization intervals.
- 6.1.6 If specified in the contractual agreement, personnel performing examinations to this practice shall be qualified in accordance with a nationally recognized NDT personnel qualification practice or standard such as ANSI/ASNT-CP-189, SNT-TC-1A, NAS-410, ASNT-ACCP, or a similar document and certified by the certifying agency as applicable. The practice or standard used and its applicable revision shall be identified in the contractual agreement between the using parties.
 - Note 3-MIL-STD-410 is canceled and has been replaced with NAS-410, however, it may be used with agreement between contracting parties.
- 6.1.7 If specified in the contractual agreement, NDT agencies shall be qualified and evaluated in accordance with Specification E543. The applicable edition of Specification E543 shall be specified in the contractual agreement.
 - 6.2 Personnel Qualifications:
- 6.2.1 Personnel performing examinations to this standard shall be qualified in accordance with ______ (identify standard or standards, for example, NAS-410, SNT-TC-1A, ANSI/ASNT-CP-189, SNT-TC-1A, NAS-410, ISO 9712) and certified by the employer or certifying agency, as applicable. Other equivalent qualification documents may be used when specified in the contract or purchase order. The applicable revision shall be the latest unless otherwise specified in the contractual agreement between parties.

7. Apparatus

- 7.1 *Electronic Apparatus*—The electronic apparatus shall be capable of energizing the encircling coils or probes with alternating current of suitable frequencies and shall be capable of sensing changes in impedance of the encircling coils or probes. Equipment may include any appropriate signal processing circuits such as a phase discriminator, filter circuits, etc., and so forth, as required for the particular application.
- 7.2 Encircling Coil Assembly—The encircling coil assembly shall consist of one or more electrical coils which encircle the article being examined. The inside geometry of the coils should closely approximate the surface geometry of the specimen so that when the specimen is passed through the coils all points on the outer circumference of the specimen are effectively equidistant from, and in close proximity to, the inner surfaces of the examining coils.