

# INTERNATIONAL STANDARD



**Semiconductor devices – Mechanical and climatic test methods –  
Part 39: Measurement of moisture diffusivity and water solubility in organic  
materials used for semiconductor components**

Document Preview

[IEC 60749-39:2021](#)

<https://standards.iteh.ai/catalog/standards/iec/2aff6b5a-3140-4d55-8bbe-28d1c6d8b807/iec-60749-39-2021>





## THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2021 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Central Office  
3, rue de Varembe  
CH-1211 Geneva 20  
Switzerland

Tel.: +41 22 919 02 11  
[info@iec.ch](mailto:info@iec.ch)  
[www.iec.ch](http://www.iec.ch)

### About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

### About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

#### IEC publications search - [webstore.iec.ch/advsearchform](http://webstore.iec.ch/advsearchform)

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, ...). It also gives information on projects, replaced and withdrawn publications.

#### IEC online collection - [oc.iec.ch](http://oc.iec.ch)

Discover our powerful search engine and read freely all the publications previews. With a subscription you will always have access to up to date content tailored to your needs.

#### IEC Just Published - [webstore.iec.ch/justpublished](http://webstore.iec.ch/justpublished)

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

#### Electropedia - [www.electropedia.org](http://www.electropedia.org)

The world's leading online dictionary on electrotechnology, containing more than 22 000 terminological entries in English and French, with equivalent terms in 18 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

#### IEC Customer Service Centre - [webstore.iec.ch/csc](http://webstore.iec.ch/csc)

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: [sales@iec.ch](mailto:sales@iec.ch).

International Standards  
standards.iteh.ai  
Document Preview

[IEC 60749-39:2021](https://standards.iteh.ai/catalog/standards/iec/2aff6b5a-3140-4d55-8bbe-28d1c6d8b807/iec-60749-39-2021)

<https://standards.iteh.ai/catalog/standards/iec/2aff6b5a-3140-4d55-8bbe-28d1c6d8b807/iec-60749-39-2021>



IEC 60749-39

Edition 2.0 2021-11  
REDLINE VERSION

# INTERNATIONAL STANDARD



**Semiconductor devices – Mechanical and climatic test methods –  
Part 39: Measurement of moisture diffusivity and water solubility in organic  
materials used for semiconductor components**

Document Preview

[IEC 60749-39:2021](#)

<https://standards.iteh.ai/catalog/standards/iec/2aff6b5a-3140-4d55-8bbe-28d1c6d8b807/iec-60749-39-2021>

INTERNATIONAL  
ELECTROTECHNICAL  
COMMISSION

ICS 31.080.01

ISBN 978-2-8322-4497-5

**Warning! Make sure that you obtained this publication from an authorized distributor.**

## CONTENTS

FOREWORD .....	3
1 Scope .....	5
2 Normative references .....	5
3 Terms and definitions .....	5
4 Apparatus .....	5
5 Samples .....	6
6 Procedure .....	6
6.1 Sample preparation .....	6
6.2 Absorption measurements below 100 °C .....	7
6.3 Solubility and diffusivity calculation .....	7
6.4 Desorption measurements above 100 °C .....	10
7 Calculation of activation energy for moisture diffusion .....	11
8 Calculation of functional fit for solubility .....	12
9 Summary .....	12
Bibliography .....	13
Figure 1 – Example of linearly increasing mass gain .....	9
Figure 2 – Alternative intercept method to estimate the reversible Fickian moisture mass .....	9

Document Preview

[IEC 60749-39:2021](https://standards.iteh.ai/catalog/standards/iec/2aff6b5a-3140-4d55-8bbe-28d1c6d8b807/iec-60749-39-2021)

<https://standards.iteh.ai/catalog/standards/iec/2aff6b5a-3140-4d55-8bbe-28d1c6d8b807/iec-60749-39-2021>

## INTERNATIONAL ELECTROTECHNICAL COMMISSION

**SEMICONDUCTOR DEVICES –  
MECHANICAL AND CLIMATIC TEST METHODS –****Part 39: Measurement of moisture diffusivity and water solubility in  
organic materials used for semiconductor components**

## FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as “IEC Publication(s)”). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

**This redline version of the official IEC Standard allows the user to identify the changes made to the previous edition IEC 60749-39:2006. A vertical bar appears in the margin wherever a change has been made. Additions are in green text, deletions are in strikethrough red text.**

IEC 60749-39 has been prepared by IEC technical committee 47: Semiconductor devices. It is an International Standard.

This second edition, based on JEDEC document JESD22-A120B, cancels and replaces the first edition published in 2006. It is used with permission of the copyright holder, JEDEC Solid State Technology Association. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) updated procedure for "dry weight" determination.

The text of this International Standard is based on the following documents:

Draft	Report on voting
47/2652/CDV	47/2725/RVC

Full information on the voting for its approval can be found in the report on voting indicated in the above table.

The language used for the development of this International Standard is English.

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at [www.iec.ch/members\\_experts/refdocs](http://www.iec.ch/members_experts/refdocs). The main document types developed by IEC are described in greater detail at [www.iec.ch/standardsdev/publications](http://www.iec.ch/standardsdev/publications).

A list of all the parts of the IEC 60749 series, under the general title *Semiconductor devices – Mechanical and climatic test methods*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under [webstore.iec.ch](http://webstore.iec.ch) in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

**IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.**

## SEMICONDUCTOR DEVICES – MECHANICAL AND CLIMATIC TEST METHODS –

### Part 39: Measurement of moisture diffusivity and water solubility in organic materials used for semiconductor components

#### 1 Scope

This part of IEC 60749 details the procedures for the measurement of the characteristic properties of moisture diffusivity and water solubility in organic materials used in the packaging of semiconductor components.

These two material properties are important parameters for the effective reliability performance of plastic packaged semiconductors after exposure to moisture and being subjected to high-temperature solder reflow.

~~NOTE—It is recommended that the moisture absorption parameters used in this standard be obtained from the material suppliers (such as the resin supplier).~~

#### 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60749-20, *Semiconductor devices – Mechanical and climatic test methods – Part 20: Resistance of plastic encapsulated SMDs to the combined effect of moisture and soldering heat*

#### 3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

#### 4 Apparatus

**4.1** Analytical balance capable of a resolution of either 0,000 01 g or 0,001 % of sample mass.

**4.2** High-temperature oven capable of maintaining uniform temperatures from 100 °C to 250 °C ± 2 °C.

**4.3** Temperature/humidity chamber(s) capable of maintaining temperatures in a range from 30 °C to 85 °C and relative humidities ( $H_R$ ) in a range from 60 %  $H_R$  to 85 %  $H_R$ . Within the chamber working area, temperature tolerance shall be ±2 °C and the  $H_R$  tolerance shall be ±3 %  $H_R$ .

**4.4** Perforated stainless steel trays or stainless steel wire mesh baskets used for holding samples and for placement into ovens.

**4.5** Large aluminium plate or disk used for heat sink capability.

**4.6** Desiccator for holding dry samples.

## 5 Samples

Samples of mould compound ~~must~~ shall be flat parallel-sided discs or coupons. The linear dimensions shall be accurately measured to within  $\pm 0,02$  mm.

To approximate one-dimensional diffusion behaviour with edge effects limited to less than 5 % of the total diffusional moisture mass uptake, the free surface area in the thickness dimension ~~must~~ shall be less than 5 % of the flat-sided free surface area of the sample. For a disc of radius,  $r$ , and thickness,  $h$ , the following relation shall be met:

$$h < 0,05r \quad (1)$$

for a coupon of length,  $L$ , and width,  $W$ ,

$$h = \frac{0,05(WL)}{(W + L)} \quad (2)$$

Recommended sample thickness should be in the range from 0,3 mm to 1,0 mm. ~~It is recommended that~~ The maximum sample thickness should not exceed 1,0 mm, because the time to achieve moisture saturation at temperatures below 60 °C will be excessively long for compounds with slow diffusivity.

The moisture absorption parameters used in this standard can be obtained from the material suppliers (such as the resin supplier).

## 6 Procedure

### 6.1 Sample preparation

**6.1.1** Process and cure the samples using recommended processing conditions in accordance with the manufacturer's specification.

**6.1.2** To obtain the appropriate sample thickness as given by Formulae (1) or (2), samples ~~may~~ can be sectioned and finely polished from larger specimens. ~~Care must be taken to maintain~~ Near parallel-sided flatness shall be maintained for samples prepared in this manner.

The prepared samples should be inspected for voids, both internal and surface, using acoustic microscopy or x-ray. The ideal samples should be nearly void-free.



## 6.2 Absorption measurements below 100 °C

**6.2.1** Measure the linear dimensions of the prepared sample to the nearest  $\pm 0,02$  mm. Record the sample thickness,  $h$ , and calculate the sample volume,  $V$ , using the appropriate geometric relationship based on the sample shape.

NOTE Calculating the volume by measuring the linear dimensions is never accurate. The error is smaller when the sample is big. One accurate way of determining the volume is to use Archimedes's principle, which is to measure the sample weight in air and immersed in a liquid with known density (ethyl alcohol, IPA, etc.). In this way, the volume of a sample with irregular shape can also be determined.

~~**6.2.2** Bake the sample at 125 °C for 24 h. Longer bake times may be required depending on the sample mass loss characteristics. The sample is considered dry when successive measurements result in less than 0,002 % difference between readings.~~

The dry weight of the sample shall be determined, in accordance with IEC 60749-20, firstly by baking the sample for 24 h at 125  $\pm 5/0$  °C and continuing to bake and weigh the sample every 12 hours until no further weight loss is observed to ensure that the sample(s) are dry. The dry weight is determined when no further weight loss is observed, less than 0,002 % difference, after two consecutive measurements with a minimum baking interval of 12 h. Within 30 minutes after removal from the oven, weigh the sample(s) using the analytical balance equipment described in 4.1 and determine the dry weight in accordance with 6.2.4.

In accordance with IEC 60749-20, small sample(s) (less than 1,5 mm total height), devices should be weighed within 30 minutes after removal from oven.

**6.2.3** Remove the sample from the bake oven and immediately cool by placing in contact with the heat sink of 4.5.

If more than one sample is to be measured, the samples and heat sink should be placed into a desiccator to limit moisture uptake during the mass measurements.

~~**6.2.4** Measure the mass of the sample according to 2.1 and record the mass as  $M_{Comp,dry,1}$~~

~~The mass gain/loss measurement shall be made within a few minutes after removal of the sample from the environmental chamber. Time delays longer than 5 min after removal from the environmental chambers could affect the resultant diffusivity measurements.~~

Weigh the sample using the balance described in 4.1 and record the mass as  $M_{Comp,dry,1}$ .

Read points: At the desired read point; remove the sample(s) from the bake oven. Within 30 minutes after removal of the sample(s) from the bake oven, remove the sample(s) from the container and determine their weight using the analytical balance equipment in 4.1. Within 30 minutes after weighing the samples, place them in a clean, dry, shallow container so that the sample bodies do not touch each other. Return the sample(s) to the bake oven for the desired time. Continue until the sample(s) have lost all their moisture as determined by the dry weight in 6.2.2.

**6.2.5** Place the sample(s) into a stainless steel holder and transfer to a temperature/humidity chamber stabilized at a pre-set temperature and humidity.

~~It is suggested that~~ The sample should be transferred into a stainless-steel holder that has been preheated and stabilized to the set chamber temperature.

**6.2.6** At accumulative times, remove the sample from the temperature/humidity chamber, cool ~~in accordance with 4.2.3 and measure the sample mass~~ and measure the sample mass in accordance with 6.2.4. Record the mass as  $M_{Comp,wet,t}$ .

~~Time intervals should be spaced so as to allow adequate measurement duration to capture the initial quick mass response and to provide a good spread in the data points during the later stages of the mass response curve. The total number of times the temperature/humidity chamber is disturbed for sample removal should be minimized.~~

~~Care should be taken that no condensed moisture from the chamber walls comes into contact with the sample during removal from the temperature/humidity chamber. If condensed water should contact the sample, immediately dry the sample using nitrogen or dry air. The sample should then be returned to the chamber for re-equilibration and another data point taken at a later time.~~

**6.2.7** Read Points: The X-axis (time) read points, in accordance with IEC 60749-20, are selected for plotting the absorption curve. For the early readings, points should be relatively short (24 h or less) because the curve will have a steep initial slope. Later readings can be spread out further (10 days or more) as the curve becomes asymptotic. The Y-axis (weight gain) should start with “0” and increase to the saturated weight gain. Most sample(s) will reach saturation between 0,3 % and 0,4 % when stored at 85 °C/85 % RH. Devices shall be kept at room ambient between removal from the oven or chamber and weighing and subsequent reinsertion into the oven or chamber.


Ensure that no condensed moisture from the chamber walls comes into contact with a sample during removal from the temperature/humidity chamber. If condensed water should contact a sample, immediately dry the sample using nitrogen or dry air. The sample should then be returned to the chamber for re-equilibration and another data point taken at a later time.

The sample weight measurement shall be made within a few minutes after removal of the sample from the temperature/humidity chamber. Time delays longer than 5 minutes after removal from the temperature/humidity chamber could affect the sample weight measurements.

Within 30 minutes after weighing the samples, place them in a clean, dry, shallow container so that the sample bodies do not touch each other. Return the sample(s) to the temperature/humidity chamber for the desired time.

**6.2.8** Place the sample back into the temperature/humidity chamber and continue mass measurements until either of the following conditions are met.

- a) additional weight gain after a 24 h period is less than 0,002 % from the previous measurement;
- b) a plot of the weight gain versus time shows a linearly increasing weight gain after an initial decreasing change in mass with time ( $dM/dt$ ), as depicted in Figure 1.

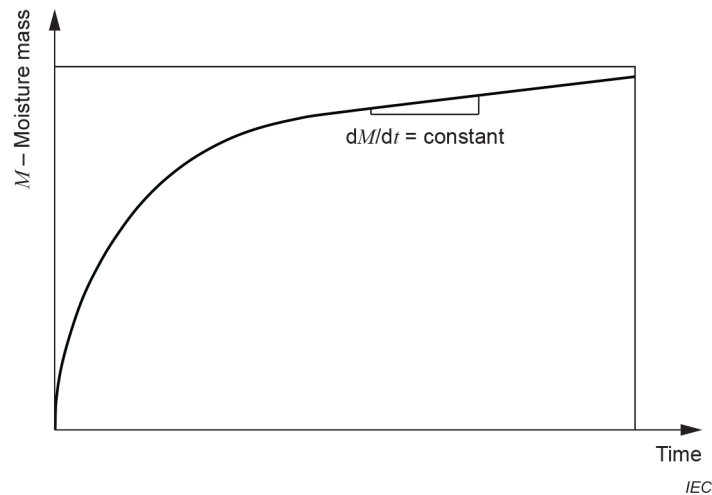

**Figure 1 – Example of linearly increasing mass gain**


**6.2.9** Record the final wet mass of the sample as  $M_{\text{Comp,wet,f}}$

**6.2.10** Bake the sample again at 125 °C until dry as determined by 6.2.2.

**6.2.11** Record the second final dry mass as  $M_{\text{Comp,dry,2}}$

**6.2.12** Record the saturated moisture mass as,  $M_{\text{Sat}} = M_{\text{Comp,wet,f}} - M_{\text{Comp,dry,2}}$

NOTE An alternative method to estimate the reversible saturated moisture mass can be determined by an intercept approach as shown in Figure 2. Using this method the intercept point between the weight gain curve and a linear extrapolation of the linear varying portion of the weight gain curve can be used to estimate the reversible Fickian moisture weight gain response.

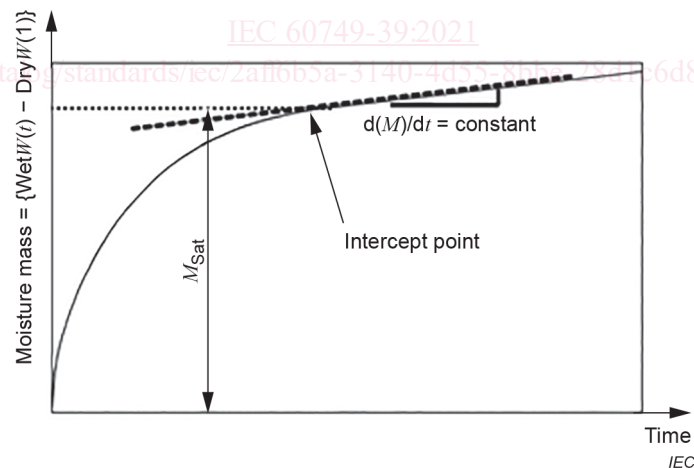

**Figure 2 – Alternative intercept method to estimate the reversible Fickian moisture mass**

### 6.3 Solubility and diffusivity calculation

**6.3.1** Calculate the solubility at the given temperature and humidity by using:

$$C_{\text{sat}}(T, H_R) = \frac{M_{\text{Comp,wet,f}} - M_{\text{Comp,dry,2}}}{V} = \frac{M_{\text{sat}}(T, H_R)}{V} \quad (3)$$

where

- $C_{\text{sat}}(T, H_R)$  is the moisture solubility at temperature  $T$  and  $H_R$  (in  $\text{mg cm}^{-3}$ );
- $M_{\text{Comp, wet, f}}$  is the final wet sample mass (in mg);
- $M_{\text{Comp, dry, 2}}$  is the final dry sample mass after the second bake (in mg);
- $V$  is the sample volume (in  $\text{cm}^3$ );
- $M_{\text{sat}}(T, H_R)$  is the reversible saturated moisture content at temperature  $T$  and  $H_R$  (in mg).

**6.3.2** Plot mass gain curve versus time using change in mass as  $M(t) - M_{\text{Comp, dry, 1}}$

**6.3.3** Using the plotted curve, calculate the moisture diffusivity from

$$D(T) = \frac{0,049\ 19\ h^2}{t_{0,5}} \tag{4}$$

where

$D(T)$  is the diffusivity at temperature  $T$  (in  $\text{mm}^2\ \text{s}^{-1}$ );

$H$  is the sample thickness (in mm);

$t_{0,5}$  is the absorption half-time defined as the time at which the absorbed mass of moisture is equal to one-half the saturated mass, for example,  $M_t/M_{\text{sat}} = 0,5$ ;

$M_t$  is the mass of moisture at time  $t$ .

~~NOTE An alternate method for determining  $D(T)$  is to use a best-fit curve fitting approach of the experimental weight gain data. Equation (4) above is recognized as an approximation to the analytical closed form solution, however, it will provide an accurate approximation of an error of less than a few per cent. The value of  $D(T)$  determined by a curve fitting technique should be compared to the value determined by equation (4) as a reference check. Repeat the sorption measurements 4.2 to 4.3.3 using different temperature and humidity conditions. Suggested environmental conditions are 30 °C/60 %  $H_R$ , 60 °C/60 %  $H_R$ , and 85 °C/60 %  $H_R$ .~~

NOTE Formula (4) is recognized as an approximation to the analytical closed form solution, however, it will provide an accurate approximation to less than a few percent error. An alternate method for determining  $D(T)$  is to use a best fit curve fitting approach of the experimental weight gain data. The following solution for rectangular or square samples can be used:

$$\frac{M_t}{M_{\text{sat}}} = 1 - \frac{512}{\pi^6} \sum_{l=0}^{\infty} \sum_{m=0}^{\infty} \sum_{n=0}^{\infty} \frac{\exp(-D t L_{\text{eqv}})}{(2l+1)^2 (2m+1)^2 (2n+1)^2} \tag{5}$$

where  $L_{\text{eqv}} = \left( \left\{ \frac{(2l+1)}{x_0} \right\}^2 + \left\{ \frac{(2m+1)}{y_0} \right\}^2 + \left\{ \frac{(2n+1)}{z_0} \right\}^2 \right)$

Here,  $x_0$ ,  $y_0$ , and  $z_0$  are the width, length, and thickness of the sample, respectively.  $l$ ,  $m$  and  $n$  represent integers relating to calculation of diffusion/concentration steps solved by iterative calculations in each principal direction. The value of  $D(T)$  determined by a curve fitting technique using Formula (5) should be compared to the value determined by Formula (4) as a reference check.

**6.3.4** Repeat the absorption measurements 6.2 to 6.3.3 using different temperature and humidity conditions. The following environmental conditions shall be used: 30 °C/60 %  $H_R$ , 60 °C/60 %  $H_R$ , and 85 °C/60 %  $H_R$ .