

INTERNATIONAL STANDARD

NORME INTERNATIONALE

**Optical fibre cables –
Part 1-312: Generic specification – Basic optical cable test procedures – Cable
element test methods – Elongation test for buffer tubes at low temperature,
Method G11B**

**Câbles à fibres optiques –
Partie 1-312: Spécification générique – Procédures fondamentales d’essai des
câbles optiques – Méthodes d’essais d’environnement – Essai d’allongement
des tubes à basse température, Méthode G11B**





THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2024 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de l'IEC ou du Comité national de l'IEC du pays du demandeur. Si vous avez des questions sur le copyright de l'IEC ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de l'IEC de votre pays de résidence.

IEC Secretariat
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, ...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

IEC Products & Services Portal - products.iec.ch

Discover our powerful search engine and read freely all the publications previews, graphical symbols and the glossary. With a subscription you will always have access to up to date content tailored to your needs.

Electropedia - www.electropedia.org

The world's leading online dictionary on electrotechnology, containing more than 22 500 terminological entries in English and French, with equivalent terms in 25 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

A propos de l'IEC

La Commission Electrotechnique Internationale (IEC) est la première organisation mondiale qui élabore et publie des Normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications IEC

Le contenu technique des publications IEC est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

Recherche de publications IEC -

webstore.iec.ch/advsearchform

La recherche avancée permet de trouver des publications IEC en utilisant différents critères (numéro de référence, texte, comité d'études, ...). Elle donne aussi des informations sur les projets et les publications remplacées ou retirées.

IEC Just Published - webstore.iec.ch/justpublished

Restez informé sur les nouvelles publications IEC. Just Published détaille les nouvelles publications parues. Disponible en ligne et une fois par mois par email.

Service Clients - webstore.iec.ch/csc

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions contactez-nous: sales@iec.ch.

IEC Products & Services Portal - products.iec.ch

Découvrez notre puissant moteur de recherche et consultez gratuitement tous les aperçus des publications, symboles graphiques et le glossaire. Avec un abonnement, vous aurez toujours accès à un contenu à jour adapté à vos besoins.

Electropedia - www.electropedia.org

Le premier dictionnaire d'électrotechnologie en ligne au monde, avec plus de 22 500 articles terminologiques en anglais et en français, ainsi que les termes équivalents dans 25 langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International (IEV) en ligne.



INTERNATIONAL STANDARD

NORME INTERNATIONALE

Optical fibre cables – Part 1-312: Generic specification – Basic optical cable test procedures – Cable element test methods – Elongation test for buffer tubes at low temperature, Method G11B

Câbles à fibres optiques – Partie 1-312: Spécification générique – Procédures fondamentales d'essai des câbles optiques – Méthodes d'essais d'environnement – Essai d'allongement des tubes à basse température, Méthode G11B

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

COMMISSION
ELECTROTECHNIQUE
INTERNATIONALE

ICS 33.180.10

ISBN 978-2-8322-8133-8

**Warning! Make sure that you obtained this publication from an authorized distributor.
Attention! Veuillez vous assurer que vous avez obtenu cette publication via un distributeur agréé.**

CONTENTS

FOREWORD..... 3

INTRODUCTION..... 5

1 Scope..... 6

2 Normative references 6

3 Terms and definitions 6

4 General requirements 7

5 Method G11B: Elongation of buffer tubes at low temperature..... 7

 5.1 Object..... 7

 5.2 Sample 7

 5.2.1 General 7

 5.2.2 Preparation and conditioning of test pieces..... 7

 5.2.3 Determination of cross-sectional area 11

 5.3 Apparatus 12

 5.4 Procedure 12

 5.5 Requirements 13

 5.6 Details to be specified..... 13

 5.7 Details to be reported 13

Bibliography..... 14

Figure 1 – Dumb-bell test piece..... 8

Figure 2 – Small dumb-bell test piece 9

Figure 3 – Punch end showing groove 9

Figure 4 – Test pieces cut by grooved punch 9

Figure 5 – Machine for preparing test pieces..... 10

ITeH Standards

(<https://standards.iteh.ai>)

Document Preview

IEC 60794-1-312:2024

<https://standards.iteh.ai/catalog/standards/iec/b2eb8dee-f326-4ed6-91b2-238b8c94b696/iec-60794-1-312-2024>

INTERNATIONAL ELECTROTECHNICAL COMMISSION

OPTICAL FIBRE CABLES –

**Part 1-312: Generic specification –
Basic optical cable test procedures – Cable element test methods –
Elongation test for buffer tubes at low temperature, method G11B**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as “IEC Publication(s)”). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) IEC draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). IEC takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, IEC had not received notice of (a) patent(s), which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at <https://patents.iec.ch>. IEC shall not be held responsible for identifying any or all such patent rights.

IEC 60794-1-312 has been prepared by subcommittee 86A: Fibres and cables, of IEC technical committee 86: Fibre optics. It is an International Standard.

This document partially cancels and replaces method G11B of IEC 60794-1-23:2019.

This edition includes the following significant technical changes with respect to IEC 60794-1-23:2019:

- alignment of the title with the content of the method.

The text of this International Standard is based on the following documents:

Draft	Report on voting
86A/2395/FDIS	86A/2414/RVD

Full information on the voting for its approval can be found in the report on voting indicated in the above table.

The language used for the development of this International Standard is English.

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at www.iec.ch/members_experts/refdocs. The main document types developed by IEC are described in greater detail at www.iec.ch/publications.

A list of all parts in the IEC 60794 series, published under the general title *Optical fibre cables*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under webstore.iec.ch in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn, or
- revised.

iTeh Standards
(<https://standards.itih.ai>)
Document Preview

[IEC 60794-1-312:2024](https://standards.itih.ai/catalog/standards/iec/b2eb8dee-f326-4ed6-91b2-238b8c94b696/iec-60794-1-312-2024)

<https://standards.itih.ai/catalog/standards/iec/b2eb8dee-f326-4ed6-91b2-238b8c94b696/iec-60794-1-312-2024>

INTRODUCTION

This document contains method G11B of IEC 60794-1-23:2019, which will be withdrawn. The title of the test method G11B and the content were not in line with each other. In the title micro tubes are mentioned, but the text stated that the test is intended for buffer tubes circular cross-section having an external diameter greater than 12,5 mm and for sector-shaped cores large enough to prepare dumb-bells. In the new title, micro tubes are skipped with respect to IEC 60794-1-23:2019.

The system for optical fibre test methods have been restructured and renumbered. The optical cable element test methods contained in IEC 60794-1-23:2019 will now be individually numbered in the IEC 60794-1-3xx series. Each test method is now considered to be an individual document rather than part of a multi-test method compendium. Full cross-reference details are given in IEC 60794-1-2.

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[IEC 60794-1-312:2024](https://standards.iteh.ai/catalog/standards/iec/b2eb8dee-f326-4ed6-91b2-238b8c94b696/iec-60794-1-312-2024)

<https://standards.iteh.ai/catalog/standards/iec/b2eb8dee-f326-4ed6-91b2-238b8c94b696/iec-60794-1-312-2024>

OPTICAL FIBRE CABLES –

Part 1-312: Generic specification – Basic optical cable test procedures – Cable element test methods – Elongation test for buffer tubes at low temperature, method G11B

1 Scope

This part of IEC 60794 describes test procedures to be used in establishing uniform requirements of optical fibre cable elements for the mechanical property – tensile strength and elongation at low temperature.

This document applies to optical fibre cables for use with telecommunication equipment and devices employing similar techniques, and to cables having a combination of both optical fibres and electrical conductors.

Throughout the document, the wording "optical cable" can also include optical fibre units, microduct fibre units, etc.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60794-1-2, *Optical fibre cables – Part 1-2: Generic specification – Basic optical cable test procedures – General guidance*

IEC 60811-401, *Electric and optical fibre cables – Test methods for non-metallic materials – Part 401: Miscellaneous tests – Thermal ageing methods – Ageing in an air oven*

IEC 60811-501, *Electric and optical fibre cables – Test methods for non-metallic materials – Part 501: Mechanical tests – Tests for determining the mechanical properties of insulating and sheathing compounds*

IEC 60811-505, *Electric and optical fibre cables – Test methods for non-metallic materials – Part 505: Mechanical tests – Elongation at low temperature for insulations and sheaths*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 General requirements

IEC 60794-1-2 is the reference guide to test methods of all types. It shall be considered for general requirements and definitions.

5 Method G11B: Elongation of buffer tubes at low temperature

5.1 Object

This test is to determine the elongation of the buffer tubes at low temperature. For this test, the test method IEC 60811-501, IEC 60811-505 and IEC 60811-401 shall apply.

5.2 Sample

5.2.1 General

Each buffer tube to be tested shall be represented by two samples of suitable length.

5.2.2 Preparation and conditioning of test pieces

After all covering has been removed, the buffer tube shall be cut open in the direction of the axis, after which the fibre and any filling compound, if any, shall be removed.

Dumb-bell test pieces are intended for buffer tubes circular cross-section having an external diameter greater than 12,5 mm and for sector-shaped cores large enough to prepare dumb-bells. Where it is not possible to prepare dumb-bells, the tubular test pieces as described below are suitable for testing the performance of cores of smaller diameter.

a) Conditioning of test pieces

1) Elevated temperature conditioning

NOTE 1 Elevated temperature conditioning is not an ageing treatment. It is used as a means of ensuring stable and consistent test pieces when required. It is used a) when called for in the relevant cable standard, or b) if there is a doubt or disagreement about a result and the test needs to be repeated. In either case, the conditioning applies only to the test piece as taken from the cable before any subsequent treatment (ageing, compatibility test, oil immersion, etc.).

Where conditioning at elevated temperature is used, such conditioning shall be carried out as follows:

- for dumb-bells:
 - i) after the removal of the buffer tube from the cable but before the cutting of strips;
 - ii) after grinding (or cutting) to obtain parallel surfaces. Where grinding (or cutting) is not needed, the conditioning shall be performed at the point in the test protocol according to i);
- for tubular test pieces: after removal of the fibre, and any filling compound, but before applying the reference marks, if any, for measurement of the extension.

Where the relevant cable standard calls for conditioning at elevated temperature, it shall be for the time and temperature given in that standard. Where, in case of doubt, the test has to be repeated, the conditioning shall be 24 h at $70\text{ °C} \pm 2\text{ °C}$, or a lower temperature corresponding to the maximum operating temperature of the cable.

2) Room temperature conditioning

Before determination of the cross-sectional area, all test pieces shall be protected from direct sunlight and maintained for at least 3 h at a temperature of $23\text{ °C} \pm 5\text{ °C}$.

b) Dumb-bell test pieces

Dumb-bell test pieces shall be used whenever possible. They shall be prepared from samples of buffer tube, cut open in the direction of the axis.


Each sample of buffer tube shall be cut into strips of an appropriate length. The strips shall be marked to identify the sample from which they are cut and their positions relative to each other in the original sample.

The strips of buffer tube shall be ground or cut, so as to obtain two parallel smooth surfaces between the reference marks mentioned below, care being taken to avoid undue heating. An example of a cutting machine is given in 5.3. For polyethylene (PE) and polypropylene (PP) buffer tube, cutting only, not grinding, shall be employed. After cutting or grinding, including any removal of burrs, the thickness of the strips shall not be less than 0,8 mm and not more than 2,0 mm. If it is not possible to prepare dumb-bell test pieces that comply with the minimum thickness of 0,8 mm, then tubular test pieces shall be used. If tubular test pieces cannot be prepared, then dumb-bells thinner than 0,8 mm may be used, but the rate of separation shall be 25 mm/min.

The test report should also include the fact that non-compliant dumb-bells were used and that the result is indicative.

A dumb-bell test piece, in accordance with Figure 1 or Figure 2, shall then be punched from each prepared strip of buffer tube, or if possible, two dumb-bell test pieces shall be punched side by side.

Dimension in millimeters

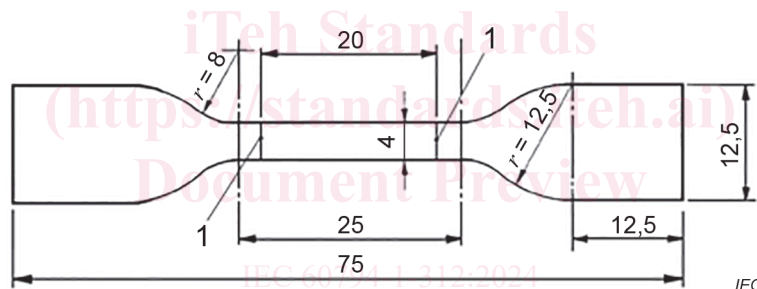

Key

- 1 reference marks

Figure 1 – Dumb-bell test piece

In order to improve the reliability of the results, the following is recommended:


- the punch should be very sharp to minimize imperfections in the test piece;
- a cardboard or other suitable support should be placed between the strip and the base plate; this support shall be marked during punching, but not completely cut through by the punch;
- burrs on the sides of the test piece should be avoided.

For materials where punching results in burrs, the following method may be used:

- 1) each end of the punch shall have a groove approximately 2,5 mm wide and 2,5 mm high (see Figure 3);
- 2) the cut dumb-bell test pieces shall remain attached at both ends with the strip previously prepared according to the requirements of 5.2.2 b) (see Figure 4);
- 3) with the machine given in 5.3, an additional 0,10 mm to 0,15 mm thickness can be cut away to remove possible burrs resulting from the dumb-bell punch; when this operation is completed, the dumb-bell test pieces shall be cut through at their ends in order to remove them from the strip.

When the diameter of the core is too small to allow the dumb-bell to be cut in accordance with Figure 1, then a smaller dumb bell test piece in accordance with Figure 2 shall be punched from each prepared strip.

Dimension in millimeters

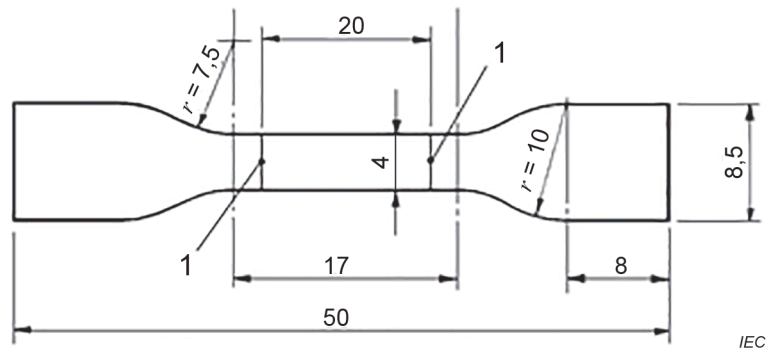


IEC

Key

1 reference marks


Figure 2 – Small dumb-bell test piece

Dimension in millimeters

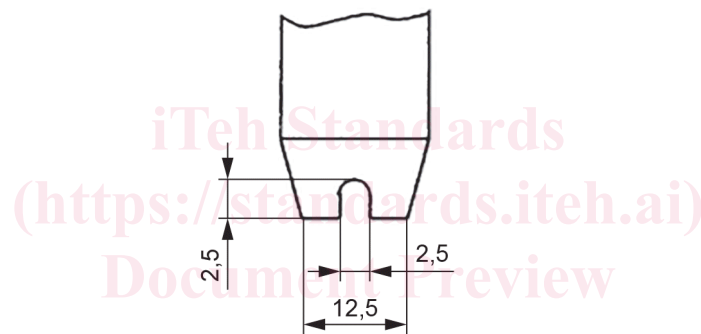

IEC 60794-1-312:202 IEC

<https://standards.iteh.ai/catalog/standards/iec/b2eb8dec-f326-4ed6-91b2-238b8c94b696/iec-60794-1-312-2024>

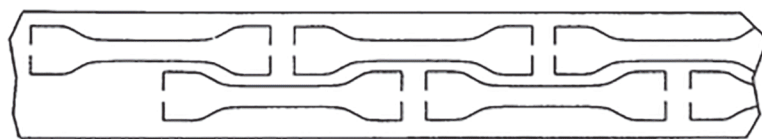Figure 3 – Punch end showing groove

IEC

Figure 4 – Test pieces cut by grooved punch

The central 20 mm for the larger dumb-bells or 10 mm for the smaller dumb-bells shall be marked on each test piece, immediately before the tensile test.

NOTE 2 Where a contact extensometer is used, the pre set grips at the required spacing are deemed to constitute a mark.

Dumb-bell test pieces with incomplete ends are permitted, provided that the breaking point occurs between the reference marks.

An example of a cutting machine is given in Figure 5.