

INTERNATIONAL
STANDARD

ISO
4639-3

First edition
1995-06-15

**Rubber tubing and hoses for fuel circuits
for internal-combustion engines —
Specification —**

Part 3:
Oxidized fuels

ISO 4639-3:1995

<https://standards.iteh.ai/catalog/standards/sist/c86ef9e8-b1e6-4f7f-828d-3189a4201480-iso-4639-3-1995>

*Tuyaux et tubes en caoutchouc pour circuits à carburants pour moteurs à
combustion interne — Spécifications —*

Partie 3: Carburants oxydés



Reference number
ISO 4639-3:1995(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 4639-3 was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 1, *Hoses (rubber and plastics)*.

ISO 4639 consists of the following parts, under the general title *Rubber tubing and hoses for fuel circuits for internal-combustion engines — Specification*:

- Part 1: *Conventional liquid fuels*
- Part 2: *Oxygenated fuels*
- Part 3: *Oxidized fuels*

Annexes A, B, C and D form an integral part of this part of ISO 4639.

© ISO 1995

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Rubber tubing and hoses for fuel circuits for internal-combustion engines — Specification —

Part 3: Oxidized fuels

1 Scope

This part of ISO 4639 specifies requirements for rubber tubing and hoses for use in fuel circuits where the fuel can become oxidized or "sour". These fuels may or may not contain compounds such as alcohols. This part of ISO 4639 does not cover any equipment used for the distribution of liquid fuels, nor tubing totally immersed in fuel tanks.

The hoses and tubing are used in recirculating fuel injection systems and in other systems which, having been charged with fuel, may be subject to exceptional storage conditions at high ambient temperatures. Such hoses and tubing are typically provided with an inner veneer of a speciality elastomeric compound (see figure 1).

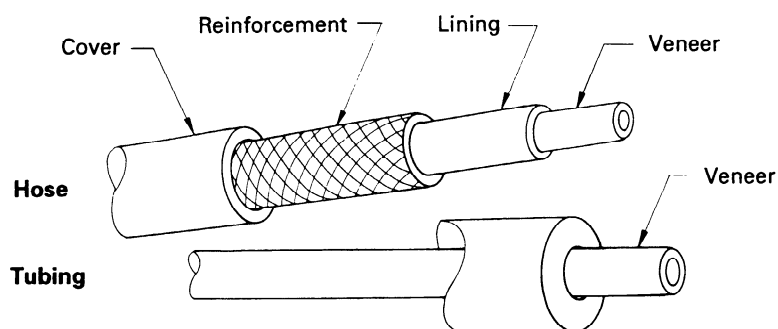


Figure 1 — Typical structure

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this part of ISO 4639. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this part of ISO 4639 are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 37:1994, *Rubber, vulcanized or thermoplastic — Determination of tensile stress-strain properties.*

ISO 48:1994, *Rubber, vulcanized or thermoplastic — Determination of hardness (hardness between 10 IRHD and 100 IRHD).*

ISO 188:1982, *Rubber, vulcanized — Accelerated ageing or heat-resistance tests.*

ISO 286-1:1988, *ISO system of limits and fits — Part 1: Bases of tolerances, deviations and fits.*

ISO 471:1995, *Rubber — Temperatures, humidities and times for conditioning and testing.*

ISO 815:1991, *Rubber, vulcanized or thermoplastic — Determination of compression set at ambient, elevated or low temperatures.*

ISO 1402:1994, *Rubber and plastics hoses and hose assemblies — Hydrostatic testing.*

ISO 1746:1983, *Rubber or plastics hoses and tubing — Bending tests.*

ISO 1817:1985, *Rubber, vulcanized — Determination of the effect of liquids.*

ISO 3302:1990, *Rubber — Dimensional tolerances for use with products.*

ISO 4671:1984, *Rubber and plastics hose and hose assemblies — Methods of measurement of dimensions.*

ISO 4672:1988, *Rubber and plastics hoses — Sub-ambient temperature flexibility tests.*

ISO 6133:1981, *Rubber and plastics — Analysis of multi-peak traces obtained in determinations of tear strength and adhesion strength.*

ISO 7233:1991, *Rubber and plastics hoses and hose assemblies — Determination of suction resistance.*

ISO 7326:1991, *Rubber and plastics hoses — Assessment of ozone resistance under static conditions.*

ISO 8033:1991, *Rubber and plastics hose — Determination of adhesion between components.*

ISO 8308:1993, *Rubber and plastics hoses and tubing — Determination of transmission of liquids through hose and tubing walls.*

3 Types of tubing and hoses

For the purpose of this part of ISO 4639, tubing and hoses are divided into three different types:

— Type 1: Tubing with a working pressure of up to 0,12 MPa inclusive;

— Type 2: Hoses with a working pressure in the range 0 to 0,12 MPa inclusive;

— Type 3: Hoses with a working pressure in the range 0 to 0,3 MPa inclusive.

In addition, the three types 1, 2 and 3 are further divided into two grades:

— Grade A: operating in an environmental temperature of up to 120 °C;

— Grade B: operating in an environmental temperature of up to 140 °C.

Grade B tubing may be provided with a cover.

4 Tubing and hose bores

The bore of all tubing and hoses shall be clean and free from any contamination when examined visually.

5 Sizes

5.1 Tubing

When determined by the methods described in ISO 4671, bore diameters and wall thicknesses shall be as specified in table 1.

Tolerances shall be selected from the appropriate categories specified in ISO 3302: M3 for moulded hoses, E2 for extrusions.

The thickness of the veneer, where applicable, shall be 0,6 mm ± 0,1 mm and this value shall be included in the total nominal wall thickness shown in table 1.

Table 1 — Tubing bore diameters and wall thicknesses

Dimensions in millimetres

Nominal bore	Nominal wall thickness
3,5	3,5
4	3,5
5	4
7	4,5
9	4,5
11	4,5
13	4,5

NOTE 1 For information, the unions on which the tubing is to be fitted have the following diameters:

4 mm, 4,5 mm, 6 mm or 6,35 mm, 8 mm, 10 mm, 12 mm and 14 mm.

5.2 Hoses

When tested by the methods described in ISO 4671, the dimensions, tolerances and concentricity of hoses shall comply with tables 2 and 3.

The thickness of the veneer, where applicable, shall be 0,6 mm ± 0,1 mm and this value shall be included in the total nominal wall thickness shown in table 2.

Table 2 — Hose dimensions

Dimensions in millimetres

Bore diameter	Tolerance	Wall thickness	Outside diameter	Tolerance
3,5	± 0,3	3	9,5	± 0,4
4			10	
5			11	
6			12	
7			13	
7,5			13,5	
8			14	
9			15	
11			18	
12			19	
13	± 0,4	3,5	20	± 0,6
16			24	
21			29	
31,5	± 0,4	4	40	± 1
40			50	
	+0,5 -1	4,25		
			5	

ITeh STANDARD PREVIEW
 (standards.iteh.ai)
 ISO 4639-3:1995
<https://standards.iteh.ai/catalog/standards/sist/c8409e8-b1e6-4f7f-828d-a1fa9a442614/iso-4639-3-1995>

6 Physical tests and specifications

6.1 Requirements for materials

Tests shall be carried out where possible on test pieces cut from finished products. Where this is not possible, test pieces shall be cut from standard test slabs with a state of cure equivalent to that of the finished product. Compression set determinations shall always be carried out on standard test slabs.

6.1.1 Hardness

Hardness, determined in accordance with the procedure in ISO 48 (microtest), shall comply with the values shown in table 4.

6.1.2 Tensile strength and elongation at break

Tensile strength and elongation at break, determined in accordance with the procedure in ISO 37 and on a No. 2 dumb-bell, shall comply with the values shown in table 4.

Table 3 — Hose concentricity

Dimensions in millimetres

Internal diameter	Maximum variation from concentricity
	Ratio of internal diameter to overall diameter
Up to and including 3,5	0,4
Over 3,5	0,8

6.1.3 Changes in properties after accelerated ageing

Accelerated ageing shall be carried out in accordance with ISO 188 in a ventilated drying oven under the following conditions, using test pieces as described in 6.1.1 and 6.1.2:

- Grade A veneer, hose lining, hose cover and tubing, and grade B veneer and hose lining: (72 ± 0) h at 120 °C ± 2 °C.

— Grade B tubing and hose cover: $(72 \begin{smallmatrix} 0 \\ -2 \end{smallmatrix})$ h at $140 \text{ °C} \pm 2 \text{ °C}$.

The change in hardness, tensile strength and elongation at break shall not exceed the values shown in table 4.

6.1.4 Ozone resistance

After accelerated ageing in accordance with 6.1.3, when tested in accordance with the appropriate method in ISO 7326:1991, under the following conditions, the test piece shall show no signs of cracking when examined under a magnification of $\times 2$ (see also table 4).

Partial pressure of ozone: $50 \text{ mPa} \pm 3 \text{ mPa}$

Duration: $(72 \begin{smallmatrix} 0 \\ -2 \end{smallmatrix})$ h

Elongation

Hose covers, linings and veneers: 20 %

Tubing (including veneers): 50 %

Temperature: $40 \text{ °C} \pm 2 \text{ °C}$

6.1.5 Compression set

The compression set, when determined in accordance with ISO 815:1991, using the large (type A) test piece, under the conditions shown in table 4, shall comply with the values shown in table 4.

Table 4 — Requirements for materials

Subclause	Characteristic	Unit	Requirements for grade A and grade B			
			Veneer	Hose lining	Hose cover	Tubing
6.1.1	Nominal hardness	IRHD	80	70	70	70
6.1.1	Tolerance	IRHD	$\begin{smallmatrix} +5 \\ -10 \end{smallmatrix}$	$\begin{smallmatrix} +10 \\ -10 \end{smallmatrix}$	$\begin{smallmatrix} +10 \\ -10 \end{smallmatrix}$	$\begin{smallmatrix} +10 \\ -10 \end{smallmatrix}$
6.1.2	Tensile strength, min.	MPa	8	8,5	10	10
6.1.2	Elongation at break, min.	%	200	200	250	250
6.1.3	Accelerated ageing					
	Increase in hardness, max. ¹⁾	IRHD	5	15	15	15
	Reduction in tensile strength, max.	%	10	20	20	20
	Reduction in elongation at break, max.	%	20	50	50	50
6.1.4	Resistance to ozone		No cracks at $\times 2$ magnification			
6.1.5	Compression set, max. $(24 \begin{smallmatrix} 0 \\ -2 \end{smallmatrix})$ h at $100 \text{ °C} \pm 1 \text{ °C}$	%	50	50	50	50
6.1.6.1	Resistance to hydrocarbons					
	Reduction in hardness, max.	IRHD	20	—	—	25
	Reduction in tensile strength, max.	%	40	40	—	40
	Reduction in elongation at break, max.	%	30	30	—	30
	Increase in volume, max.	%	25	30	—	30
6.1.6.2	Resistance to oxygenated fuel					
	Reduction in hardness, max.	IRHD	25	—	—	25
	Reduction in tensile strength, max.	%	40	50	—	50
	Reduction in elongation at break, max.	%	30	40	—	40
	Increase in volume, max.	%	30	45	—	45
6.1.6.3	Resistance to oxidized fuel					
	Reduction in hardness, max.	IRHD	25	—	—	25
	Reduction in tensile strength, max.	%	40	50	—	50
	Reduction in elongation at break, max.	%	30	40	—	40
	Increase in volume, max.	%	30	45	—	45
6.1.7	Resistance to oil No. 3					
	Reduction in tensile strength, max.	%	—	—	50	50
	Reduction in elongation at break, max.	%	—	—	50	50
	Change in volume, max. increase	%	—	—	75	75
	max. decrease	%	—	—	5	5

1) The absolute maximum is 90 IRHD and shall not be exceeded.

6.1.6 Resistance to fuels

WARNING — Fuels at elevated temperatures are extremely hazardous. Tests should be conducted under reflux in an explosion-proof hood.

6.1.6.1 Resistance to hydrocarbons (liquid C of ISO 1817:1985)

This requirement applies only to tubing and to the veneer and lining of hoses.

Any changes in hardness (see 6.1.1), tensile strength (see 6.1.2), elongation at break (see 6.1.2) and volume, when determined in accordance with the procedures specified in ISO 1817, after a period of (72 ± 2) h of immersion in liquid C at a temperature of $60 \text{ °C} \pm 1 \text{ °C}$, shall comply with the values shown in table 4.

6.1.6.2 Resistance to oxygenated fuel

This requirement applies only to tubing and to the veneer and lining of hoses.

Any changes in hardness (see 6.1.1), tensile strength (see 6.1.2), elongation at break (see 6.1.2) and volume, when determined in accordance with the procedures specified in ISO 1817, after a period of (72 ± 2) h of immersion in a liquid comprising a mixture of 85 % by volume of liquid C (ISO 1817) and 15 % by volume of methanol, at a temperature of $60 \text{ °C} \pm 1 \text{ °C}$, shall comply with the values shown in table 4.

6.1.6.3 Resistance to oxidized fuel

This requirement applies only to tubing and to the veneer and lining of hoses.

Any changes in hardness (see 6.1.1), tensile strength (see 6.1.2), elongation at break (see 6.1.2) and volume, when determined in accordance with the procedures specified in ISO 1817, after a period of $140 \text{ h} \pm 2 \text{ h}$ of immersion in the test liquid specified in annex A, at a temperature of $60 \text{ °C} \pm 1 \text{ °C}$, shall comply with the values shown in table 4.

6.1.7 Resistance to oil No. 3

This requirement applies only to tubing and hose covers.

Any changes in tensile strength (see 6.1.2), elongation at break (see 6.1.2) and volume, when determined in accordance with the procedures specified in

ISO 1817, after a period of (72 ± 2) h immersion in oil No. 3 at a temperature of $120 \text{ °C} \pm 2 \text{ °C}$ for grade A and $140 \text{ °C} \pm 2 \text{ °C}$ for grade B, shall comply with the values shown in table 4.

6.2 Requirements for finished products

6.2.1 Leak test

This requirement applies only to tubing.

The rubber tubing shall be placed over the polished end of a piece of metal tubing, machined to tolerance H14 as defined in ISO 286-1 and having a diameter equal to the appropriate value given in note 1. The rubber tubing shall be pushed along the metal tubing to a distance equal to three times the nominal bore of the rubber tubing. The other end of the metal tubing shall be closed and the other end of the rubber tubing shall be attached to an air supply.

The assembly shall then be subjected to an internal pressure of 0.12 MPa for a period of 2 min, using liquid C. No leak shall appear during the duration of the test (see also table 5).

6.2.2 Tension test

This requirement applies only to tubing.

A piece of rubber tubing shall be placed over the end of a piece of metal tubing in the manner described in 6.2.1. This assembly shall then be suspended from the metal tubing in a vertical position in which it shall be capable of withstanding an applied load of 10 N at its other end, which shall be plugged.

The tubing shall not rupture nor slip off (see also table 5).

6.2.3 Minimum burst pressure

The minimum burst pressures, determined in accordance with the procedure in ISO 1402, shall comply with the values shown in table 5.

6.2.4 Adhesion

This requirement applies only to hoses and veneered tubing.

The adhesion between components, determined in accordance with the appropriate procedure in ISO 8033, shall comply with the values shown in table 5.

6.2.5 Low-temperature flexibility

The test shall be carried out in accordance with ISO 4672:1988, procedure B, under the following conditions:

Empty tubing or hose:	$(24 \begin{smallmatrix} 0 \\ -2 \end{smallmatrix})$ h at $-25 \text{ °C} \pm 2 \text{ °C}$
Tubing or hose filled with liquid C:	$(72 \begin{smallmatrix} 0 \\ -2 \end{smallmatrix})$ h at $-40 \text{ °C} \pm 2 \text{ °C}$

Not more than 30 min shall be allowed to elapse between the time at which the tubing or hose is filled and that at which cooling is started.

The bending radius shall be 12 times the nominal bore size for hoses and 25 times the nominal bore size for tubing.

After flexing, the tubing or hose shall show no signs of cracking when examined under $\times 2$ magnification (see also table 5).

NOTE 2 The "empty" test, which is widely used by industry, is included only as a referee test.

6.2.6 Cleanliness

The amount of impurities, determined in accordance with annex B, shall comply with the values shown in table 5.

6.2.7 Determination of waxy products extracted by liquid C

The amount of waxy products extractable, determined in accordance with annex B, shall comply with the values shown in table 5.

6.2.8 Permeability to liquid C

The values of permeability to liquid C, determined in accordance with the procedure in ISO 8308, for $100 \text{ h} \pm 2 \text{ h}$ at $40 \text{ °C} \pm 1 \text{ °C}$, shall comply with the values shown in table 5.

6.2.9 Tear resistance

This requirement applies only to tubing.

The resistance to tearing, determined in accordance with annex C, shall comply with the values shown in table 5.

6.2.10 Suction resistance

The test shall be carried out on straight hoses only, using ISO 7233:1991, procedure A, under the following conditions:

Vacuum:	80 kPa
Duration:	15 s to 60 s
Ball diameter:	$0,8 \times$ nominal bore

The ball shall traverse the full length of the hose (see also table 5).

6.2.11 Resistance to kinking

This requirement applies only to straight tubing and hoses of 16 mm bore size or less.

The test shall be carried out in accordance with the procedure in ISO 1746, using mandrel diameters as follows:

- for tubing and hoses of 7 mm up to and including 11 mm diameter: 140 mm
- for tubing and hoses of 12 mm up to and including 16 mm diameter: 220 mm.

The coefficient of deformation T/D shall comply with the values given in table 5.

6.2.12 Long-term resistance to oxygenated fuel

Tubing or hose test pieces are subjected to long-term circulation of oxygenated fuel for 1 000 h at $60 \text{ °C} \pm 1 \text{ °C}$ in accordance with annex D.

One test piece is then subjected sequentially to the tests in 6.2.12.1 to 6.2.12.4.

A second test piece is subjected to the test in 6.2.12.5.

A third test piece is subjected to the test in 6.2.12.6.

6.2.12.1 Suction resistance: When tested in accordance with the procedure in 6.2.10, the ball shall traverse the full length of the hose (see also table 5).

6.2.12.2 Resistance to kinking: The coefficient of deformation T/D , determined in accordance with 6.2.11, shall comply with the values given in table 5.

6.2.12.3 Ozone resistance: When tested in accordance with method 1 of ISO 7326:1991, under the following conditions, the test piece shall show no signs of cracking when examined under a magnification of $\times 2$ (see also table 5):

Partial pressure of ozone:	50 mPa \pm 3 mPa
Duration:	(72 $\begin{smallmatrix} 0 \\ -2 \end{smallmatrix}$) h

Elongation

Hose covers, linings and veneer:	20 %
Tubing (including veneer):	50 %
Temperature:	40 °C \pm 2 °C

6.2.12.4 Minimum burst pressure: The minimum burst pressure, determined in accordance with 6.2.3, shall comply with the values shown in table 5.

6.2.12.5 Adhesion: The adhesion between components, both cover and lining to reinforcement, when determined in accordance with 6.2.4 using the second test piece specified in 6.2.12, shall comply with the values shown in table 5.

6.2.12.6 Low-temperature flexibility: When tested in accordance with 6.2.5, the third test piece specified in 6.2.12 shall show no signs of cracking under $\times 2$ magnification (see also table 5).

6.2.13 Long-term resistance to oxidized fuel

Tubing or hose test pieces are subjected to long-term circulation of oxidized fuel prepared as described in annex A for 1 000 h at 60 °C \pm 1 °C in accordance with annex D. One test piece is then subjected sequentially to the tests in 6.2.12.1 to 6.2.12.4. Separate test pieces are subjected to the tests in 6.2.12.5 and 6.2.12.6.

The results shall comply with the requirements given, respectively, in 6.2.12.1 to 6.2.12.6 (see also table 5).

6.2.14 Change in properties after accelerated ageing

A test piece of tubing or hose of suitable length, bent into a free loop approximately 250 mm in diameter until its ends meet, is aged in an air-circulating oven for (72 $\begin{smallmatrix} 0 \\ -2 \end{smallmatrix}$) h at 150 °C \pm 3 °C. At the end of the ageing period, the test piece is straightened over a period of 4 s to 8 s. After straightening, it shall show no signs of cracking or disintegration, internally or externally, when examined under $\times 2$ magnification (see also table 5).

7 Marking

Except where the component is too small to label, the tubing and hose shall be marked with the following information:

- fuel;
- the manufacturer's name or trade mark;
- the number and date of this part of ISO 4639;
- the type and grade;
- the month and year of manufacture;
- the bore.

EXAMPLE

FUEL; MN; ISO 4639-3:1995; 2B; 08/1995; 7 mm

Table 5 — Requirements for finished products

Subclause	Characteristic	Unit	Requirement	
			Tubing	Hose
6.2.1	Leak test	—	No leak	—
6.2.2	Tension test	—	No rupture; shall not slip off	—
6.2.3	Minimum burst pressure	MPa	0,5	3,0
6.2.4	Adhesion Separation force, min. — cover and lining to reinforcement — veneer to lining	kN/m kN/m	— 1,5	1,5 1,5
6.2.5	Low-temperature flexibility	—	No cracks at × 2 magnification	
6.2.6	Cleanliness Insoluble impurities, max. Fuel-soluble solids, max.	g/m ² g/m ²	5 3	5 3
6.2.7	Waxy extractables, max.	g/m ²	1,5	1,5
6.2.8	Permeability to liquid C	cm ³ /m ²	25	25
6.2.9	Tear resistance, min.	kN/m	4,5	—
6.2.10	Suction resistance	—	Ball shall traverse the full length of the hose	
6.2.11	Resistance to kinking Coefficient of deformation T/D , min.	—	0,7	0,7
6.2.12 and 6.2.13	Long-term resistance to oxygenated fuel and oxidized fuels	—	Ball shall traverse the full length of the hose	
6.2.12.1	Suction resistance	—	Ball shall traverse the full length of the hose	
6.2.12.2	Resistance to kinking Coefficient of deformation T/D , min.	—	0,7	0,7
6.2.12.3	Resistance to ozone	—	No cracks at × 2 magnification	
6.2.12.4	Minimum burst pressure	MPa	—	1,2
6.2.12.5	Adhesion Separation force, min. — cover and lining to reinforcement — veneer to lining	kN/m kN/m	— 0,8	0,8 0,8
6.2.12.6	Low-temperature flexibility	—	No cracks at × 2 magnification	
6.2.14	Accelerated ageing	—	No cracking or disintegration internally or externally at × 2 magnification	

Annex A (normative)

Preparation of oxidized-fuel test liquid

A.1 Scope

This annex specifies a method of preparing oxidized ("sour") gasoline test solutions for use in the determination of their effects on elastomeric, plastic and metallic materials and components. The annex covers the preparation of a solution with peroxide number PN90 using a mixture of a *t*-butyl hydroperoxide (70 % aqueous solution), soluble cupric ion ($0,01 \text{ mg/dm}^3$) and a base fuel consisting of 80 % ISO 1817 liquid C, 15 % methanol and 5 % 2-methylpropan-2-ol (*t*-butyl alcohol), by volume. Other base fuels and peroxide numbers may be used as required by the engineering drawing or specification, but it should be noted that some base fuels may give rise to separation of the aqueous phase of the hydroperoxide solution.

This annex also describes the determination of the peroxide number of fuel.

A.2 Reagents

During the analysis, unless otherwise stated, use only reagents of recognized analytical grade and only distilled water or water of equivalent purity.

A.2.1 *t*-Butyl hydroperoxide, 70 % aqueous solution, $\rho = 0,935 \text{ g/cm}^3$.

A.2.2 Cupric ion concentrate, solution of cupric naphthenate containing 6 % to 12 % by mass of copper in an appropriate hydrocarbon solvent.

A.2.3 2,2,4-trimethylpentane (iso-octane).

CAUTION — Low flash point.

A.2.4 Toluene.

CAUTION — Low flash point.

A.2.5 Methanol.

CAUTION — Low flash point.

A.2.6 2-Methylpropan-2-ol (*t*-butyl alcohol).

CAUTION — Low flash point.

A.3 Apparatus

A.3.1 Polyethylene bottle, capacity 1 000 ml, wide-mouth, with screw cap.

A.3.2 Glass volumetric flasks, capacity 1 000 cm³.

A.3.3 Graduated glass pipettes, capacity 10 cm³.

A.3.4 Graduated glass measuring cylinders, capacity 100 cm³ and 1 000 cm³.

A.4 Procedure

CAUTION — This procedure must be carried out under a fume hood. Eye protection and disposable plastic gloves must be worn.

A.4.1 Preparation of test liquids

A.4.1.1 Base fuel mixture

Prepare ISO 1817 liquid C by mixing equal volumes of 2,2,4-trimethylpentane (A.2.3) and toluene (A.2.4). Store in a dark-glass bottle.

Mix the ISO 1817 liquid C, methanol (A.2.5) and 2-methylpropan-2-ol (A.2.6) in the ratio 80:15:5 by volume to make the base fuel. Store in a dark-glass bottle.

A.4.1.2 Cupric ion stock solution (1 mg/dm³)

Add the appropriate volume of cupric ion concentrate (A.2.2) to base fuel to produce 1 000 cm³ of a 1,140 mg/cm³ cupric ion solution (Cu-1). Store in a dark-glass bottle.

Add 100 cm³ of Cu-1 to 1 040 cm³ of base fuel to produce a 0,1 mg/cm³ cupric ion solution (Cu-2). Store in a dark-glass bottle.