

---

# INTERNATIONAL STANDARD



# 4646

---

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

---

## Rubber or plastics coated fabrics — Low temperature impact test

*Support textile revêtu de caoutchouc ou de plastique — Essai de choc à basse température*

First edition — 1978-07-01

**ITeH STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 4646:1978

<https://standards.iteh.ai/catalog/standards/sist/72126120-b7f5-4594-821b-103315d97f71/iso-4646-1978>

---

UDC 678.066 : 677.017.56 : 536.485

Ref. No. ISO 4646-1978 (E)

**Descriptors :** coated fabrics, fabrics coated with rubber, fabrics coated with plastics, low-temperature tests, impact tests.

Price based on 5 pages

## FOREWORD

ISO (the International Organization for Standardization) is a worldwide federation of national standards institutes (ISO member bodies). The work of developing International Standards is carried out through ISO technical committees. Every member body interested in a subject for which a technical committee has been set up has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council.

International Standard ISO 4646 was developed by Technical Committee ISO/TC 45, *Rubber and rubber products*, and was circulated to the member bodies in June 1976.

(standards.iteh.ai)

It has been approved by the member bodies of the following countries :

Australia	Hungary	ISO 4646:1978
Austria	India	<a href="http://standards.iteh.ai/catalog/standards/sist/72126120-b7f5-4594-821b-103315d9">http://standards.iteh.ai/catalog/standards/sist/72126120-b7f5-4594-821b-103315d9</a>
Belgium	Ireland	Spain
Brazil	Mexico	Sweden 4646-1978
Canada	Netherlands	Switzerland
Chile	Philippines	Turkey
France	Romania	U.S.A.
		U.S.S.R.

The member body of the following countries expressed disapproval of the document on technical grounds :

United Kingdom

# Rubber or plastics coated fabrics — Low temperature impact test

## 1 SCOPE AND FIELD OF APPLICATION

1.1 This International Standard specifies a procedure for determining the lowest temperature at which fabrics coated with rubber or plastics will not exhibit fractures or coating cracks when subjected to specific impact conditions.

1.2 Fabrics coated with rubber or plastics are used in many applications involving low-temperature flexing with or without impact. Data obtained by this method may be used to predict the behaviour of these coated fabrics at low temperatures only in the applications in which the conditions of deformation are similar to those specified in the method.

## 2 REFERENCES

ISO 2231, *Fabric coated with rubber or plastics — Standard atmospheres for conditioning and testing.*

ISO 2286, *Fabrics coated with rubber or plastics — Determination of roll characteristics.*

## 3 APPARATUS

### 3.1 Test piece clamps and striking arm

The test piece clamps shall be designed to hold the test piece or pieces as a cantilever beam. Each individual test piece shall be held firmly and securely in the clamps.

The striking edge shall move relative to the test piece(s) along a trajectory normal to the upper surface at a linear speed of 1,8 to 2,1 m/s at impact and during at least the following 6 mm of travel. In order to maintain this speed, it may be necessary to reduce the number of test pieces tested at one time. (See annex.)

The striking edge shall have a radius of  $1,6 \pm 0,1$  mm.

The striking arm and the test piece clamps shall have a clearance at and immediately following impact in accordance with the dimensions listed in the table.

### 3.2 Insulated tank

3.3 **Heat-transfer medium.** Any liquid heat-transfer medium that remains fluid at the test temperature and

which will not appreciably affect the materials being tested may be used.

Where a flammable or toxic solvent is used as the cooling medium, the customary precautions in handling such a material shall be exercised. Methanol is the recommended heat-transfer medium for rubber.

NOTE — The following materials have been used down to the indicated temperatures :

Dow Corning 200 fluids :

— kinematic viscosity 5 mm<sup>2</sup>/s — 60 °C  
— kinematic viscosity 2 mm<sup>2</sup>/s — 76 °C

Methanol — 90 °C

Dichlorodifluoromethane — 120 °C

When dichlorodifluoromethane refrigerant is used, it must be cooled below its boiling temperature of  $-29,8$  °C before being transferred from the cylinder to the tank of the testing machine.

3.4 **Stirrer**, to provide thorough circulation of the heat-transfer medium.

3.5 **Temperature control** (automatic or manual), for controlling the temperature of the heat-transfer medium to within  $\pm 0,5$  °C of the desired temperature.

Powdered solid carbon dioxide (dry ice), liquid nitrogen or liquid carbon dioxide are recommended for lowering the temperature. An electric immersion heater is required for raising the temperature.


3.6 **Thermocouple**, with associated temperature indicator graduated in 1 °C divisions and having a range suitable for the temperature at which the tests are to be made.

The thermocouple shall be constructed of copper-constantan wire between 0,2 mm and 0,5 mm in diameter and shall be fusion-bonded at the junction. It shall be located as near the test piece as possible.

NOTE — A thermometer may be used if it is shown to be in agreement with the specified thermocouple.

## 4 TEST PIECE

4.1 The test piece shall be die punched. It shall be  $6,4 \pm 0,5$  mm wide. All test pieces shall be cut with the longer dimensions parallel to the lengthwise direction of the coated fabric unless otherwise specified.

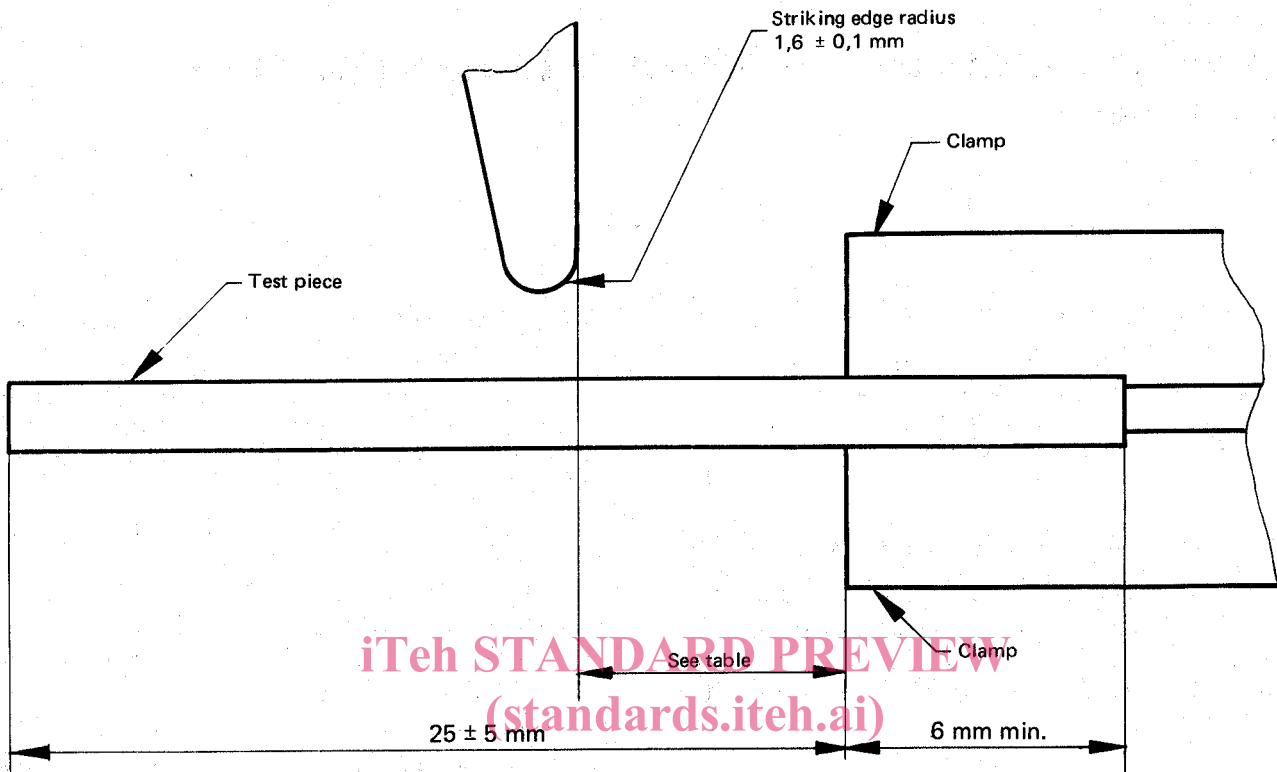

ISO 4646:1978  
<https://standards.iteh.ai/catalog/standards/sist/72126120-b7f5-4594-821b-103315d97f71/iso-4646-1978>

FIGURE 1 – Test piece holder and striker

TABLE – Clearance of striking arm and test piece clamps

Dimension in millimetres	
Thickness of test piece*	Required clearance
1,65 to 2,15	6,4 ± 0,3
1,05 to 1,64	5,7 ± 0,3
0,55 to 1,04	5,2 ± 0,3
0,10 to 0,54	4,8 ± 0,3

\* As determined by ISO 2286.

NOTES

- 1 The dimensional requirements may be obtained by fabricating an adjustment plate or individual plates to fit the test piece holder illustrated in figure 1.
- 2 Apparatus for this test may have any type of activation provided that it meets the dimensional and velocity requirements given above and in clause 3. If the striker is electrically driven, a means of controlling the voltage may be needed to control the speed when testing light gauge material.

4.2 A minimum of 6 mm of the test piece shall be held in the clamps, and the length extending from the clamp shall be  $25 \pm 5$  mm.

NOTE — Sharp dies must be used in the preparation of test pieces for this test if reliable results are to be obtained. Light honing of the cutting edges with a jeweller's honing stone may be carried out daily.

## 5 TIME-INTERVAL BETWEEN MANUFACTURING AND TESTING

5.1 For all test purposes, the minimum time between manufacturing and testing shall be 16 h.

5.2 For non-product tests the maximum time between manufacturing and testing shall be 4 weeks and for evaluations intended to be comparable the tests, as far as possible, should be carried out after the same time-interval.

5.3 For product tests, wherever possible, the time between manufacturing and testing should not exceed 3 months. In other cases, tests shall be made within 2 months of the date of receipt by the customer.

## 6 CONDITIONING OF TEST PIECES

Condition the test pieces in atmosphere "A" of ISO 2231.

NOTE — In ISO 2231, atmosphere "A" is defined by two of its characteristics :

- temperature  $20 \pm 2$  °C, relative humidity  $65 \pm 5$  %
- or
- temperature  $23 \pm 2$  °C, relative humidity  $50 \pm 5$  %
- for tropical countries only, temperature  $27 \pm 2$  °C, relative humidity  $65 \pm 5$  %

Test pieces shall be exposed to this atmosphere for a minimum of 3 h.

## 7 PROCEDURE

7.1 Prepare the tank (3.2) and bring the apparatus to the desired temperature. This may be accomplished by placing a suitable amount of solid carbon dioxide (dry ice) in the tank and slowly adding the heat-transfer medium (3.3) until the tank is filled within 50 mm of the top. During the test, the temperature of the bath may be maintained constant by judicious addition of small quantities of dry ice.

NOTE — The desired temperature may also be obtained by filling the tank with the heat-transfer medium and lowering the temperature by the addition of liquid carbon dioxide controlled by a solenoid actuated with an associated temperature control. Where temperatures below that obtainable with dry ice or liquid carbon dioxide are required, liquid nitrogen may be used.

7.2 Mount the test pieces in their holder and immerse them for  $3,0 \pm 0,5$  min at the desired temperature. The side to be evaluated shall face toward the striking arm unless otherwise specified.

7.3 After immersion for the specified time at the test temperature, record the temperature and deliver a single impact.

7.4 For each test, check the speed of the striker, which shall be between 1,8 and 2,1 m/s. (See annex.)

7.5 After taking out the test pieces from the tank examine each test piece to determine whether or not it has failed. Failure is defined as any fracture or crack visible in the coating when examined under a 5 X magnifier. Bend the test piece to an angle of  $180^\circ$  around a 6 mm diameter mandrel in the same direction as the bend caused by the impact prior to examining it under the 5 X magnifier.

7.6 Use new test pieces for each test temperature.

NOTE — For routine testing of all coated fabrics, subject five test pieces to the impact test at a specified temperature as stated in the relevant material specification.

7.7 For compliance with this International Standard no test piece shall fail at the specified temperature.

## 8 TEST REPORT

The test report shall include the following particulars :

- a) reference to this International Standard;
- b) identification of the coated fabric;
- c) temperature at which the test pieces were tested;
- d) type of testing apparatus used;
- e) conditioning temperature, humidity and period;
- f) length of time test pieces were immersed;
- g) number of test pieces tested;
- h) speed of striker at impact;
- j) behaviour of individual test pieces;
- k) whether the material complies with this International standard (see 7.7).

## ANNEX

## SPEED CALIBRATION OF THE SOLENOID-ACTUATED LOW TEMPERATURE IMPACT TESTER

## A.1 SPEED CALIBRATION PRIOR TO TESTING

## A.1.1 Principle

Measurement of the height,  $h$ , to which a steel ball, suspended on the striker mechanism of the tester, rises after the striker has had its upward motion halted by contact with a mechanical stop. Acceleration of the ball in such a manner that the law governing a freely falling body applies.

## A.1.2 Procedure

## A.1.2.1 Securing ball support

Remove either one of the nuts that fasten the striking bar guide rods to the solenoid armature yoke. Place the small hole of the ball support (see figure 2) over the guide rod and replace and secure the nut.

## A.1.2.2 Adjusting stroke of striker

Remove the metal guard from around the solenoid. Spread open the rubber bumper (see figure 3) and insert it around the armature. Replace the solenoid guard. Insert a typical test piece into the specimen holder of the tester. Raise the striking mechanism by hand until the end of the stroke is reached. It is essential that, with the striking mechanism raised to its maximum height, the striker bar of the tester is in contact with the test piece but that the bar is not in the plane of the test piece. If the striker bar is not in contact with the test piece, the rubber bumper must be removed and replaced by a thinner bumper. Conversely, if the striker bar moves into the plane of the test piece, the bumper must be replaced by a thicker one.

## A.1.2.3 Placement of ball and measuring tube

Place a 19 mm diameter steel ball on the ball holder. (In theory, the upward flight of the ball is independent of the mass of the ball. However, if the mass is too large, the motion of the striker bar may be impeded.) Clamp a glass or clear plastic tube with a minimum inside diameter of 25,4 mm in a vertical position directly over the ball. The tube should contain a scale divided into 5 mm intervals. The zero position on the scale should be aligned with the top of the ball when the ball is at the top of the stroke of the striker mechanism.

## A.1.2.4 Measurement and calculation

With the tester equipped as described above and devoid of test pieces and immersion medium, actuate the solenoid and read the ball height to the nearest 5 mm. Make at least five measurements. Average all results and convert the

average to metres. Determine the striker speed,  $v$ , in metres per second, from the following equation :

$$v = \sqrt{2gh}$$

where

$g$  is the acceleration due to gravity, in metres per second squared (= 9,8 m/s<sup>2</sup>);

$h$  is the average ball height, in metres.

NOTE — Calibration measurements should be made with the tester supported on a non-resilient surface, such as a laboratory bench or concrete floor. Resilient mountings tend to absorb some of the striker energy causing low ball height values.

## A.2 SPEED CALIBRATION DURING TESTING

A.2.1 With the tester equipped with ball support, ball and measuring tube (see clause A.1), but without the rubber bumper (tester in normal operating condition) and devoid of test pieces and immersion medium, actuate the solenoid and read the ball height to the nearest 5 mm. Make ten measurements. From the lowest and highest ball height readings, determine the range in striker speed, using the equation in A.1.2.4. This range is termed "range of speed at the top of the stroke".

A.2.2 With the tester equipped as described in A.2.1, but also with test piece(s) and immersion medium, conduct the brittleness test as described in clause 7. Read the ball height each time the solenoid is actuated. Convert the ball height to speed as shown in A.1.2.4. If the speed lies within the predetermined range of speed at the top of the stroke, the test should be considered valid. If the speed lies outside of the predetermined range, the test is invalid and should not be reported. Should successive tests be invalid, adjustments should be made to bring the speed at the top of the stroke within the acceptable, predetermined range. This may be accomplished by reducing the number of test pieces tested per impact.

A.2.3 The following example typifies the entire speed calibration procedure for solenoid actuated testers :

a) Using the procedure in clause A.1, the striker speed at the point of impact of a tester devoid of test pieces and immersion medium was found to be 1,9 m/s. This speed is within the specified limits of 7.4.

b) Using the procedure in A.2.1, with the tester devoid of test pieces and immersion medium, the range of striker speeds at the top of the stroke was found to be 2,5 to 2,7 m/s. This range becomes the acceptable range for this series of tests. The acceptable range should be established each time the striker speed at the point of impact is determined (see clause A.1).


c) Using the procedure of A.2.2, with the tester containing a test piece(s) and immersion medium, the speed at the top of the stroke during the first solenoid actuation was found to be 2,5 m/s. This speed is within the acceptable range and the test is valid.

d) The speeds at the top of the stroke during the second and third solenoid actuations were found to be 2,4 and 2,3 m/s, respectively. These speeds were outside of the acceptable range and both tests were invalid.

e) Adjustments were made to increase the speed at the top of the stroke, using the procedures given in A.2.2.

f) The speeds at the top of the stroke during the fourth and all subsequent solenoid actuations were found to lie between 2,5 and 2,7 m/s. The results of all these tests were valid.

Dimensions in millimetres (inches)

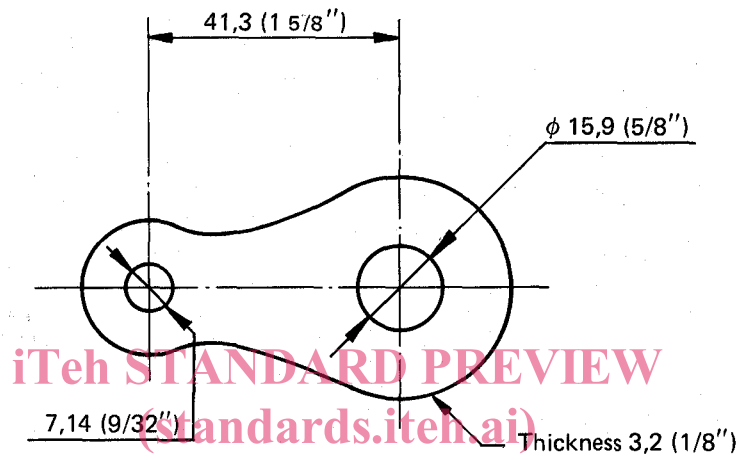

ISO 4646:1978  
 FIGURE 2 — Ball support  
<https://standards.itech.ai/catalog/standards/sis/72126120-b7f5-4594-821b-103315d97f71/iso-4646-1978>

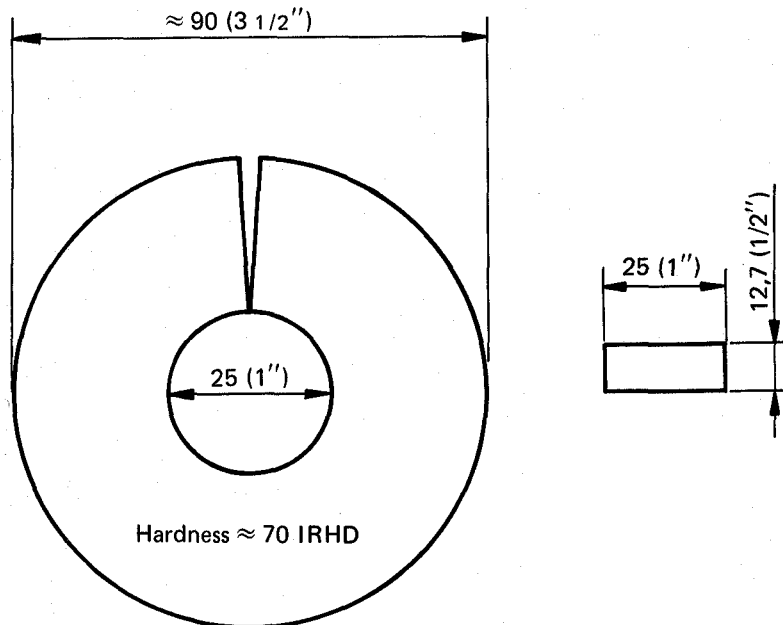


FIGURE 3 — Rubber bumper

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 4646:1978

<https://standards.iteh.ai/catalog/standards/sist/72126120-b7f5-4594-821b-103315d97f71/iso-4646-1978>