



Designation: **F835—18** F835 – 20

Standard Specification for Alloy Steel Socket Button and Flat Countersunk Head Cap Screws¹

This standard is issued under the fixed designation F835; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the U.S. Department of Defense.

1. Scope*

1.1 This specification covers the requirements for quenched and tempered alloy steel hexagon socket button (SBHCS) 0.060 through 0.625 thread sizes and flat countersunk (SFHCS) 0.060 through 1.5 thread sizes head cap screws having material properties for high-strength requirements.

1.2 Fasteners meeting this specification are intended for shear-type applications and have tensile requirements ranging from 122 to 150 ksi.

1.3 The values stated in inch-pound units are to be regarded as standard. No other units of measurement are included in this standard.

1.4 The hazard statement applies only to the test method section, Section 11, of this specification. *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 ASTM Standards:²

[A751 Test Methods, Practices, and Terminology for Chemical Analysis of Steel Products](#)

[D3951 Practice for Commercial Packaging](#)

[E3 Guide for Preparation of Metallographic Specimens](#)

[E18 Test Methods for Rockwell Hardness of Metallic Materials](#)

[E112 Test Methods for Determining Average Grain Size](#)

[E384 Test Method for Microindentation Hardness of Materials](#)

[F606/F606M Test Methods for Determining the Mechanical Properties of Externally and Internally Threaded Fasteners, Washers, Direct Tension Indicators, and Rivets](#)

¹ This specification is under the jurisdiction of ASTM Committee F16 on Fasteners and is the direct responsibility of Subcommittee F16.02 on Steel Bolts, Nuts, Rivets and Washers.

Current edition approved Dec. 1, 2018/Aug. 1, 2020. Published December 2018/August 2020. Originally approved in 1986. Last previous edition approved in 2016/2018 as F835—16/F835 – 18. DOI: 40.1520/F0835-18.10.1520/F0835-20.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

*A Summary of Changes section appears at the end of this standard

[F788 Specification for Surface Discontinuities of Bolts, Screws, Studs, and Rivets, Inch and Metric Series](#)
[F2328 Test Method for Determining Decarburization and Carburization in Hardened and Tempered Threaded Steel Bolts, Screws, Studs, and Nuts](#)

2.2 *ASME Standards*:³

[B18.3 Socket Cap, Shoulder and Set Screws—Inch Series](#)

[B18.24 Part Identifying Number \(PIN\) Code System Standard for B18 Fastener Products](#)

3. Ordering Information

3.1 Orders for material under this specification shall include the following:

3.1.1 Quantity (number of screws).

3.1.2 Dimensions, including nominal thread designation, thread pitch, and nominal screw length (inches). A standard part number may be used for this definition.

3.1.3 Name of the screw: SBHCS or SFHCS.

3.1.4 Coating, if required. If a protective finish other than black oxide is required, it must be specified on the order or product standard.

3.1.5 Lot testing, if required (see [10.3](#)).

3.1.6 Certification, if required (see [14.1](#)).

3.1.7 ASTM designation and year of issue.

3.1.8 Any special requirements.

3.1.9 For establishment of a part identifying system, see ASME B18.24.

3.2 *Example*—1000 pieces 0.250 – 20 × 0.375 SBHCS lot tensile test. ASTM F835–XX.

4. Materials and Manufacture

4.1 The screws shall be fabricated from alloy steel made to fine grain practice. In the event of controversy over grain size, referee tests on finished screws conducted in accordance with Test Methods [E112](#) shall prevail.

4.2 Screws shall be hot or cold upset or extruded, or both.

4.3 Unless otherwise specified, threads shall be rolled for diameters through 0.625 in. and for screw lengths through 4 in. For diameters and lengths other than this, threads may be rolled, cut or ground.

4.4 Screws shall be heat treated by quenching in oil from above the transformation temperature and then tempering by reheating to at least 650°F to be within the hardness range specified in [Table 1](#).

4.4.1 The minimum tempering temperature may be verified by submitting screws to 635°F for 30 min at temperature. The average cross-section hardness of three readings on the screw before and after retempering shall not differ by more than 20 DPH.

4.5 When protective or decorative coatings are applied to the screws, precautions as required by the coatings shall be taken to prevent embrittlement.

³ Available from American Society of Mechanical Engineers (ASME), ASME International Headquarters, Two Park Ave., New York, NY 10016-5990, <http://www.asme.org>.

TABLE 1 Mechanical Requirements

	Nominal Thread Size, in.	
	0.500 and smaller	Over 0.500
<i>Full-size Screws:</i>		
Tensile, min, ksi	144	136
<i>Machined Test Specimen:</i>		
Yield strength at 0.2 % offset, min, ksi	^A	153
Tensile strength, min, ksi	^A	170
Elongation in 4 <i>D</i> , min, %	^A	8
Reduction of area, min, %	^A	35
<i>Product Hardness:</i>		
Rockwell C	39–44	37–44
Vickers DPH	382–434	363–434

^A Not applicable.

5. Chemical Composition

5.1 The chemical composition of the screw material shall conform to the heat analysis specified in [Table 2](#).

5.2 One or more of the following alloying elements, chromium, nickel, molybdenum, or vanadium, shall be present in the steel in sufficient quantity to ensure the specific strength properties are met after oil quenching and tempering. The steel shall meet the AISI definition of alloy steel, that is, maximum and minimum element content requirement or minimum element limits specified.

5.3 Steel to which bismuth, selenium, tellurium, or lead has been added intentionally shall not be permitted.

5.4 Material analysis may be made by the purchaser from finished products and the chemical composition thus determined shall conform to the requirements specified for the product analysis in [Table 2](#).

6. Mechanical Properties

6.1 The finished screws shall conform to the mechanical requirements specified in [Table 1](#).

6.2 Screws having a nominal length equal to or greater than 3 diameters shall be tested full size and shall conform to the full-size tensile requirements specified in [Table 3](#). Tensile failures through the head are acceptable provided the load requirements are satisfied.

6.3 Screws having a nominal thread diameter-length combination as specified in [6.2](#) and a breaking load exceeding 200 000 lb preferably shall be tested full size and shall meet the full-size tensile properties in [Table 3](#). When equipment of sufficient capacity for such tests is not available or if excessive length of the screws makes full-size testing impractical, standard round machined specimens may be used that shall meet the machined test specimen tensile properties in [Table 1](#). If discrepancy between full-size and machined specimen results, full-size tests shall be used as the referee method to determine acceptance.

6.4 Screws that are too short (lengths less than three times nominal size) or that have insufficient threads for tension testing shall not be subject to tension tests but shall conform to the hardness (minimum and maximum) requirements of [Table 1](#).

TABLE 2 Chemical Requirements

Element	Composition, %	
	Heat Analysis	Product Analysis
Carbon	0.30 to 0.48	0.28 to 0.50
Phosphorus, max	0.035	0.040
Sulfur, max	0.040	0.045
Alloying elements	see 5.2	see 5.2

TABLE 3 Minimum Ultimate Tensile Loads

Thread Size		Stress Area, ^B in. ²		Button and Countersunk Heads, Tensile Load, min lb ^A	
Coarse	Fine	Coarse	Fine	Coarse Thread Series	Fine Thread Series
...	0.060-80	...	0.00180	...	260
0.073-64	0.073-72	0.00263	0.00278	380	400
0.086-56	0.086-64	0.00370	0.00394	530	570
0.099-48	0.099-56	0.00487	0.00523	700	750
0.112-40	0.112-48	0.00604	0.00661	870	950
0.125-40	0.125-44	0.00796	0.00830	1150	1200
0.138-32	0.138-40	0.00909	0.01015	1310	1460
0.164-32	0.164-36	0.0140	0.01474	2020	2120
0.190-24	0.190-32	0.0175	0.0200	2520	2900
0.250-20	0.250-28	0.0318	0.0364	4580	5240
0.3125-18	0.3125-24	0.0524	0.0580	7550	8350
0.375-16	0.375-24	0.0775	0.0878	11 200	12600
0.4375-14	0.4375-20	0.1063	0.1187	15 300	17100
0.500-13	0.500-20	0.1419	0.1599	20 400	23000
0.625-11	0.625-18	0.226	0.256	30 700	34800
0.750-10	0.750-16	0.334	0.373	45 400	50700
0.875-9	0.875-14	0.462	0.509	62 800	69200
1.000-8	1.000-12	0.606	0.663	82 400	90400
...	1.00-14	...	0.680	...	92500
	UNS ^C				
1.125-7	1.125-12	0.763	0.858	104 000	116400
1.250-7	1.250-12	0.969	1.073	132 000	146000
1.375-6	1.375-12	1.155	1.315	157 000	179000
1.500-6	1.500-12	1.405	1.581	191 000	215000

^A Because of the head critical configuration of these parts, the full size tensile loads are based on 80 % of the minimum heat treated material strength (180 ksi for sizes 0.500 in. and smaller and 170 ksi for sizes larger than 0.500 in.)

^B Stress Area, in.² = 0.7854[D - 0.9743/n]² where D = nominal diameter, in., and n = threads/in.

^C In the Unified Screw Thread System, 1-12 UNF is the standard for inch series fine threads; however, 1-14 UNS is more commonly available.

6.5 All screws, regardless of size, shall conform to the hardness specified in **Table 1**. Hardness shall be met anywhere on the cross section through the threaded portion one diameter from the screw point.

7. Other Requirements

7.1 Carburization or Decarburization:

7.1.1 There shall be no evidence of carburization or gross decarburization on the surfaces of the heat-treated screws when measured in accordance with **11.5**. Test Method **F2328** (Class 3 Product).

7.1.2 The depth of partial decarburization shall be limited to the values criteria in **Table 4** Test Method **F2328** when measured as shown in **Fig. 1**, and in accordance with **11.5**.

7.2 *Embrittlement*—Coated screws shall withstand the embrittlement test in accordance with **11.4** without showing indications of discontinuities. The loading shall be calculated with minimum screw tensile requirements.

8. Dimensions

8.1 Unless otherwise specified, the dimensions shall conform to the requirements of ASME B 18.3.

9. Workmanship, Finish, and Appearance

9.1 *Surface Finish*—The screws shall have a black (thermal or chemical) oxide finish, unless otherwise specified.

9.2 *Surface Discontinuities:*

9.2.1 The surface discontinuities for these products shall conform to Specification F788 and the additional limitations specified herein.

9.2.2 Forging defects that connect the socket to the periphery of the head are not permissible. Defects originating on the periphery and with a traverse indicating a potential to intersect are not permissible. Other forging defects are permissible, provided those located in the bearing area, fillet and top surfaces shall not have a depth exceeding $0.03 D$ or 0.005 in., whichever is greater. For peripheral discontinuities, the maximum depth may be $0.06 D$ not to exceed 0.040 in. (see Fig. 21).

9.2.3 Forging defects located in the socket wall within 0.1 times the actual key engagement, T , from the bottom of the socket are not permissible. Discontinuities located elsewhere in the socket shall not have a length exceeding $0.25 T$ or a maximum depth of $0.03 D$ not to exceed 0.005 in. (see Fig. 32).

9.2.4 Seams in the shank shall not exceed a depth of $0.03 D$ or 0.008 in., whichever is greater.

9.2.5 No transverse discontinuities shall be permitted in the head-to-shank fillet area.

9.2.6 Threads shall have no laps at the root or on the flanks, as shown in Fig. 43. Laps are permitted at the crest (Fig. 43c) that do not exceed 25 % of the basic thread depth and on the flanks outside the pitch cylinder. Longitudinal seams rolled beneath the root of the thread and across the crests of cut threads are acceptable within the limits of 9.2.4.

9.2.7 Quench cracks of any depth, any length, or in any location are not permitted.

10. Number of Tests

10.1 The requirements of this specification shall be met in continuous mass production for stock, and the manufacturer shall make sample inspections to ensure that the product conforms to the specified requirements. Additional tests of individual shipments of material are not ordinarily contemplated. A record of individual heats of steel in each test lot shall be maintained. The container shall be coded to permit identification of the lot.

10.2 When specified in the order, the manufacturer shall furnish a test report certified to be the last complete set of mechanical tests for each stock size in each shipment.

10.3 When additional tests are specified on the purchase order, a lot, for purposes of selecting test samples, shall consist of all

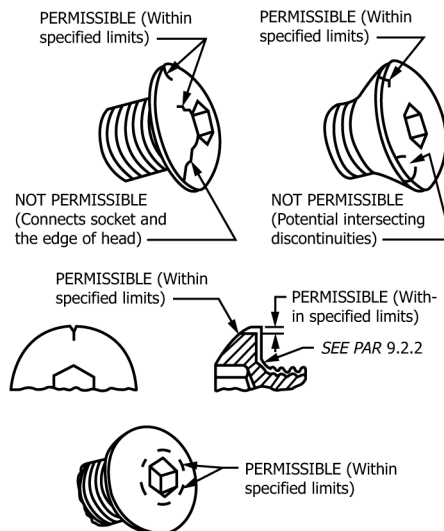


FIG. 21 Head and Body Discontinuity Limitations