



Designation: **D7199–07 (Reapproved 2012) D7199 – 20**

Standard Practice for Establishing Characteristic Values for Reinforced Glued Laminated Timber (Glulam) Beams Using Mechanics-Based Models¹

This standard is issued under the fixed designation D7199; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This practice covers mechanics-based requirements for calculating describes procedures for establishing the characteristic values for the strength and stiffness of reinforced structural glued laminated timbers (glulam) manufactured in accordance with applicable provisions of ANSI/AITC A190.1, subjected to quasi-static loadings. It addresses methods to obtain bending properties parallel to grain, about the x-x axis (F_{vx} and E_x) for horizontally-laminated reinforced glulam beams. Secondary properties such as bending about the y-y axis (F_{vy}), shear parallel to grain (F_{vx} and F_{vy}), tension parallel to grain (F_t), compression parallel to grain (F_c), and compression perpendicular to grain (F_c±) are beyond the scope of this practice. When determination of secondary properties is deemed necessary, testing according to other applicable methods, such as Test Methods D143, D198 or analysis in accordance with Practice D3737, is required to establish these secondary properties. Reinforced glulam beams subjected to axial loads are outside the scope of this standard. This practice also provides minimum test requirements to validate the mechanics-based model.

1.2 TheThis practice also describes a minimum set of performance-based durability test requirements for reinforced glulams, glulam beams, as specified in Annex A1. Additional durability test requirements shall be considered in accordance with the specific end-use environment. Appendix X1 provides an example of a mechanics-based methodology that satisfies the requirements set forth in this standard.practice.

1.3 This practice is limited to procedures for establishing flexural properties (modulus of rupture, MOR, and modulus of elasticity, MOE) about the x-x axis of horizontally-laminated reinforced glulam beams.

1.4 The establishment of secondary properties, such as bending about the y-y axis, shear parallel to grain, tension parallel to grain, compression parallel to grain, and compression perpendicular to grain, for the reinforced glulam beams are beyond the scope of this practice.

NOTE 1—When the establishment of secondary properties is deemed necessary, testing according to other applicable methods, such as Test Methods D143 and D198 or analysis in accordance with Practice D3737, may be considered.

1.5 Reinforced glulam beams subjected to axial loads are outside the scope of this practice.

¹ This practice is under the jurisdiction of ASTM Committee D07 on Wood and is the direct responsibility of Subcommittee D07.02 on Lumber and Engineered Wood Products.

Current edition approved Oct. 1, 2012 Aug. 1, 2020. Published October 2012 August 2020. Originally approved in 2006. Last previous edition approved in 2007/2012 as D7199–07/D7199–07 (2012). DOI: 10.1520/D7199-07R12.10.1520/D7199-20.

1.6 Characteristic strength and elastic properties obtained using this standard may be used as a basis for developing design values. However, the proper safety, serviceability, and adjustment factors including duration of load, to be used in design are outside the scope of this standard.

1.7 This practice does not cover unbonded reinforcement, prestressed reinforcement, nor shear reinforcement. Evaluation of unbonded, prestressed, and shear reinforcement is outside the scope of this practice.

1.8 The values stated in inch-pound units are to be regarded as standard. The mechanics-based model may be values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard. The mechanics-based model shall be permitted to be developed using SI or in-inch-pound units.

1.9 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.10 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 ASTM Standards:²

D9 Terminology Relating to Wood and Wood-Based Products

D143 Test Methods for Small Clear Specimens of Timber

D198 Test Methods of Static Tests of Lumber in Structural Sizes

D905 Test Method for Strength Properties of Adhesive Bonds in Shear by Compression Loading

D1990 Practice for Establishing Allowable Properties for Visually-Graded Dimension Lumber from In-Grade Tests of Full-Size Specimens

D2559 Specification for Adhesives for Bonded Structural Wood Products for Use Under Exterior Exposure Conditions

D2915 Practice for Sampling and Data-Analysis for Structural Wood and Wood-Based Products

D3039/D3039M Test Method for Tensile Properties of Polymer Matrix Composite Materials

D3410/D3410M Test Method for Compressive Properties of Polymer Matrix Composite Materials with Unsupported Gage Section by Shear Loading

D3737 Practice for Establishing Allowable Properties for Structural Glued Laminated Timber (Glulam)

D4761 Test Methods for Mechanical Properties of Lumber and Wood-Based Structural Materials

D5124 Practice for Testing and Use of a Random Number Generator in Lumber and Wood Products Simulation

2.2 Other Standard:

ANSI/AIAA/ANSI A190.1 Structural Glued Laminated Timber³

3. Terminology

3.1 *Definitions*—Standard definitions of wood terms are given in Terminology D9 and standard definitions of structural glued laminated timber terms are given in Practice D3737.

3.2 *Definitions of Terms Specific to This Standard:*

3.2.1 *bonded reinforcement*—a reinforcing material that is continuously attached to a glulam beam through adhesive bonding.

3.2.2 *bumper lamination*—a wood lamination continuously bonded to the outer side of reinforcement.

3.2.3 *compression compressive reinforcement*—reinforcement placed on the compression side of a flexural member.

3.2.4 *conventional wood lamstock*—solid sawn wood laminations with a net thickness of 2 in. or less, graded either visually or through mechanical means, finger-jointed and face-bonded to form a glulam.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Available from American National Standards Institute (ANSI), 25 W. 43rd St., 4th Floor, New York, NY 10036, <http://www.ansi.org>. APA – The Engineered Wood Association, 7011 South 19th Street, Tacoma, WA 98466, <http://www.apswood.org>.

3.2.5 *development length*—~~the length of the bond line along the axis of the beam required to develop the design tensile strength of the reinforcement.~~

3.2.6 *fiber-reinforced polymer (FRP)*—~~any composite material consisting of at least two distinct components: reinforcing fibers and a binder matrix (a polymer). The reinforcing fibers are permitted to be either synthetic (for example, glass), metallic, or natural (for example, wood), and are permitted to be long and continuously-oriented, or short and randomly oriented. The binder matrix is permitted to be either thermoplastic (for example, polypropylene or nylon) or thermosetting (for example, epoxy or vinyl-ester).~~

3.2.6.1 *Discussion*—

The reinforcing fibers may be either synthetic (for example, glass), metallic, or natural (for example, wood), and may be long and continuously-oriented, or short and randomly oriented. The binder matrix may be either thermoplastic (for example, polypropylene or nylon) or thermosetting (for example, epoxy or vinyl-ester).

3.2.7 *laminating effect*—~~an apparent increase of lumber lamination tensile strength because it is bonded to adjacent laminations within a glulam beam. This apparent increase may be attributed to a redirection of stresses around knots and grain deviations through adjacent laminations.~~

3.2.7.1 *Discussion*—

This apparent increase may be attributed to a redirection of stresses around knots and grain deviations through adjacent laminations.

3.2.8 *partial length reinforcement*—reinforcement that is terminated within the length of the ~~timber~~ glulam.

3.2.9 *reinforcement*—~~any lamination or material that is not a conventional lamstock whose wood lamstock and having a mean longitudinal ultimate strength exceeds 20 ksi for tension and compression, and whose tensile and compressive strength greater than 20 ksi (138 MPa) and a mean tension and compression MOE exceeds 3000 ksi, when placed into a glulam timber. Acceptable reinforcing materials include but are not restricted to: fiber-reinforced polymer (FRP) plates and bars, metallic plates and bars, FRP-reinforced laminated veneer lumber (LVL), FRP-reinforced parallel strand lumber (PSL); greater than 3000 ksi (20.7 GPa).~~

3.2.9.1 *Discussion*—

Examples of acceptable reinforcing materials include fiber-reinforced polymer (FRP) plates and bars, metallic plates and bars, FRP-reinforced laminated veneer lumber (LVL), and FRP-reinforced parallel strand lumber (PSL).

3.2.10 *shear reinforcement*—reinforcement intended to increase the shear strength of the beam. This standard does not cover shear reinforcement.

3.2.10 *tension* ~~tensile~~ *reinforcement*—reinforcement placed on the tension side of a flexural member.

3.3 *Symbols*—~~*Symbols*~~:

Arm = moment arm, distance between ~~compression~~ compressive and ~~tension~~ tensile force couple applied to beam cross-section

b = beam width

C = total internal ~~compression~~ compressive force within the beam cross-section (see Fig. [2A2.2](#))

CFRP = carbon fiber reinforced polymer

d = beam depth

E = long-span flatwise-bending modulus of elasticity for wood lamstock (Test Methods [D4761](#); also see Fig. [1A2.1](#))

F_b = allowable bending stress parallel to grain

F_x = internal horizontal force on the beam cross-section (see Eq [2A2.2](#))

GFRP = Glass fiber-reinforced polymer

LEL = lower exclusion limit (point estimate with 50 % confidence, includes volume factor)

LTL = lower tolerance limit (typically calculated with 75 % confidence) with 75 % confidence

M_{applied} = external moment applied to the beam cross-section

M_{internal} = internal moment on the beam cross-section

MC = moisture content (%)

MOE = modulus of elasticity

MOR = modulus of rupture

MOR_{5%} = 5 % one-sided lower tolerance limit for modulus of rupture, including the volume factor

$MOR_{BL5\%BL5\%} = 5\%$ one-sided lower tolerance limit for modulus of rupture corresponding to failure of the bumper lamination, including the volume factor

m^*E = downward slope of bilinear compression stress-strain curve for wood lamstock (see Fig. [A2.1](#))

N.A. = neutral axis

T = total internal tension/tensile force within the beam cross-section (see Fig. [A2.2](#))

UCS = ultimate compressive stress parallel to grain

UTS = ultimate tensile stress parallel to grain

Y = distance from extreme compression fiber to neutral axis (see Fig. [A2.2](#))

y = distance from extreme compression fiber to point of interest on beam cross-section (see Fig. [A2.2](#))

ϵ_c = strain at extreme compression fiber of beam cross-section (see Fig. [A2.2](#))

$\epsilon_{c_{ult}}$ = ~~compression~~ = compressive strain at lamstock failure (see Fig. [A2.1](#))

ϵ_{c_y} = ~~compression~~ = compressive yield strain at lamstock UCS (see Fig. [A2.1](#))

ϵ_{ult} = tensile strain at lamstock failure (see Fig. [A2.1](#))

$\epsilon(y)$ = strain distribution through beam depth (see Fig. [A2.2](#))

ρ = ~~tension~~ ρ = tensile reinforcement ratio (%); cross-sectional area of ~~tension~~ tensile reinforcement divided by cross-sectional area of beam between the e.g.-of ~~tension~~ center of gravity of tensile reinforcement and the extreme compression fiber

ρ' = ~~compression~~ ρ' = compressive reinforcement ratio (%); cross-sectional area of ~~compression~~ compressive reinforcement divided by cross-sectional area of beam between the e.g.-of ~~compression~~ center of gravity of compressive reinforcement and the extreme tension fiber

$\sigma(y)$ = stress distribution through beam depth (see Fig. [A2.2](#))

4. Requirements for ~~Mechanics-Based Analysis Methodology~~ Modeling Requirements

NOTE 1—At a minimum, the mechanics-based analysis shall account for: (1) Stress-strain relationships for wood laminations and reinforcement; (2) Strain compatibility; (3) Equilibrium; (4) Variability of mechanical properties; (5) Volume effects; (6) Finger-joint effects; (7) Laminating effects; and (8) Stress concentrations at termination of reinforcement in beams with partial-length reinforcement. In addition to the above factors, characteristic values developed using the mechanics-based model need to be further adjusted to address end-use conditions including moisture effects, duration of load, preservative treatment, temperature, fire, and environmental effects. The development and application of these additional factors are outside the scope of this practice. [Annex A1](#) addresses the evaluation of durability effects. The minimum output requirements for the analysis are mean MOE (based on gross section) and 5% LTL MOR with 75% confidence (based on gross section), both at 12% MC. These analysis requirements are described below.

4.1 ~~Stress-strain Relationships—General:~~

4.1.1 ~~Conventional Wood Lamstock—Purpose for Modeling—~~

4.1.1.1 The stress-strain relationship shall be established through in-grade testing following Test Methods [D198](#) or Test Methods [D4761](#), or other established relationships as long as the resulting model meets the criteria established in Section 5. Test lamstock shall be sampled in sufficient quantity from enough sources to insure that the test results are representative of the lamstock population that will be used in the fabrication of the beams. Follow-up testing shall be performed annually in order to track changes in lamstock properties over time, so that the layup designs may be adjusted accordingly. Characteristic values for the flexural properties about the x-x axis of horizontally-laminated reinforced glulam beams shall be established through the use of an analytical model. The establishment of flexural properties using full-scale beam tests is outside the scope of this practice.

4.1.1.2 The stress-strain relationship shall be linear in tension. The stress-strain relationship shall be nonlinear in compression if compression is the governing failure mode. In this case, a bilinear approximation is acceptable, and shall be used throughout this standard (see Fig. 1). In the bilinear model both tension and compression MOE shall be permitted to be approximated by using the long-span flatwise-bending MOE obtained using Test Methods [D4761](#). In Fig. 1, m^*E is the downward slope of the compression stress-strain curve, defined as the best-fit downward line through the point (UCS, ϵ_{c_y}) on the compression stress-strain curve. The downward best-fit line shall be permitted to be terminated at the point where the ultimate compressive strain ϵ_{cu} is approximately 1%.

4.1.2 ~~Reinforcement—Mechanics-Based Models—~~

4.1.2.1 The stress-strain relationship shall be established through material-level testing in accordance with Test Method [D3039/D3039M](#) and [D3410/D3410M](#). Models used to develop new combinations and predict characteristic values shall be able to predict accurately these values for a broad range of combinations and validated by full-scale tests according to Section 5.

4.1.2.2 Nonlinearities in the stress-strain relationship shall be included in the analysis, if present.

4.1.2.3 Acceptable stress-strain models for unidirectional E-glass FRP (GFRP), Aramid, or Carbon FRP (CFRP) in tension are

linear-elastic. Acceptable models for hybrid E-glass/Carbon composites in tension are linear or bilinear. Acceptable models for mild steel reinforcement are elastic-plastic. Similar models may also apply in compression.

4.2 *Strain Compatibility:*

4.2.1 Fig. 2 shows the cross section of a beam with a linear strain and bilinear stress distribution, with the neutral axis a distance Y below the top of the beam. Using the extreme compression fiber as the origin, the strain distribution for a given applied moment (M_{applied}) is defined by the equation:

$$\varepsilon(y) = \varepsilon_c - \varepsilon_c * (y/Y) \quad (1)$$

4.2 *Equilibrium:—Minimum Model Inputs—*

4.3.1 In order to maintain equilibrium, the cross-section shall satisfy the conditions of horizontal equilibrium (Eq 2), and the internal moment (M_{internal}) shall equal the external moment applied to that cross section (M_{applied}) (Eq 3). See Fig. 2 as an example of strain compatibility and equilibrium:

$$\sum F_x = 0 \Rightarrow \int_{\text{depth}} \sigma(y) dA = 0 \quad (2)$$

$$M_{\text{applied}} = M_{\text{internal}} = C(\text{or } T) * \text{Arm} = \int_{\text{depth}} -y * \sigma(y) * dA \quad (3)$$

Any numerical solution methodology shall be permitted for use, so long as it incorporates the nonlinearities in mechanical properties for wood and reinforcement as specified in A2.1 and satisfies the conditions of strain compatibility (A2.2), and equilibrium (A2.3). In addition, the mechanics-based analysis shall account for variability of mechanical properties, volume effects, finger-joint effects, laminating effects, and stress concentrations at termination of reinforcement in beams with partial length reinforcement.

NOTE 2—These analysis input requirements are described in detail in Annex A2.

4.4 *Variability of Mechanical Properties:*

4.4.1 The model shall properly account for the variability of the mechanical properties of the wood lamstock and the FRP reinforcement. This includes variability of individual properties and correlations among those properties as appropriate. The mechanics-based analysis shall address statistical properties for and correlations between Ultimate Tensile Stress (UTS), Ultimate Compressive Stress (UCS) and long-span flatwise-bending modulus of elasticity (E). One example of how this may be achieved is provided in Appendix X1.

4.4.2 These correlation values are obtained from test data. Test lamstock shall be sampled in sufficient quantity, from enough sources to insure that the test results are representative of the lamstock population that will be used in the fabrication of the beams. Follow-up testing shall be performed annually in order to track changes in lamstock properties over time, so that the layup designs may be adjusted accordingly.

4.5 *Volume Effects:*

4.5.1 The model shall properly account for changes in beam strength properties as affected by beam size. In conventional glulam, this is achieved by using a volume factor C_v , which was derived from laboratory test data. With adequate reinforcement, glulams can achieve a reduction or even elimination of volume effects. The model shall properly account for this phenomenon. One possible approach to address the volume effect is described in Appendix X1.

4.6 *Finger-Joint Effects:*

4.6.1 Finger joints affect the mechanical properties of lamstock used in glulams. The model shall account for these effects on both the mean and variability of the beam mechanical properties. One example of how this may be achieved is provided in Appendix X1.

4.7 *Laminating Effects:*

4.7.1 The laminating effects may be predicted by the model or else developed outside the model (and applied in the model) using an empirical, numerical or analytical approach. One way to achieve this for a beam subjected to 4-point bending is described in [Appendix X1](#).

4.8 *Stress Concentrations at Termination of Reinforcement in Beams with Partial Length Reinforcement:*

4.8.1 Beams with partial length reinforcement have stress concentrations near the ends of the reinforcement. These stress concentrations are in the form of tension or compression stresses parallel to grain, combined with peeling stresses perpendicular to grain. The model shall have the ability to account for the effects of these stress concentrations if partial length reinforcement will be used.

4.3 *Mechanical Properties Predicted by Model: Minimum Model Analyses:*

4.9.1 The model shall at a minimum predict the following properties, including the effects of a bumper lamination if one is used, which are the basis for design values:

4.3.1 *Bending Strength: Strength—*

4.9.2.1 The bending strength calculated by the model assumes adequate bond development length is provided for the reinforcement. The model shall predict the lower 5 % tolerance limit for modulus of rupture ($MOR_{5\%}$) for the reinforced layup being analyzed. Beam MOR shall be based on gross (full width and depth) cross section properties:

$$MOR = \frac{6 * M_{max}}{b * d^2} \quad (4)$$

Where M_{max} is the maximum moment applied to the beam, and b and d are respectively the full width and depth of the beam cross-section. The transformed section properties shall not be used. The model shall predict the lower 5 % tolerance limit (LTL) for modulus of rupture ($MOR_{5\%}$) for the reinforced layup being analyzed. The model-predicted bending strength characteristic values $MOR_{5\%}$ shall include the volume effect. Beam MOR shall be based on gross (full width and depth) cross-sectional properties.

4.9.2.2 If a bumper lamination is used, an additional characteristic bending strength value $MOR_{BL5\%}$ corresponding to bumper lamination failure shall also be reported. It should be noted that the model-predicted bending strength characteristic values $MOR_{5\%}$ and $MOR_{BL5\%}$ shall include the volume effect, so that the volume factor will not be applied separately.

4.3.2 *Bending Stiffness—*The model shall predict the mean modulus of elasticity (MOE) for the reinforced layup being analyzed. Beam MOE shall be based on gross (full width and depth) cross-sectional properties.

4.3.3 *Bending Stiffness: Bumper Lamination—*

4.9.3.1 The model shall predict the mean modulus of elasticity (MOE) for the reinforced layup being analyzed. MOE shall be based on gross (full width and depth) cross-section properties. If a bumper lamination is present, the model shall predict the beam stiffness properties before and after failure of the bumper lamination. If a bumper lamination is to be used, the characteristic bending strength value $MOR_{BL5\%}$ corresponding to bumper lamination failure shall also be calculated and reported. In addition, the beam stiffness properties before and after failure of the bumper lamination shall be calculated and reported.

4.9.3.2 If a bumper lamination is used, the model shall be able to predict failure of the bumper lamination, as well as its contribution to beam strength and stiffness. The modeling approach described in [Appendix X1](#) is an example of how to accomplish this:

NOTE 3—See [Appendix X1](#) for example calculations.

NOTE 4—A bumper lamination, if used, will likely fail prior to reaching the ultimate capacity of the reinforced beam. In tests of GFRP-reinforced glulam with 1.1 % to 3.3 %, the bumper lam failure load was typically 10–20 % below the ultimate strength. This range will differ depending on the reinforcement type, reinforcement ratio, beam layup, and grade of the bumper lamination.

NOTE 2—A bumper lamination, if used, will likely fail prior to reaching the ultimate capacity of the reinforced beam. In tests of GFRP-reinforced glulam with 1.1 % to 3.3 %, the bumper lam failure load was typically 10–20 % below the ultimate strength. This range will differ depending on the reinforcement type, reinforcement ratio, beam layup, and grade of the bumper lamination.

TABLE 1 Initial Qualification Using Primary Species: DF, SP or SPF—Minimum Beam Test Matrix for Mechanics-Based Model Validation^{A,B}

Beam Size	Reinforcement Ratio ρ %		
	Min ^C	Typical ^C	Max ^C
5 1/8 in. by 12 in. by 21 ft	10	10	10
6 3/4 in. by 24 in. by 42 ft.	10	10	10

TABLE 1 Initial Qualification Using Primary Species: DF, SP_i or SPF—Minimum Beam Test Matrix for Mechanics-Based Model Validation^{A,B}

Beam Size	Number of Beam Tests		
	Min ^C	Typical ^C	Max ^C
5 1/8 in. by 12 in. by 21 ft (130 mm by 305 mm by 6.40 m)	10	10	10
6 3/4 in. by 24 in. by 42 ft (171 mm by 610 mm by 12.8 m)	10	10	10

^A All beams shall use the same layup, species, reinforcement type, and wood lam thickness.

^B A larger set may shall be required in order to keep if the Standard Error less is greater than 0.1 ± (5%LEL) × 5 % LTL. See Practice D2915, Section 3.4.3.2 for determining a minimum sample size.

^C See Table 3. The model will shall only be considered valid for ρ within the tested minimum and maximum.

TABLE 2 Subsequent Qualification of Additional Species (DF, SP, SPF or hardwoods)—Minimum Beam Test Matrix for Mechanics-Based Model Validation^{A,B}

Beam Size	Reinforcement Ratio ρ %		
	Min ^C	Typical ^C	Max ^C
5 1/8 in. by 18 in. by 32 ft.	10	—	10

TABLE 2 Subsequent Qualification of Additional Species (DF, SP, SP_F or Hardwoods)—Minimum Beam Test Matrix for Mechanics-Based Model Validation^{A,B}

Beam Size	Number of Beam Tests		
	Min ^C	Typical ^C	Max ^C
5 1/8 in. by 18 in. by 32 ft (130 mm by 457 mm by 9.75 m)	10	—	10

^A All beams shall use the same layup, species, reinforcement type, and wood lam thickness.

^B A larger set may shall be required in order to keep if the Standard Error less is greater than 0.1 ± (5%LEL) × 5 % LTL. See Practice D2915 Section 3.4.3.2 for determining a minimum sample size.

^C See Table 3. The model will shall only be considered valid for ρ within the tested minimum and maximum.

TABLE 3 Typical Reinforcement Ratios^A

	Reinforcement Material			
	E-glass FRP	Aramid FRP	Carbon FRP	Steel Plate
MOE (ksi)	6 000	10 000	20 000	30 000
MOE, ksi (GPa)	6 000 (41)	10 000 (69)	20 000 (138)	30 000 (207)
Minimum ρ^B %	1	0.6	0.3	0.2
Typical ρ %	2	1.2	0.6	0.4
Maximum ρ %	3	1.8	0.9	0.6

^A The The Reinforcement Ratios presented in this table represent typical values. The manufacturer may shall use any minimum, maximum, or typical value considered appropriate, although the model will shall only be valid within the range tested.

^B ρ = Tension Tensile reinforcement ratio (%); cross-sectional area of tensile reinforcement divided by cross-sectional area of beam above e.g. of tension center of gravity of tensile reinforcement.

4.10.1 Secondary properties such as bending about the y-y axis (F_{by}), shear parallel to grain (F_{vx} and F_{vy}), tension parallel to grain (F_t), compression parallel to grain (F_c), and compression perpendicular to grain ($F_{c\perp}$) shall be determined following methods described in Practice [D3737](#).

4.4.1 Analysis has shown that with the level of FRP extreme fiber tensile reinforcement typically envisioned (up to 3 % GFRP or 1 % CFRP), the maximum shear stress at the reinforced beam neutral axis is very similar to that of an unreinforced rectangular section. In addition, under the same conditions, the shear stress at the FRP-wood interface is always significantly smaller than the shear stress at the reinforced beam neutral axis.

NOTE 5—Analysis has shown that with the level of FRP extreme fiber tensile reinforcement typically envisioned (up to 3 % GFRP or 1 % CFRP), the maximum shear stress at the reinforced beam neutral axis is very similar to that of an unreinforced rectangular section. In addition, under the same conditions, the shear stress at the FRP-wood interface is always significantly smaller than the shear stress at the reinforced beam neutral axis.

4.11 Numerical Solution Methodology:

4.11.1 Any numerical solution methodology⁴ shall be permitted for use, so long as it incorporates the nonlinearities in mechanical properties for wood and FRP as specified in section 4.1, and satisfies the conditions of strain compatibility (section 4.2), and equilibrium (section 4.3).

5. Model Validation Testing Requirements

5.1 **Test Method**—Tests for flexural strength and modulus of elasticity shall be conducted in accordance with Test Methods [D198](#) or [D4761](#). If Test Methods [D4761](#) is used, the load rate shall be modified to be in accordance with Test Methods [D198](#). Specimens shall be tested under dry-service conditions where the moisture content of the wood, excluding non-wood reinforcement, is 12 ± 3 %. The temperature of the test specimens shall not be less than 50°F (10°C) nor more than 90°F (32°C) at the time of the tests.

5.2 **Sampling Requirements**—Mechanics-based models which satisfy the requirements set forth in this standard shall be validated through physical testing as shown in [Tables 1 and 2](#). The sample size shall be large enough to provide the standard error of the sample less than 10 % of the 5 % LTL of MOR, but not less than 10 beams for each size/reinforcement ratio. Six sample sets shall be tested using a primary wood species ([Table 1](#)) equating to a minimum of 60 beams, and two sample sets shall be tested for each additional wood species ([Table 2](#)) equating to a minimum of 20 beams.

6. Standard Methodology for Validating Mechanics-Based Models which Satisfy the Requirements Set Forth in This Standard Analysis and Applicability of Test Results

6.1 **Failure Modes**—Mechanics-based models which satisfy the requirements set forth in this standard shall be validated through physical testing as shown in [Tables 1-3](#). Each failed specimen shall be inspected to determine the failure mode(s). The failure mode(s) of observed failures shall be documented ([Table 1](#)), and 20 beams for each additional wood species (and compared to [Table 2](#)). All beams in [Table 3](#) shall utilize the same wood layup, and the same type of reinforcement; the model. Lamination characteristics influencing failure shall be noted.

⁴ Typical solutions for the nonlinear set. The boldface numbers in parentheses refer to a list of [Eq 1-3](#) may be Newton-Raphson or other iterative techniques; references at the end of this standard.

6.2 The predicted 5% LEL using the mechanics-based model (5% LEL_{model}) shall be compared with the 5% LEL calculated from the test results (5% LEL_{test}) for each of the eight cells in **Tables 1 and 2**. Conditions of model acceptance are as follows: Mechanical Properties:

$$\begin{aligned} & |(5\% \text{ LEL}_{\text{model}} - 5\% \text{ LEL}_{\text{test}})| / 5\% \text{ LEL}_{\text{model}} < 0.10 \\ & \text{—for each of the 8 cells in Tables 1 and 2} \\ & \frac{1}{8} \sum (5\% \text{ LEL}_{\text{model}} - 5\% \text{ LEL}_{\text{test}}) / 5\% \text{ LEL}_{\text{model}} < 0.06 \\ & \text{—for all 8 cells in Tables 1 and 2} \end{aligned}$$

6.2.1 Modulus of Rupture—The predicted 5 % LTL using the mechanics-based model (5 % LTL_{model}) shall be compared with the 5 % LTL calculated from the test results (5 % LTL_{test}) for each of the eight cells in **Tables 1 and 2**. Conditions of model acceptance are as follows:

$$\begin{aligned} & |(5\% \text{ LTL}_{\text{model}} - 5\% \text{ LTL}_{\text{test}})| / 5\% \text{ LTL}_{\text{model}} < 0.10 \\ & \text{for each of the 8 cells in Tables 1 and 2} \\ & \frac{1}{8} \sum [(5\% \text{ LTL}_{\text{model}} - 5\% \text{ LTL}_{\text{test}}) / 5\% \text{ LTL}_{\text{model}}] < 0.06 \\ & \text{for all 8 cells in Tables 1 and 2} \end{aligned}$$

6.2.2 Modulus of Elasticity—Conditions for model acceptance include the mean MOE in the linear elastic range based on gross section dimensions as follows:

$$\begin{aligned} & |(\text{mean MOE}_{\text{model}} - \text{mean MOE}_{\text{test}})| / \text{mean MOE}_{\text{model}} < 0.10 \\ & \text{for each of the 8 cells in Tables 1 and 2} \\ & \frac{1}{8} \sum [(\text{mean MOE}_{\text{model}} - \text{mean MOE}_{\text{test}}) / \text{mean MOE}_{\text{model}}] < 0.06 \\ & \text{for all 8 cells in Tables 1 and 2} \end{aligned}$$

5.3 Similarly, conditions for model acceptance include the mean MOE in the linear elastic range based on gross section dimensions as follows:

$$\begin{aligned} & |(\text{mean MOE}_{\text{model}} - \text{mean MOE}_{\text{test}})| / \text{mean MOE}_{\text{model}} < 0.10 \\ & \text{—for each of the 8 cells in Tables 1 and 2} \\ & \frac{1}{8} \sum (\text{mean MOE}_{\text{model}} - \text{mean MOE}_{\text{test}}) / \text{mean MOE}_{\text{model}} < 0.06 \\ & \text{—for all 8 cells in Tables 1 and 2} \end{aligned}$$

5.4 It is important to stress that a test sample size larger than indicated in **Tables 1 and 2** shall be considered in order to keep the Standard Error less than 0.1 * (5 % LEL). Section 3.4.3.2 of Practice **D2915** shall be used for determining an adequate minimum test sample size.

5.5 In addition to the 5 % LEL predictions, the predominant mode of failure shall be identified by the model for each reinforcement level tested, and this mode of failure shall compare with the mode of failure observed in the laboratory testing program. For the beam confirmation testing the characteristics of the wood laminations (for example, finger-joint spacing, lumber grade etc.) need to be consistent with the model.

5.6 In addition to Test Methods **D198** test reporting requirements, the report shall include: (1) details of the layups tested including grades, distribution of finger-joint spacings and strengths, reinforcement location, strength and stiffness, (2) failure modes (predicted and lab test results), (3) load to failure (predicted and lab test results), (4) load-deflection curves (predicted and lab test results), (5) 5 % LEL analysis (predicted and lab test results as described above).

7. Periodic Evaluation

7.1 Lumber Properties—The lumber characteristics used as a basis for establishing grades and as inputs to predictive models shall be maintained through continuous process control. Strength and stiffness properties for each grade shall be evaluated periodically or maintained through continuous process control to ensure that they are maintained over time.

7.2 Reinforcement Properties—The reinforcement characteristics used as inputs to predictive models shall be evaluated periodically or maintained through continuous process control to ensure that they are maintained over time.

7.3 End Joint Strength—Lamination end joint strengths shall be subject to ongoing process control to maintain the required strengths.

7.4 Beam Tests—Full-scale beam tests shall be conducted to verify the continued applicability of the model used for assigning characteristic values when the trend of the lumber properties, reinforcement properties or end joint strengths, evaluated in 7.1 through 7.3, warrants such an evaluation.

8. Report

8.1 The report shall include the following:

8.1.1 Description of the sample(s), including species, lamination properties, layup(s), size(s), conditioning, location of end joints, matched end joint strength, quality control requirements, etc.

8.1.2 Description of the test machine and setup, including method and location of load application, test span or gauge length, etc.

8.1.3 Description of measurement methods for dimensions, load, deflections, moisture content, etc.

8.1.4 Rate of testing and the method of controlling the rate of load application.

8.1.5 Equation(s) used to determine stresses and elastic moduli.

8.1.6 Data for specimens, including: dimensions; maximum load or stress, or both; moisture content; time to failure; description and location of failure; load versus deformation curves, etc.

8.1.7 Description of statistical analyses used to determine characteristic value(s).

8.1.8 Identification and description of any model(s) used or evaluated.

8.1.9 Details of any deviations from the recommended procedures.

9. Keywords

9.1 bending; characteristic value; composites; flexural; flexure; FRP; full-scale; glulam; laminated; layup; modulus; reinforcement; timber

ANNEXANNEXES

(Mandatory Information)

A1. PERFORMANCE-BASED DURABILITY REQUIREMENTS

~~A1.1 Reinforcement~~—Reinforcement—The reinforcement shall maintain adequate strength and stiffness based on the anticipated end-use conditions over the lifetime of the structure. Synergistic effects of the exposure conditions described in **Table A1.1** shall be considered if appropriate for the end-use environment, using the appropriate ASTM standards.

~~A1.1.1 Beams reinforced with FRP shall not be post-treated unless testing verifies that the required FRP-reinforced beam strength and stiffness retentions can be achieved. Tests results have shown that post-treatment with CCA causes significant strength degradation of E-glass FRP reinforcement. It should be noted that for other reasons, the laminating industry specifically recommends against post-treatment of glulam beams with any waterborne treatments.~~

TABLE A1.1 Potential Reinforcement Exposure Conditions

Condition	Static	Fatigue
Water	X	X
Hot Water	X	X
Salt water	X	X
Salt Water	X	X
CaCO ₃	X	X
Diesel Fuel	X	X
Freeze-thaw	X	X
Freeze-Thaw	X	X
Heat Aging	X	X
UV Cycling	X	X
Fire	X	X
Wood Preservatives	X	X
Sustained Loading	X	X

NOTE A1.1—Tests results have shown that post-treatment with CCA causes significant strength degradation of E-glass FRP reinforcement. It should be noted that for other reasons, the laminating industry specifically recommends against post-treatment of glulam beams with any waterborne treatments.

A1.1.2 After fabrication, reinforcement shall not be cut, drilled, or otherwise damaged (including penetration by fasteners) unless proper mechanics-based engineering analyses are conducted to verify net section capacity, including effects of stress-concentrations and potential for accelerated degradation.

A1.2 *Bond*—The bond shall provide strain compatibility between the wood and the reinforcement through the length of the reinforcement and be effective during the design life of the structure.

A1.2.1 *Wood-to-Wood Bond*—Wood-to-wood bonds shall comply with requirements of ANSI/AITC/ANSI A190.1 as well as Specification D2559.

ASTM D7199-20
<https://standards.iteh.ai/catalog/standards/sist/795cf9b6-20a7-43d5-a206-a8e10a1ef6d8/astm-d7199-20>

A1.2.2 *Wood-to-Reinforcement Bond*:

A1.2.2.1 *Shear by Compression Loading*—Wood-to-reinforcement bond strength shall be evaluated for resistance to shear by compression loading as specified in Specification D2559 with the following modifications:

(1) When reinforcement sheets are too thin to allow proper application of the compression load in the Test Method D905 test apparatus, the FRP sheets shall be backed up by another wood layer (as shown in Fig. A1.1(b)).

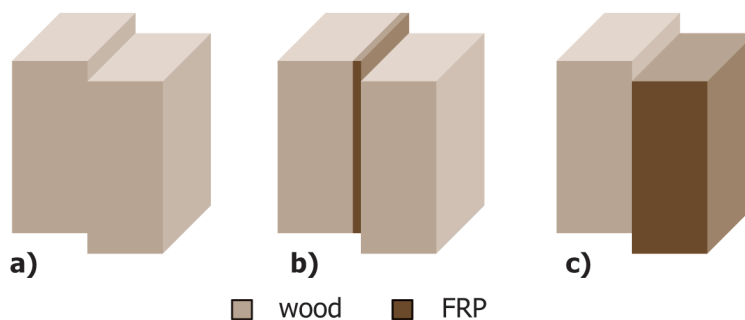


FIG. A1.1 Block Shear Specimens for Modified Specification D2559 Test

(a) Regular Wood-Wood Specimen; (b) Modified Reinforcement-Wood Specimen—for Thin Reinforcement Sheets; (c) Modified Reinforcement-Wood Specimen for Thick Reinforcement Sheets