



Designation: B933 – 20

Standard Test Method for Microindentation Hardness of Powder Metallurgy (PM) Materials¹

This standard is issued under the fixed designation B933; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope*

1.1 This test method covers the determination of the micro-indentation hardness of powder metallurgy (PM) materials. The test method differs from the approach used for pore-free materials in terms of the precautions required to deal with the porosity.

1.2 This procedure covers tests made with the Knoop or Vickers indenters under loads in the range from 1 to 200 gf.

1.3 Automated testing is not generally suitable for use with porous PM materials, because acceptable indentations require avoiding placing indentations in the immediate vicinity of a pore, a condition not guaranteed with automated placement of the indentations. Any automated testing shall allow for review of indentations post-test to reject any distorted or unusually large indentations in accordance with 9.4.

1.4 A method for converting the directly measured indentation lengths to other hardness scales, for example, HRC is described in [Appendix X1](#).

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.6 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

¹ This test method is under the jurisdiction of ASTM Committee B09 on Metal Powders and Metal Powder Products and is the direct responsibility of Subcommittee B09.05 on Structural Parts.

Current edition approved Oct. 1, 2020. Published October 2020. Originally approved in 2004. Last previous edition approved in 2016 as B933 – 16. DOI: 10.1520/B0933-20.

2. Referenced Documents

2.1 ASTM Standards:²

[B243 Terminology of Powder Metallurgy](#)

[E384 Test Method for Microindentation Hardness of Materials](#)

[E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method](#)

2.2 MPIF Standards:³

[Standard 70 Guide to Sample Preparation of Ferrous Powder Metallurgy \(PM\) Materials for Cross-Sectional Metallographic Evaluation](#)

[Standard 71 Guide to Sample Preparation of Copper-Based Powder Metallurgy \(PM\) Materials for Cross-Sectional Metallographic Evaluation](#)

[Standard 72 Guide to Sample Preparation of Aluminum Powder Metallurgy \(PM\) Materials for Cross-Sectional Metallographic Evaluation](#)

3. Terminology

3.1 Definitions of powder metallurgy (PM) terms can be found in Terminology [B243](#). Additional descriptive information is available under *General Information on PM* on the ASTM B09 web page.

4. Summary of Test Method

4.1 Microindentation hardness testing uses a calibrated machine to force a pyramidal-pointed diamond indenter into the surface of the test material under a known test load. The microindentation hardness value is calculated from the indenting force divided by the projected area of the resulting indentation.

NOTE 1—This test method is designed specifically for use on porous PM materials. It is intended to be a companion to Test Method [E384](#). There are specific differences that are intentional, such as restricting the applied load to a maximum of 200 gf; otherwise, the details on equipment and procedures in Test Method [E384](#) shall be adhered to. The specific differences relate to the presence of porosity in the PM materials. Special

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Available from Metal Powder Industries Federation (MPIF), 105 College Rd. East, Princeton, NJ 08540, <http://www.mpif.org>.

*A Summary of Changes section appears at the end of this standard

precautions are required during sample preparation to reveal pores and heterogeneous microstructural features so that appropriate test locations may be selected.

5. Significance and Use

5.1 Microindentation hardness testing provides a measure of the hardness of the microstructural constituents of a porous material. It indicates the hardness the material would have if there were no pores present and the material was tested using macroindentation hardness methods. Loads are limited to a maximum of 200 gf to reduce the likelihood of interference from the porosity.

5.2 Microindentation hardness tests allow the evaluation of specific phases, microstructural constituents, and regions or gradients too small for macroindentation hardness testing.

6. Apparatus

6.1 *Microindentation Hardness Testing Machine*, capable of applying the required load, equipped with a Knoop or Vickers indenter, and provision for measuring the length of the diagonals of the indentation.

6.2 Apparatus requirements are summarized in method Test Method E384.

7. Reagents and Materials

7.1 *Metallographic Etchants*, suitable for the material being tested.

8. Test Specimen

8.1 Specimen Mounting:

8.1.1 Sample mounting is recommended for convenience in surface preparation, edge retention, and ease of testing. The sample should be supported adequately in the mounting medium.

8.2 Specimen Preparation:

8.2.1 Guidelines for grinding and polishing specimens are provided in MPIF Standard Guides 70, 71, and 72.

8.2.2 Care should be taken to ensure that the true area fraction of porosity is revealed throughout the entire cross section of the specimen. It is essential in surface preparation to remove all smeared metal and to identify pores clearly so that they may be avoided during testing.

8.2.3 The specimen should be lightly etched prior to microindentation hardness testing. Careful etching is necessary as heavy etching obscures features and interferes with the measurement of the diagonals of the indentation.

8.2.4 For heat treated steels, swabbing with, or immersion in, 2 % nital for 4 to 7 s gives an appropriate structure.

9. Procedure

9.1 Support the specimen so that its surface is perpendicular to the axis of the indenter.

9.2 Select a suitable location for testing and an appropriate load and magnification for the test. A 100 gf load is recommended for hardened materials. Lower loads may be used for softer materials or when small regions need to be tested. For the best precision, use the highest load compatible with the

feature to be tested. Magnification ranges for various indentation lengths are as follows:

Indentation Length (μm)	Magnification	
	Max	Min
<76	...	400
76 to 125	800	300
>125	600	200

9.3 Apply the test load.

9.4 Examine the indentation for possible sources of error such as distorted or unusually large indentations. The two sections of each diagonal should agree within 20 % of each other. Discard any distorted or unusually large indentations. Unusually large indentations sometimes occur due to the presence of pores directly under the indentation.

9.5 Measure the length of the diagonals of the indentation, taking care to avoid backlash by moving only in one direction. For Knoop microindentation hardness, read the length of the larger diagonal to 0.1 μm . For Vickers microindentation hardness, measure both diagonals to the nearest 0.1 μm and calculate the average.

9.6 Make additional indentations. Space the indentations, so that adjacent tests do not interfere with each other. The minimum spacing between tests is illustrated in Fig. 1.

10. Calculation or Interpretation of Results

10.1 The Knoop or Vickers microindentation hardness numbers may be calculated using the following formulae or by using tables in Test Method E384.

10.1.1 *Knoop*—Using the units of force and length commonly employed, that is, for force P in gf, and a long diagonal d in micrometres, the Knoop hardness is calculated:

$$HK = 14\ 229 P/d^2$$

10.1.2 *Vickers*—Using the units of force and length commonly employed, that is, for force P in gf, and the mean of the two diagonals d in micrometres, the Vickers hardness is calculated:

$$HV = 1854.4 P/d^2$$

10.1.3 For indentation diagonals measured in millimetres, tables of HK and HV values are tabulated in Test Method E384.

11. Report

11.1 Report the following information:

11.1.1 The identification of the sample and the location at which the microindentation hardness was measured,

11.1.2 The type of indenter, Knoop or Vickers, and the load used,

11.1.3 The magnification used,

11.1.4 The identity, or description of the phase or microstructural constituent measured,

11.1.5 The type of etchant used, the duration, and method of etching, and

11.1.6 The average of at least five acceptable measurements shall be reported as the microindentation hardness of the material, microstructural constituent, or other feature measured.

11.1.7 Knoop (HK) or Vickers (HV) microindentation hardness shall be reported along with the test load used, for

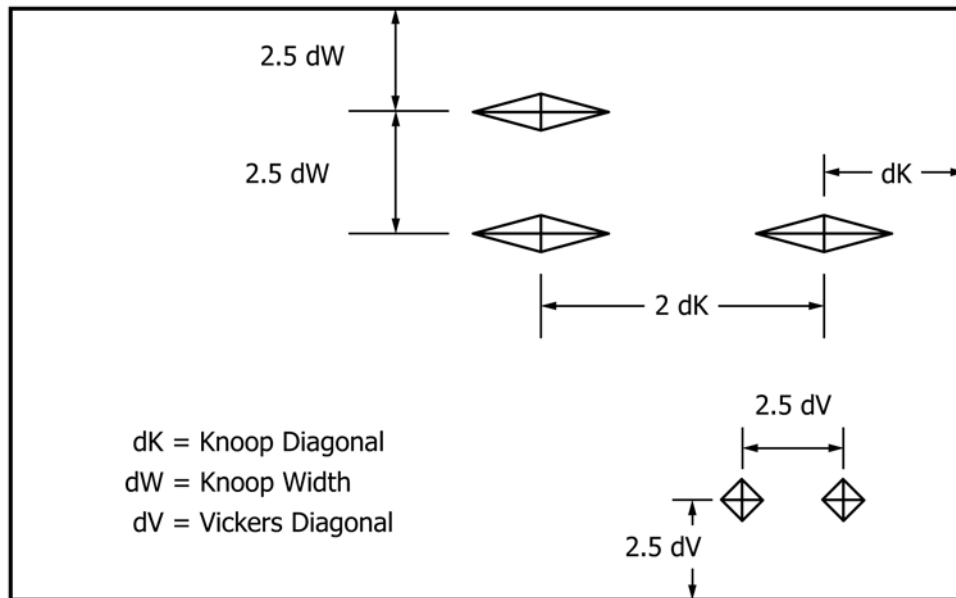


FIG. 1 Minimum Spacing Between Indentations

example, 400 *HK* 100 gf or 400 *HV* 100 gf. This is the preferred method. However, an alternative method expressing the load in kilograms force may be used in accordance with ISO, for example, 400 *HK* 0.1 or 400 *HV* 0.1. Report *HK* and *HV* values to the nearest whole number.

12. Precision and Bias

12.1 The repeatability, *r*, and reproducibility, *R*, of measurements were determined in accordance with Practice E691. Members of the Powder Metallurgy Parts Association of the Metal Powder Industries Federation conducted the interlaboratory test program. The test sample was prepared from heat treated FL-4605. One Knoop and one Vickers microindentation hardness indent was made in the surface of the test sample, and these indentations were measured by 12 participating laboratories.

12.2 The mean Knoop microindentation hardness value was 701 *HK* 100 gf with a repeatability of 22 and a reproducibility of 76. Duplicate microindentation hardness results from one laboratory should not be considered suspect at the 95 %

confidence level unless they differ by more than 22. For the same test specimen, Knoop microindentation hardness results from two different laboratories should not be considered suspect at the 95 % confidence level unless they differ by more than 76.

12.3 The mean Vickers microindentation hardness value was 716 *HV* 100 gf with a repeatability of 43 and a reproducibility of 178. Duplicate microindentation hardness results from one laboratory should not be considered suspect at the 95 % confidence level unless they differ by more than 43. For the same test specimen, Vickers microindentation hardness results from two different laboratories should not be considered suspect at the 95 % confidence level unless they differ by more than 178.

13. Keywords

13.1 Knoop microindentation hardness; microindentation hardness; PM; powder metallurgy; Vickers microindentation hardness