



Designation: ~~E2533 – 17~~^{ε1} E2533 – 21

Standard Guide for Nondestructive Testing Examination of Polymer Matrix Composites Used in Aerospace Applications¹

This standard is issued under the fixed designation E2533; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reappraisal.

^{ε1} NOTE — An editorial correction was made to subsection 4.2 in November 2017.

This standard has been approved for use by agencies of the U.S. Department of Defense.

1. Scope

1.1 This guide provides information to help engineers select appropriate nondestructive testing (NDT) methods to characterize aerospace polymer matrix composites (PMCs). This guide does not intend to describe every inspection technology. Rather, emphasis is placed on established NDT methods that have been developed into consensus standards and that are currently used by industry. Specific practices and test methods are not described in detail, but are referenced. The referenced NDT practices and test methods have demonstrated utility in quality assurance of PMCs during process design and optimization, process control, after manufacture inspection, in-service inspection, and health monitoring.

1.2 This guide does not specify accept-reject criteria and is not intended to be used as a means for approving composite materials or components for service.

1.3 This guide covers the following established NDT methods as applied to PMCs: Acoustic Emission (AE, Section 7); Computed Tomography (CT, Section 8); Leak Testing (LT, Section 9); Radiographic Testing, Computed Radiography, Digital Radiography, and Radioscopy (RT, CR, DR, RTR, Section 10); Shearography (Section 11); Strain Measurement (contact methods, Contact Methods, Section 12); Thermography (Section 13); Ultrasonic Testing (UT, Section 14); and Visual Testing (VT, Section 15).

1.4 The value of this guide consists of the narrative descriptions of general procedures and significance and use sections for established NDT practices and test methods as applied to PMCs. Additional information is provided about the use of currently active standard documents (an emphasis is placed on applicable standard guides, practices, and test methods of ASTM Committee E07 on Nondestructive Testing), geometry and size considerations, safety and hazards considerations, and information about physical reference standards.

1.5 To ensure proper use of the referenced standard documents, there are recognized NDT specialists that are certified in accordance with industry and company NDT specifications. It is recommended that a NDT specialist be a part of any composite component design, quality assurance, in-service maintenance, or damage examination.

1.6 This guide summarizes the application of NDT procedures to fiber- and fabric-reinforced polymeric matrix composites. The

¹ This guide is under the jurisdiction of ASTM Committee E07 on Nondestructive Testing and is the direct responsibility of Subcommittee E07.10 on Specialized NDT Methods.

Current edition approved June 1, 2017/ Feb. 1, 2021. Published June 2017/ March 2021. Originally approved in 2009. Last previous edition approved in 2016/ 2017 as E2533E2533 – 17^{ε1} – 16^{ε2}. DOI: 10.1520/E2533-17E01-10.1520/E2533-21.

composites of interest are primarily, but not exclusively, limited to those containing high modulus (greater than 20 GPa (3×10^6 psi)) fibers. Furthermore, an emphasis is placed on composites with continuous (versus discontinuous) fiber reinforcement.

1.7 This guide is applicable to PMCs containing, but not limited to, bismaleimide, epoxy, phenolic, poly(amide imide), polybenzimidazole, polyester (thermosetting and thermoplastic), poly(ether ether ketone), poly(ether imide), polyimide (thermosetting and thermoplastic), poly(phenylene sulfide), or polysulfone matrices; and alumina, aramid, boron, carbon, glass, quartz, or silicon carbide fibers.

NOTE 1—Per the discretion of the cognizant engineering organization, composite materials not developed and qualified in accordance with the guidelines in CMH-17, Volumes 1 and 3 should have an approved material usage agreement.

1.8 The composite materials considered herein include uniaxial laminae, cross-ply laminates, angle-ply laminates, and sandwich constructions. The composite components made therefrom include filament-wound pressure vessels, flight control surfaces, and various structural composites.

1.9 For current and potential NDT procedures for finding indications of discontinuities in the composite overwrap and thin-walled metallic liners in filament-wound pressure vessels, also known as composite overwrapped pressure vessels (COPVs), refer to Guide Guides E2981 and E2982, respectively.

1.10 For a summary of the application of destructive ASTM standard practices and test methods (and other supporting standards) to continuous-fiber reinforced PMCs, refer to Guide D4762.

1.11 Units—The values stated in SI units are to be regarded as the standard. The values given in parentheses after SI units are provided for information only and are not considered standard.

1.12 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.13 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

[ASTM E2533-21](https://standards.iteh.ai/catalog/standards/sist/8a85dd82-91d8-4673-bad5-e17e83177de1/astm-e2533-21)

<https://standards.iteh.ai/catalog/standards/sist/8a85dd82-91d8-4673-bad5-e17e83177de1/astm-e2533-21>

2.1 ASTM Standards:²

[D3878 Terminology for Composite Materials](#)

[D4762 Guide for Testing Polymer Matrix Composite Materials](#)

[E94/E94M Guide for Radiographic Examination Using Industrial Radiographic Film](#)

[E114 Practice for Ultrasonic Pulse-Echo Straight-Beam Contact Testing](#)

[E214 Practice for Immersed Ultrasonic Testing by the Reflection Method Using Pulsed Longitudinal Waves \(Withdrawn 2007\)³](#)

[E251 Test Methods for Performance Characteristics of Metallic Bonded Resistance Strain Gages](#)

[E317 Practice for Evaluating Performance Characteristics of Ultrasonic Pulse-Echo Testing Instruments and Systems without the Use of Electronic Measurement Instruments](#)

[E427 Practice for Testing for Leaks Using the Halogen Leak Detector Alkali-Ion Diode \(Withdrawn 2013\)³](#)

[E432 Guide for Selection of a Leak Testing Method](#)

[E493/E493M Practice for Leaks Using the Mass Spectrometer Leak Detector in the Inside-Out Testing Mode](#)

[E498/E498M Practice for Leaks Using the Mass Spectrometer Leak Detector or Residual Gas Analyzer in the Tracer Probe Mode](#)

[E499/E499M Practice for Leaks Using the Mass Spectrometer Leak Detector in the Detector Probe Mode](#)

[E515 Practice for Leaks Using Bubble Emission Techniques](#)

[E543 Specification for Agencies Performing Nondestructive Testing](#)

[E569/E569M Practice for Acoustic Emission Monitoring of Structures During Controlled Stimulation](#)

[E650/E650M Guide for Mounting Piezoelectric Acoustic Emission Sensors](#)

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ The last approved version of this historical standard is referenced on www.astm.org.

- [E664/E664M Practice for the Measurement of the Apparent Attenuation of Longitudinal Ultrasonic Waves by Immersion Method](#)
- [E747 Practice for Design, Manufacture and Material Grouping Classification of Wire Image Quality Indicators \(IQI\) Used for Radiology](#)
- [E750 Practice for Characterizing Acoustic Emission Instrumentation](#)
- [E976 Guide for Determining the Reproducibility of Acoustic Emission Sensor Response](#)
- [E1000 Guide for Radioscopy](#)
- [E1001 Practice for Detection and Evaluation of Discontinuities by the Immersed Pulse-Echo Ultrasonic Method Using Longitudinal Waves](#)
- [E1002 Practice for Leaks Using Ultrasonics](#)
- [E1003 Practice for Hydrostatic Leak Testing](#)
- [E1025 Practice for Design, Manufacture, and Material Grouping Classification of Hole-Type Image Quality Indicators \(IQI\) Used for Radiography](#)
- [E1065/E1065M Practice for Evaluating Characteristics of Ultrasonic Search Units](#)
- [E1066/E1066M Practice for Ammonia Colorimetric Leak Testing](#)
- [E1067/E1067M Practice for Acoustic Emission Examination of Fiberglass Reinforced Plastic Resin \(FRP\) Tanks/Vessels](#)
- [E1118/E1118M Practice for Acoustic Emission Examination of Reinforced Thermosetting Resin Pipe \(RTRP\)](#)
- [E1211/E1211M Practice for Leak Detection and Location Using Surface-Mounted Acoustic Emission Sensors](#)
- [E1213 Practice for Minimum Resolvable Temperature Difference for Thermal Imaging Systems](#)
- [E1237 Guide for Installing Bonded Resistance Strain Gages](#)
- [E1255 Practice for Radioscopy](#)
- [E1311 Practice for Minimum Detectable Temperature Difference for Thermal Imaging Systems](#)
- [E1316 Terminology for Nondestructive Examinations](#)
- [E1324 Guide for Measuring Some Electronic Characteristics of Ultrasonic Testing Instruments](#)
- [E1411 Practice for Qualification of Radioscopic Systems](#)
- [E1419/E1419M Practice for Examination of Seamless, Gas-Filled, Pressure Vessels Using Acoustic Emission](#)
- [E1441 Guide for Computed Tomography \(CT\)](#)
- [E1543 Practice for Noise Equivalent Temperature Difference of Thermal Imaging Systems](#)
- [E1570 Practice for Fan Beam Computed Tomographic \(CT\) Examination](#)
- [E1603/E1603M Practice for Leakage Measurement Using the Mass Spectrometer Leak Detector or Residual Gas Analyzer in the Hood Mode](#)
- [E1647 Practice for Determining Contrast Sensitivity in Radiology](#)
- [E1672 Guide for Computed Tomography \(CT\) System Selection](#)
- [E1695 Test Method for Measurement of Computed Tomography \(CT\) System Performance](#)
- [E1742/E1742M Practice for Radiographic Examination](#)
- [E1815 Test Method for Classification of Film Systems for Industrial Radiography](#)
- [E1817 Practice for Controlling Quality of Radiological Examination by Using Representative Quality Indicators \(RQIs\)](#)
- [E1862 Practice for Measuring and Compensating for Reflected Temperature Using Infrared Imaging Radiometers](#)
- [E1897 Practice for Measuring and Compensating for Transmittance of an Attenuating Medium Using Infrared Imaging Radiometers](#)
- [E1901 Guide for Detection and Evaluation of Discontinuities by Contact Pulse-Echo Straight-Beam Ultrasonic Methods](#)
- [E1932 Guide for Acoustic Emission Examination of Small Parts](#)
- [E1933 Practice for Measuring and Compensating for Emissivity Using Infrared Imaging Radiometers](#)
- [E1934 Guide for Examining Electrical and Mechanical Equipment with Infrared Thermography](#)
- [E1935 Test Method for Calibrating and Measuring CT Density](#)
- [E2002 Practice for Determining Total Image Unsharpness and Basic Spatial Resolution in Radiography and Radioscopy](#)
- [E2007 Guide for Computed Radiography](#)
- [E2024/E2024M Practice for Atmospheric Leaks Using a Thermal Conductivity Leak Detector](#)
- [E2033 Practice for Radiographic Examination Using Computed Radiography \(Photostimulable Luminescence Method\)](#)
- [E2076/E2076M Practice for Examination of Fiberglass Reinforced Plastic Fan Blades Using Acoustic Emission](#)
- [E2104 Practice for Radiographic Examination of Advanced Aero and Turbine Materials and Components](#)
- [E2191/E2191M Practice for Examination of Gas-Filled Filament-Wound Composite Pressure Vessels Using Acoustic Emission](#)
- [E2208 Guide for Evaluating Non-Contacting Optical Strain Measurement Systems](#)
- [E2445/E2445M Practice for Performance Evaluation and Long-Term Stability of Computed Radiography Systems](#)
- [E2446 Practice for Manufacturing Characterization of Computed Radiography Systems](#)
- [E2580 Practice for Ultrasonic Testing of Flat Panel Composites and Sandwich Core Materials Used in Aerospace Applications](#)
- [E2581 Practice for Shearography of Polymer Matrix Composites and Sandwich Core Materials in Aerospace Applications](#)
- [E2582 Practice for Infrared Flash Thermography of Composite Panels and Repair Patches Used in Aerospace Applications](#)

- [E2597/E2597M Practice for Manufacturing Characterization of Digital Detector Arrays](#)
- [E2661/E2661M Practice for Acoustic Emission Examination of Plate-like and Flat Panel Composite Structures Used in Aerospace Applications](#)
- [E2662 Practice for Radiographic Examination of Flat Panel Composites and Sandwich Core Materials Used in Aerospace Applications](#)
- [E2736 Guide for Digital Detector Array Radiography](#)
- [E2737 Practice for Digital Detector Array Performance Evaluation and Long-Term Stability](#)
- [E2981 Guide for Nondestructive Examination of Composite Overwraps in Filament Wound Pressure Vessels Used in Aerospace Applications](#)
- [E2982 Guide for Nondestructive Testing of Thin-Walled Metallic Liners in Filament-Wound Pressure Vessels Used in Aerospace Applications](#)
- [F1364 Practice for Use of a Calibration Device to Demonstrate the Inspection Capability of an Interferometric Laser Imaging Nondestructive Tire Inspection System](#)
- 2.2 *ASNT Standard: Standards and Documents:*⁴
- [ASNT CP-189 Standard for Qualification and Certification of Nondestructive Testing Personnel](#)
- [SNT-TC-1A Recommended Practice for Personnel Qualification and Certification in Nondestructive Testing Leak Testing, Volume 1, Nondestructive Testing Handbook](#)
- [Nondestructive Testing Handbook, Visual and Optical Testing, Vol. 8](#)
- 2.3 *ASTM Adjuncts:*
- [Curing Press Straining Block \(13 Drawings\)](#)⁵
- 2.4 *ISO Standard:*⁶
- [ISO 9712 Non-destructive Testing—Qualification and Certification of NDT Personnel](#)
- 2.5 *AIA Standard:*⁷
- [NAS 410 Certification & Qualification of Nondestructive Test Personnel](#)
- 2.6 *MIL Documents:*⁸
- [CMH-17 Composite Materials Handbook, Volume 1. Polymer Matrix Composites, Guidelines For Characterization Of Structural Materials \(formerly MIL-HDBK-17\)](#)
- [CMH-17 Composite Materials Handbook, Volume 3. Polymer Matrix Composites, Materials Usage, Design, and Analysis \(formerly MIL-HDBK-17\)](#)
- [MIL-HDBK-6870 Inspection Program Requirements, Nondestructive for Aircraft and Missile Materials and Parts](#)
- [MIL-HDBK-732A Nondestructive Testing Methods of Composite Materials—Acoustic Emission](#)
- [MIL-HDBK-728 /5A Radiologic Testing](#)
- [MIL-HDBK-733 Nondestructive Testing Methods of Composite Materials—Radiography](#)
- [MIL-HDBK-731 Nondestructive Testing Methods of Composite Materials—Thermography](#)
- [MIL-HDBK-787 Nondestructive Testing Methods of Composite Materials—Ultrasonics](#)
- [MIL-L-25567D Leak Detection Compound, Oxygen Systems](#)
- 2.7 *NASA Documents:*⁹
- [NASA-STD-\(I\)-5019 Fracture Control Requirements for Spaceflight Hardware](#)
- [MSFC-RQMT-3479 Fracture Control Requirements for Composite and Bonded Vehicle and Payload Structures](#)
- 2.8 *Federal Standards:*⁸
- [NBS Handbook 114 General Radiation Safety Installations Using Nonmedical X-ray and Sealed Gamma Sources up to 10 MeV](#)¹⁰
- [Title 10, Code of Federal Regulations \(CFR\), Part 20, Standards for Protection Against Radiation](#)
- [Title 21, Code of Federal Regulations \(CFR\), 1020.40, Safety Requirements of Cabinet X-ray Systems](#)
- [Title 29, Code of Federal Regulations \(CFR\), 1910.96, Ionizing Radiation \(X-rays, RF, etc.\)](#)
- 2.9 *FDA Standards:*¹¹
- [21 CFR 1040.10 Laser Products](#)
- [21 CFR 1040.11 Specific Purpose Laser Products](#)

⁴ Available from American Society for Nondestructive Testing, P. O. Box 28518, 1711 Arlington Lane, Columbus, OH 43228-0518.

⁵ Available from ASTM International Headquarters, Order Adjunct No. ADJf1364.

⁶ Available from Compressed Gas Association, 14501 George Carter Way, Suite 103, Chantilly, VA 20151-International Organization for Standardization (ISO), ISO Central Secretariat, Chemin de Blandonnet 8, CP 401, 1214 Vernier, Geneva, Switzerland, <https://www.iso.org>.

⁷ Available from Aerospace Industries Association (AIA), 1000 Wilson Blvd., Suite 1700, Arlington, VA 22209, <http://www.aia-aerospace.org>.

⁸ Available for Standardization Documents Order Desk, Bldg 4 Section D, 700 Robbins Ave., Philadelphia, PA 19111-5094, Attn: NPODS.

⁹ Available from National Aeronautics and Space Administration, Technical Standards Program, 300 E. Street SW, Suite 5R30, Washington, D. C. 20546, <https://standards.nasa.gov/documents/nasa>.

¹⁰ Available from National Technical Information Service (NTIS), U. S. Department of Commerce, 5285 Port Royal Road, Springfield, VA 22161.

⁸ Available from NCRP Publications, 7010 Woodmont Ave., Suite 1016, Bethesda, MD 20814.

² Available from Society of Automotive Engineers, Inc., 400 Commonwealth Dr., Warrendale, PA 15096-0001.

2.10 *ASME Standard*.¹²

[ASME Boiler and Pressure Vessel Code, Section V, Nondestructive Examination, Article 11, Acoustic Emission Examination of Fiber-Reinforced Plastic Vessels](#)

2.11 *CGA Standard*.¹³

[Pamphlet C-6.4 Methods for External Visual Inspection of Natural Gas Vehicle \(NGV\) and Hydrogen Gas Vehicle \(HGV\) Fuel Containers and Their Installations](#)

2.12 *NCRP Documents*.¹⁴

[NCRP 49 Structural Shielding Design and Evaluation for Medical Use of X-Rays and Gamma Rays of Energies up to 10 MeV](#)

[NCRP 51 Radiation Protection Design Guidelines for 0.1–100 MeV Particle Accelerator Facilities](#)

[NCRP 91 Recommendation on Limits for Exposures to Ionizing Radiation](#)

2.13 *SAE Standard*.¹⁵

[SAE-ARP 1611, Revision A Quality Inspection Procedures, Composites: Tracer Fluoroscopy and Radiography](#)

2.14 *European Standards*.¹⁶

[EN 14784-1, Non-Destructive Testing—Industrial Computed Radiography with Storage Phosphor Imaging Plates—Part 1: Classification of Systems](#)

[EN 14784-2, Non-Destructive Testing—Industrial Computed Radiography with Storage Phosphor Imaging Plates— Part 2: General Principles for Testing of Metallic Materials Using X-Rays and Gamma Rays](#)

[EN 13068-1, Non-Destructive Testing—Radioscopic Testing—Part 1: Quantitative Measurement of Imaging Properties](#)

[EN 13068-2, Non-Destructive Testing—Radioscopic Testing—Part 2: Check of Long Term Stability of Imaging Devices](#)

[EN 13068-3, Non-Destructive Testing—Radioscopic Testing—Part 3: General Principles of Radioscopic Testing of Metallic Materials by X- and Gamma Rays](#)

2.15 *LIA Document*.¹⁷

[ANSI, Z136.1-2000, Safe Use of Lasers](#)

2.16 *BSI Document*.¹⁸

[EN 60825-1 Safety of Laser Products—Part 1: Equipment Classification, Requirements and User's Guide](#)

3. Terminology

3.1 *Abbreviations*—The following abbreviations are adopted in this guide: Acoustic Emission (AE), Computed Radiography (CR), Computed Tomography (CT), Digital Radiography (DR), Leak Testing (LT), Radiographic Testing (RT), Radioscopy (RTR), and Ultrasonic Testing (UT).

3.2 *Definitions*—Definitions of terms related to NDT of aerospace composites which appear in Terminology [E1316](#) and Terminology [D3878](#) shall apply to the terms used in this guide.

3.3 *Definitions of Terms Specific to This Standard*:

3.3.1 *aerospace*—*aerospace, n*—any component that will be installed on a system that flies.

3.3.2 *cognizant engineering organization*—*organization, n*—the company, government agency, or other authority responsible for the design, or end use, of the system or component for which NDT is required. This, in addition to the design personnel, may include personnel from engineering, materials and process engineering, stress analysis, NDT, or quality groups and other, as appropriate.

3.3.2.1 *Discussion*—

This, in addition to the design personnel, may include personnel from engineering, materials and process engineering, stress analysis, NDT, or quality groups and other, as appropriate.

¹⁰ Available from European Committee for Standardization (Electrotechnical), CENELEC Customer service (info@cenelec.org).

¹¹ Published by the Center for Devices and Radiological Health (CDRH) of the Food and Drug Administration (FDA), available from Government Printing Office Superintendent of Documents, 732 N. Capitol St., NW, Mail Stop: SDE, Washington, DC 20401.

¹² Available from American Society of Mechanical Engineers (ASME), ASME International Headquarters, Two Park Ave., New York, NY 10016-5990, <http://www.asme.org>.

¹³ Available from Compressed Gas Association (CGA), 14501 George Carter Way, Suite 103, Chantilly, VA 20151, <http://www.cganet.com>.

¹⁴ Available from NCRP Publications, 7010 Woodmont Ave., Suite 1016, Bethesda, MD 20814.

¹⁵ Available from SAE International (SAE), 400 Commonwealth Dr., Warrendale, PA 15096, <http://www.sae.org>.

¹⁶ Available from European Committee for Standardization (Electrotechnical), CENELEC Customer service (info@cenelec.org).

¹⁷ Available from the Laser Institute of America, 13501 Ingenuity Drive, Suite 128, Orlando, FL 32826.

¹⁸ Available from the British Standards Institution (BSI), 389 Chiswick High Road, London Rd., London W4 4AL, United Kingdom.U.K., <http://www.bsigroup.com>.

3.3.3 *composite material*—*material, n*—see Terminology [D3878](#).

3.3.4 *composite component*—*component, n*—a finished part containing composite material(s) that is in its end use application configuration, and which has undergone processing, fabrication, and assembly to the extent specified by the drawing, purchase order, or contract.

3.3.5 *disbond*—*disbond, n*—see Terminology [D3878](#).

3.3.6 *in-service*—*in-service, n*—refers to composite components that have completed initial fabrication and are in use (or in storage) for their intended function.

3.3.7 *microcrack*—*microcrack, n*—invisible cracks (< 50 to 100 μm size) that are precursors to visible cracks. ~~In angle-ply continuous fiber-reinforced composites, for example, microcracks form preferentially under tensile loading in the matrix in off-axis plies. Since most microcracks do not penetrate the reinforcing fibers, microcracks in a cross-plyed tape laminate or in a laminate made from cloth prepreg are usually limited to the thickness of a single ply.~~

3.3.7.1 Discussion—

In angle-ply continuous fiber-reinforced composites, for example, microcracks form preferentially under tensile loading in the matrix in off-axis plies. Since most microcracks do not penetrate the reinforcing fibers, microcracks in a cross-plyed tape laminate or in a laminate made from cloth prepreg are usually limited to the thickness of a single ply.

3.3.8 *reference standards*—*standards, n*—objects that provide a known, reproducible, and repeatable response to a specific stimulus. ~~May~~stimulus; may be in the form of hardware or software.

3.3.9 *sandwich construction*—*construction, n*—see Terminology [D3878](#).

4. Summary of Guide

4.1 This guide describes and provides references for the practice and utilization of the following established NDT procedures as applied to polymeric matrix composites:

4.1.1 Acoustic Emission (Section [7](#)).

4.1.2 Computed Tomography (X-ray Method) (Section [8](#)).

4.1.3 Leak Testing (Section [9](#)).

4.1.4 Radiography, Computed Radiography, Digital Radiography with Digital Detector Array Systems, and Radioscopy (Section [10](#)).

4.1.5 Shearography (Section [11](#)).

4.1.6 Strain Measurement (Strain Gauges) (Section [12](#)).

4.1.7 Infrared Thermography (Non-Contact Methods Using Infrared Camera) (Section [13](#)).

4.1.8 Ultrasonic Testing (Section [14](#)).

4.1.9 Visual Testing (Section [15](#)).

4.2 *NDT Method Selection*—Composite components such as laminates, moldings, and subassemblies may be inspected by simple procedures consisting of dimensional and tolerance measurements, weight and density determinations, cure determinations by hardness measurements, visual testing for defects, and tapping for void determinations. If the integrity of the subassembly warrants a more complete inspection, this can be accomplished by using various NDT procedures discussed in this guide. Nondestructive tests can usually be made rapidly. However, nondestructive testing will, in general, add to component cost and should be used only when warranted on critical applications. Also, the extent of NDT on composite parts depends on whether the part is a primary

structure safety of flight part, or secondary structure non-safety of flight part. The type or class of part is usually defined on the engineering drawing. Some of the flaws that can be detected by NDT are given in **Table 1**.

4.3 Other critical defect characteristics not mentioned in **Table 1** that need to be considered when establishing NDE procedures include defect size, defect shape, defect depth, defect orientation, fiber volume fraction, resin rich regions, resin poor regions, cure state, fiber sizing, fiber-matrix bonding, crazing (cracking of amorphous matrix resins due to exposure to stress or the service environment), residual and internal stress, degradation (chemical and physical attack), and impact damage.

4.4 *General Facility and Personnel Qualification*—Minimum general requirements for NDT facilities and personnel qualification are given in **Practice Specification E543**. This **practice specification** can be used as a basis to evaluate testing or inspection agencies, or both, and is intended for use for the qualifying or accrediting, or both, of testing or inspection agencies, public or private.

4.5 *Personnel Certification*—NDT personnel should be certified in accordance with a nationally or internationally recognized practice or standard such as ANSI/ASNT-CP-189, SNT-TC-1A, NAS 410, ISO 9712, or a similar document. The practice or standard used and its applicable revisions should be specified in any contractual agreement between the using parties.

4.6 *Personnel Qualification*—NDT personnel should be qualified by accepted training programs, applicable on-the-job training, or a competent mentor or component manufacturer. Personnel will be only qualified to inspect parts that come under direct training experience or production.

4.7 *General Equipment and Instrumentation Considerations*—General equipment and instrumentation considerations are provided in **Practice Specification E543**. NDT method specific considerations are discussed in the appropriate section of this guide (Sections **77 – 15 to 15**).

4.8 *Reference Standards*—Physical reference standards simulating target imperfections or discontinuities are used to validate NDT results. The use of physical reference standards also helps to ensure reproducibility and repeatability of measurements. Certified physical reference standards calibrated by accepted government or industrial agencies may be used.

4.9 *Extent of Examination*—Specific applications may require local regions or the entire component to be examined. Examination may be real time or delayed based upon the availability of data. Examination may be direct, or indirect, on site or remote as specified in the contractual agreement or established requirements documents.

TABLE 1 Flaws Detected By NDT Procedures

Defect	Acoustic Emission	Computed Tomography	Leak Testing	Radiography with DDA; Radiography, CR, Radioscopy	Shearography	Strain Measurement	Thermography	Ultrasonic Testing	Visual Testing
Contamination		X		X				X	X
Damaged Filaments	X	X		X					
Delamination	X	X			X		X	X	X
Density Variation		X		X			X	X	
Deformation under Load					X	X			
Disbond		X			X		X	X	X
Fiber Debonding	X	X ^A					X	X	
Fiber Misalignment		X		X			X		
Fractures	X	X		X			X	X	X
Inclusions		X		X			X	X	X
Leaks	X		X					X	
Loose or Moving Parts	X								
Microcracks	X	X ^B		X ^{B,C}	X			X	
Moisture		X		X ^{D,E}			X		
Porosity	X	X		X			X	X	
Thickness Variation		X		X ^F	X		X	X	
Undercure								X	
Volumetric Effects		X							
Voids	X	X	X	X			X	X	

^A Can detect after impact (voids).

^B Depends on opening/size of crack.

^C Depends on angle of beam relative to planar defect and opening.

^D Only in central projection (Radiography, CR).

^E Radioscopic mode (Radiography with DDA).

^F For Radiography, applicable to CR and digitized films only.

4.10 *Timing of Examination*—Examinations ~~shall~~should be performed in accordance with the contractual agreement or established requirements documents, and may be performed during the life cycle of the article under test.

4.11 *Type of Examinations*—Many different NDT system configurations are possible due to the wide range of system components available. It is important for the purchaser of NDT to understand the capability and limitations of the applicable configuration. Selection of the NDT procedure and system ~~shall~~should be at the discretion of the testing agency unless specified by the purchaser in a contract or requirements document (that is, engineering drawing, specifications, etc.).

4.12 A tabular comparison of most of the established NDT procedures discussed in the guide is given in Appendix X1 of Practice Specification E543; namely, acoustic emission, leak testing, radiography, strain measurement, thermography (infrared), and ultrasound are covered. The comparison summarizes properties sensed or measured, typical discontinuities detected, representative application, applicable ASTM standards, and advantages and limitations. A similar overview is provided in Table 2.

5. Significance and Use

5.1 This guide references requirements that are intended to control the quality of NDT data. The purpose of this guide, therefore, is not to establish acceptance criteria and therefore approve composite materials or components for aerospace service.

5.2 Following the discretion of the cognizant engineering organization, NDT for fracture control of composite and bonded materials should follow additional guidance described in MIL-HDBK-6870, NASA-STD-(I)-5019, or MSFC-RQMT-3479, or a combination thereof, as appropriate (not covered in this guide).

5.3 Certain procedures referenced in ~~the~~this guide are written so they can be specified on the engineering drawing, specification, purchase order, or contract, for example, Practice E1742/E1742M (Radiography).

5.4 *Acceptance Criteria*—Determination about whether a composite material or component meets acceptance criteria and is suitable for aerospace service ~~must~~should be made by the cognizant engineering organization. When examinations are performed in accordance with the referenced documents in this guide, the engineering drawing, specification, purchase order, or contract ~~shall~~should indicate the acceptance criteria.

5.4.1 Accept/reject criteria ~~shall~~should consist of a listing of the expected kinds of imperfections and the rejection level for each.

5.4.2 The classification of the articles under test into zones for various accept/reject criteria ~~shall~~should be determined from contractual documents.

5.4.3 *Rejection of Composite Articles*—If the type, size, or quantities of defects are found to be outside the allowable limits specified by the drawing, purchase order, or contract, the composite article ~~shall~~should be separated from acceptable articles, appropriately identified as discrepant, and submitted for material review by the cognizant engineering organization, and dispositioned as (1) acceptable as is, (2) subject to further rework or repair to make the materials or component acceptable, or (3) scrapped when required by contractual documents.

5.4.4 Acceptance criteria and interpretation of result ~~shall~~should be defined in requirements documents prior to performing the examination. Advance agreement should be reached between the purchaser and supplier regarding the interpretation of the results of the examinations. All discontinuities having signals that exceed the rejection level as defined by the process requirements documents ~~shall~~should be rejected unless it is determined from the part drawing that the rejectable discontinuities will not remain in the finished part.

5.5 *Life Cycle Considerations*—The referenced NDT practices and test methods have demonstrated utility in quality assurance of PMCs during the life cycle of the product. The modern NDT paradigm that has evolved and matured over the last twenty-five years has been fully demonstrated to provide benefits from the application of NDT during: (a) product and process design and optimization, (b) on-line process control, (c) after manufacture inspection, (d) in-service inspection, and (e) health monitoring.

5.5.1 In-process NDT can be used for feedback process control since all tests are based upon measurements which do not damage the article under test.

TABLE 2 General Overview of Established NDT Procedures

NDT Method	Applications	Advantages	Limitations	What Is Seen and Reported?	Other Considerations
Acoustic Emission	Global monitoring of composite structures to detect and locate active sources in real time.	Remote and continuous monitoring on an entire composite article in real time is possible. Can also detect growth of active imperfections or discontinuities, and detect and determine the location of discontinuities and defects that may be inaccessible by other NDT procedures.	The part being inspected must be stressed by mechanical, load, pressure, temperature, or other stimulus. With the exception of certain imperfections or discontinuities that AE detects by friction-generated AE (for example, delamination surfaces rubbing), AE-inactive (non-propagating) imperfections or discontinuities cannot be detected and structurally insignificant imperfections or discontinuities may produce AE. Therefore, the significance of a detected AE source cannot be assessed unambiguously.	The AE technique records transient elastic waves produced by applied stress or resulting stress relaxation of the composite material or component. The mechanical waves are produced as either burst or continuous AE. AE activity, intensity and severity correlated with applied stress yield information on the degradation within the article under test.	Inspection tests and results are unique to each application and should be conducted with expert oversight.
Computed Tomography	Detects sub-surface volumetric imperfections or discontinuities. Provides quantitative, volumetric analysis of imperfections or discontinuities detectable by other NDT procedures. Also suitable for measuring geometric characteristics.	Produces clear cross-sectional image slices of an object. Obtains 3D imperfection or discontinuity data. Extensive image processing capability.	Requires access to all sides of the article under test. Not very applicable to the inspection of large areas, or objects with high (>15) aspect ratios.	A digitized cross-sectional CT-density map (tomogram) of the article under test. Allows full, three dimensional CT-density maps to be obtained for sufficiently small composite parts.	Tooling and/or part-handling fixtures may be required.
Computed Tomography	Detects sub-surface volumetric imperfections or discontinuities. Provides quantitative, volumetric analysis of imperfections or discontinuities detectable by other NDT procedures. Also suitable for measuring geometric characteristics.	Produces clear cross-sectional image slices of an object. Obtains 3D imperfection or discontinuity data. Extensive image processing capability.	Requires access to all sides of the article under test. Not very applicable to the inspection of large areas, or objects with high (>15) aspect ratios.	A digitized cross-sectional CT-density map (tomogram) of the article under test. Allows full, three dimensional CT-density maps to be obtained for sufficiently small composite parts.	Tooling or part-handling fixtures, or both, may be required.
Leak Testing	Any composite material or component across which a differential pressure exists and where through-leakage or in-leakage of product, air, water vapor, or other contaminant over the projected service life are of concern.	Less ambiguous than liquid penetrant testing; more sensitive than AE or UT.	Test equipment costs increase as the required leak test sensitivity increases.	Qualitative indications, for example bubbles, or quantitative measurements, for example, detector deflections, that ascertain the presence or location, or concentration or leak rate of a leaking fluid.	Different techniques are available for characterization of large leaks (with rates as high as 10^{-2} Pa m ³ s ⁻¹ (10^{-1} std cm ³ s ⁻¹)) and small leaks (rates less than 10^{-5} Pa m ³ s ⁻¹ (10^{-4} std cm ³ s ⁻¹)).

5.5.2 The applicability of NDT procedures to evaluate PMC materials and components during their life cycle is summarized in [Tables 3 and 4](#).

5.6 *General Geometry and Size Considerations*—Part contour, curvature, and surface condition may limit the ability of certain tests to detect imperfections with the desired accuracy.

5.7 *Reporting*—Reports and records should be specified by agreement between purchaser and supplier. It is recommended that any NDT report or archival record contain information, when available, about the material type; method of fabrication;

TABLE 2 *Continued*

NDT Method	Applications	Advantages	Limitations	What Is Seen and Reported?	Other Considerations
Radiography, Computed Radiography, Radiography with Digital Detector Arrays, Radioscopy	Primarily detects subsurface imperfections or discontinuities such as porosity & inclusions. Planar imperfections or discontinuities are detected if the beam is directed along the imperfection or discontinuity and the unsharpness is less than the imperfection or discontinuity opening/size.	Film and some imaging plates can be cut and placed almost anywhere on the part. Digital images can be processed for additional information and automated defect recognition. In radioscopy, techniques using an image intensifier and DDA can be automated by interfacing with a robot or part manipulator thus allowing the potential for a faster inspection.	Requires access to both sides of the article under test. Accessibility may need to be evaluated. Unable to determine depth of imperfections or discontinuities; sometimes possible from digital images after calibration or with additional X-ray exposures from different directions.	Projected area and density variation of subsurface imperfections or discontinuities.	Part may need to be moved to an X-ray lab; Film RT requires film storage and disposal of chemicals which can be expensive. Digital techniques (CR, DDA) are usually faster. Radiation safety. In radioscopy, radiation safety more problematic if a moving source is used, versus movement of part.
Shearography	Detects subsurface imperfections or discontinuities or changes in modulus or out-of-plane deformation.	Well suited for high speed, automated inspection in production environments.	Subsurface imperfection or discontinuity must be sufficiently large to cause measurable surface deformation under load. Surface condition, especially glossiness, can interfere with accurate shearographic detection, thus requiring the use of surface dulling agents (exception: thermal shearography).	An interference pattern created by subtracting or superimposing images of the article under test taken before and after loading, thus revealing localized strain concentrations.	Additional equipment is required to determine surface derivative slope changes, and thus uses the method as a quantitative tool.
Shearography	Detects subsurface imperfections or discontinuities or changes in modulus or out-of-plane deformation.	Well suited for high speed, automated inspection in production environments.	Subsurface imperfection or discontinuity should be sufficiently large to cause measurable surface deformation under load. Surface condition, especially glossiness, can interfere with accurate shearographic detection, thus requiring the use of surface dulling agents (exception: thermal shearography).	An interference pattern created by subtracting or superimposing images of the article under test taken before and after loading, thus revealing localized strain concentrations.	Additional equipment is required to determine surface derivative slope changes, and thus uses the method as a quantitative tool.
Strain Measurement	Can be used to measure static and dynamic tensile and compressive strain, as well as shearing, Poisson, bending, and torsional strains.	Relatively inexpensive, and less bulky and better resolution than extensometers (can achieve an overall accuracy of better than $\pm 0.10\%$ strain).	Individual strain gauges cannot be calibrated and are susceptible to unwanted noise and other sources of error such as expansion or contraction of the strain-gauge element, change in the resistivity, and hysteresis and creep caused by imperfect bonding.	The output of a resistance measuring circuit is expressed in millivolts output per volt input.	Depending on desired sensitivity, resistance to drift, insensitivity to temperature variations, or stability of installation, a variety of strain gauges are available (for example, semiconductor wafer sensors, metallic bonded strain gauges, thin-film and diffused semiconductor strain gauges).

manufacturers name, part number, lot, fabrication; manufacturer's name; part number; lot; date of lay-up and/or of cure, or both; date and pressure load of previous tests (for pressure vessels); and previous service history (for in-service and failed composite articles). Forwards and backwards compatibility of data, data availability, criticality (length of data retention), specification change, specification revision and date, software and hardware considerations will also govern how reporting is performed.

6. Procedure

6.1 When NDT produces an indication of a material discontinuity, the indication is subject to interpretation as false, nonrelevant,

TABLE 2 Continued

NDT Method	Applications	Advantages	Limitations	What Is Seen and Reported?	Other Considerations
Thermography	Detects disbonds, delaminations, voids, pits, cracks, inclusions, and occlusions, especially in thin articles under test having low thermal conductivity, low reflectivity/high emissivity surfaces, and in materials which dissipate energy efficiently.	Quick observation of large surfaces and identification of regions that should be examined more carefully.	Composites have temperature limits beyond which irreversible matrix and fiber damage can occur. Imperfection or discontinuity detection depends on orientation of an imperfection or discontinuity relative to the direction of heat flow. In thicker materials, only qualitative indications of imperfections or discontinuities are possible.	The areal temperature distribution is measured by mapping contours of equal temperature (isotherms), thus yielding a heat emission pattern related to surface and subsurface defects.	Both contact (requires application of a coating) and noncontact methods (relies on detection of infrared blackbody radiation) are available. Thermography is either passive or active; active thermography can be further subdivided into pulse or lock-in techniques.
Thermography	Detects disbonds, delaminations, voids, pits, cracks, inclusions, and occlusions, especially in thin articles under test having low thermal conductivity, low reflectivity/high emissivity surfaces, and in materials which dissipate energy efficiently.	Quick observation of large surfaces and identification of regions that should be examined more carefully.	Composites have temperature limits beyond which irreversible matrix and fiber damage can occur. Imperfection or discontinuity detection depends on orientation of an imperfection or discontinuity relative to the direction of heat flow. In thicker materials, only qualitative indications of imperfections or discontinuities are possible.	The areal temperature distribution is measured by mapping contours of equal temperature (isotherms), thus yielding a heat emission pattern related to surface and subsurface defects.	Both contact (requires application of a coating) and noncontact methods (relies on detection of infrared blackbody radiation) are available. Thermography is either passive or active; active thermography can be further subdivided into pulse or lock-in techniques.
Ultrasonic Testing	Detects sub-surface imperfections or discontinuities. There are two primary techniques; pulse echo for one sided inspections and through transmission for two sided inspections.	Detects sub-surface imperfections or discontinuities including porosity, inclusions, and delaminations.	Requires a relatively flat and smooth surface. Material type can affect inspectability.	Imperfections or discontinuities are directly recorded on amplitude images.	Possible fluid entrapment; possible fluid absorption into porous materials such as composites. Numerous techniques available including longitudinal, shear or surface waves. Attenuation can be comparatively high in PMCs compared to metallic articles.
Visual Testing	Detects disruptions on surfaces being viewed.	Low cost. Detect surface imperfections or discontinuities including delaminations, fiber breakage, impact damage.	Requires direct line of sight.	Imperfections or discontinuities are directly recorded on inspection documentation sometimes photographs.	Can find imperfections or discontinuities on inside diameters if a central conductor can be inserted and satisfactory electrical contact made.
Visual Testing	Detects disruptions on surfaces being viewed.	Low cost. Detect surface imperfections or discontinuities including delaminations, fiber breakage, impact damage.	Requires direct line of sight.	Imperfections or discontinuities are directly recorded on inspection documentation sometimes photographs.	Can find imperfections or discontinuities on inaccessible surfaces if a borescope can be inserted and satisfactory imagining performed.

or relevant (Fig. 1). If the indication has been interpreted as relevant, the necessary subsequent evaluation will result in the decision to accept or reject the composite material or component.

7. Acoustic Emission

7.1 Referenced Documents

7.1.1 ASTM Standards:²

E569 Practice for Acoustic Emission Monitoring of Structures during Controlled Simulation

TABLE 3 Application Examples of Established NDT Procedures During Life Cycle

NDT Method	Application
Acoustic Emission	May be used for quality control of production and fabrication processes (for example, to evaluate adhesive bonding after lay-up winding or curing), for proof-testing of pressure vessels after fabrication, and for periodic in-service and health monitoring inspections prior to failure.
Computed Tomography	May be used as a post-fabrication metrological method to verify engineering tolerances.
Leak Testing	May be used to validate leak tightness following fabrication, and in-service re-qualification of pressure vessels. For example, helium leak detection can be used during composite article fabrication to detect and seal leaks permanently (preferable) or temporarily in such a manner to allow repair at a later time. Similarly, halogen gas leak detection has been used in production examination.
Radiography and Radioscopy	May be used during fabrication inspection to evaluate honeycomb core imperfections or discontinuities such as node bonds, core-to-core splices, core-to-structure splices, porosity, included material as well as verification of structural placement.
Shearography	May be used in quality assurance, material optimization, and manufacturing process control.
Strain Measurement	May be used during proof testing before placement into service, or during periodic re-qualification. Can be destructive depending on the strain thresholds reached during test.
Thermography	May be used to follow imperfection or discontinuity growth during service. If video thermographic equipment is used, systems that are being dynamically tested or used can be examined in real-time.
Ultrasonic Testing	Automatic recording systems allow parts to be removed from a processing line when defect severity exceeds established limits. Measurement of the apparent attenuation in composite materials is useful in applications such as comparison of crystallinity and fiber loading in different lots, or the assessment of environmental degradation. The most common method is applied for laminar oriented defect detection such as impact damage causing delamination fiber fracturing, included material, and porosity.
Visual Testing	Used primarily for quality inspections of composite materials and components upon receipt (after fabrication and before installation).

TABLE 4 Application of Established NDT Procedures During the Life Cycle of Polymeric Matrix Composites

Defect	Product and Process Design and Optimization	On-Line Process Control	After Manufacture Inspection	In-Service Inspection	Health Monitoring
Acoustic Emission	X	X	X	X	X
Computed Tomography	X		X		
Leak Testing	X	X		X ^A	
Radiography and Radioscopy	X	X	X	X	
Shearography	X	X	X	X	
Strain Measurement			X		X
Thermography			X	X	
Ultrasonic Testing	X	X	X	X	X
Visual Testing	X	X	X	X	X

^A Applicable to composites used in storage and distribution of fluids and gases, for example, filament-wound pressure vessels.

~~E650 Guide for Mounting Piezoelectric Acoustic Emission Sensors~~

~~E750 Practice for Characterizing Acoustic Emission Instrumentation~~

~~E976 Guide for Determining the Reproducibility of Acoustic Emission Sensor Response~~

~~E1067 Practice for Acoustic Emission Examination of Fiberglass Reinforced Plastic Resin (FRP) Tanks/Vessels~~

~~E1118 Practice for Acoustic Emission Examination of Reinforced Thermosetting Resin Pipe (RTRP)~~

~~E1211 Practice for Leak Detection and Location Using Surface-Mounted Acoustic Emission Sensors~~

~~E1419 Test Method for Examination of Seamless, Gas-Filled, Pressure Vessels Using Acoustic Emission~~

~~E1932 Guide for Acoustic Emission Examination of Small Parts~~

~~E2076 Test Method for Examination of Fiberglass Reinforced Plastic Fan Blades Using Acoustic Emission~~

~~E2191 Test Method for Examination of Gas-Filled Filament-Wound Composite Pressure Vessels Using Acoustic Emission~~

~~7.1.2 Compressed Gas Association Standard:⁵~~

~~Pamphlet C-6.4 Methods for External Visual Inspection of Natural Gas Vehicle (NGV) and Hydrogen Gas Vehicle (HGV) Fuel Containers and Their Installations~~

~~7.1.3 Military Handbooks and Standard:⁶~~

~~MIL-HDBK-732A Nondestructive Testing Methods of Composite Materials—Acoustic Emission~~

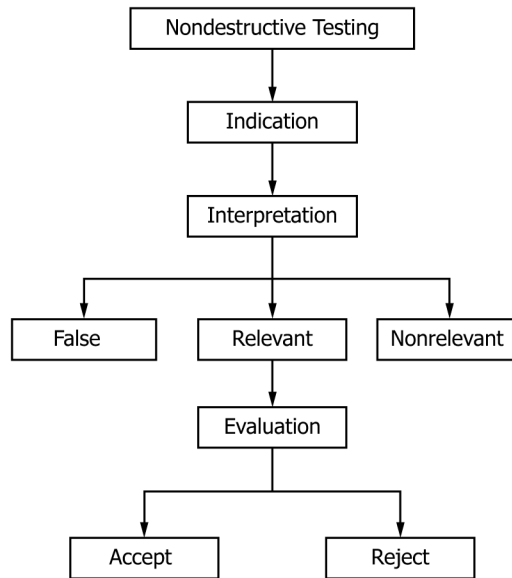


FIG. 1 Consequences of Detecting a Material Discontinuity (Indication) by NDT

7.1 General Procedure

7.1.1 Specially designed sensors (transducers) are used to detect transient elastic stress waves (AE) in a material produced as a result of applied stress (tension, compression, torsion, internal pressure, or thermal). The sensors are coupled to the article under test with a suitable couplant (for example, grease), or by means of an epoxy cement or other adhesive. The output from the sensor is amplified and filtered to eliminate unwanted frequencies. The conditioned AE signal is then digitized and segmented into discrete AE waveform packets through a process of threshold detection. Digital signal processing converts the transient waveform packets into extracted time and frequency features which describe the transient waveform's shape, size, and frequency content. In sophisticated approaches, these features are sometimes analyzed together using artificial intelligence, pattern recognition and/or recognition, or neural network techniques, or a combination thereof, to distinguish true AE sources from noise. When multiple sensors in an array detect the same AE transient, location determination can be accomplished using arrival time analysis (triangulation) techniques. When multiple events are located close together they form an event cluster indicating continuing activity which is indicative of an active growing source. In addition to AE activity generated by growing imperfections or discontinuities, activity can also originate from preexisting imperfections or discontinuities that are not growing (for example, delamination surfaces rubbing together during depressurization of a pressure vessel).

7.2 Significance and Use

7.2.1 Acoustic emission is a term used to describe transient elastic stress waves produced in solids as a result of the application of stress. The applied stress may include mechanical forces (tension, compression or torsion), internal pressure, or thermal gradients (can often be accomplished by use of a hot-air gun). The applied stress may be short to long, random, or cyclic. The applied stress may be controlled by the examiner, or may already exist as part of the process. In either case, the applied stress is measured along with the AE activity.

7.2.2 The resulting AE stress waves are produced by the rapid release of energy within the material from a localized source. The AE signal from composites often consists of both continuous AE (qualitative description of a sustained signal level produced by rapidly occurring AE events) and burst AE (qualitative description of discrete signals of varying duration that are usually of higher amplitude than continuous AE).

7.2.3 The AE technique records transient elastic stress waves produced by applied stress or resulting stress relaxation of the composite material or component. The stress waves are produced as either burst or continuous AE. AE activity, intensity, and severity correlated with applied stress yield information on the degradation within the article under test. Lack of AE activity is an indication of a sound structure, while more activity is an indication that the structure is degraded. The source is located by triangulation or zone location methods.

TABLE 5 Summary of Acoustic Emission

Applications	How It Works	Advantages	Limitations	What Is Seen and Reported?
Global monitoring of composite structures to detect and locate active sources: — Evaluation of the structural integrity of finished composite components such as pipes, tubes, tanks, and pressure vessels: — Quality control of production and fabrication processes (for example, during lay-up winding, or curing): — Proof testing after fabrication. Also can be used as an alternative method to periodic hydrostatic proof testing: — Periodic monitoring of regions of interest or concern during service: — Continuous, real-time monitoring of structures (health monitoring): — Evaluation of adhesive bonding: — Monitoring crack growth prior to failure: — Leak detection.	AE transducers are coupled to the article under test to detect transient elastic stress waves (or AE) produced during application of stress (mechanical, thermal or pressure). The location of the source is located by triangulation or area (zonal) location methods.	Remote and continuous monitoring of the entire article under test in real time is possible: — Can detect growing of active imperfections or discontinuities: — Can detect discontinuities and defects that may be inaccessible to other NDT procedures, and determine their location: — Can be used for proof testing of new or in-service composite material components: — Can be used for periodic or continuous (in situ) health monitoring.	The part or article under test must be stressed by mechanical load, pressure, or temperature, or other stimulus: — Inactive (nonpropagating) imperfections or discontinuities cannot be detected and structurally insignificant imperfections or discontinuities may produce AE. Therefore, the significance of a detected AE source cannot be assessed unambiguously: — Nonrelevant noise must be filtered out: — Transducers must be placed on the part or article under test: — Usually requires other NDT procedures to characterize detected imperfections or discontinuities.	The AE technique monitors transient elastic stress waves generated by various local processes that occur in a short time period in a structure under stress. The lack of sensed AE signals can be an indication of a composite structure having structural integrity. — Alternatively, if increasing AE activity is detected, that can be an indication of damage occurring in the structure and of a potential loss of structural integrity. The AE signal from composites often consists of both continuous AE (qualitative description of a sustained signal level produced by rapidly occurring AE events) and burst AE (qualitative description of discrete signals of varying duration that are usually of higher amplitude than continuous AE).

iTech Standards
 (https://standards.itih.ai)
 Document Preview

[ASTM E2533-21](#)

<https://standards.itih.ai/catalog/standards/sist/8a85dd82-91d8-4673-bad5-e17e83177de1/astm-e2533-21>

7.2.4 In fiber-reinforced composites, AE is generated by release of stored elastic energy during processes such as cracking of the matrix, or fracture or splitting of fibers. Irreversible viscoelastic processes such as crazing of amorphous matrices or plastic (irreversible) deformation of either the matrix or fiber are not detectable under normal measurement conditions with commercial AE systems.

7.2.5 Interfacial sources of AE in fiber-reinforced composites include debonding of the matrix from the fibers, subsequent fiber pull-out (rubbing), and interlaminar debonding.

7.2.6 AE can also be produced by other acoustic sources in the composite not directly related to the matrix or fiber. These sources include leakage of gas or liquid through a crack, orifice, seal break, or other opening (for example, in composite-overwrapped pressure vessels); and by movement or loosening of parts (thread failure in assembled composite piping systems, for example).

7.2.7 Most AE signals that are useful in NDT have frequencies that are above the audible range. Ordinarily they are between 20 kHz and 1 MHz, depending on application. The rate and amplitude of acoustic emission signals are noted and correlated to structure or composite article characteristics. Lower and higher frequencies are filtered out to avoid interferences from unwanted sources of noise such as machine vibrations or electrical equipment generated noise.

NOTE 2—When detecting leaks using low frequencies generally lower than 100 kHz, it is possible for the leak to excite mechanical resonances within the article under test that may enhance the acoustic signal used to detect leakage.

7.2.8 In addition to immediate evaluation of the emissions detected during application of the stimulus, a permanent record of the number and location of emitting sources and the relative amount of AE detected from each source provides a basis for comparison with sources detected during the examination and during subsequent stimulation.

TABLE 5 Summary of Acoustic Emission

Applications	How It Works	Advantages	Limitations	What Is Seen and Reported?
<u>Global monitoring of composite structures to detect and locate active sources.</u> <u>Evaluation of the structural integrity of finished composite components such as pipes, tubes, tanks, and pressure vessels.</u> <u>Quality control of production and fabrication processes (for example, during lay-up winding, or curing).</u> <u>Proof-testing after fabrication. Also can be used as an alternative method to periodic hydrostatic proof testing.</u> <u>Periodic monitoring of regions of interest or concern during service.</u> <u>Continuous, real-time monitoring of structures (health monitoring).</u> <u>Evaluation of adhesive bonding.</u> <u>Monitoring crack growth prior to failure.</u> <u>Leak detection.</u>	<u>AE transducers are coupled to the article under test to detect transient elastic stress waves (or AE) produced during application of stress (mechanical, thermal or pressure). The location of the source is located by triangulation or area (zonal) location methods.</u>	<u>Remote and continuous monitoring of the entire article under test in real time is possible.</u> <u>Can detect growing of active imperfections or discontinuities.</u> <u>Can detect discontinuities and defects that may be inaccessible to other NDT procedures, and determine their location.</u> <u>Can be used for proof testing of new or in-service composite material components.</u> <u>Can be used for periodic or continuous (in situ) health monitoring.</u>	<u>The part or article under test should be stressed by mechanical load, pressure, or temperature, or other stimulus.</u> <u>A delamination can be detected by friction generated AE, most easily during unloading.</u> <u>Inactive (nonpropagating) imperfections cannot be detected and structurally insignificant imperfections or discontinuities may produce AE. Therefore, the significance of a detected AE source cannot be assessed unambiguously.</u> <u>Nonrelevant noise must be filtered out.</u> <u>Transducers must be placed on the part or article under test.</u> <u>Usually requires other NDT procedures to characterize detected imperfections or discontinuities.</u>	<u>The AE technique monitors transient elastic stress waves generated by various local processes that occur in a short time period in a structure under stress. The lack of sensed AE signals can be an indication of a composite structure having structural integrity.</u> <u>Alternatively, if increasing AE activity is detected, that can be an indication of damage occurring in the structure and of a potential loss of structural integrity. The AE signal from composites often consists of both continuous AE (qualitative description of a sustained signal level produced by rapidly occurring AE events) and burst AE (qualitative description of discrete signals of varying duration that are usually of higher amplitude than continuous AE).</u>

iTech Standard
<https://standards.iteh.ai>
 Document Preview

ASTM E2533-21

<https://standards.iteh.ai/catalog/standards/sist/8a85dd82-91d8-4673-bad5-e17e83177de1/astm-e2533-21>

7.2.9 The basic functions of an AE monitoring system are to detect, locate, and possibly classify emission sources. Other NDT procedures (for example, visual testing, ultrasonic testing, and eddy current testing) should be used to further evaluate the damage detected in an AE-located region.

NOTE 3—Determining the significance of damage with respect to residual strength or remaining life in a composite sample is presently not possible at the same level as is done with a crack in a metallic sample, for example, where fracture mechanics can be used to determine the significance of damage.

7.2.10 *Felicity Ratio*—The Felicity ratio is the numerical value of the applied stress at which “significant AE” begins divided by the applied stress during the previous cycle. The term “significant AE” has no quantitative definition at this time, and is open to interpretation by the AE practitioner. However, Practice E1067E1067/E1067M suggests three guidelines for determining the onset of significant AE:

7.2.10.1 More than 5 bursts during a 10 % increase in applied stress.

7.2.10.2 More than 20 counts during a 10 % increase in applied stress.

7.2.10.3 Increasing AE at constant applied stress.

7.2.11 *Effect of Variables on the Felicity Ratio*—Rate of application and removal of stress, time at peak applied stress, AE system sensitivity, time between load cycles, stress state during loading, AE source mechanism, test environment, and the applied stress relative to the ultimate strength of the article under test (stress ratio) can all affect the Felicity ratio. Composite materials and components which have rate dependent properties, such as fiber-reinforced composites with plastic matrices, will be affected to a greater extent.