

INTERNATIONAL STANDARD

NORME INTERNATIONALE

Measurement of the average viscometric degree of polymerization of new and aged cellulosic electrically insulating materials

(<https://standards.iteh.ai>)

Mesure du degré de polymérisation moyen viscosimétrique des matériaux isolants cellulosiques neufs et vieillis à usage électrique

IEC 60450:2004

<https://standards.iteh.ai/catalog/standards/iec/117b568e-22c0-4e28-b602-e80cbf7b7098/iec-60450-2004>



THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2007 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de l'IEC ou du Comité national de l'IEC du pays du demandeur. Si vous avez des questions sur le copyright de l'IEC ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de l'IEC de votre pays de résidence.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
Fax: +41 22 919 03 00
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

IEC Catalogue - webstore.iec.ch/catalogue

The stand-alone application for consulting the entire bibliographical information on IEC International Standards, Technical Specifications, Technical Reports and other documents. Available for PC, Mac OS, Android Tablets and iPad.

IEC publications search - www.iec.ch/searchpub

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and also once a month by email.

Electropedia - www.electropedia.org

The world's leading online dictionary of electronic and electrical terms containing 20 000 terms and definitions in English and French, with equivalent terms in 15 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Glossary - std.iec.ch/glossary

65 000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: csc@iec.ch.

A propos de l'IEC

La Commission Electrotechnique Internationale (IEC) est la première organisation mondiale qui élabore et publie des Normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications IEC

Le contenu technique des publications IEC est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

Catalogue IEC - webstore.iec.ch/catalogue

Application autonome pour consulter tous les renseignements bibliographiques sur les Normes internationales, Spécifications techniques, Rapports techniques et autres documents de l'IEC. Disponible pour PC, Mac OS, tablettes Android et iPad.

Recherche de publications IEC - www.iec.ch/searchpub

La recherche avancée permet de trouver des publications IEC en utilisant différents critères (numéro de référence, texte, comité d'études,...). Elle donne aussi des informations sur les projets et les publications remplacées ou retirées.

IEC Just Published - webstore.iec.ch/justpublished

Restez informé sur les nouvelles publications IEC. Just Published détaille les nouvelles publications parues. Disponible en ligne et aussi une fois par mois par email.

Electropedia - www.electropedia.org

Le premier dictionnaire en ligne de termes électroniques et électriques. Il contient 20 000 termes et définitions en anglais et en français, ainsi que les termes équivalents dans 15 langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International (IEV) en ligne.

Glossaire IEC - std.iec.ch/glossary

65 000 entrées terminologiques électrotechniques, en anglais et en français, extraites des articles Termes et Définitions des publications IEC parues depuis 2002. Plus certaines entrées antérieures extraites des publications des CE 37, 77, 86 et CISPR de l'IEC.

Service Clients - webstore.iec.ch/csc

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions contactez-nous: csc@iec.ch.



IEC 60450

Edition 2.1 2007-07
CONSOLIDATED VERSION

INTERNATIONAL STANDARD

NORME INTERNATIONALE

Measurement of the average viscometric degree of polymerization of new and aged cellulosic electrically insulating materials

Mesure du degré de polymérisation moyen viscosimétrique des matériaux isolants cellulosiques neufs et vieillis à usage électrique

IEC 60450:2004

<https://standards.iteh.ai/catalog/standards/iec/117b568e-22c0-4e28-b602-e80cbf7b7098/iec-60450-2004>

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

COMMISSION
ELECTROTECHNIQUE
INTERNATIONALE

ICS 17.220.99; 29.035.01

ISBN 2-8318-9234-1

**Warning! Make sure that you obtained this publication from an authorized distributor.
Attention! Veuillez vous assurer que vous avez obtenu cette publication via un distributeur agréé.**

CONTENTS

FOREWORD.....	3
INTRODUCTION.....	5
1 Scope.....	6
2 Normative references	6
3 Terms, definitions and symbols	6
3.1 Terms and definitions	6
3.2 Symbols	7
4 Principle	8
5 Apparatus and reagents	8
6 Specimens	9
6.1 Preparation of specimens	9
7 Experimental procedure.....	10
7.1 Measurement of water content of paper.....	10
7.2 Determination of viscosity	10
8 Test report.....	16
Annex A (normative) Cuen solution	17
Annex B (normative) Preparation of Cuen solution	18
Annex C (normative) Procedure for the verification of the ratio $\frac{c_{En}}{c_{Cu}}$ of the Cuen solution.....	21
Annex D (informative) Numerical values of the product $[\nu] \cdot c$ as a function of ν_s according to Martin's formula	22
Bibliography.....	23
Table 1 – Symbols	7
Table 2 – \overline{DP}_v values of specimen	10
Table D.1 – $[\nu] \cdot c$ as a function of ν_s ($k = 0,14$).....	22
Figure 1 – Chemical structure of cellulose	6
Figure 2 – Ubbelohde viscometer tube.....	14

INTERNATIONAL ELECTROTECHNICAL COMMISSION

**MEASUREMENT OF THE AVERAGE VISCOMETRIC DEGREE OF
POLYMERIZATION OF NEW AND AGED CELLULOSIC ELECTRICALLY
INSULATING MATERIALS**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC provides no marking procedure to indicate its approval and cannot be rendered responsible for any equipment declared to be in conformity with an IEC Publication.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

This consolidated version of the official IEC Standard and its amendment has been prepared for user convenience.

IEC 60450 edition 2.1 contains the second edition (2004) [documents 15E/229/FDIS and 15E/235/RVD] and its amendment 1 (2007) [documents 112/49/CDV and 112/66/RVC].

A vertical line in the margin shows where the base publication has been modified by amendment 1.

International Standard IEC 60450 has been prepared by subcommittee 15E: Methods of test, of IEC technical committee 15: Insulating materials.

This second edition cancels and replaces the first edition, published in 1974, and constitutes a technical revision. Experience has indicated the need for improved description of the experimental method. It describes a revised procedure that overcomes the limitations of the first edition.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 3.

The committee has decided that the contents of the base publication and its amendments will remain unchanged until the maintenance result date indicated on the IEC web site under "<http://webstore.iec.ch>" in the data related to the specific publication. At this date, the publication will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[IEC 60450:2004](#)

<https://standards.iteh.ai/catalog/standards/iec/117b568e-22c0-4e28-b602-e80cbf7b7098/iec-60450-2004>

INTRODUCTION

Experience has indicated the need for an improved description of the experimental method for the reproducible determination of the average viscometric degree of polymerization of new and aged cellulosic electrically insulating material.

The major error appears to arise from oxidative degradation occurring during processing and effluxing. Other significant factors include the need to ensure that all of the material is dissolved and used, as well as the effect of the speed of effluxing.

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[IEC 60450:2004](#)

<https://standards.iteh.ai/catalog/standards/iec/117b568e-22c0-4e28-b602-e80cbf7b7098/iec-60450-2004>

MEASUREMENT OF THE AVERAGE VISCOMETRIC DEGREE OF POLYMERIZATION OF NEW AND AGED CELLULOSIC ELECTRICALLY INSULATING MATERIALS

1 Scope

This International standard describes a standardized method for the determination of the average viscometric degree of polymerization (\overline{DP}_v) of new and aged cellulosic electrically insulating materials. It may be applied to all cellulosic insulating materials such as those used in transformer, cable or capacitor manufacturing.

The methods described can also be used for the determination of the intrinsic viscosity of solutions of chemically modified kraft papers, provided that these dissolve completely in the selected solvent.

Caution should be taken if the method is applied to loaded kraft papers.

NOTE Within a sample of material, all the cellulose molecules do not have the same degree of polymerization so that the mean value measured by viscometric methods is not necessarily the same as that which may be obtained by, for instance, osmotic or ultra centrifuging methods.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60814, *Insulating liquids – Oil-impregnated paper and pressboard – Determination of water by automatic coulometric Karl Fischer titration*

ISO 287, *Paper and board – Determination of moisture content – Oven-drying method*

ISO 3105, *Glass capillary kinematic viscometers – Specifications and operating instructions*

3 Terms, definitions and symbols

For the purposes of this document, the following terms, definitions and symbols apply.

3.1 Terms and definitions

3.1.1

degree of polymerization of a cellulose molecule

number of anhydrous- β -glucose monomers, $C_6H_{10}O_5$, in the cellulose molecule

NOTE Figure 1 shows the chemical structure of cellulose.

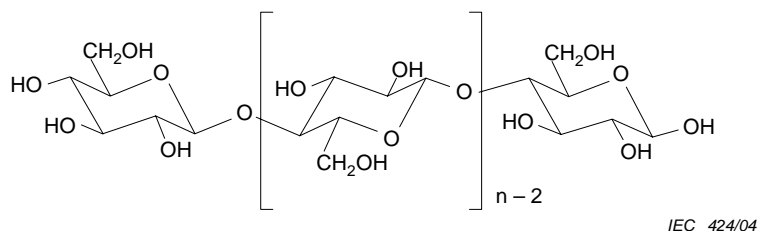


Figure 1 – Chemical structure of cellulose

3.1.2**Cuen**

1 mol/l aqueous solution of bis(ethylenediamine)copper(II) hydroxide
 $\text{Cu}(\text{H}_2\text{NCH}_2\text{CH}_2\text{NH}_2)_2(\text{OH})_2$. [CAS 14552-35-3]¹

NOTE In some countries the abbreviation CED is used for bis(ethylenediamine)copper(II) hydroxide.

3.1.3**paper**

cellulosic electrically insulating material, such as paper, presspaper, pressboard and components made thereof

NOTE In the present document such paper is termed "paper".

3.2 Symbols

Symbols used in this standard are shown in Table 1.

Table 1 – Symbols

Symbol	Definition
α	Mark Houwink constant of the cellulose monomer
c_{Cu}	Molarity of copper in Cuen solution
c_{En}	Molarity of ethylenediamine in Cuen solution
C_0, C_1 and C_2	Constants for viscometer tubes 0, 1 and 2 respectively
c	Concentration of solution
\overline{DP}_v	Average viscometric degree of polymerization
ν	Kinematic viscosity of solution
ν_0	Kinematic viscosity of solvent
K	Mark Houwink characteristic constant of the polymer/solvent system
k	Constant in Martin's formula
m_{D}	Mass of dry paper
m_{T}	Mass of swollen paper in tared vessel
$m_{\text{H}_2\text{O}}$	Mass of added water
$\rho_{\text{H}_2\text{O}}$	Density of water
$\nu_{\text{H}_2\text{O}}$	Volume of added water
ν_{Cu}	Volume of added Cuen
$[V]$	Intrinsic viscosity
ν_s	Specific viscosity
t_{1A}, t_{1B}	Efflux time for tests A and B on dissolved specimen 1
t_{2A}, t_{2B}	Efflux time for tests A and B on dissolved specimen 2
t_{0A}, t_{0B}	Efflux time for tests A and B on pure solvent
t_0	Efflux time for diluted Cuen solvent (50 % Cuen and 50 % water)
t_s	Efflux time for Cuen dissolved specimen

¹ Chemical Abstracts Service (CAS) Registry numbers®

4 Principle

The specific viscosity ν_s of a solution of the paper in Cuen is determined. From this result the intrinsic viscosity $[\nu]$ of the solution is deduced, and from this the degree of polymerization is calculated.

NOTE Solutions of cellulose are non-Newtonian fluids. Their viscosity decreases as the flow velocity increases (sometimes known as "structural viscosity"). Although the viscosity of dilute solutions varies only slightly with the gradient of the velocity modulus, the use of conditions outside those specified in this standard may result in unacceptable errors.

Specific viscosity ν_s is defined by

$$\nu_s = \frac{\text{viscosity of paper solution} - \text{viscosity of solvent}}{\text{viscosity of solvent}} \quad (1)$$

Intrinsic viscosity $[\nu]$ is defined by

$$[\nu] = \lim_{c \rightarrow 0} \left[\frac{\nu_s}{c} \right] \quad (2)$$

where c is the concentration of the solution.

The average viscometric degree of polymerization \overline{DP}_v (the ratio of the mean molecular mass indicated viscometrically to the molecular mass of the monomeric unit) is related to the intrinsic viscosity $[\nu]$ by the equation:

$$[\nu] = K \cdot \overline{DP}_v^\alpha \quad (3)$$

K and α being characteristic Mark Houwink coefficients of the polymer-solvent system (paper/Cuen) and of the monomer respectively.

The intrinsic viscosity $[\nu]$ is calculated from the specific viscosity ν_s and the concentration c by Martin's empirical formula:

$$\nu_s = [\nu] \cdot c \cdot 10^{k[\nu] \cdot c} \quad (4)$$

where k is Martin's constant. For kraft papers $k = 0,14$.

5 Apparatus and reagents

NOTE 1 Apparatus and reagents for the preparation of Cuen are given separately in Annexes A and B.

During the analysis, unless otherwise specified, use only reagents of recognized analytical grade and only distilled /de-ionized water or equivalent quality.

A glass fronted, thermostatically controlled bath, suitable for the immersion of the viscometer tubes, capable of maintaining a temperature of 20 °C to within $\pm 0,1$ K and fitted with appropriate means for illuminating the tubes. It shall be fitted with a means of displaying the temperature to within an accuracy of $\pm 0,05$ K.

NOTE 2 To obtain the required degree of temperature stability, it may be necessary to use a refrigeration unit in addition to the bath heater.

Calibrated capillary type viscometer tubes according to ISO 3105 with a capillary constant of 0,005 or 0,01. Non calibrated tubes can be used as long as the viscosities of the Cuen solvent and solution of paper in Cuen are measured in the same tube.

A timer/stopwatch capable of measuring to within an accuracy of $\pm 0,1$ s.

Suitable blender or grinder to “activate” the paper sample to allow dissolution.

Suitable vials (typically 25 ml to 50 ml) with lids (not paper) that make an effective seal for the preparation of paper/Cuen solution. Alternative glass containers can be used. However, these shall be sealed during dissolution to minimize oxidative degradation of the Cuen.

Cuen (see Annex A).

Distilled or de-ionized water.

Low oxygen content nitrogen supply (minimum 99,9 % nitrogen).

Acetone minimum 99,0 % pure.

Pentane or hexane minimum 99,0 % .

20 % aqueous nitric acid.

Vented drying oven thermostatically controlled to $105\text{ °C} \pm 2\text{ K}$.

Analytical balance capable of weighing 20 g to within $\pm 0,1$ mg.

Soxhlet extractor.

Pipette to deliver $\pm 0,1$ ml.

Mechanical shaker capable of holding the glass vials used to prepare the paper/Cuen solutions or a magnetic stirrer can be used to dissolve the paper/Cuen solution.

6 Specimens

6.1 Preparation of specimens

The paper under evaluation shall only be handled with gloves or forceps. It shall not be touched by hand.

Pressboard with a thickness greater than 1 mm, shall be split into layers of less than 1 mm.

The samples shall be cut into pieces sufficiently small to facilitate the subsequent processes. For very thin paper, the material may be cut into small pieces using scissors.

6.1.1 Impregnated papers

Impregnated papers shall be degreased before weighing and absorbing solution.

Wash a sufficient amount of the paper under evaluation so as to give a degreased mass of approximately 3 g in a Soxhlet using pentane or hexane for a minimum of five washings, or by rinsing in five portions of fresh pentane or hexane in an appropriate glass vessel. Allow the degreased material to dry and leave it exposed to the atmosphere until equilibrium with the atmospheric humidity is reached. Two portions of the paper are separated, one for use in the \overline{DP}_v determination and one for use in the moisture determination.

6.1.2 Non-impregnated papers

Take a sample having an approximate mass of 3 g and continue with the test procedures. Two portions of the paper are separated, one for use in the \overline{DP}_v determination and one for use in the moisture determination.

7 Experimental procedure

7.1 Measurement of water content of paper

Measure the water content according to ISO 287 or IEC 60814.

The water content shall be measured at the same time as the Cuen/paper solution is prepared.

7.2 Determination of viscosity

7.2.1 Number of test specimens

One specimen shall be used in a preliminary experiment to obtain data on which to base a valid test.

One specimen shall be used for each valid test, unless otherwise specified. If $[\eta] \cdot c$ of the preliminary experiment is outside of the range 0,5 to 1,5, two test specimens shall be used.

7.2.2 Concentration of the solution

The concentration of the solution to be used is dependent upon the expected \overline{DP}_v value as given in the following table.

Table 2 – \overline{DP}_v values of specimen

Specimen condition	Expected \overline{DP}_v	Approximate resulting concentration g/dl or %
New	1 000 to 2 000	0,05 to 0,15
Good	650 to 1 000	0,08 to 0,25
Average	350 to 650	0,15 to 0,45
Aged	< 350	0,25 to 0,80

NOTE The purpose of this operation is to achieve a fixed value of the product's intrinsic viscosity and concentration which is in the range $0,5 \leq [\eta] \cdot c \leq 1,5$. The higher the product of $[\eta] \cdot c$ the more accurate its precision.

7.2.3 Fibre separation

The cellulose fibres need to be separated in order to facilitate dissolution in Cuen. Two techniques are described as follows.

7.2.3.1 Dry fluffing

Fluff the material in a suitable blender or grinder. Ensure enough sample remains after fluffing as some sample may be lost during the process. The temperature rise during fluffing must not cause any detrimental effect to the specimen.

The fluffed sample is left to acclimatize with the atmospheric humidity before determining the water content.

Weigh the necessary amount of sample to the nearest 0,1 mg according to Table 2 and place it in a suitable vessel for dissolution. Calculate the mass of dry paper as m_D .

Add water and allow the fibres to disperse.

7.2.3.2 Wet mulching

Weigh the necessary amount of sample to the nearest 0,1 mg and place in the blender cup with sufficient distilled/de-ionized water to cover it. Mulch the paper by operating the blender at approximately 18 000 r/min for about 30 s or until the fibres are well separated. After mulching, remove the excess water by either centrifuging or using a Grade 3 sintered glass filter.

Place the swollen paper in a tared vial and weigh it to within $\pm 0,1$ mg (m_T). Calculate the total mass of water (i.e. original mass of water plus the mass of water remaining after mulching) by subtracting the dry paper mass (m_D) and the tare mass from m_T .

Calculate the quantity of water required to make the total water content up to 10,000 g. Selecting this amount to within $\pm 0,5$ mg, use a sufficient amount of this water to rinse any residual paper out of the centrifuge/filter into the vial and then place the remainder of the water into the vial. Alternatively, make up to 10,000 g, then weigh to within $\pm 0,5$ mg and calculate the concentration.

7.2.4 Dissolution of specimen

Before use, the Cuen solution sample shall be inspected, refurbished and verified as follows:

- ensure that the solution contains no precipitate by filtering or decanting;
- using the method described in Annex C, verify that the ratio $\frac{c_{En}}{c_{Cu}} = 2,0 \pm 0,1$
- in the event of non-conformance, reject the solution and prepare a new sample.

Transfer into the same vial the same volume ($\pm 0,1$ ml, using a pipette) of Cuen as the quantity of water already added to the cellulose fibres.

If there is some contact between the solution and the atmospheric air in the vial, flush the vial with nitrogen and shake by hand to ensure good mixing of the components. Flush the vial again with nitrogen and seal it to ensure a low oxygen environment. Preferably the vial should be flushed with nitrogen throughout the whole time of dissolution.

NOTE 1 The solution is placed in a nitrogen environment and sealed in the vial because the alkaline solvent is susceptible to oxidative degradation.

Mechanically shake or stir the specimen until dissolution is complete.

NOTE 2 The time taken is dependent upon the type of paper and the extent of degradation.

- a) For heavily aged papers ($\overline{DP}_v < 350$) a shaking time of 1 h to 2 h is usually adequate.
- b) For most papers ($\overline{DP}_v > 350$) shaking for a period of 16 h (overnight) usually ensures complete dissolution.
- c) Some types of new or nearly new papers do not dissolve easily at room temperature. The dissolution rate may be increased by using a magnetic stirrer to stir the specimen at 4 °C, in a refrigerator overnight. The use of a few glass balls can also aid the dispersion of the cellulose fibres.

When testing heavily degraded papers ($\overline{DP}_v < 150$) they should be tested immediately after dissolution.

7.2.5 Determination of the viscosity

7.2.5.1 Selection and filling of the viscometer tube

Select a viscometer tube and support it in a constant temperature bath at 20 °C ± 0,1 K.

Ensure that the viscometer tube is dry, dust free and flushed thoroughly with nitrogen.

Fill the viscometer according to the manufacturer's instructions. Figure 2 gives an example of a viscometer.

During the filling and the following measurement procedure, visually observe the solution to determine the presence of any undissolved matter. In the event of finding undissolved matter, reject the solution and repeat the experiment.

Wait for 5 min to 10 min before the first measurement of the viscosity, until the solution has reached its temperature equilibrium.

7.2.5.2 Measurement procedure

An Ubbelohde viscometer is used as an example (see Figure 2). For other viscometers, see ISO 3105 as well as the manufacturer's instructions.

Seal the ventilation tube (1) with a finger, a stopper or with plastic film and apply a vacuum to the capillary tube (2) until the lower reservoir (10), the working capillary (6), the timing bulb (5), and the upper reservoir (4) are filled.