

INTERNATIONAL STANDARD

ISO
4986

First edition
1992-06-01

Steel castings — Magnetic particle inspection

Pièces moulées en acier — Contrôle par magnétoscopie

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 4986:1992

<https://standards.iteh.ai/catalog/standards/sist/dd4356e7-47a8-4542-acf4-0ebba9275360/iso-4986-1992>



Reference number
ISO 4986:1992(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 4986 was prepared by Technical Committee ISO/TC 17, *Steel*, Sub-Committee SC 11, *Steel castings*.

Annexes A, B, C, D, E and F of this International Standard are for information only.

ITeH STANDARD PREVIEW
(standards.iteh.ai)
ISO 4986:1992
<https://standards.iteh.ai/catalog/standards/sis/4986/4986-47a8-4542-acf4-0ebba9275360/iso-4986-1992>

© ISO 1992

All rights reserved. No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Steel castings — Magnetic particle inspection

1 Scope

This International Standard specifies a test method for determining the acceptance limits of surface discontinuities¹⁾ detected by magnetic particle inspection, when such an inspection procedure has been contractually agreed upon at the request of the purchaser. It applies to all magnetic steel castings, whatever casting process is used.

A steel shall be considered to be magnetic if the magnetic induction is greater than 1 T for a magnetic field strength equal to 2,4 kA/m.

NOTE 1 It should be remembered that magnetic particle inspection, like all methods of non-destructive inspection, forms part of an overall or special assessment, which is defined in the contract.

2 Conditions of magnetic particle inspection

This International Standard only applies to the parts of castings and the percentage of castings to be inspected. The conditions shall be clearly indicated on the enquiry, in the request for prices and, more particularly, in the order sent to the supplier and accepted by him.

The manufacturing stage(s) at which the inspection is to be carried out shall be clearly defined by agreement between the parties.

For each part of the castings to be inspected, the following shall be indicated:

- the severity level (see table 1);
- the type of discontinuity indication (linear or non-linear) (see annex A).

The severity level and the type of discontinuity indication could differ according to the part of the casting to be inspected. (For surface condition, see 3.3.)

Unless otherwise specified, the severity level applies both to linear or aligned indications and to non-linear indications (clusters).

The test is considered to be satisfactory if the discontinuity indications obtained are of levels below or equal to those selected from table 1 and in accordance with clause 5.

If not, it shall be the responsibility of the founder to bring the casting into conformity with the specification defined above, by a method approved by the purchaser.

In general, there is no limit to the extent of discontinuities acceptable in a casting, provided that in the casting as a whole no area of 105 mm × 148 mm²⁾ contains discontinuities which exceed the severity level specified.

3 Method of inspection

3.1 Operating mode

The general principles of magnetic particle inspection are described in annex F.

3.2 Qualification of the operators

The tests shall be carried out and interpreted by technically competent operators whose qualifications shall be agreed upon at the time of the enquiry or order.

1) "Surface discontinuities" means discontinuities located in the metal which are open to the surface or come very close to it, so that the magnetic bridge is narrow.

2) Format ISO A6.

Table 1 — Severity levels for magnetic particle inspection

This table fixes the maximum surface area, in square millimetres, and/or the length, in millimetres, within the frame ISO A6 — 105 mm x 148 mm.

Severity levels		001	01	1	2	3	4	5
Means of observing indications		Magnifying glass or eye ¹⁾		Eye	Eye	Eye	Eye	Eye
Magnification		≤ 3		1	1	1	1	1
Length (L) of the smallest indication considered (mm)		0,3		1,5	2	3	5	10
Total area (mm ²)		—	—	10	35	70	200	500
Non-linear clusters (SM) ²⁾	Length of individual indication (mm)	1	1	2 ³⁾	4 ³⁾	6 ³⁾	10 ³⁾	16 ³⁾
Linear indications (LM) ⁴⁾ or aligned (AM) ⁵⁾	Indication type	Isolated or cumulative	Isolated or cumulative	Isolated	Isolated	Isolated	Isolated	Cumulative
	Wall thickness $\delta \leq 16$ mm	0	1	2	4	6	10	18
	Wall thickness 16 mm < $\delta \leq 50$ mm	0	1	3	6	9	18	27
	Wall thickness $\delta > 50$ mm	0	2	5	10	15	30	45
Examples of applications	Fabrication for aircraft or space craft: — lost wax casting — special applications		Other casting, according to surface and application					
1) The use of a magnifying instrument with a measuring graticule is permitted. 2) Non-linear indications (SM): $L < 3b$ where L is the length and b the larger indication. 3) At the most, two indications of the designated length are permitted. 4) Linear indication (LM): $L \geq 3b$ 5) Aligned indications (AM): linear, or non-linear, separated by a maximum of 2 mm and comprising at least three indications.								

3.3 Surface condition

The surface to be examined shall be clean, free from oil, grease, sand or scale or any other condition which could interfere with the correct interpretation of magnetic particle indications. It shall be sand or shot blasted (round or angular shot), ground or machined in line with the severity level demanded.

When a non-fluorescent inspection medium is used this shall be of a colour that will provide adequate contrast with the background of the surface being inspected. This can be obtained by the use of a coloured pigment inspection medium or the surface may be covered with a contrast paint.

The required surface condition of the areas of the casting to be inspected shall be subject to agreement at the time of enquiry or order (see annex B).

3.4 Conditions of examination

The inspection shall be carried out with the naked eye or at a maximum magnification of 3 × (see table 1).

4 Acceptance test

4.1 Discontinuity indications

Magnetic particle inspection is a means of non-destructive inspection which allows the detection of surface discontinuities which cannot normally be observed by visual examination. The discontinuity indications are linear³⁾ or aligned⁴⁾, or non-linear (clusters). The discontinuities listed in annex A may correspond to the different types of magnetic particle inspection.

Detection of the discontinuities is connected with the direction of the magnetic flux in the casting. It is therefore essential to carry out a control in two directions which are essentially perpendicular, unless otherwise specified in the order, to make sure that the discontinuity runs counter to the flux in at least one direction.

4.2 Severity levels

Seven severity levels are recognized in accordance with table 1. Depending on the severity level required, it is necessary to carry out the test on a surface corresponding to a given degree of finish (see annex B):

— precision;

3) The largest dimension L (length) is at least three times the smallest b (width) ($L \geq 3b$). (See table 1.)

4) See note 5 of table 1.

— smooth;

— rough.

The maximum permissible length for linear or aligned indications varies with the casting section thickness δ . Three thickness categories are specified:

— $\delta \leq 16$ mm

— $16 \text{ mm} < \delta \leq 50$ mm

— $\delta > 50$ mm

Table 1 shows the minimum length below which the indications are not to be taken into consideration in the respective category.

Examples of linear and non-linear indications, given to a scale of 1, are shown in annex C. These have been established in accordance with table 1 and in compliance with the procedure given in annex F.

5 Interpretation of results

In order to classify discontinuity indications obtained by magnetic particle inspection of the casting, it is necessary to place a frame measuring 105 mm × 148 mm positioned in the most unfavourable location relative to the indications being evaluated. The test is considered satisfactory if the indications being evaluated are less severe or equal to those specified in the order.

Indications are equivalent when they show the same clusters of non-linear indications or the same length of linear indications of similar appearance.

The types of indications are given only as a guide and the classification by severity level is based on the length of the discontinuities, in accordance with table 1.

Aligned and non-aligned indications shall be taken into account for the calculation of the cumulative length.

6 Order

The enquiry and/or order shall specify the following points:

- the parts of castings and percentage of castings to be inspected (see clause 2);
- the manufacturing stage(s) at which the inspection is to be carried out, as agreed between the parties concerned (see clause 2);

- c) the surface condition for the areas to be inspected (see 3.3);
- d) the type of discontinuity indication and the severity level for each part of casting to be inspected (see clause 2 and 4.2);
- e) the qualification of the operators carrying out the inspection (see 3.2);
- f) if the inspection is not to be carried out in two perpendicular directions (see 4.1);
- g) whether or not the casting should be demagnetized after the inspection has been carried out (see F.6.7).

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 4986:1992

<https://standards.iteh.ai/catalog/standards/sist/dd4356e7-47a8-4542-acf4-0ebba9275360/iso-4986-1992>

Annex A (informative)

Nature of discontinuities — Types of indication

Nature of discontinuities	Nomenclature	Indications obtained by passage of the magnetic flux in the optimum direction	Type	Definition
Blow-holes Pitting	A	Non-linear clusters Aligned	SM AM	$L < 3b$ $d < 2$
Sand spots Inclusions	B	Non-linear clusters Aligned	SM AM	$L < 3b$ $d < 2$
Shrinkage	C	Linear Non-linear clusters Aligned	LM SM AM	$L \geq 3b$ $L < 3b$ $d < 2$
Tears	D	Linear Aligned	LM AM	$L \geq 3b$ $d < 2$
Cracks	E	Linear Aligned	LM AM	$L \geq 3b$ $d < 2$
Core supports	F	Linear Non-linear clusters Aligned	LM SM AM	$L \geq 3b$ $L < 3b$ $d < 2$
Chills	G	Linear Non-linear clusters Aligned	LM SM AM	$L \geq 3b$ $L < 3b$ $d < 2$
Cold shuts	H	Linear Aligned	LM AM	$L \geq 3b$ $d < 2$
<i>L</i> = length of indication <i>b</i> = width of indication <i>d</i> = distance, in millimetres, between two indications, edge-to-edge				

Annex B
(informative)

Equivalence of surface conditions (as a guide)

Surface condition	Precision						Smooth				Rough	
Roughness R_a (μm) ¹⁾	1,6		3,2		6,3		12,5		25		> 25	
Surface preparation	Very smooth grinding Smooth precision	Very smooth shot blasting	Very smooth grinding Very smooth machining Precision	Smooth shot blasting Investment cast	Smooth grinding	Smooth shot blasting Precision cast (ceramic)	Grinding Smooth machining	Smooth shot blasting Precision cast (shell moulded, ceramic)	Grinding Rough machining	Medium shot blasting Careful moulding	Rough preparation	Sand cast
BNIF 341-02	—	—	—	—	1S2	—	2S2 3S2	1S1	4S2 5S2	2S1 3S1	1S3 2S3 5S3 6S3	4S1 5S1 6S1
ACI	—	—	—	—	—	SIS1	—	SIS3	—	SIS4	—	—
CSC (Cast Surface Comparator)	—	—	—	C30	—	C40	—	C70	—	C90	—	—
SCRATA	—	—	—	—	—	—	—	A1	H1 H2	A2 A3	G2 G3	A4 C3 D3
LCA 2 Grinding	15	—	16	—	17	—	18	—	19	—	—	—
LCA 3 Shot blasting	—	N7 (15)	—	N8 (16)	—	N9 (17)	—	N10 (18)	—	N11 (19)	—	—

1) The roughness values R_a indicated in this table are those given by the manufacturers of small plates.
S1: As cast or shot blasted
S2: Ground

Annex C
(informative)

Examples of severity levels

C.1 Non-linear indications

Sketches of non-linear indications (SM 1 to SM 5) are given in C.1.1 to C.1.5.

C.1.1 Severity level SM 1




C.1.2 Severity level SM 2



[ISO 4986:1992](https://standards.iteh.ai/catalog/standards/sist/dd4356e7-47a8-4542-acf4-0ebba9275360/iso-4986-1992)

<https://standards.iteh.ai/catalog/standards/sist/dd4356e7-47a8-4542-acf4-0ebba9275360/iso-4986-1992>

C.1.3 Severity level SM 3

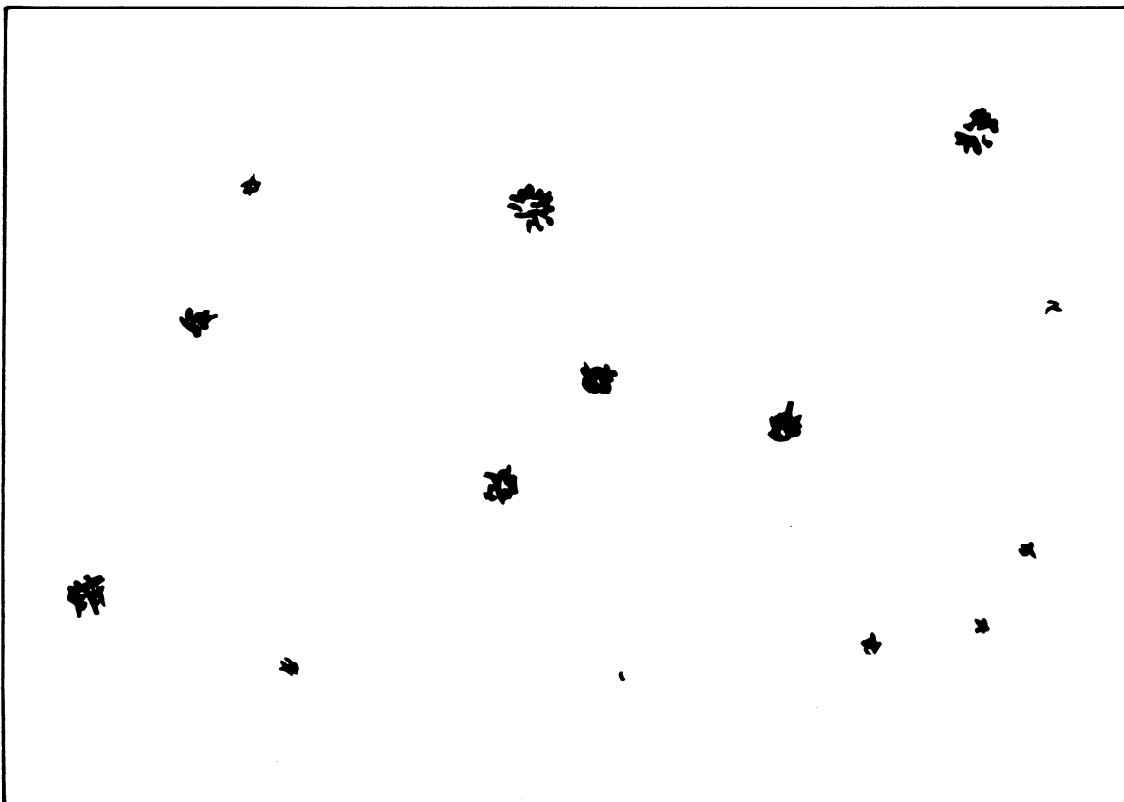

C.1.4 Severity level SM 4



ISO 4986:1992

C.1.5 Severity level SM 5 <https://standards.iteh.ai/catalog/standards/sist/dd4356e7-47a8-4542-acf4-0ebba9275360/iso-4986-1992>

