

INTERNATIONAL STANDARD

**ISO
4996**

Second edition
1991-04-15

Hot-rolled steel sheet of high yield stress structural quality

iTeh STANDARD PREVIEW
*Tôles laminées à chaud en acier de construction à haute limite
d'élasticité*
(standards.iteh.ai)

ISO 4996:1991

<https://standards.iteh.ai/catalog/standards/sist/63ac8cb0-2705-425a-a48d-8cfd5b92de17/iso-4996-1991>



Reference number
ISO 4996:1991(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 4996 was prepared by Technical Committee ISO/TC 17, *Steel*.

This second edition cancels and replaces the first edition (ISO 4996:1978), table 3 of which has been technically revised and the annex deleted.

© ISO 1991

All rights reserved. No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Hot-rolled steel sheet of high yield stress structural quality

1 Scope

1.1 This International Standard applies to hot-rolled steel sheet of high yield stress structural quality in the grades and classes listed in table 1 and table 2, with the use of microalloying elements. The product is intended for structural purposes where particular mechanical properties are required. It is generally used in the delivered condition and is intended for bolted, riveted or welded structures.

Because of the combination of higher strength and microalloy composition, it is possible to obtain savings in mass along with better formability and weldability as compared with steel sheet without microalloying elements. The product is produced on a wide strip mill, not a plate mill.

1.2 This product is commonly produced in thicknesses from 1,6 mm to 6 mm and widths of 600 mm and over, in coils and cut lengths.

1.3 Hot-rolled sheet less than 600 mm wide may be slit from wide sheet and will be considered as sheet.

NOTE 1 Hot-rolled sheet up to but not including 3 mm in thickness is commonly known as "sheet". Hot-rolled sheet 3 mm and over in thickness is commonly known as either "sheet" or "plate".

1.4 This International Standard does not cover steels intended for boilers or pressure vessels, or steels designated as commercial quality or drawing qualities (covered in ISO 3573¹⁾) or steels to be re-rolled to cold-reduced products, or steels designated as weathering steels, having increased atmospheric corrosion resistance, or steels having improved formability properties compared with those included in this document.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 6892:1984, *Metallic materials — Tensile testing*.

ISO 7438:1985, *Metallic materials — Bend test*.

3 Definitions

For the purposes of this International Standard, the following definitions apply.

3.1 microalloying elements: Elements, such as niobium, vanadium, titanium, etc., added singly or in combination to obtain higher strength levels combined with better formability, weldability, and toughness as compared to non-alloyed steel produced to equivalent strength levels.

3.2 hot-rolled steel sheet: A product obtained by rolling heated steel through a continuous-type or reversing-type wide strip mill to the required sheet thickness. The product has a surface covered with oxide or scale resulting from the hot rolling operation.

3.3 hot-rolled descaled steel sheet: Hot-rolled steel sheet from which oxide or scale has been removed, commonly by pickling in an acid solution. Descaling may also be performed by mechanical means such as grit blasting. Some change in properties may result from descaling.

1) ISO 3573:1986, *Hot-rolled carbon steel sheet of commercial and drawing qualities*.

As a deterrent to rusting, a coating of oil is usually applied to hot-rolled descaled steel sheet, but sheet may be furnished not oiled if required. The oil is not intended as a forming lubricant and shall be easily removable with degreasing chemicals. On request, the manufacturer shall advise the purchaser which type of oil has been used.

3.4 mill edge: A normal side edge produced in hot rolling. Mill edges may contain some irregularities such as cracked or torn edges or thin (feathered) edges.

3.5 edge trimmed: A normal edge obtained by shearing, slitting or trimming a mill edge product.

4 Conditions of manufacture

4.1 Steelmaking

Unless otherwise agreed by the interested parties, the processes used in making the steel and in manufacturing hot-rolled sheet are left to the discretion of the manufacturer. On request, the purchaser shall be informed of the steelmaking process being used.

4.2 Chemical composition

The chemical composition (cast analysis) shall not exceed the values given in table 1.

Table 1 — Chemical composition (cast analysis), %

Grade	Class	Method of deoxidation	C	Mn	Si	P	S
			max.	max.	max.	max.	max.
HS355	C	NE	0,20	1,60	0,50	0,040	0,040
	D	CS	0,20	1,60	0,50	0,035	0,035
HS390	C	NE	0,20	1,60	0,50	0,040	0,040
	D	CS	0,20	1,60	0,50	0,035	0,035
HS420	C	NE	0,20	1,70	0,50	0,040	0,040
	D	CS	0,20	1,70	0,50	0,035	0,035
HS460	C	NE	0,20	1,70	0,50	0,040	0,040
	D	CS	0,20	1,70	0,50	0,035	0,035
HS490	C	NE	0,22	1,70	0,50	0,040	0,040
	D	CS	0,22	1,70	0,50	0,035	0,035

NOTES

1 NE = Non-rimming

CS = Special killed

2 The nitrogen content is controlled; normally it should not exceed 0,009 % for NE steel or 0,015 % for CS steel.

3 Each grade includes at least one microalloying element such as vanadium, titanium, niobium, etc.

4 Class C steels are to be used in cases where, owing to conditions and the general design of the structure, some resistance to brittle fracture is necessary.

5 Class D steels are to be used in cases where, owing to loading conditions and the general design of the structure, a high resistance to brittle fracture is necessary.

4.3 Chemical analysis

4.3.1 Cast analysis

A cast analysis of each cast of steel shall be made by the manufacturer to determine the percentage of carbon, manganese, phosphorus and sulphur. On request, this analysis shall be reported to the purchaser or his representative.

4.3.2 Verification analysis

A verification analysis may be made by the purchaser to verify the specified analysis of the semi-finished or finished steel and shall take into consideration any normal heterogeneity. The sampling method and deviation limits shall be agreed

upon between manufacturer and purchaser at the time of ordering.

4.4 Weldability

This product is normally suitable for welding if appropriate welding conditions are selected. For undescaled steel, it may be necessary to remove the scale or oxide depending upon the welding method. As the carbon content increases above 0,15 %, spot welding becomes increasingly difficult.

4.5 Application

It is desirable that hot-rolled steel sheet be identified for fabrication by the name of the part or by the intended application, which shall be compatible with the grade and class specified.

Table 2 — Mechanical properties

Grade	R_o min. ¹⁾ N/mm ²		R_m min. (information only) N/mm ²	A min. % ²⁾				180° bend mandrel diameter ³⁾
	R_{oH}	R_{oL}		$e < 3$		$3 \leq e \leq 6$		
				$L_o = 50$ mm	$L_o = 80$ mm	$L_o = 5,65 \sqrt{S_o}$	$L_o = 50$ mm	
HS355	355	335	430	18	16	22	21	2a
HS390	390	370	460	16	14	20	19	2a
HS420	420	400	490	14	12	19	18	3a
HS460	460	440	530	12	10	17	16	3a
HS490	490	470	570	10	8	15	14	4a

R_{oH} = upper yield stress
 R_{oL} = lower yield stress
 R_m = tensile strength
 A = percentage elongation after fracture
 L_o = gauge length on test piece
 S_o = original cross-sectional area of gauge length
 a = thickness of bend test piece
 e = thickness of steel sheet, in millimetres
 1 N/mm² = 1 MPa

1) Either R_{oH} or R_{oL} shall be measured and either value shall meet the minimum requirement. The yield stress values can be measured by 0,5 % elongation proof stress (proof stress under load) or by 0,2 % offset when a definite yield phenomenon is not present.

2) For thicknesses up to 3 mm, use either $L_o = 50$ mm or $L_o = 80$ mm. For thicknesses from 3 mm to 6 mm, use either $L_o = 5,65 \sqrt{S_o}$ or $L_o = 50$ mm. In case of dispute, however, only the results obtained on a proportional test piece will be valid for material 3 mm and over in thickness.

3) The bend test is performed only when specified (see 7.2). The bend mandrel diameters in table 2 are for test pieces prepared for laboratory testing. Conditions during fabrication may be more severe and not simulate those during laboratory testing.

4.6 Mechanical properties

At the time that the steel is made available for shipment, the mechanical properties shall be as stated in table 2, when they are determined on test pieces obtained in accordance with the requirements of clause 7.

4.7 Surface condition

Oxide or scale on hot-rolled steel sheet is subject to variations in thickness, adherence and colour. Removal of the oxide or scale by pickling or blast cleaning may disclose surface imperfection not readily visible prior to this operation.

5 Dimensional tolerances

Dimensional tolerances applicable to hot-rolled steel sheet of high yield stress structural quality shall be as given in table 3A to table 10 inclusive.

6 Sampling

6.1 Tensile test

One representative sample for the tensile test required in table 2 shall be taken from each lot of sheet for shipment. A lot consists of 50 tonnes or less of sheet of the same grade and class rolled to the same thickness and condition.

6.2 Bend test (when specified)

One representative sample for the bend test shall be taken from each lot of sheet for shipment. A lot consists of all sheet of the same grade and class rolled to the same thickness and condition.

7 Mechanical property tests

7.1 Tensile test

The tensile test shall be carried out in accordance with ISO 6892. Transverse test pieces shall be taken midway between the centre and edge of the sheet as rolled.

7.2 Bend test (when specified)

The transverse bend test piece shall withstand being bent through 180°, in the direction as shown in figure 1, around an inside diameter as shown in table 2, without cracking on the outside of the bent portion. The bend test shall be carried out at ambient temperature and as specified in ISO 7438.

Small cracks on the edges of test pieces and cracks which require magnification to be visible shall be disregarded.

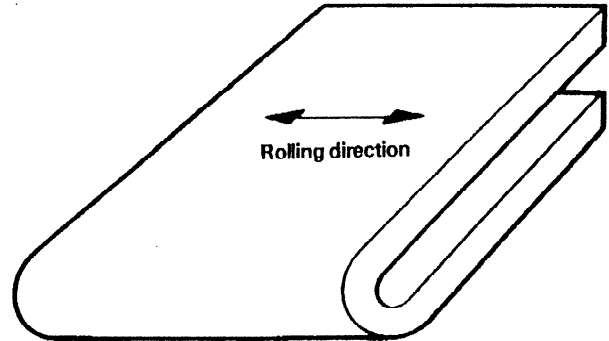


Figure 1 — Transverse bend test piece (after bending)

8 Retests

8.1 Machining and flaws

If any test piece shows defective machining or develops flaws, it shall be discarded and another test piece substituted.

8.2 Elongation

If the percentage elongation of any test piece is less than that specified in table 2 and if any part of the fracture is outside the middle half of the gauge length as scribed before the test, the test shall be discarded and a retest shall be carried out.

8.3 Additional tests

If a test does not give the specified results, two more tests shall be carried out at random on the same lot. Both retests shall conform to the requirements of this International Standard; otherwise, the lot may be rejected.

9 Resubmission

9.1 The manufacturer may resubmit for acceptance the products that have been rejected during earlier inspection because of unsatisfactory properties, after he has subjected them to a suitable treatment (selection, heat treatment) which, on request, will be indicated to the purchaser.

In this case, the tests shall be carried out as if they applied to a new batch.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 4996:1991
https://standards.iteh.ai/catalog/standards/sist/63ac8cb0-2705-425a-a48d-392de17/iso-4996-1991

9.2 The manufacturer has the right to present the rejected products to a new examination for compliance with the requirements for another grade or class.

10 Workmanship

The surface condition shall be that normally obtained in a hot-rolled or hot-rolled descaled product.

The steel sheet in cut lengths shall be free from amounts of laminations, surface flaws and other imperfections that are detrimental to subsequent appropriate processing.

Processing for shipment in coils does not afford the manufacturer the opportunity to observe readily or to remove defective portions as can be carried out on the cut length product.

11 Inspection and acceptance

11.1 While not usually required for products covered by this International Standard, when the purchaser specifies that inspection and tests for acceptance be observed prior to shipment from the manufacturer's works, the manufacturer shall afford the purchaser's inspector all reasonable facilities to determine that the steel is being furnished in accordance with this International Standard.

11.2 Steel that is reported to be defective after arrival at the user's works shall be set aside, properly and correctly identified and adequately protected. The manufacturer shall be notified in order that he may properly investigate.

12 Coil size

When hot-rolled steel sheet is ordered in coils, a minimum inside diameter (I.D.) or range of acceptable inside diameters shall be specified. In addition, the maximum outside diameter (O.D.) and the maximum acceptable coil mass shall be specified.

13 Marking

Unless otherwise stated, the following minimum requirements for identifying the steel shall be legibly stencilled on the top of each lift or shown on a tag attached to each coil or shipping unit:

- a) the manufacturer's name or identifying brand;
- b) the number of this International Standard;

- c) the grade and class designations;
- d) the order number;
- e) the product dimensions;
- f) the lot number;
- g) the mass.

14 Information to be supplied by the purchaser

To specify requirements adequately according to this International Standard, inquiries and orders shall include the following information:

- a) the number of this International Standard;
- b) the name, quality, grade and class of the material (for example, hot-rolled steel sheet, high yield stress structural quality, grade HS355 class C);
- c) the dimensions of the product and the quantity required;
- d) the application (name of part) if possible (see 4.5);
- e) whether pickling or descaling by grit or shot blasting is required (material so specified will be oiled unless ordered not oiled) (see 3.3);
- f) the type of edge (see 3.4 and 3.5);
- g) whether cropped ends are required;
- h) the report of the mechanical properties and/or the cast analysis, if required (see 4.6 and 4.3.1);
- i) limitations on masses and dimensions of individual coils and bundles, if applicable (see clause 12);
- j) inspection and tests for acceptance prior to shipment from the manufacturer's works, if required (see 11.1).

NOTE 2 A typical ordering description is as follows:

International Standard 4996, hot-rolled steel sheet, high yield stress structural quality, grade HS355 class D, 3 × 1200 × 2440 mm, 40 000 kg, for part No. 5432, bumper bracket, edge trimmed, furnish report of mechanical properties, maximum lift 4 000 kg.

Table 3A — Thickness tolerances for coils and cut lengths, in grades HS355, HS390 and HS420 (including descaled material)

Values in millimetres

Specified widths	Thickness tolerances ¹⁾ , over and under, for specified thicknesses					
	1,6 up to and including 2,0	over 2,0 up to and including 2,5	over 2,5 up to and including 3,0	over 3,0 up to and including 4,0	over 4,0 up to and including 5,0	over 5,0 up to and including 6,0
600 up to and including 1 200	0,19	0,20	0,22	0,24	0,26	0,29
Over 1 200 up to and including 1 500	0,21	0,23	0,24	0,26	0,29	0,31
Over 1 500 up to and including 1 800	0,23	0,25	0,26	0,29	0,31	0,32
Over 1 800	—	0,27	0,29	0,30	0,32	0,34
The values specified do not apply to the uncropped ends for a length <i>l</i> of a mill edge coil. Length <i>l</i> would be calculated using the formula Length <i>l</i> in metres = 90/Thickness in millimetres provided that the result was not greater than 20 m.						
1) Thickness is measured at any point on the sheet not less than 40 mm from a side edge for untrimmed material and not less than 25 mm from the edge for trimmed material.						

(standards.itech.ai)

Table 3B — Thickness tolerances for coils and cut lengths, in grades HS460 and HS490 (including descaled material)

<https://standards.itech.ai/catalog/standards/sist/63ac8cb0-2705-425a-a48d-8cf15b92de17/iso-4996-1991>

Values in millimetres

Specified widths	Thickness tolerances ¹⁾ , over and under, for specified thicknesses					
	1,6 up to and including 2,0	over 2,0 up to and including 2,5	over 2,5 up to and including 3,0	over 3,0 up to and including 4,0	over 4,0 up to and including 5,0	over 5,0 up to and including 6,0
600 up to and including 1 200	0,21	0,22	0,25	0,27	0,30	0,32
Over 1 200 up to and including 1 500	0,24	0,26	0,27	0,30	0,32	0,35
Over 1 500 up to and including 1 800	0,26	0,29	0,26	0,32	0,35	0,36
Over 1 800	—	0,31	0,32	0,34	0,36	0,39
The values specified do not apply to the uncropped ends for a length <i>l</i> of a mill edge coil. Length <i>l</i> would be calculated using the formula Length <i>l</i> in metres = 90/Thickness in millimetres provided that the result was not greater than 20 m.						
1) Thickness is measured at any point on the sheet not less than 40 mm from a side edge for untrimmed material and not less than 25 mm from the edge for trimmed material.						

Table 4 — Width tolerances for coils and cut lengths (including descaled material), mill edge

Values in millimetres

Specified widths	Tolerance ¹⁾
Up to and including 1 200	+30 0
Over 1 200 up to and including 1 500	+35 0
Over 1 500 up to and including 1 800	+40 0
Over 1 800	+50 0

1) The values specified do not apply to the uncropped ends for a length *l* of a mill edge coil.

Length *l* would be calculated using the formula

$$\text{Length } l \text{ in metres} = 90/\text{Thickness in millimetres}$$

provided that the result was not greater than 30 m.

Table 6 — Length tolerances for cut lengths (including descaled material), not resquared

Values in millimetres

Specified lengths	Tolerance
Up to and including 3 000	+20 0
Over 3 000 up to and including 6 000	+30 0
Over 6 000	+0,5 % × length 0


Table 5 — Width tolerances for coils and cut lengths (including descaled material), edge trimmed, not resquared

Values in millimetres

Specified widths	Tolerance
Up to and including 1 200	+8 0
Over 1 200 up to and including 1 500	+8 0
Over 1 500	+10 0

Table 7 — Camber tolerances for coils and cut lengths (including descaled material), not resquared

Form	Camber tolerance
Coils	25 mm in any 5 000 mm length
Cut lengths	0,5 % × length

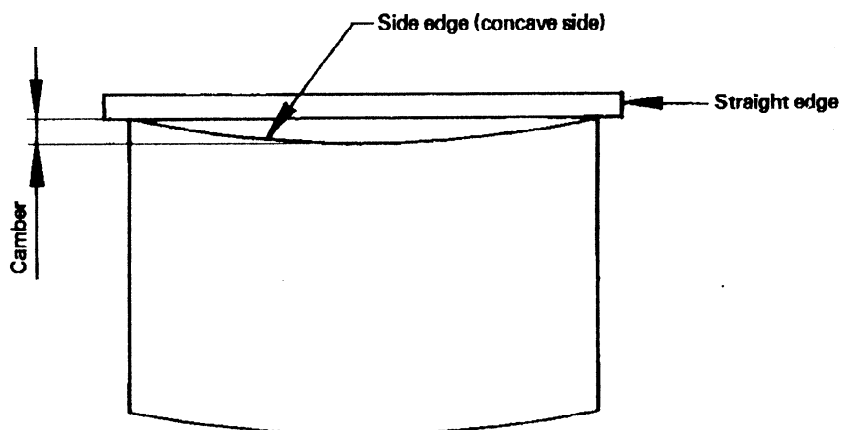

Camber is the greatest deviation of a side edge from a straight line, the measurement being taken on the concave side with a straight edge.

Figure 2 — Measurement of camber