

INTERNATIONAL STANDARD



Optical fibres –
Part 1-45: Measurement methods and test procedures – Mode field diameter

iTeh Standards
(<https://standards.iteh.ai>)

Document Preview

[IEC 60793-1-45:2024](https://standards.iteh.ai/catalog/standards/iec/46c4bdf0-df10-49c8-a629-100c7b73148f/iec-60793-1-45-2024)

<https://standards.iteh.ai/catalog/standards/iec/46c4bdf0-df10-49c8-a629-100c7b73148f/iec-60793-1-45-2024>





THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2024 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Secretariat
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, ...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

IEC Products & Services Portal - products.iec.ch

Discover our powerful search engine and read freely all the publications previews, graphical symbols and the glossary. With a subscription you will always have access to up to date content tailored to your needs.

Electropedia - www.electropedia.org

The world's leading online dictionary on electrotechnology, containing more than 22 500 terminological entries in English and French, with equivalent terms in 25 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

International
Standards
Document Preview
standards.iteh.ai

[IEC 60793-1-45:2024](https://standards.iteh.ai/catalog/standards/iec/46c4bdf0-df10-49c8-a629-100c7b73148f/iec-60793-1-45-2024)

<https://standards.iteh.ai/catalog/standards/iec/46c4bdf0-df10-49c8-a629-100c7b73148f/iec-60793-1-45-2024>



IEC 60793-1-45

Edition 3.0 2024-04
REDLINE VERSION

INTERNATIONAL STANDARD



Optical fibres –
Part 1-45: Measurement methods and test procedures – Mode field diameter

iTeh Standards
(<https://standards.itih.ai>)
Document Preview

[IEC 60793-1-45:2024](https://standards.itih.ai/catalog/standards/iec/46c4bdf0-df10-49c8-a629-100c7b73148f/iec-60793-1-45-2024)

<https://standards.itih.ai/catalog/standards/iec/46c4bdf0-df10-49c8-a629-100c7b73148f/iec-60793-1-45-2024>

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 33.180.10

ISBN 978-2-8322-8812-2

Warning! Make sure that you obtained this publication from an authorized distributor.

CONTENTS

FOREWORD.....	5
1 Scope.....	7
2 Normative references	7
3 Terms, definitions and abbreviated terms	7
3.1 Terms and definitions.....	7
3.2 Abbreviated terms.....	7
4 General consideration about mode field diameter	8
5 Reference test method	8
6 Apparatus.....	8
6.1 General.....	8
6.2 Light source	9
6.3 Input optics	9
6.4 Input positioner	9
6.5 Cladding mode stripper	9
6.6 High-order mode filter	9
6.7 Output positioner	9
6.8 Output optics	10
6.9 Detector.....	10
6.10 Computer.....	10
7 Sampling and samples.....	10
7.1 Sample length.....	10
7.2 Sample end face.....	10
8 Procedure.....	10
9 Calculations.....	10
9.1 Basic formulae.....	10
9.2 Method A – Direct far-field scan.....	10
9.3 Method B – Variable aperture in the far field	11
9.4 Method C – Near-field scan.....	12
10 Results	13
10.1 Information available with each measurement.....	13
10.2 Information available upon request	13
11 Specification information	13
Annex A (normative) Requirements specific to method A – Mode field diameter by direct far-field scan	14
A.1 Apparatus	14
A.1.1 General	14
A.1.2 Scanning detector assembly – Signal detection electronics	14
A.1.3 Computer.....	15
A.2 Procedure	15
A.3 Calculations	15
A.3.1 Determine folded power curve	15
A.3.2 Compute the top (T) and bottom (B) integrals of Formula (1)	15
A.3.3 Complete the calculation	16
A.4 Sample data	16
Annex B (normative) Requirements specific to method B – Mode field diameter by variable aperture in the far field	17

B.1	Apparatus	17
B.1.1	General	17
B.1.2	Output variable aperture assembly	17
B.1.3	Output optics system	18
B.1.4	Detector assembly and signal detection electronics	18
B.2	Procedure	18
B.3	Calculations	18
B.3.1	Determine complementary aperture function	18
B.3.2	Complete the integration	19
B.3.3	Complete the calculation	19
B.4	Sample data	19
Annex C (normative) Requirements specific to method C – Mode field diameter by near-field scan		20
C.1	Apparatus	20
C.1.1	General	20
C.1.2	Magnifying output optics	20
C.1.3	Scanning detector	21
C.1.4	Detection electronics	21
C.2	Procedure	21
C.3	Calculations	21
C.3.1	Calculate the centroid	21
C.3.2	Fold the intensity profile	22
C.3.3	Compute the integrals	22
C.3.4	Complete the calculation	23
C.4	Sample data	23
Annex D (normative) Requirements specific to method D – Mode field diameter by optical time domain reflectometer (OTDR)		24
D.1	General	24
D.2	Apparatus	24
D.2.1	OTDR	24
D.2.2	Optional auxiliary switches	24
D.2.3	Optional computer	25
D.2.4	Test sample	25
D.2.5	Reference sample	25
D.3	Procedure – Orientation and notation	25
D.4	Calculations	26
D.4.1	Reference fibre mode field diameter	26
D.4.2	Computation of the sample mode field diameter	26
D.4.3	Validation	27
Annex E (informative) Sample data sets and calculated values		29
E.1	General	29
E.2	Method A – Mode field diameter by direct far-field scan	29
E.3	Method B – Mode field diameter by variable aperture in the far field	30
E.4	Method C – Mode field diameter by near-field scan	30
Bibliography		31
Figure 1 – Transform relationships between measurement results		8
Figure A.1 – Far-field measurement set		14

Figure B.1 – Variable aperture by far-field measurement set.....	17
Figure C.1 – Near-field measurement set-ups.....	20
Figure D.1 – Optical switch arrangement	25
Figure D.2 – View from reference fibre A	26
Figure D.3 – View from reference fibre B	26
Figure D.4 – Validation example – Comparison of methods.....	27
Table 1 – Abbreviated terms	7
Table E.1 – Sample data, method A – Mode field diameter by direct far-field scan.....	29
Table E.2 – Sample data set, method B – Mode field diameter by variable aperture in the far field	30
Table E.3 – Sample data set, method C – Mode field diameter by near-field scan.....	30

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[IEC 60793-1-45:2024](#)

<https://standards.iteh.ai/catalog/standards/iec/46c4bdf0-df10-49c8-a629-100c7b73148f/iec-60793-1-45-2024>

INTERNATIONAL ELECTROTECHNICAL COMMISSION

OPTICAL FIBRES –

Part 1-45: Measurement methods and test procedures – Mode field diameter

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) IEC draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). IEC takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, IEC had not received notice of (a) patent(s), which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at <https://patents.iec.ch>. IEC shall not be held responsible for identifying any or all such patent rights.

This redline version of the official IEC Standard allows the user to identify the changes made to the previous edition IEC 60793-1-45:2017. A vertical bar appears in the margin wherever a change has been made. Additions are in green text, deletions are in strikethrough red text.

IEC 60793-1-45 has been prepared by subcommittee 86A: Fibres and cables, of IEC technical committee 86: Fibre optics. It is an International Standard.

This third edition cancels and replaces the second edition published in 2017. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) Modification of the minimum distance between the fibre end and the detector for the direct far field scan (Annex A).
- b) Generalization of the requirement for the minimum dynamic range for all fibre types (Annex A).

The text of this International Standard is based on the following documents:

Draft	Report on voting
86A/2300/CDV	86A/2366/RVC

Full information on the voting for its approval can be found in the report on voting indicated in the above table.

The language used for the development of this International Standard is English.

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at www.iec.ch/members_experts/refdocs. The main document types developed by IEC are described in greater detail at www.iec.ch/publications.

A list of all parts in the IEC 60793 series, published under the general title *Optical fibres*, can be found on the IEC website.

<https://standards.iteh.ai/catalog/standards/iec/46c4bdf0-df10-49c8-a629-100c7b73148f/iec-60793-1-45-2024>

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under webstore.iec.ch in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn, or
- revised.

IMPORTANT – The "colour inside" logo on the cover page of this document indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

OPTICAL FIBRES –

Part 1-45: Measurement methods and test procedures – Mode field diameter

1 Scope

This part of IEC 60793 establishes uniform requirements for measuring the mode field diameter (MFD) of single-mode optical fibre, thereby assisting in the inspection of fibres and cables for commercial purposes.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60793-1-40:~~2004~~, *Optical fibres – Part 1-40: Attenuation measurement methods* ~~and test procedures – Attenuation~~

~~IEC 60793-2, Optical fibres – Part 2: Product specifications – General~~

3 Terms, definitions and abbreviated terms

3.1 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- IEC Electropedia: available at <https://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp>

3.2 Abbreviated terms

The abbreviated terms are given in Table 1.

Table 1 – Abbreviated terms

Abbreviated term	Full term
CCD	charge-coupled devices
FWHM	full width half maximum
MFD	mode field diameter
OTDR	optical time domain reflectometer
RTM	reference test method

4 General consideration about mode field diameter

The mode field diameter measurement represents a measure of the transverse extent of the electromagnetic field intensity of the guided mode in a fibre cross section, and it is defined from the far-field intensity distribution as a ratio of integrals known as the Petermann II definition. See Formula (1).

The definitions of mode field diameter are strictly related to the measurement configurations. The mathematical equivalence of these definitions results from transform relationships between measurement results obtained by different implementations summarized in Figure 1.

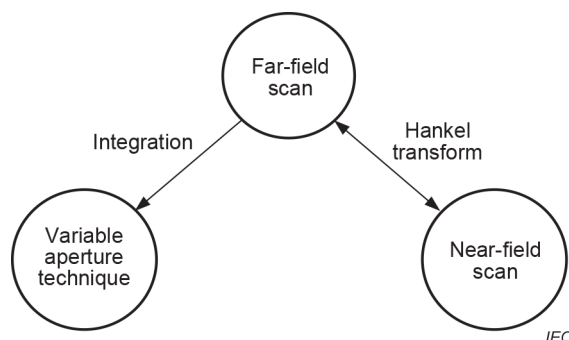


Figure 1 – Transform relationships between measurement results

Four methods are described for measuring mode field diameter:

- method A: direct far-field scan;
- method B: variable aperture in the far field;
- method C: near-field scan;
- method D: bi-directional backscatter using an optical time domain reflectometer (OTDR).

All four methods apply to all categories of type B single-mode fibre shown in IEC 60793-2 and operating near 1 310 nm or 1 550 nm. Method D is not recommended for the measurement of fibres of unknown type or design.

Information common to all four methods is contained in Clause 1 to Clause 11, and information pertaining to each individual method appears in Annex A, Annex B, Annex C, and Annex D respectively.

5 Reference test method

Method A, direct far-field scan, is the reference test method (RTM), which shall be the one used to settle disputes.

6 Apparatus

6.1 General

The following apparatus is common to all measurement methods. Annex A, Annex B, Annex C, and Annex D include layout drawings and other equipment requirements for each of the four methods, respectively.

6.2 Light source

For method A, method B and method C, use a suitable coherent or non-coherent light source, such as a semiconductor laser or a ~~sufficiently~~ powerful filtered white light source. ~~The source shall produce sufficient radiation at the intended wavelength(s) and be stable in intensity over a time period sufficient to perform the measurement.~~

A monochromator or interference filter(s) may be used, if required, for wavelength selection. The detail specification shall ~~specify~~ indicate the wavelength of the source. The full width half maximum (FWHM) spectral line width of the source shall ≤ 10 nm, unless otherwise specified.

The source power level shall be chosen so it is not impacting the repeatability of the mode diameter measurement.

The source power shall be stable for the complete duration of the measurement.

See Annex D for method D.

6.3 Input optics

For method A, method B, and method C, an optical lens system or fibre pigtail may be employed to excite the ~~specimen~~ sample. It is recommended that the power coupled into the ~~specimen~~ sample be relatively insensitive to the position of its input end face. This can be accomplished by using a launch beam that spatially and angularly overfills the input end face.

If using a butt splice, employ index-matching material between the fibre pigtail and the ~~specimen~~ sample to avoid interference effects. The coupling shall be stable for the duration of the measurement.

See Annex D for method D.

6.4 Input positioner

Provide means of positioning the input end of the ~~specimen~~ sample to the light source. Examples include the use of x-y-z micropositioner stages, or mechanical coupling devices such as connectors, vacuum splices, or three-rod splices. The position of the fibre shall remain stable over the duration of the measurement.

6.5 Cladding mode stripper

Use a device that extracts cladding modes. Under some circumstances, the fibre coating will perform this function.

6.6 High-order mode filter

Use a means to remove high-order propagating modes in the wavelength range that is greater than or equal to the cut-off wavelength of the ~~specimen~~ sample. For example, a one-turn bend with a radius of 30 mm on the fibre is generally sufficient for most ~~B1.1 to B6~~ B-652, B-653, B-654, B-655, B-656 and B-657 fibres. For some ~~B6~~ B-657 fibres, smaller radius, multiple bends, or longer ~~specimen~~ sample length can be applied to remove high-order propagating modes.

6.7 Output positioner

Provide a suitable means for aligning the fibre output end face to allow an accurate axial adjustment of the output end, such that, at the measurement wavelength, the scan pattern is suitably focused on the plane of the scanning detector. Such coupling may include the use of lenses or ~~may be~~ a mechanical connector to a detector pigtail.

Provide means such as a side-viewing microscope or camera with a crosshair to locate the fibre at a fixed distance from the apertures or detectors. It ~~may~~ can be sufficient to provide only longitudinal adjustment if the fibre is constrained in the lateral plane by a device such as a vacuum chuck (this depends mainly upon the size of the light detector).

6.8 Output optics

See the appropriate annex: Annex A, Annex B, Annex C or Annex D.

6.9 Detector

See the appropriate annex: Annex A, Annex B, Annex C or Annex D.

6.10 Computer

Use a computer to perform operations such as controlling the apparatus, taking intensity measurements, and processing the data to obtain the final results. For individual details, see the appropriate annex: Annex A, Annex B, Annex C or Annex D.

7 Sampling and ~~specimens~~ samples

7.1 ~~Specimen~~ Sample length

For method A, method B and method C, the ~~specimen~~ sample shall be a known length, typically $2\text{ m} \pm 0,2\text{ m}$ for most ~~B1.1 to B6~~ B-652, B-653, B-654, B-655, B-656 and B-657 fibres. For some ~~B6~~ B-657 fibres, longer ~~specimen~~ sample length can be used to avoid high-order propagating modes, 22 m for example.

For method D, OTDR, the sample shall be long enough to exceed (or be positioned beyond) the dead zone of the OTDR, with both ends accessible, as described in the backscatter test method in IEC 60793-1-40.

7.2 ~~Specimen~~ Sample end face

Prepare a flat end face, orthogonal to the fibre axis, at the input and output ends of each ~~specimen~~ sample.

8 Procedure

See Annex A, Annex B, Annex C and Annex D for method A, method B, method C, and method D, respectively.

9 Calculations

9.1 Basic formulae

The basic formulae for calculating mode field diameter are Formula (1) for method A, Formula (2) for method B and Formula (6) for method C. For additional calculations, see the appropriate annex: Annex A, Annex B, Annex C or Annex D. Sample data sets for method A, method B and method C are included in Annex E.

9.2 Method A – Direct far-field scan

The following formula defines the mode field diameter for method A in terms of the electromagnetic field emitted from the end of the ~~specimen~~ sample.

Calculate the mode field diameter by scanning the far-field data and evaluating the Petermann II integral, which is defined from the far-field intensity distribution:

$$2W_0 = \frac{\lambda\sqrt{2}}{\pi} \left[\frac{\int_0^{\pi/2} P_F(\theta) \sin(\theta) \cos(\theta) d\theta}{\int_0^{\pi/2} P_F(\theta) \sin^3(\theta) \cos(\theta) d\theta} \right]^{1/2} \quad (1)$$

where

$2W_0$ is the mode field diameter in μm ;

$P_F(\theta)$ is the far-field intensity distribution;

λ is the wavelength of measurement in μm ;

θ is the angle in the far-field measurement from the axis of the fibre.

NOTE 1 The integration limits are shown to be from zero to $\pi/2$, but it is understood that the integrands approach zero with increasing argument so that, in practice, the integrals can be truncated.

NOTE 2 P_F is $F^2(\theta)$ in ITU-T documents.

The far-field method for obtaining the mode field diameter of a single-mode fibre is a two-step procedure. First, measure the far-field radiation pattern of the fibre. Second, use a mathematical procedure based on the Petermann II far-field definition to calculate the mode field from far-field data, as described in Formula (1).

Annex E provides sample data and calculated $2W_0$ values for verifying the numerical evaluation of the Petermann II Integral. The sample data are in the form of the folded power, $P_F(\theta)$, as a function of the angle, θ .

9.3 Method B – Variable aperture in the far field

Formula (2) defines the mode field diameter for method B in terms of the electromagnetic field emitted from the end of the ~~specimen~~ sample.

Calculate the mode field diameter, $2W_0$, as follows:

$$2W_0 = \left(\frac{\lambda}{\pi D} \right) \left[\int_0^{\infty} a(x) \frac{x}{(x^2 + D^2)^2} dx \right]^{-1/2} \quad (2)$$

where

$2W_0$ is the mode field diameter, in μm ;

λ is the wavelength of measurement, in μm ;

D is the distance between the aperture and the fibre, in mm;

$a(x)$ is the complementary aperture transmission function, calculated as

$$a(x) = 1 - \frac{P(x)}{P(\text{max})} \quad (3)$$

where

$P_{(x)}$ is the power measured through an aperture of radius, x , or half angle, θ ;

$P_{(max)}$ is the maximum power, assuming an infinite aperture;

x is the aperture radius, calculated as

$$x = D \tan(\theta) \tag{4}$$

Another equivalent expression of Formula (2) is

$$2W_0 = \frac{\lambda\sqrt{2}}{\pi} \left[\int_0^\infty a(\theta) \sin 2\theta d\theta \right]^{-1/2} \tag{5}$$

The variable aperture far-field method for obtaining the mode field diameter of a single-mode fibre is a two-step procedure. First, measure the two-dimensional far-field pattern as the power passing through a series of transmitting apertures of various size. Second, use a mathematical procedure to calculate the mode field diameter from the far-field data.

The mathematical basis for the calculation of mode field diameter is based on the Petermann II far-field definition from Formula (1). Formula (2) and Formula (5) can be derived from Formula (1) by integration.

9.4 Method C – Near-field scan

The following formula defines the mode field diameter for method C in terms of the electromagnetic field emitted from the end of the specimen sample.

Calculate the mode field diameter from the measured near-field intensity distribution, using the following integral:

$$2W_0 = 2 \left(\frac{\int_0^\infty r f^2(r) dr}{\int_0^\infty r \left(\frac{df(r)}{dr} \right)^2 dr} \right)^{1/2} \tag{6}$$

where

$2W_0$ is the mode field diameter, in μm ;

r is the radial coordinate, in μm ;

$f^2(r)$ is the near-field intensity distribution.

NOTE The upper integration limits are shown to infinity, but it is understood that since the integrands approach zero with increasing argument, in practice the integrals can be truncated. A smoothing algorithm can be used for the calculation of the derivative.

The near-field scan method for obtaining the mode field diameter of a single-mode fibre is a two-step procedure. First, measure the radial near-field pattern. Second, use a mathematical procedure to calculate the mode field diameter from the near-field data.