



Designation: **D6482–06 (Reapproved 2016) D6482 – 21**

## Standard Test Method for Determination of Cooling Characteristics of Aqueous Polymer Quenchants by Cooling Curve Analysis with Agitation (Tensi Method)<sup>1</sup>

This standard is issued under the fixed designation D6482; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope—Scope\*

1.1 This test method covers the equipment and the procedure for evaluation of quenching characteristics of a quenching fluid by cooling rate determination.

1.2 This test method is designed to evaluate quenching fluids with agitation, using the Tensi agitation apparatus.

1.3 The values stated in SI units are to be regarded as standard. The values given in parentheses are for information only.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

### 2. Referenced Documents

#### 2.1 ASTM Standards:<sup>2</sup>

[D4175 Terminology Relating to Petroleum Products, Liquid Fuels, and Lubricants](#)

[D6200 Test Method for Determination of Cooling Characteristics of Quench Oils by Cooling Curve Analysis](#)

[E220 Test Method for Calibration of Thermocouples By Comparison Techniques](#)

[E230 Specification for Temperature-Electromotive Force \(emf\) Tables for Standardized Thermocouples](#)

#### 2.2 SAE Standard:<sup>3</sup>

[AMS 5665 Nickel Alloy Corrosion and Heat Resistant Bars, Forgings and Rings](#)

#### 2.3 Japanese Industrial Standards:<sup>4</sup>

[JIS K 2242 Heat Treating Oil](#)

[JIS K 6753 Di-2-ethylhexyl Phthalate](#)

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D02 on Petroleum Products, Liquid Fuels, and Lubricants and is the direct responsibility of Subcommittee D02.L0.06 on Non-Lubricating Process Fluids.

Current edition approved July 1, 2016 Dec. 1, 2021. Published July 2016 January 2022. Originally approved in 1999. Last previous edition approved in 2011 as D6482–06 (2011) (2016). DOI: 10.1520/D6482-06R16-10.1520/D6482-21.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> Available from SAE International (SAE), 400 Commonwealth Dr., Warrendale, PA 15096-0001, http://www.sae.org.

<sup>4</sup> Available from Japanese Standards Organization (JSA), 4-1-24 Akasaka Minato-Ku, Tokyo, 107-8440, Japan, http://www.jsa.or.jp.

\*A Summary of Changes section appears at the end of this standard

2.4 Wolfson Engineering Group:<sup>5</sup>

Wolfson Engineering Group Specification Laboratory Tests for Assessing the Cooling Curve of Industrial Quenching Media

2.5 ASTM Adjuncts:<sup>6</sup>

ADJD6300 D2PP, Determination of Precision and Bias Data for Use in Test Methods for Petroleum Products

### 3. Terminology

3.1 Definitions of Terms Specific to This Standard:

3.1.1 For definitions of terms used in this test method, refer to Terminology **D4175**.

3.1.2 *aqueous polymer quenchant*—*quenchant, n*—an aqueous solution containing a water soluble polymer; typically including poly(alkylene glycol), poly(ethyl oxazoline), poly(sodium acrylate) and poly(vinyl pyrrolidone) **(1, 2)**.<sup>7</sup> The quenchant solution also typically contains additives for corrosion and foam control, if needed. Quench severity of aqueous polymer quenchants is dependent on concentration and molecular weight of the specific polymer being evaluated, quenchant temperature, and agitation rate as shown in **Figs. 1-3**, respectively.

3.1.3 *cooling curve*—*curve, n*—a graphical representation of the cooling time (*t*)-temperature (*T*) response of the probe (see **7.3**). An example is illustrated in **Fig. 4A**.

3.1.4 *cooling curve analysis*—*analysis, n*—the process of quantifying the cooling characteristics of a quenchant based on the temperature versus time profile obtained by cooling a preheated metal probe assembly (see **Fig. 5**) under standard conditions **(1, 3, 4)**.

3.1.5 *cooling rate curve*—*curve, n*—obtained by calculating the first derivative ( $dT/dt$ ) of the cooling time-temperature curve. An example is illustrated in **Fig. 4B**.

3.1.6 *quench severity*—*severity, n*—the ability of a quenching medium to extract heat from a hot metal **(5)**.

3.1.7 *quenchant*—*quenchant, n*—any medium, liquid or gas that may be used to mediate heat transfer during the cooling of hot metal.

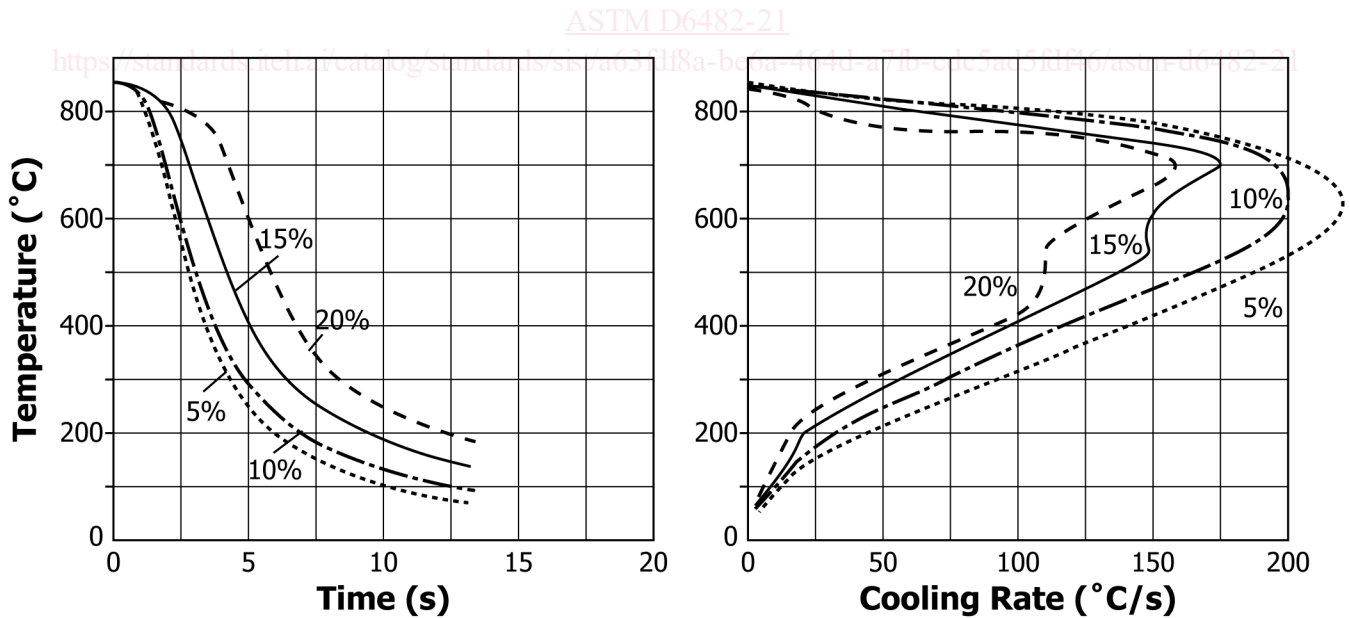


FIG. 1 Illustration of the Effect of Quenchant Concentration on Cooling Curve Performance for Poly(Alkylene Glycol) Quenchant at 30°C and 0.5 m/s

<sup>5</sup> Wolfson Heat Treatment Centre, Federation House, Vyse St., Birmingham, B18 6LT, UK, <http://www.sea.org.uk/whtc>.

<sup>6</sup> No longer available from ASTM International Headquarters.

<sup>7</sup> The boldface numbers in parentheses refer to the list of references at the end of this standard.

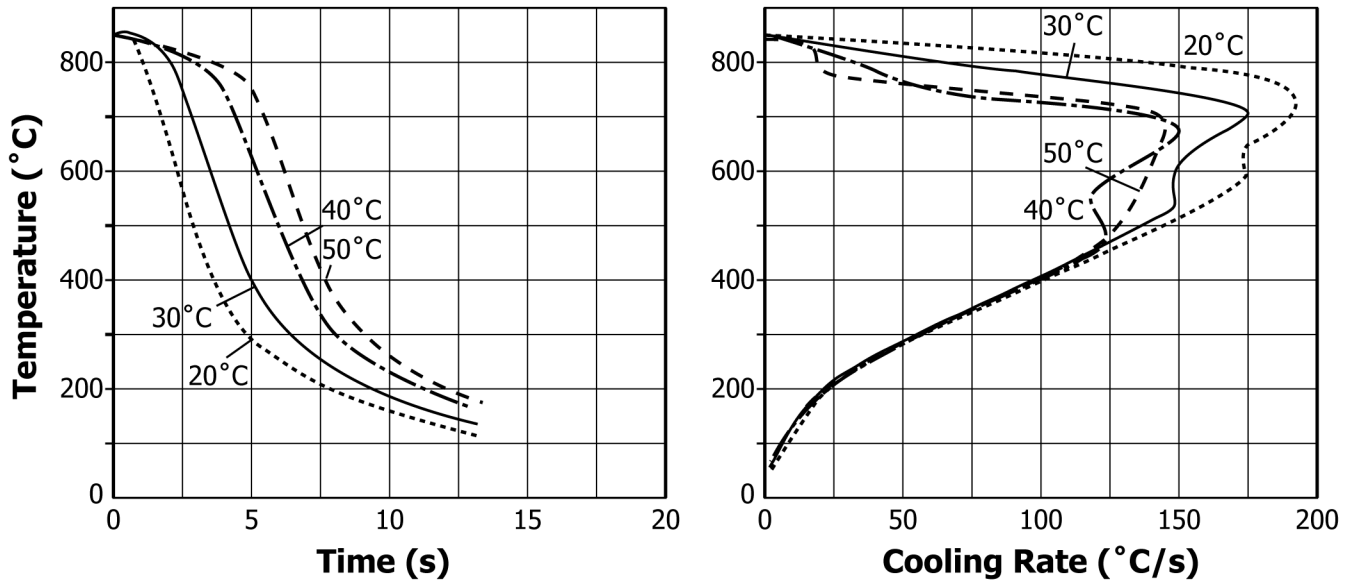


FIG. 2 Illustration of the Effect of Bath Temperature Variation on Cooling Curve Performance for 15 % Aqueous Solution of Poly (Alkylene Glycol) Quenchant at 0.5 m/s

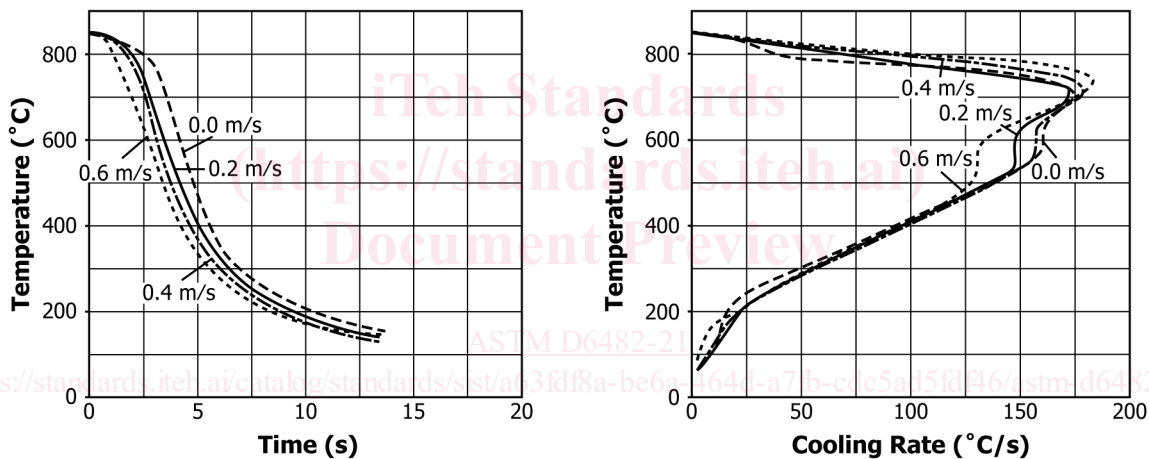


FIG. 3 Effect of Agitation Rate Variation on Cooling Curve Performance for a 15 % Aqueous Poly(Alkylene Glycol) Quenchant Solution at 30°C

#### 4. Summary of Test Method

4.1 The nickel alloy probe assembly’s cooling time versus temperature is determined after placing the assembly in a furnace and heating to 850 °C (1562 °F) and then quenching into an aqueous polymer quenchant solution. The temperature inside the probe assembly and the cooling times are recorded at selected time intervals to establish a cooling temperature versus time curve. The resulting cooling curve may be used to evaluate quench severity (see Note 1).


NOTE 1—For production testing, the furnace temperature of 815 °C to 857 °C (1500 °F to 1575 °F) may be used.

#### 5. Significance and Use

5.1 This test method provides a cooling time versus temperature pathway that is directly proportional to physical properties such as the hardness obtainable upon quenching of a metal. The results obtained by this test method may be used as a guide in quenchant selection or comparison of quench severities of different quenchants, new or used.

#### 6. Interferences

6.1 The presence of contaminants, such as oil, salt, metalworking fluids, forging lubricants, and polymer degradation, may affect

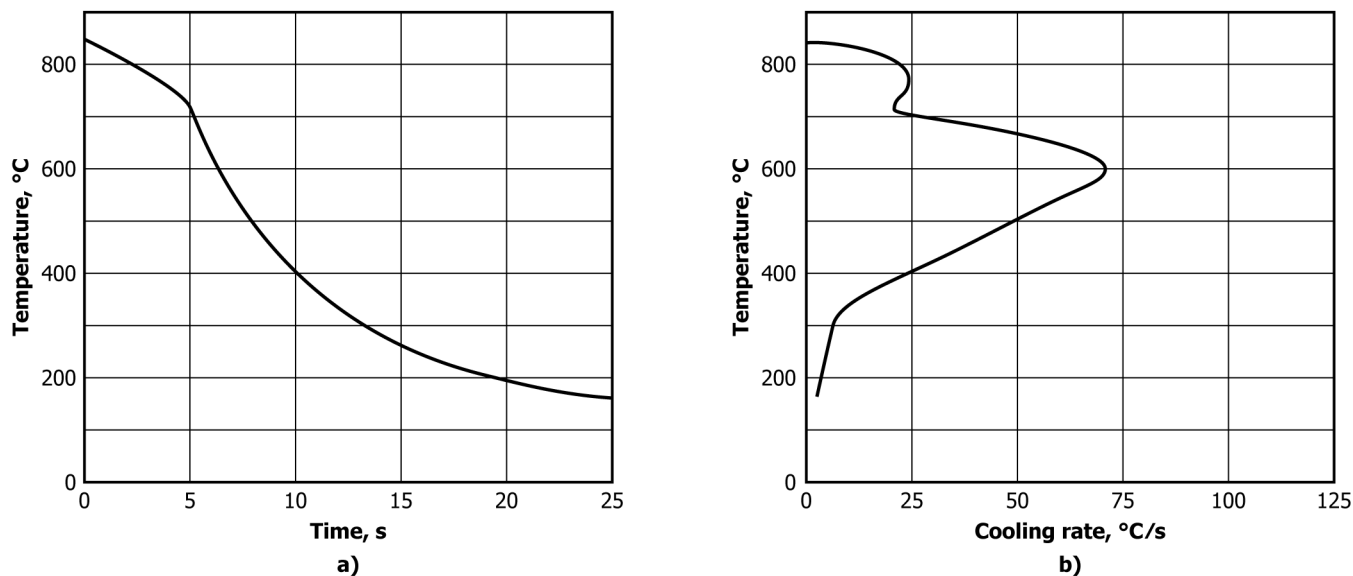

A. Cooling time - temperature curve (cooling curve)

B. Cooling rate - temperature curve (cooling rate curve)

FIG. 4 Typical Temperature/Time and Temperature/Cooling Rate Plots for Test Probe Cooled in Quenching Oil

iTeh Standards  
<https://standards.itih.ai>  
 Document Preview

cooling curve results obtained by this test method for aqueous polymer quenchants. Contaminants, such as water, hydraulic fluids, sludge, additive loss, and oil degradation, may similarly affect the cooling curve behavior of oil quenchants.

## 7. Apparatus

7.1 *Furnace*—Use a horizontal or vertical electrical resistance tube-type furnace capable of maintaining a constant minimum temperature of 850 °C (1562 °F) over a heated length of not less than 120 mm (4.72 in.) and a probe positioned in the center of the heating chamber. The furnace shall be capable of maintaining the probe’s temperature within  $\pm 2.5$  °C (4.5 °F) over the specimen length. The furnace, that is, the radiant tube heating media, shall be used with ambient atmosphere.

7.2 *Measurement System*—The temperature-time measurement system shall be a computer based data acquisition system capable of providing a permanent record of the cooling characteristics of each oil sample tested, producing a record of variation in the test probe assembly of temperature with respect to time and of cooling rate with respect to temperature.

7.3 *Probe*, shall be cylindrical, having a diameter of 12.5 mm  $\pm$  0.01 mm (0.492 in.  $\pm$  0.0004 in.) and a length of 60 mm  $\pm$  0.25 mm (2.362 in.  $\pm$  0.01 in.) with a 1.45 mm to 1.65 mm (0.057 in. to 0.065 in.) sheathed type *K* thermocouple in its geometric center. The probe shall be made of a nickel alloy 600 (UNS N06600) purchased to SAE specification (see AMS 5665), that has a nominal composition of 76.0 % Ni, 15.5 % Cr, 8.0 % Fe, 0.08 % C, and 0.25 % maximum Cu. The probe shall be attached to a support tube with a minimum length of 200 mm (7.874 in.). The thermocouple sheathing and the support tube shall be the same material as the probe (see Note 2). See Fig. 4 for recommended manufacturing details.


NOTE 2—Exercise care that the probe specimen is not damaged because surface irregularities will influence the results of the test.

### 7.4 Tensi Agitation Assembly:


#### 7.4.1 Construction:

ALL DIMENSIONS IN MILLIMETERS

Notes:

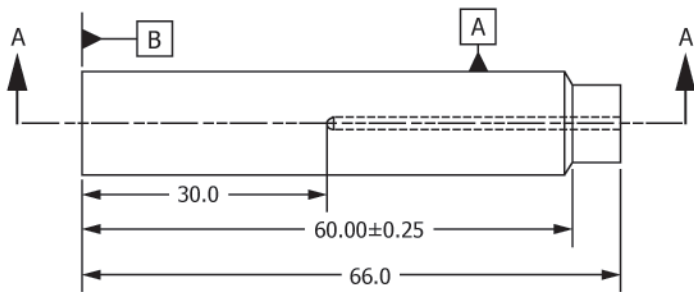


1. Dautm surface B not to be center drilled.
2. Material must be same as Type "K" thermocouple sheath material (Inconel 600).
3. Nominal hole diameter to be same as Type 'K' sheathed thermocouple within 1.45mm to 1.65 mm.
4. Full radius based on size specified in Note 3.
5. All surfaces  $\nabla \frac{1}{}$  unless otherwise specified.
6. Break all sharp edges.

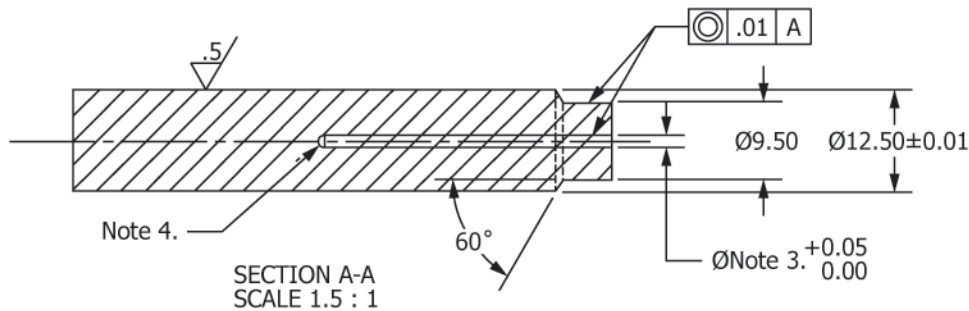

Tolerance Unless Otherwise Noted:

- X.X = ± 0.5
- X.XX = ± 0.1
- X.XXX = ± 0.05

(a) Probe Details

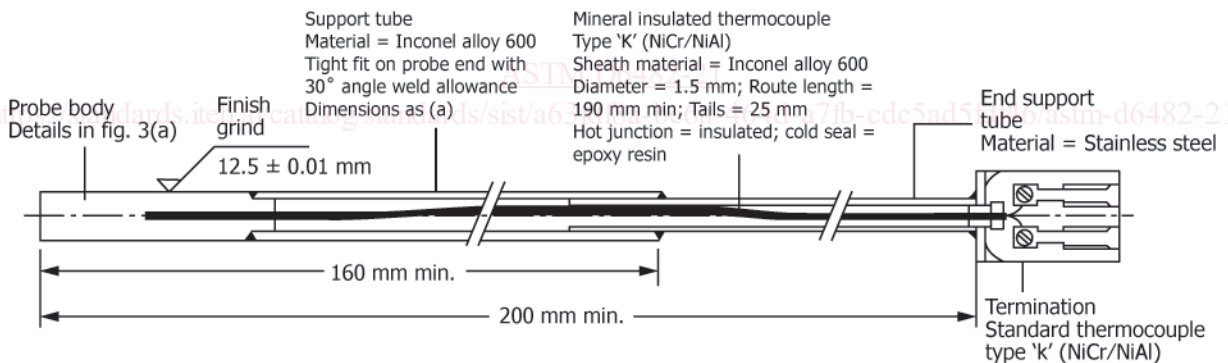

(b) General assembly

FIG. 5 Probe Details and General Probe Assembly

7.4.1.1 The 125 mm by 60 mm by 60 mm Tensi agitation assembly is illustrated in Fig. 6. The volume of the assembly is approximately  $1.5 \times 10^{-3} \text{ m}^3$ . This assembly may be constructed from glass or any transparent and temperature-resistant synthetic material that is chemically compatible with the quenching fluids to be evaluated. Alternatively, the agitation assembly, illustrated in Fig. 7, may be purchased assembled.<sup>8</sup>

7.4.1.2 Quenchant agitation is provided by an impeller mixer. The three-blade impeller is 50 mm in diameter with a pitch setting  $42 \text{ mm} \approx \_ \times 0.85$ . The impeller is commercially available.

<sup>8</sup> The sole source of supply of the Tensi agitation apparatus, fully assembled, known to the committee at this time is IVF, The Swedish Institute of Production Engineering Research, Argongatan 30, S-431 53 Mölndal, Sweden. If you are aware of alternative suppliers, please provide this information to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee,<sup>1</sup> which you may attend.

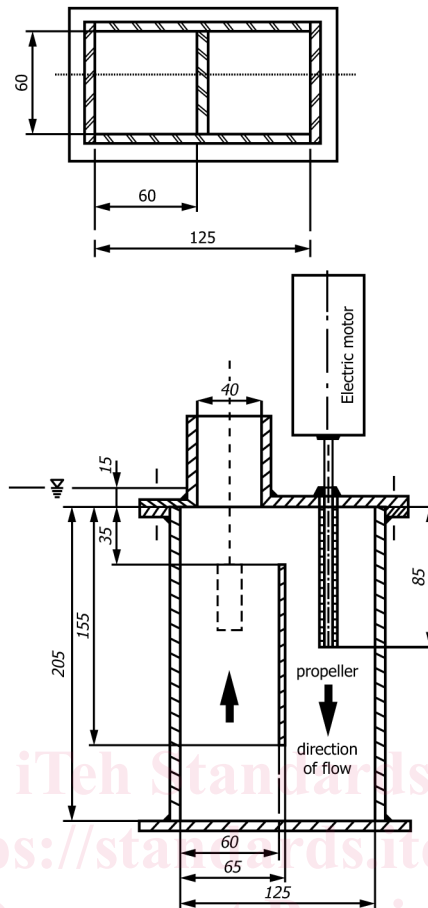


FIG. 6 Schematic Drawing of Tensi Agitation Assembly

ASTM D6482-21

<https://standards.iteh.ai/catalog/standards/sist/a63fd8a-be6a-464d-a7fb-cdc5ad5fd46/astm-d6482-21>

NOTE 3—This procedure is recommended for aqueous polymer quenchants. Quench oils are not compatible with the poly(methyl methacrylate) materials used for construction of this apparatus.

7.4.2 *Cleaning*—The agitation assembly shall be cleaned prior to use with a detergent solution. After cleaning, the assembly shall be rinsed with water at least three times to ensure that no quenchant residue or detergent solution remains.

7.4.3 *Flow Velocity*—Correlation of flow velocity through the quenching chamber and impeller rotational speed for water is illustrated in Fig. 8. Flow velocity for other fluids will vary with fluid viscosity.

7.4.3.1 *Impeller Speed*—Fluids shall be controlled by the rotational speed of the impeller. Standard impeller speed of 1000 r/min is recommended and is obtained from a plot of revolutions per minute versus potentiometer setting as illustrated in Fig. 9 and described as impeller speed calibration: Impeller speed shall be determined using an optical tachometer. Optional tachometers operate by emitting and receiving light to and from a reflector fastened on to the impeller shaft. A typical calibration plot is illustrated in Fig. 8.

NOTE 4—The impeller velocity will depend to some extent on the viscosity of the quenchant solution. However, the variation was found to be minimal over a wide range of viscosities from water to a polymer quenchant at 30 % by volume.

7.4.3.2 *Flow Direction*—The correct fluid flow direction is illustrated in Fig. 6. However, if the wiring of the electrical motor is reversed, it is possible that the flow direction will also be reversed. If this occurs, which is easily detected visually, the polarity of the electrical motor is reversed by reversing the two wire leads to the motor.

7.4.4 *Fluid Volume*—The resulting cooling curve will be dependent on the temperature rise during the quench, which is dependent

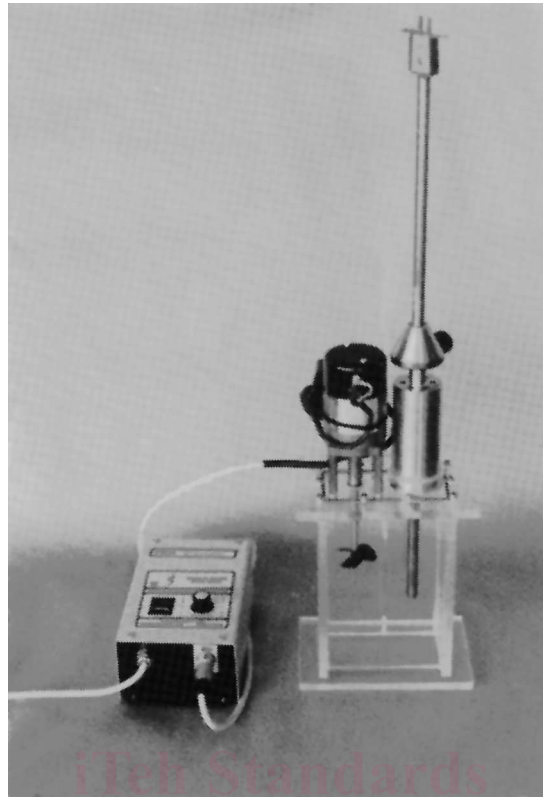


FIG. 7 Commercially Available Tensi Agitation Assembly

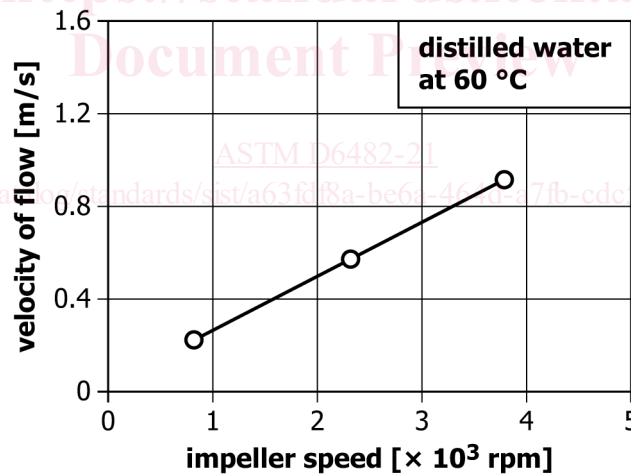


FIG. 8 Correlation of Flow Velocity Through Quenching Chamber and Impeller Rotational Speed for Water

on the total fluid volume. Therefore, the cooling curve analysis shall be performed with the same volume of fluid. The fluid shall be level with the lower distance ring in the support tube, as shown in Fig. 10.

7.5 *Temperature Measurement*—Any temperature detection device may be used that is capable of measuring quenching fluid temperature to within  $\pm 1$  °C (1.8 °F).

7.6 *Transfer Mechanism*—The heated probe is transferred manually to the Tensi agitation assembly, which shall be equipped with a fixture to ensure correct placement in the center of the quenching chamber, as illustrated in Figs. 6 and 7. A timer shall be used to ensure a maximum transfer time of 3.0 s.

7.7 *Timer*, graduated in seconds and minutes, and may be part of a computer clock.