



Designation: D731 – 22

# Standard Test Method for Molding Index of Thermosetting Molding Powder<sup>1</sup>

This standard is issued under the fixed designation D731; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope\*

1.1 This test method covers the measurement of the molding index (plasticity) of thermosetting plastics ranging in flow from soft to stiff by selection of appropriate molding pressures within the range from 3.7 to 36.5 MPa (530 to 5300 psi).

1.2 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.4 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

## 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

- D256 Test Methods for Determining the Izod Pendulum Impact Resistance of Plastics
- D883 Terminology Relating to Plastics
- D957 Practice for Determining Surface Temperature of Molds for Plastics
- E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method

## 3. Terminology

3.1 Definitions are in accordance with Terminology D883, unless otherwise specified.

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D20 on Plastics and is the direct responsibility of Subcommittee D20.30 on Thermal Properties (Section D20.30.08).

Current edition approved March 15, 2022. Published March 2022. Originally approved in 1950. Last previous edition approved in 2018 as D731 - 18. DOI: 10.1520/D0731-22.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

3.2 *Definitions of Terms Specific to This Standard:*

3.3 *plasticity, n*—a measure of the resistance of a molten thermosetting material to flow under heat and pressure. A measure of the apparent viscosity of the material.

## 4. Summary of Test Method

4.1 A cup mold is mounted in a semi-automatic type press. A predetermined quantity of test sample is charged into the mold, controlled at a temperature dependent upon the test material. The minimum force required to mold a cup having a flash or fin thickness within a specified tolerance is determined. This force along with the mold closing time is reported as molding index.

## 5. Significance and Use

5.1 This test method provides a guide for evaluating the moldability of thermosetting molding powders. This test method does not necessarily denote that the molding behavior of different materials will be alike and trials may be necessary to establish the appropriate molding index for each material in question.

5.2 The sensitivity of this test diminishes when the molding pressure is decreased below 5.3 MPa (764 psi), so pressures lower than this are not ordinarily recommended. This is due to the friction of moving parts and the insensitivity of the pressure switch actuating the timer at these low pressures.


## 6. Apparatus

6.1 *Mold*—A cup mold of the flash type, to produce a molded cup as shown in Fig. 1, operated under controlled pressure and temperatures and provided with stops so that flash or fin thickness cannot be less than 0.14 mm (0.0055 in.). The area of the mold casting creating the molded flash shall be located on top of the cup, flat, perpendicular to the axis of the cup, and in the form of an annular ring 3.17 mm (0.125 in.) in width.

6.2 *Pyrometer*—A calibrated pyrometer, traceable to a national standard (for example, NIST), and accurate to  $\pm 1^\circ\text{C}$  shall be used to determine the temperature of the mold surfaces. For properly measuring mold temperatures, reference Practice D957.

6.3 *Heating System*—Any conventional means for heating the press platens, provided the heat source is constant enough

\*A Summary of Changes section appears at the end of this standard

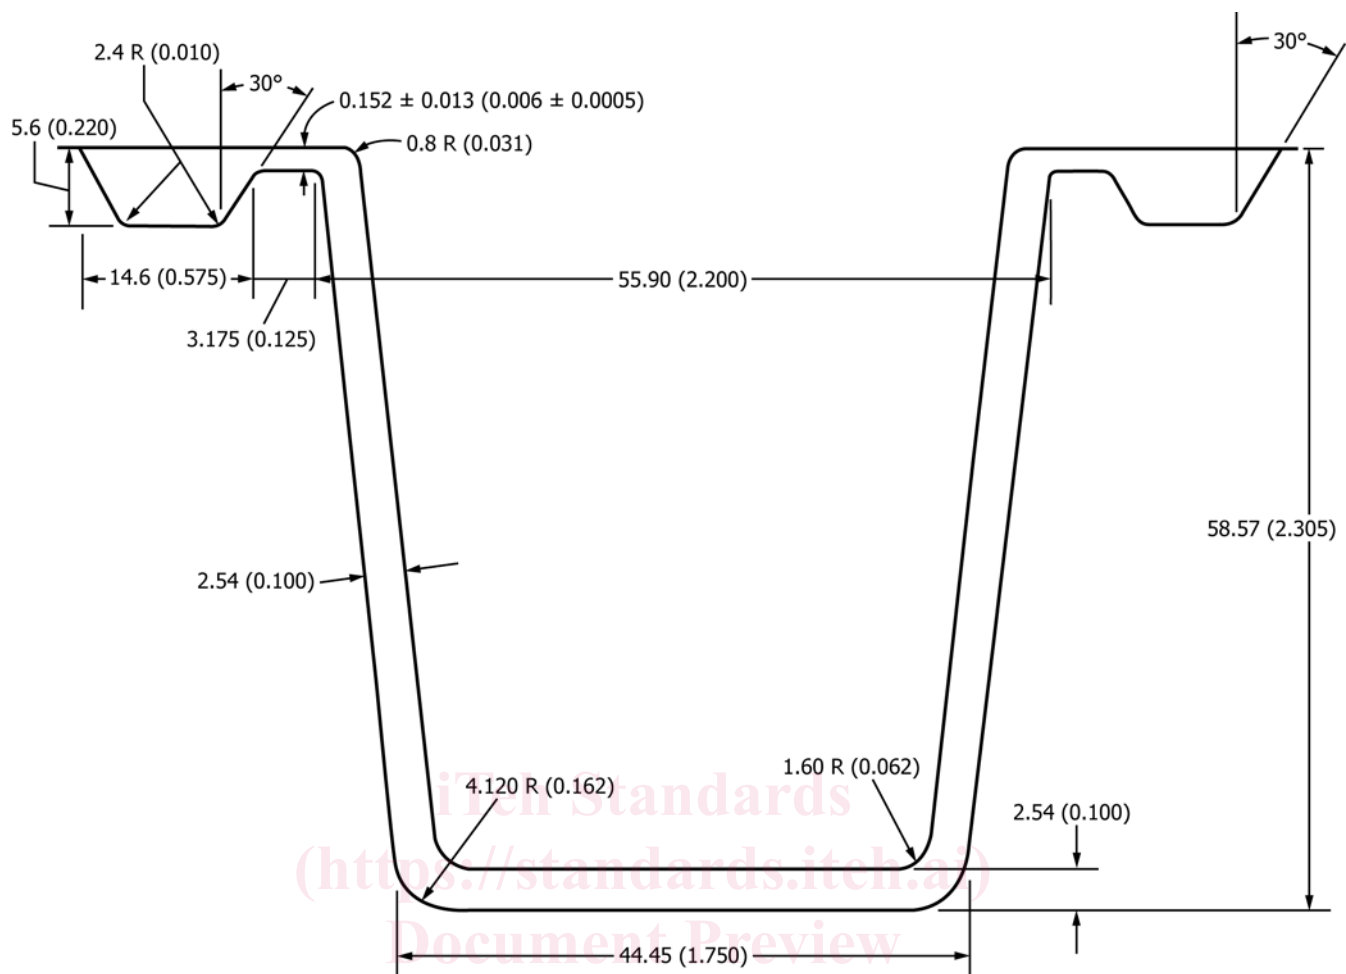

ASTM D731-22

Note:

<https://standards.iteh.ai/catalog/standards/sist/39e9fe52-6551-4266-8288-2022-000000000000/astm-d731-22>  
 All surfaces polished to SPE/SPI #2 Finish -d731-22  
 Steel: D-2 Hardened to 62 RC  
 Dimensions in mm (inches)  
 Tolerance  $\pm 0.25$  (0.001) Except where noted

FIG. 1 Cup Mold

to maintain the molding temperature within  $\pm 1^\circ\text{C}$  of the specified temperature (see 9.2).

6.4 *Pressure System*—A semiautomatic press with a fixed mold and fully insulated to minimize heat losses shall be used. The hydraulic system shall be provided with a means of pressure regulation so that the load on the mold shall differ by not more than  $\pm 1112$  N ( $\pm 250$  lbf) from the stated value. The capacity of the hydraulic system shall permit a ram travel of approximately 25 mm/s (1 in./s). The ram diameter shall not exceed 100 mm (4 in.).

NOTE 1—The use of hand molds is not recommended but may be used to give an estimate of the molding index.

## 7. Test Specimen

7.1 To determine the weight of the test specimen for materials having an Izod impact strength of 27 J/m (0.50 ft-lb/in.) of notch, or less, a cup having a flash or fin thickness

of 0.15 to 0.20 mm (0.006 to 0.008 in.) shall be molded (see Note 2). The adhering fin shall be removed and the cup weighed to the nearest 0.1 g. This weight multiplied by 1.1 shall be the weight of the test specimen used. For materials having an impact above 27 J/m (0.50 ft-lb/in.) of notch, the specimen weight is determined in a similar manner, except that cup flash shall not be more than 0.66 mm (0.026 in.) or less than 0.51 mm (0.020 in.), and the amount of material shall be 1.05 times the weight of this cup. The test specimen shall be in the form of loose powder unless preforming is necessary for materials of high bulk. Minimum pressure shall be employed in the preforming operation to minimize the increase in closing time resulting from the use of preforms.

NOTE 2—While the mold is provided with stops so that the flash or fin thickness cannot be less than  $0.15 \pm 0.013$  mm ( $0.006 \pm 0.0005$  in.), the molded cup itself may have a flash thickness of 0.15 to 0.20 mm ( $0.006 \pm 0.0008$  in.) as the micro switch controlling the closing time must have a tolerance in which to operate.

## 8. Conditioning

8.1 Materials are normally tested in the “as received” condition, except in referee tests, when they shall be conditioned in accordance with 8.2 (see Note 3).

8.2 For referee testing, all materials shall be shipped and stored in sealed moisture barrier containers. These materials shall be stored for a minimum period of 48 h at standard laboratory temperature before breaking the seal on the carton. A representative sample shall be taken from this carton immediately after opening and tested within 3 min in order to preserve the original moisture content. Alternative methods of conditioning samples are acceptable provided they are mutually agreed upon between the manufacturer and the purchaser.

NOTE 3—Conditioning may alter the moisture content of most materials and thereby change their molding index or molding behavior.

## 9. Procedure

9.1 Mount the mold in the semi-automatic press. The rate of flow is sensitive to the condition of the mold surfaces. To avoid erroneous results, any residue deposited from prior tests shall be completely removed from the mold surfaces. Discard the first few cups molded and accept the flow time as correct when two successive cups molded under test do not differ by more than 1 s in time of flow.

9.2 The preferred mold temperature for testing the molding index for the following materials shall be:

	°C (°F)
Phenolic	165 ± 1 (330 ± 1.8)
Melamine	155 ± 1 (310 ± 1.8)
Urea	150 ± 1 (300 ± 1.8)
Epoxy	150 ± 1 (300 ± 1.8)
Diallyl phthalate	150 ± 1 (300 ± 1.8)
Alkyd	150 ± 1 (300 ± 1.8)

Other temperatures are acceptable provided they are mutually agreed upon between the manufacturer and the purchaser.

9.3 First determine the proper weight to be used as outlined in 6.1. Then begin the test with a load sufficient to close the mold to the fin thickness specified for the type of material being tested as defined in 6.1. For example, if a 44482 N (10,000 lb) load is applied on the mold to make the initial cup and the required fin thickness is obtained, the next lower load, 33362 N (7500 lb) is applied as indicated in the following table. If the mold closes to the required thickness again, then the 22241 N (5000 lb) load is applied. If the mold then does not close, the “molding index” is the closing time obtained with the 33362 N (7500 lb) load. It is recommended that the mold loads used be selected from the following table (see Note 4):

Total Force Between Platens N (lb)	Plastic Pressure MPa (psi)
16 014 (3600)	5.3 (764)
22 241 (5000)	7.3 (1060)
33 362 (7500)	11 (1591)
44 482 (10 000)	14.6 (2121)

59 161 (13 300)	19.4 (2821)
66 723 (15 000)	21.9 (3181)
88 964 (20 000)	29.2 (4242)
111 206(25 000)	36.5 (5302)

NOTE 4—These fixed mold loads are recommended based upon common practice and materials and plasticities currently available. Other mold loads may be defined, if agreed to by supplier and customer, to better define the plasticity of a material.

9.4 The time of flow in seconds shall be measured from the instant that the hydraulic gage indicates an applied load of 4448 N (1000 lb) to the instant that the fin has reached 0.20 mm (0.008 in.) in thickness for materials with an Izod impact strength of 27 J/m (0.50 ft-lb/in.) of notch, or less, and 0.66 mm (0.026 in.) for materials with an impact above 27 J/m (0.50 ft-lb/in.) of notch.

NOTE 5—The molding pressure is calculated by dividing the total load by the projected area of the mold cavity.

NOTE 6—A convenient method for determining fin thickness is to indicate the final movement of the platen with a dial micrometer.

**TABLE 1 Molding Index in Seconds**

NOTE 1— $S_r$  is the within-laboratory standard deviation of the average,  $S_R$  is the between-laboratories standard deviation of the average,  $r = 2.8 S_r$ , and  $R = 2.8 S_R$ .

Material	Average	Load, N (lb)	$S_r$	$S_R$	$r$	$R$
Polyester (B) <sup>A</sup>	4.78	112 (25)	0.025	0.909	0.070	2.545
Glass-Filled (B) <sup>B</sup>	8.99	112 (25)	0.038	0.727	0.106	2.036
Polyester (A) <sup>A</sup>	9.63	112 (25)	0.072	0.577	0.202	1.616
Mineral Filled (A) <sup>B</sup>	11.54	112 (25)	0.072	0.881	0.202	2.467
Mineral Filled (B) <sup>A</sup>	11.57	112 (25)	0.098	1.736	0.274	4.861
General Purpose (B) <sup>A</sup>	11.78	112 (25)	0.041	1.264	0.115	3.539
DAP (B) <sup>A</sup>	12.64	112 (25)	0.054	0.892	0.151	2.498
Impact Type (B) <sup>A</sup>	14.92	168 (36)	0.090	0.965	0.252	2.702
Glass-filled (A) <sup>B</sup>	16.06	224 (50)	0.083	0.912	0.232	2.554
General Purpose (A) <sup>B</sup>	18.37	168 (36)	0.056	1.331	0.157	3.727

<sup>A</sup> Sample B obtained from Occidental Chemical Corp., Fort Green, Ontario, Canada.

<sup>B</sup> Sample A obtained from Occidental Chemical Corp., Tonawanda, NY.

## 10. Report

10.1 Report the following information:

10.1.1 A statement indicating the nature of the material tested and the manufacturer’s material number and batch number,

10.1.2 The molding index expressed as the total minimum force in newtons (pounds) required to close the mold, with the closing time in seconds (for example, 445/13.4 N (100/13.4)<sub>18</sub>),

10.1.3 Temperature of the mold,

10.1.4 Weight of the test sample in grams, and form of sample (loose powder or preform),

10.1.5 Thickness of flash or fin measured to the nearest 0.025 mm (0.001 in.),

10.1.6 Description of any unusual characteristics of the test sample, such as discoloration and sticking,

10.1.7 Details of conditioning,

10.1.8 Impact strength of the material expressed as Izod in J/m (ft-lb/in.) of notch in accordance with Test Methods D256, and