



Designation: A240/A240M – 22

Standard Specification for Chromium and Chromium-Nickel Stainless Steel Plate, Sheet, and Strip for Pressure Vessels and for General Applications¹

This standard is issued under the fixed designation A240/A240M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reappraisal.

This standard has been approved for use by agencies of the U.S. Department of Defense.

1. Scope*

1.1 This specification² covers chromium, chromium-nickel, and chromium-manganese-nickel stainless steel plate, sheet, and strip for pressure vessels and for general applications including architectural, building, construction, and aesthetic applications.

1.2 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.3 This specification is expressed in both inch-pound and SI units. However, unless the order specifies the applicable “M” specification designation (SI units), the material shall be furnished in inch-pound units.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

¹ This specification is under the jurisdiction of ASTM Committee A01 on Steel, Stainless Steel and Related Alloys and is the direct responsibility of Subcommittee A01.17 on Flat-Rolled and Wrought Stainless Steel.

Current edition approved May 1, 2022. Published May 2022. Originally approved in 1940. Last previous edition approved in 2020 as A240/A240M – 20a. DOI: 10.1520/A0240_A0240M-22.

² For ASME Boiler and Pressure Vessel Code applications see related Specification SA-240 in Section II of that Code.

2. Referenced Documents

2.1 ASTM Standards:³

A370 Test Methods and Definitions for Mechanical Testing of Steel Products

A480/A480M Specification for General Requirements for Flat-Rolled Stainless and Heat-Resisting Steel Plate, Sheet, and Strip

A923 Test Methods for Detecting Detrimental Intermetallic Phase in Duplex Austenitic/Ferritic Stainless Steels

A1084 Test Method for Detecting Detrimental Phases in Lean Duplex Austenitic/Ferritic Stainless Steels

E112 Test Methods for Determining Average Grain Size

E140 Hardness Conversion Tables for Metals Relationship Among Brinell Hardness, Vickers Hardness, Rockwell Hardness, Superficial Hardness, Knoop Hardness, Scleroscope Hardness, and Leeb Hardness

E527 Practice for Numbering Metals and Alloys in the Unified Numbering System (UNS)

2.2 SAE Standard:⁴

J 1086 Practice for Numbering Metals and Alloys (UNS)

3. General Requirements

3.1 The following requirements for orders for material furnished under this specification shall conform to the applicable requirements of the current edition of Specification A480/A480M.

3.1.1 Definitions,

3.1.2 General requirements for delivery,

3.1.3 Ordering information,

3.1.4 Process,

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard’s Document Summary page on the ASTM website.

⁴ Available from SAE International (SAE), 400 Commonwealth Dr., Warrendale, PA 15096, <http://www.sae.org>.

*A Summary of Changes section appears at the end of this standard

- 3.1.5 Special tests,
- 3.1.6 Heat treatment,
- 3.1.7 Dimensions and permissible variations,
- 3.1.8 Workmanship, finish and appearance,
- 3.1.9 Number of tests/test methods,
- 3.1.10 Specimen preparation,
- 3.1.11 Retreatment,
- 3.1.12 Inspection,
- 3.1.13 Rejection and reheating,
- 3.1.14 Material test report,
- 3.1.15 Certification, and
- 3.1.16 Packaging, marking, and loading.

4. Chemical Composition

4.1 The steel shall conform to the requirements as to chemical composition specified in **Table 1**. and shall conform to applicable requirements specified in Specification **A480/A480M**.

5. Mechanical Properties

5.1 The material shall conform to the mechanical properties specified in **Table 2**.

5.2 When specified by the purchaser, Charpy impact tests shall be performed in accordance with Supplementary Requirement S1.

5.3 When specified by the purchaser, 1 % offset yield strength shall be measured and reported in accordance with Supplementary Requirement S3.

6. Materials for High-temperature Service

6.1 The austenitic *H* Types shall conform to an average grain size of ASTM No. 7 or coarser as measured by Test Methods **E112**.

6.2 Supplementary Requirement S2 shall be invoked when non-H grade austenitic stainless steels are ordered for ASME Code applications for service above 1000 °F [540 °C].

6.3 Grade S31060, unless otherwise specified in the purchase order, shall conform to an average grain size of ASTM No. 7 or coarser, as measured by Test Methods **E112**.

7. Keywords

7.1 architectural; building; chromium; chromium-manganese-nickel stainless steel; chromium-nickel stainless steel; construction

iTeh Standards
(<https://standards.itih.ai>)
Document Preview

[ASTM A240/A240M-22](#)

<https://standards.itih.ai/catalog/standards/sist/cda7262c-ad3b-4c64-98d5-8280dcf988b8/astm-a240-a240m-22>

TABLE 1 Chemical Composition Requirements, %^A

| UNS Desig. ^B | Type ^C | C ^D | Mn | P | S | Si | Cr | Ni | Mo | N | Cu | Other Elements ^{E,F} |
|-------------------------|----------------------|----------------|-------------|-------|-------|-----------|-----------|-----------|-----------|-----------|-----------|--|
| | | | | | | | | | | | | |
| N08020 | ... | 0.07 | 2.00 | 0.045 | 0.035 | 1.00 | 19.0–21.0 | 32.0–38.0 | 2.00–3.00 | ... | 3.00–4.00 | Nb 8xC min, 1.00 max |
| N08367 | ... | 0.030 | 2.00 | 0.040 | 0.030 | 1.00 | 20.0–22.0 | 23.5–25.5 | 6.0–7.0 | 0.18–0.25 | 0.75 | ... |
| N08700 | ... | 0.04 | 2.00 | 0.040 | 0.030 | 1.00 | 19.0–23.0 | 24.0–26.0 | 4.3–5.0 | ... | 0.50 | Nb 8xC min 0.40 max |
| N08800 | 800 ^G | 0.10 | 1.50 | 0.045 | 0.015 | 1.00 | 19.0–23.0 | 30.0–35.0 | ... | ... | 0.75 | Fe ^H 39.5 min Al 0.15–0.60 Ti 0.15–0.60 |
| N08810 | 800H ^G | 0.05–0.10 | 1.50 | 0.045 | 0.015 | 1.00 | 19.0–23.0 | 30.0–35.0 | ... | ... | 0.75 | Fe ^H 39.5 min Al 0.15–0.60 Ti 0.15–0.60 |
| N08811 | ... | 0.06–0.10 | 1.50 | 0.040 | 0.015 | 1.00 | 19.0–23.0 | 30.0–35.0 | ... | ... | 0.75 | Fe ^H 39.5 min Ti ^I 0.25–0.60 Al ^I 0.25–0.60 |
| N08904 | 904L ^G | 0.020 | 2.00 | 0.045 | 0.035 | 1.00 | 19.0–23.0 | 23.0–28.0 | 4.00–5.00 | 0.10 | 1.00–2.00 | ... |
| N08925 | ... | 0.020 | 1.00 | 0.045 | 0.030 | 0.50 | 19.0–21.0 | 24.0–26.0 | 6.00–7.00 | 0.10–0.20 | 0.80–1.50 | ... |
| N08926 | ... | 0.020 | 2.00 | 0.030 | 0.010 | 0.50 | 19.0–21.0 | 24.0–26.0 | 6.00–7.00 | 0.15–0.25 | 0.50–1.50 | ... |
| S20100 | 201 | 0.15 | 5.50–7.50 | 0.060 | 0.030 | 1.00 | 16.0–18.0 | 3.5–5.5 | ... | 0.25 | ... | ... |
| S20103 | ... | 0.03 | 5.50–7.50 | 0.045 | 0.030 | 0.75 | 16.0–18.0 | 3.5–5.5 | ... | 0.25 | ... | ... |
| S20153 | 201LN ^G | 0.03 | 6.40–7.50 | 0.045 | 0.015 | 0.75 | 16.0–17.5 | 4.0–5.0 | ... | 0.10–0.25 | 1.00 | ... |
| S20161 | ... | 0.15 | 4.00–6.00 | 0.040 | 0.040 | 3.00–4.00 | 15.0–18.0 | 4.0–6.0 | ... | 0.08–0.20 | ... | ... |
| S20200 | 202 | 0.15 | 7.50–10.00 | 0.060 | 0.030 | 1.00 | 17.0–19.0 | 4.0–6.0 | ... | 0.25 | ... | ... |
| S20400 | ... | 0.030 | 7.00–9.00 | 0.040 | 0.030 | 1.00 | 15.0–17.0 | 1.50–3.00 | ... | 0.15–0.30 | ... | ... |
| S20431 | ... | 0.12 | 5.00–7.00 | 0.045 | 0.030 | 1.00 | 17.0–18.0 | 2.0–4.0 | ... | 0.10–0.25 | 1.50–3.50 | ... |
| S20432 | ... | 0.08 | 3.00–5.00 | 0.045 | 0.030 | 1.00 | 17.0–18.0 | 4.0–6.0 | ... | 0.05–0.20 | 2.00–3.00 | ... |
| S20433 | ... | 0.08 | 5.50–7.50 | 0.045 | 0.030 | 1.00 | 17.0–18.0 | 3.5–5.5 | ... | 0.10–0.25 | 1.50–3.50 | ... |
| S20910 | XM-19 ^J | 0.06 | 4.00–6.00 | 0.040 | 0.030 | 0.75 | 20.5–23.5 | 11.5–13.5 | 1.50–3.00 | 0.20–0.40 | ... | Nb 0.10–0.30 V 0.10–0.30 |
| S21400 | XM-31 ^J | 0.12 | 14.00–16.00 | 0.045 | 0.030 | 0.30–1.00 | 17.0–18.5 | 1.00 | ... | 0.35 min | ... | ... |
| S21600 | XM-17 ^J | 0.08 | 7.50–9.00 | 0.045 | 0.030 | 0.75 | 17.5–22.0 | 5.0–7.0 | 2.00–3.00 | 0.25–0.50 | ... | ... |
| S21603 | XM-18 ^J | 0.03 | 7.50–9.00 | 0.045 | 0.030 | 0.75 | 17.5–22.0 | 5.0–7.0 | 2.00–3.00 | 0.25–0.50 | ... | ... |
| S21640 | ... | 0.08 | 3.50–6.50 | 0.060 | 0.030 | 1.00 | 17.5–19.5 | 4.0–6.5 | 0.50–2.00 | 0.08–0.30 | ... | Nb 0.10–1.00 |
| S21800 | ... | 0.10 | 7.00–9.00 | 0.060 | 0.030 | 3.5–4.5 | 16.0–18.0 | 8.0–9.0 | ... | 0.08–0.18 | ... | ... |
| S21904 | XM-11 ^J | 0.04 | 8.00–10.00 | 0.060 | 0.030 | 0.75 | 19.0–21.5 | 5.5–7.5 | ... | 0.15–0.40 | ... | ... |
| S24000 | XM-29 ^J | 0.08 | 11.50–14.50 | 0.060 | 0.030 | 0.75 | 17.0–19.0 | 2.3–3.7 | ... | 0.20–0.40 | ... | ... |
| S30100 | 301 | 0.15 | 2.00 | 0.045 | 0.030 | 1.00 | 16.0–18.0 | 6.0–8.0 | ... | 0.10 | ... | ... |
| S30103 | 301L ^G | 0.03 | 2.00 | 0.045 | 0.030 | 1.00 | 16.0–18.0 | 6.0–8.0 | ... | 0.20 | ... | ... |
| S30153 | 301LN ^G | 0.03 | 2.00 | 0.045 | 0.030 | 1.00 | 16.0–18.0 | 6.0–8.0 | ... | 0.07–0.20 | ... | ... |
| S30200 | 302 | 0.15 | 2.00 | 0.045 | 0.030 | 0.75 | 17.0–19.0 | 8.0–10.0 | ... | 0.10 | ... | ... |
| S30400 | 304 | 0.08 | 2.00 | 0.045 | 0.030 | 0.75 | 18.0–20.0 | 8.0–11.0 | ... | 0.10 | ... | ... |
| S30403 | 304L | 0.030 | 2.00 | 0.045 | 0.030 | 0.75 | 18.0–20.0 | 8.0–12.0 | ... | 0.10 | ... | ... |
| S30409 | 304H | 0.04–0.10 | 2.00 | 0.045 | 0.030 | 0.75 | 18.0–20.0 | 8.0–10.5 | ... | ... | ... | ... |
| S30415 | ... | 0.04–0.06 | 0.80 | 0.045 | 0.030 | 1.00–2.00 | 18.0–19.0 | 9.0–10.0 | ... | 0.12–0.18 | ... | Ce 0.03–0.08 |
| S30435 | ... | 0.08 | 2.00 | 0.045 | 0.030 | 1.00 | 16.0–18.0 | 7.0–9.0 | ... | ... | 1.50–3.00 | ... |
| S30441 | ... | 0.08 | 2.00 | 0.045 | 0.030 | 1.0–2.0 | 17.5–19.5 | 8.0–10.5 | ... | 0.10 | 1.5–2.5 | Nb 0.1–0.5 W 0.2–0.8 |
| S30451 | 304N | 0.08 | 2.00 | 0.045 | 0.030 | 0.75 | 18.0–20.0 | 8.0–10.5 | ... | 0.10–0.16 | ... | ... |
| S30452 | XM-21 ^J | 0.08 | 2.00 | 0.045 | 0.030 | 0.75 | 18.0–20.0 | 8.0–10.5 | ... | 0.16–0.30 | ... | ... |
| S30453 | 304LN | 0.030 | 2.00 | 0.045 | 0.030 | 0.75 | 18.0–20.0 | 8.0–12.0 | ... | 0.10–0.16 | ... | ... |
| S30500 | 305 | 0.12 | 2.00 | 0.045 | 0.030 | 0.75 | 17.0–19.0 | 10.5–13.0 | ... | ... | ... | ... |
| S30530 | ... | 0.08 | 2.00 | 0.045 | 0.030 | 0.50–2.50 | 17.0–20.5 | 8.5–11.5 | 0.75–1.50 | ... | 0.75–3.50 | ... |
| S30600 | ... | 0.018 | 2.00 | 0.020 | 0.020 | 3.7–4.3 | 17.0–18.5 | 14.0–15.5 | 0.20 | ... | 0.50 | ... |
| S30616 | ... | 0.020 | 1.50 | 0.030 | 0.015 | 3.9–4.7 | 16.5–18.5 | 13.0–15.5 | 0.50 | ... | 0.40 | Nb 0.30–0.70 |
| S30601 | ... | 0.015 | 0.50–0.80 | 0.030 | 0.013 | 5.0–5.6 | 17.0–18.0 | 17.0–18.0 | 0.20 | 0.05 | 0.35 | ... |
| S30615 | ... | 0.16–0.24 | 2.00 | 0.030 | 0.030 | 3.2–4.0 | 17.0–19.5 | 13.5–16.0 | ... | ... | ... | Al 0.80–1.50 |
| S30815 | ... | 0.05–0.10 | 0.80 | 0.040 | 0.030 | 1.40–2.00 | 20.0–22.0 | 10.0–12.0 | ... | 0.14–0.20 | ... | Ce 0.03–0.08 |
| S30908 | 309S | 0.08 | 2.00 | 0.045 | 0.030 | 0.75 | 22.0–24.0 | 12.0–15.0 | ... | ... | ... | ... |
| S30909 | 309H ^G | 0.04–0.10 | 2.00 | 0.045 | 0.030 | 0.75 | 22.0–24.0 | 12.0–15.0 | ... | ... | ... | ... |
| S30940 | 309Cb ^G | 0.08 | 2.00 | 0.045 | 0.030 | 0.75 | 22.0–24.0 | 12.0–16.0 | ... | ... | ... | Nb 10xC min, 1.10 max |
| S30941 | 309HCb ^G | 0.04–0.10 | 2.00 | 0.045 | 0.030 | 0.75 | 22.0–24.0 | 12.0–16.0 | ... | ... | ... | Nb 10xC min, 1.10 max |
| S31008 | 310S | 0.08 | 2.00 | 0.045 | 0.030 | 1.50 | 24.0–26.0 | 19.0–22.0 | ... | ... | ... | ... |
| S31009 | 310H ^G | 0.04–0.10 | 2.00 | 0.045 | 0.030 | 0.75 | 24.0–26.0 | 19.0–22.0 | ... | ... | ... | ... |
| S31040 | 310Cb ^G | 0.08 | 2.00 | 0.045 | 0.030 | 1.50 | 24.0–26.0 | 19.0–22.0 | ... | ... | ... | Nb 10xC min, 1.10 max |
| S31041 | 310HCb ^G | 0.04–0.10 | 2.00 | 0.045 | 0.030 | 0.75 | 24.0–26.0 | 19.0–22.0 | ... | ... | ... | Nb 10xC min, 1.10 max |
| S31050 | 310MoLN ^G | 0.020 | 2.00 | 0.030 | 0.010 | 0.50 | 24.0–26.0 | 20.5–23.5 | 1.60–2.60 | 0.09–0.15 | ... | ... |
| S31060 | ... | 0.05–0.10 | 1.00 | 0.040 | 0.030 | 0.50 | 22.0–24.0 | 10.0–12.5 | ... | 0.18–0.25 | ... | Ce + La 0.025–0.070 B 0.001–0.010 |
| S31254 | ... | 0.020 | 1.00 | 0.030 | 0.010 | 0.80 | 19.5–20.5 | 17.5–18.5 | 6.0–6.5 | 0.18–0.25 | 0.50–1.00 | ... |
| S31266 | ... | 0.030 | 2.00–4.00 | 0.035 | 0.020 | 1.00 | 23.0–25.0 | 21.0–24.0 | 5.2–6.2 | 0.35–0.60 | 1.00–2.50 | W 1.50–2.50 |
| S31277 | ... | 0.020 | 3.00 | 0.030 | 0.010 | 0.50 | 20.5–23.0 | 26.0–28.0 | 6.5–8.0 | 0.30–0.40 | 0.50–1.50 | ... |
| S31600 | 316 | 0.08 | 2.00 | 0.045 | 0.030 | 0.75 | 16.0–18.0 | 10.0–14.0 | 2.00–3.00 | 0.10 | ... | ... |
| S31603 | 316L | 0.030 | 2.00 | 0.045 | 0.030 | 0.75 | 16.0–18.0 | 10.0–14.0 | 2.00–3.00 | 0.10 | ... | ... |
| S31609 | 316H | 0.04–0.10 | 2.00 | 0.045 | 0.030 | 0.75 | 16.0–18.0 | 10.0–14.0 | 2.00–3.00 | ... | ... | ... |

TABLE 1 *Continued*

| UNS Desig. ^B | Type ^C | C ^D | Mn | P | S | Si | Cr | Ni | Mo | N | Cu | Other Elements ^{E,F} |
|------------------------------|---------------------|----------------|-----------|-------|-------|-----------|-----------|-----------|-----------|-----------|-----------|---|
| S31635 | 316Ti ^G | 0.08 | 2.00 | 0.045 | 0.030 | 0.75 | 16.0–18.0 | 10.0–14.0 | 2.00–3.00 | 0.10 | ... | Ti 5x(C+N) min, 0.70 max |
| S31640 | 316Cb ^G | 0.08 | 2.00 | 0.045 | 0.030 | 0.75 | 16.0–18.0 | 10.0–14.0 | 2.00–3.00 | 0.10 | ... | Nb 10xC min, 1.10 max |
| S31651 | 316N | 0.08 | 2.00 | 0.045 | 0.030 | 0.75 | 16.0–18.0 | 10.0–14.0 | 2.00–3.00 | 0.10–0.16 | ... | ... |
| S31653 | 316LN | 0.030 | 2.00 | 0.045 | 0.030 | 0.75 | 16.0–18.0 | 10.0–14.0 | 2.00–3.00 | 0.10–0.16 | ... | ... |
| S31655 | ... | 0.030 | 2.00 | 0.045 | 0.015 | 1.00 | 19.5–21.5 | 8.0–9.5 | 0.50–1.50 | 0.14–0.25 | 1.00 | ... |
| S31700 | 317 | 0.08 | 2.00 | 0.045 | 0.030 | 0.75 | 18.0–20.0 | 11.0–15.0 | 3.0–4.0 | 0.10 | ... | ... |
| S31703 | 317L | 0.030 | 2.00 | 0.045 | 0.030 | 0.75 | 18.0–20.0 | 11.0–15.0 | 3.0–4.0 | 0.10 | ... | ... |
| S31725 | 317LM ^G | 0.030 | 2.00 | 0.045 | 0.030 | 0.75 | 18.0–20.0 | 13.5–17.5 | 4.0–5.0 | 0.20 | ... | ... |
| S31726 | 317LMN ^G | 0.030 | 2.00 | 0.045 | 0.030 | 0.75 | 17.0–20.0 | 13.5–17.5 | 4.0–5.0 | 0.10–0.20 | ... | ... |
| S31727 | ... | 0.030 | 1.00 | 0.030 | 0.030 | 1.00 | 17.5–19.0 | 14.5–16.5 | 3.8–4.5 | 0.15–0.21 | 2.80–4.00 | ... |
| S31730 | ... | 0.030 | 2.00 | 0.040 | 0.010 | 1.00 | 17.0–19.0 | 15.0–16.5 | 3.0–4.0 | 0.045 | 4.0–5.0 | ... |
| S31753 | 317LN ^G | 0.030 | 2.00 | 0.045 | 0.030 | 0.75 | 18.0–20.0 | 11.0–15.0 | 3.0–4.0 | 0.10–0.22 | ... | ... |
| S32050 | ... | 0.030 | 1.50 | 0.035 | 0.020 | 1.00 | 22.0–24.0 | 20.0–23.0 | 6.0–6.8 | 0.21–0.32 | 0.40 | ... |
| S32053 | ... | 0.030 | 1.00 | 0.030 | 0.010 | 1.00 | 22.0–24.0 | 24.0–26.0 | 5.0–6.0 | 0.17–0.22 | ... | ... |
| S32100 | 321 | 0.08 | 2.00 | 0.045 | 0.030 | 0.75 | 17.0–19.0 | 9.0–12.0 | ... | 0.10 | ... | Ti 5x(C+N) min, 0.70 max |
| S32109 | 321H | 0.04–0.10 | 2.00 | 0.045 | 0.030 | 0.75 | 17.0–19.0 | 9.0–12.0 | ... | ... | ... | Ti 4x(C+N) min, 0.70 max |
| S32615 | ... | 0.07 | 2.00 | 0.045 | 0.030 | 4.80–6.00 | 16.5–19.5 | 19.0–22.0 | 0.30–1.50 | ... | 1.50–2.50 | ... |
| S32654 | ... | 0.020 | 2.00–4.00 | 0.030 | 0.005 | 0.50 | 24.0–25.0 | 21.0–23.0 | 7.0–8.0 | 0.45–0.55 | 0.30–0.60 | ... |
| S33228 | ... | 0.04–0.08 | 1.00 | 0.020 | 0.015 | 0.30 | 26.0–28.0 | 31.0–33.0 | ... | ... | ... | Ce 0.05–0.10 Nb 0.6–1.0 Al 0.025 |
| S33400 | 334 ^G | 0.08 | 1.00 | 0.030 | 0.015 | 1.00 | 18.0–20.0 | 19.0–21.0 | ... | ... | ... | Al 0.15–0.60 Ti 0.15–0.60 |
| S33425 | ... | 0.08 | 1.50 | 0.045 | 0.020 | 1.00 | 21.0–23.0 | 20.0–23.0 | 2.00–3.00 | ... | ... | Al 0.15–0.60 Ti 0.15–0.60 |
| S33426 | ... | 0.030 | 1.00 | 0.030 | 0.015 | 0.80–1.50 | 19.5–22.0 | 19.0–21.0 | 1.80–2.20 | ... | ... | ... |
| S33550 | ... | 0.04–0.10 | 1.50 | 0.040 | 0.030 | 1.00 | 25.0–28.0 | 16.5–20.0 | ... | 0.18–0.25 | ... | Nb 0.05–0.15 La+Ce 0.025–0.070 Nb 0.10 |
| S34565 | ... | 0.030 | 5.00–7.00 | 0.030 | 0.010 | 1.00 | 23.0–25.0 | 16.0–18.0 | 4.0–5.0 | 0.40–0.60 | ... | Nb 10xC min, 1.00 max |
| S34700 | 347 | 0.08 | 2.00 | 0.045 | 0.030 | 0.75 | 17.0–19.0 | 9.0–13.0 | ... | ... | ... | Nb 8xC min, 1.00 max |
| S34709 | 347H | 0.04–0.10 | 2.00 | 0.045 | 0.030 | 0.75 | 17.0–19.0 | 9.0–13.0 | ... | ... | ... | Nb 0.20–0.50, 15xC min |
| S34751 | 347LN | 0.005–0.020 | 2.00 | 0.045 | 0.030 | 1.00 | 17.0–19.0 | 9.0–13.0 | ... | 0.06–0.10 | ... | Nb 0.20–0.50 B 0.001–0.005 |
| S34752 | ... | 0.005–0.02 | 2.00 | 0.035 | 0.010 | 0.60 | 17.0–19.0 | 10.0–13.0 | 0.20–1.20 | 0.06–0.12 | 2.50–3.50 | Nb/C ratio, min 15 (Nb+Ta) 10xC min, 1.00 max Ta 0.10 Co 0.20 |
| S34800 | 348 | 0.08 | 2.00 | 0.045 | 0.030 | 0.75 | 17.0–19.0 | 9.0–13.0 | ... | ... | ... | (Nb+Ta) 8xC min, 1.00 max Ta 0.10 Co 0.20 |
| S34809 | 348H | 0.04–0.10 | 2.00 | 0.045 | 0.030 | 0.75 | 17.0–19.0 | 9.0–13.0 | ... | ... | ... | (Nb+Ta) 8xC min, 1.00 max Ta 0.10 Co 0.20 |
| S35045 | ... | 0.06–0.10 | 1.50 | 0.045 | 0.015 | 1.00 | 25.0–29.0 | 32.0–37.0 | ... | ... | 0.75 | Al 0.15–0.60 Ti 0.15–0.60 |
| S35115 | ... | 0.030 | 1.00 | 0.045 | 0.015 | 0.50–1.50 | 23.0–25.0 | 19.0–22.0 | 1.50–2.50 | 0.20–0.30 | ... | ... |
| S35125 | ... | 0.10 | 1.00–1.50 | 0.045 | 0.015 | 0.50 | 20.0–23.0 | 31.0–35.0 | 2.00–3.00 | ... | ... | Nb 0.25–0.60 |
| S35135 | ... | 0.08 | 1.00 | 0.045 | 0.015 | 0.60–1.00 | 20.0–25.0 | 30.0–38.0 | 4.0–4.8 | ... | 0.75 | Ti 0.40–1.00 |
| S35140 | ... | 0.10 | 1.00–3.00 | 0.045 | 0.030 | 0.75 | 20.0–22.0 | 25.0–27.0 | 1.00–2.00 | 0.08–0.20 | ... | Nb 0.25–0.75 |
| S35315 | ... | 0.04–0.08 | 2.00 | 0.040 | 0.030 | 1.20–2.00 | 24.0–26.0 | 34.0–36.0 | ... | 0.12–0.18 | ... | Ce 0.03–0.10 |
| S38100 | XM-15 ^J | 0.08 | 2.00 | 0.030 | 0.030 | 1.50–2.50 | 17.0–19.0 | 17.5–18.5 | ... | ... | ... | ... |
| S38815 | ... | 0.030 | 2.00 | 0.040 | 0.020 | 5.50–6.50 | 13.0–15.0 | 15.0–17.0 | 0.75–1.50 | ... | 0.75–1.50 | Al 0.30 |
| Duplex (Austenitic-Ferritic) | | | | | | | | | | | | |
| S31200 | ... | 0.030 | 2.00 | 0.045 | 0.030 | 1.00 | 24.0–26.0 | 5.5–6.5 | 1.20–2.00 | 0.14–0.20 | ... | ... |
| S31260 | ... | 0.03 | 1.00 | 0.030 | 0.030 | 0.75 | 24.0–26.0 | 5.5–7.5 | 2.5–3.5 | 0.10–0.30 | 0.20–0.80 | W 0.10–0.50 |
| S31803 | ... | 0.030 | 2.00 | 0.030 | 0.020 | 1.00 | 21.0–23.0 | 4.5–6.5 | 2.5–3.5 | 0.08–0.20 | ... | ... |
| S32001 | ... | 0.030 | 4.00–6.00 | 0.040 | 0.030 | 1.00 | 19.5–21.5 | 1.00–3.00 | 0.60 | 0.05–0.17 | 1.00 | ... |
| S32003 | ... | 0.030 | 2.00 | 0.030 | 0.020 | 1.00 | 19.5–22.5 | 3.0–4.0 | 1.50–2.00 | 0.14–0.20 | ... | ... |
| S32101 | ... | 0.040 | 4.00–6.00 | 0.040 | 0.030 | 1.00 | 21.0–22.0 | 1.35–1.70 | 0.10–0.80 | 0.20–0.25 | 0.10–0.80 | ... |
| S32202 | ... | 0.030 | 2.00 | 0.040 | 0.010 | 1.00 | 21.5–24.0 | 1.00–2.80 | 0.45 | 0.18–0.26 | ... | ... |
| S32205 | 2205 ^G | 0.030 | 2.00 | 0.030 | 0.020 | 1.00 | 22.0–23.0 | 4.5–6.5 | 3.0–3.5 | 0.14–0.20 | ... | ... |
| S32304 | 2304 ^G | 0.030 | 2.50 | 0.040 | 0.030 | 1.00 | 21.5–24.5 | 3.0–5.5 | 0.05–0.60 | 0.05–0.20 | 0.05–0.60 | ... |
| S32506 | ... | 0.030 | 1.00 | 0.040 | 0.015 | 0.90 | 24.0–26.0 | 5.5–7.2 | 3.0–3.5 | 0.08–0.20 | ... | W 0.05–0.30 |
| S32520 | ... | 0.030 | 1.50 | 0.035 | 0.020 | 0.80 | 24.0–26.0 | 5.5–8.0 | 3.0–4.0 | 0.20–0.35 | 0.50–2.00 | ... |
| S32550 | 255 ^G | 0.04 | 1.50 | 0.040 | 0.030 | 1.00 | 24.0–27.0 | 4.5–6.5 | 2.9–3.9 | 0.10–0.25 | 1.50–2.50 | ... |
| S32750 | 2507 ^{G,O} | 0.030 | 1.20 | 0.035 | 0.020 | 0.80 | 24.0–26.0 | 6.0–8.0 | 3.0–5.0 | 0.24–0.32 | 0.50 | ... |
| S32760 ^K | ... | 0.030 | 1.00 | 0.030 | 0.010 | 1.00 | 24.0–26.0 | 6.0–8.0 | 3.0–4.0 | 0.20–0.30 | 0.50–1.00 | W 0.50–1.00 |
| S32808 | ... | 0.030 | 1.10 | 0.030 | 0.010 | 0.50 | 27.0–27.9 | 7.0–8.2 | 0.80–1.2 | 0.30–0.40 | ... | W 2.10–2.50 |
| S32900 | 329 | 0.08 | 1.00 | 0.040 | 0.030 | 0.75 | 23.0–28.0 | 2.0–5.00 | 1.00–2.00 | ... | ... | ... |
| S32906 | ... | 0.030 | 0.80–1.50 | 0.030 | 0.030 | 0.80 | 28.0–30.0 | 5.8–7.5 | 1.50–2.60 | 0.30–0.40 | 0.80 | ... |

TABLE 1 *Continued*

| UNS Desig. ^B | Type ^C | C ^D | Mn | P | S | Si | Cr | Ni | Mo | N | Cu | Other Elements ^{E,F} |
|------------------------------------|--------------------|----------------|-----------|-------|--------|---------|-----------|-----------|-----------|----------------------|-----------|---|
| S32950 | ... | 0.030 | 2.00 | 0.035 | 0.010 | 0.60 | 26.0–29.0 | 3.5–5.2 | 1.00–2.50 | 0.15–0.35 | ... | ... |
| S39274 | ... | 0.030 | 1.00 | 0.030 | 0.020 | 0.80 | 24.0–26.0 | 6.0–8.0 | 2.5–3.5 | 0.24–0.32 | 0.20–0.80 | W 1.50–2.50 |
| S81921 | ... | 0.030 | 2.00–4.00 | 0.040 | 0.030 | 1.00 | 19.0–22.0 | 2.0–4.0 | 1.00–2.00 | 0.14–0.20 | ... | ... |
| S82011 | ... | 0.030 | 2.00–3.00 | 0.040 | 0.020 | 1.00 | 20.5–23.5 | 1.0–2.0 | 0.10–1.00 | 0.15–0.27 | ... | ... |
| S82012 | ... | 0.05 | 2.00–4.00 | 0.040 | 0.005 | 0.80 | 19.0–20.5 | 0.8–1.5 | 0.10–0.60 | 0.16–0.26 | 1.00 | ... |
| S82013 | ... | 0.060 | 2.50–3.50 | 0.040 | 0.030 | 0.90 | 19.5–22.0 | 0.5–1.5 | ... | 0.20–0.30 | 0.20–1.20 | ... |
| S82031 | ... | 0.05 | 2.50 | 0.040 | 0.005 | 0.80 | 19.0–22.0 | 2.0–4.0 | 0.60–1.40 | 0.14–0.24 | 1.00 | ... |
| S82121 | ... | 0.035 | 1.00–2.50 | 0.040 | 0.010 | 1.00 | 21.0–23.0 | 2.0–4.0 | 0.30–1.30 | 0.15–0.25 | 0.20–1.20 | ... |
| S82122 | ... | 0.030 | 2.0–4.0 | 0.040 | 0.020 | 0.75 | 20.5–21.5 | 1.5–2.5 | 0.60 | 0.15–0.20 | 0.50–1.50 | ... |
| S82441 | ... | 0.030 | 2.50–4.00 | 0.035 | 0.005 | 0.70 | 23.0–25.0 | 3.0–4.5 | 1.00–2.00 | 0.20–0.30 | 0.10–0.80 | ... |
| Ferritic or Martensitic (Chromium) | | | | | | | | | | | | |
| S32803 | ... | 0.015 | 0.50 | 0.020 | 0.0035 | 0.55 | 28.0–29.0 | 3.0–4.0 | 1.80–2.50 | 0.020 (C+N) 0.030 | ... | Nb 12×(C+N) min, 0.15–0.50 |
| S40300 | 403 | 0.15 | 1.00 | 0.040 | 0.030 | 0.50 | 11.5–13.0 | 0.60 | ... | ... | ... | ... |
| S40500 | 405 | 0.08 | 1.00 | 0.040 | 0.030 | 1.00 | 11.5–14.5 | 0.60 | ... | ... | ... | Al 0.10–0.30 |
| S40900 ^L | 409 ^L | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... |
| S40910 | ... | 0.030 | 1.00 | 0.040 | 0.020 | 1.00 | 10.5–11.7 | 0.50 | ... | 0.030 | ... | Ti 6×(C+N) min, 0.50 max; Nb 0.17 |
| S40920 | ... | 0.030 | 1.00 | 0.040 | 0.020 | 1.00 | 10.5–11.7 | 0.50 | ... | 0.030 | ... | Ti 8×(C+N) min, Ti 0.15–0.50; Nb 0.10 |
| S40930 | ... | 0.030 | 1.00 | 0.040 | 0.020 | 1.00 | 10.5–11.7 | 0.50 | ... | 0.030 | ... | (Ti+Nb) [0.08+8×(C+N)] min, 0.75 max; Ti 0.05 min |
| S40945 | ... | 0.030 | 1.00 | 0.040 | 0.030 | 1.00 | 10.5–11.7 | 0.50 | ... | 0.030 | ... | Nb 0.18–0.40 Ti 0.05–0.20 |
| S40975 | ... | 0.030 | 1.00 | 0.040 | 0.030 | 1.00 | 10.5–11.7 | 0.50–1.00 | ... | 0.030 | ... | Ti 6×(C+N) min, 0.75 max |
| S40977 | ... | 0.030 | 1.50 | 0.040 | 0.015 | 1.00 | 10.5–12.5 | 0.30–1.00 | ... | 0.030 | ... | ... |
| S41000 | 410 | 0.08–0.15 | 1.00 | 0.040 | 0.030 | 1.00 | 11.5–13.5 | 0.75 | ... | ... | ... | ... |
| S41003 | ... | 0.030 | 1.50 | 0.040 | 0.030 | 1.00 | 10.5–12.5 | 1.50 | ... | 0.030 | ... | ... |
| S41008 | 410S | 0.08 | 1.00 | 0.040 | 0.030 | 1.00 | 11.5–13.5 | 0.60 | ... | ... | ... | ... |
| S41045 | ... | 0.030 | 1.00 | 0.040 | 0.030 | 1.00 | 12.0–13.0 | 0.50 | ... | 0.030 | ... | Nb 9×(C+N) min, 0.60 max |
| S41050 | ... | 0.04 | 1.00 | 0.045 | 0.030 | 1.00 | 10.5–12.5 | 0.60–1.10 | ... | 0.10 | ... | ... |
| S41500 ^M | ... | 0.05 | 0.50–1.00 | 0.030 | 0.030 | 0.60 | 11.5–14.0 | 3.5–5.5 | 0.50–1.00 | ... | ... | ... |
| S42000 | 420 | 0.15 min | 1.00 | 0.040 | 0.030 | 1.00 | 12.0–14.0 | 0.75 | 0.50 | ... | ... | ... |
| S42035 | ... | 0.08 | 1.00 | 0.045 | 0.030 | 1.00 | 13.5–15.5 | 1.0–2.5 | 0.2–1.2 | ... | ... | Ti 0.30–0.50 |
| S42200 | 422 | 0.20–0.25 | 0.50–1.00 | 0.025 | 0.025 | 0.50 | 11.0–12.5 | 0.50–1.00 | 0.90–1.25 | ... | ... | V 0.20–0.30, W 0.90–1.25 |
| S42900 | 429 ^G | 0.12 | 1.00 | 0.040 | 0.030 | 1.00 | 14.0–16.0 | ... | ... | ... | ... | ... |
| S43000 | 430 | 0.12 | 1.00 | 0.040 | 0.030 | 1.00 | 16.0–18.0 | 0.75 | ... | ... | ... | ... |
| S43035 | 439 | 0.030 | 1.00 | 0.040 | 0.030 | 1.00 | 17.0–19.0 | 0.50 | ... | 0.030 | ... | Ti [0.20+4(C+N)] min, 1.10 max; Al 0.15 |
| S43037 | ... | 0.030 | 1.00 | 0.040 | 0.030 | 1.00 | 16.0–19.0 | ... | ... | ... | ... | Ti 0.10–1.00 |
| S43100 | 431 | 0.20 | 1.00 | 0.040 | 0.030 | 1.00 | 15.0–17.0 | 1.25–2.50 | ... | ... | ... | ... |
| S43400 | 434 | 0.12 | 1.00 | 0.040 | 0.030 | 1.00 | 16.0–18.0 | ... | 0.75–1.25 | ... | ... | ... |
| S43600 | 436 | 0.12 | 1.00 | 0.040 | 0.030 | 1.00 | 16.0–18.0 | ... | 0.75–1.25 | ... | ... | Nb 5×C min, 0.80 max |
| S43932 | ... | 0.030 | 1.00 | 0.040 | 0.030 | 1.00 | 17.0–19.0 | 0.50 | ... | 0.030 | ... | (Ti+Nb) [0.20+4(C+N)] min, 0.75 max; Al 0.15 |
| S43940 | ... | 0.030 | 1.00 | 0.040 | 0.015 | 1.00 | 17.5–18.5 | ... | ... | ... | ... | Ti 0.10–0.60 Nb [0.30+(3×C)] min |
| S44100 | ... | 0.030 | 1.00 | 0.040 | 0.030 | 1.00 | 17.5–19.5 | 1.00 | ... | 0.030 | ... | Ti 0.1–0.5 Nb [0.3+(9×C)] min, 0.90 max |
| S44200 | 442 | 0.20 | 1.00 | 0.040 | 0.040 | 1.00 | 18.0–23.0 | 0.60 | ... | ... | ... | ... |
| S44330 | ... | 0.025 | 1.00 | 0.040 | 0.030 | 1.00 | 20.0–23.0 | ... | ... | 0.025 | 0.30–0.80 | (Ti+Nb) 8×(C+N) min, 0.80 max |
| S44400 | 444 | 0.025 | 1.00 | 0.040 | 0.030 | 1.00 | 17.5–19.5 | 1.00 | 1.75–2.50 | 0.035 | ... | (Ti+Nb)[0.20+4(C+N)] min, 0.80 max |
| S44500 | ... | 0.020 | 1.00 | 0.040 | 0.012 | 1.00 | 19.0–21.0 | 0.60 | ... | 0.03 | 0.30–0.60 | Nb 10×(C+N) min, 0.80 max |
| S44535 | ... | 0.030 | 0.30–0.80 | 0.050 | 0.020 | 0.50 | 20.0–24.0 | ... | ... | ... | 0.50 | La 0.04–0.20 Ti 0.03–0.20 Al 0.50 |
| S44536 | ... | 0.015 | 1.00 | 0.040 | 0.030 | 1.00 | 20.0–23.0 | 0.5 | ... | 0.015 | ... | (Ti+Nb) 8×(C+N)–0.8, Nb min 0.05 |
| S44537 | ... | 0.030 | 0.8 | 0.050 | 0.006 | 0.1–0.6 | 20.0–24.0 | 0.5 | ... | 0.04 | 0.5 | Al 0.1 W 1.0–3.0 Nb 0.2–1.0 Ti 0.02–0.20 La 0.04–0.20 |
| S44626 | XM-33 ^J | 0.06 | 0.75 | 0.040 | 0.020 | 0.75 | 25.0–27.0 | 0.50 | 0.75–1.50 | 0.04 | 0.20 | Ti 0.20–1.00; Ti 7(C+N) min |

TABLE 1 *Continued*

| UNS Desig. ^B | Type ^C | C ^D | Mn | P | S | Si | Cr | Ni | Mo | N | Cu | Other Elements ^{E,F} |
|-------------------------|--------------------|--------------------|------|-------|-------|-------|-----------|-----------|-----------|--------------------|------|---|
| S44627 | XM-27 ^J | 0.010 ^N | 0.40 | 0.020 | 0.020 | 0.40 | 25.0–27.5 | 0.50 | 0.75–1.50 | 0.015 ^N | 0.20 | Nb 0.05–0.20 (Ni+Cu) 0.50 |
| S44635 | ... | 0.025 | 1.00 | 0.040 | 0.030 | 0.75 | 24.5–26.0 | 3.5–4.5 | 3.5–4.5 | 0.035 | ... | (Ti+Nb) [0.20+4 (C+N)] min, 0.80 max |
| S44600 | 446 | 0.20 | 1.50 | 0.040 | 0.030 | 1.00 | 23.0–27.0 | 0.75 | ... | 0.25 | ... | ... |
| S44660 | ... | 0.030 | 1.00 | 0.040 | 0.030 | 1.00 | 25.0–28.0 | 1.0–3.5 | 3.0–4.0 | 0.040 | ... | (Ti+Nb) 0.20–1.00, Ti+Nb 6×(C+N) min (C+N) 0.025 |
| S44700 | ... | 0.010 | 0.30 | 0.025 | 0.020 | 0.20 | 28.0–30.0 | 0.15 | 3.5–4.2 | 0.020 | 0.15 | (Ti+Nb) ≥ 8×(C+N) |
| S44725 | ... | 0.015 | 0.40 | 0.040 | 0.020 | 0.040 | 25.0–28.5 | 0.30 | 1.5–2.5 | 0.018 | ... | (Ti+Nb) 0.20–1.00, |
| S44735 | ... | 0.030 | 1.00 | 0.040 | 0.030 | 1.00 | 28.0–30.0 | 1.00 | 3.6–4.2 | 0.045 | ... | (Ti+Nb) 6×(C+N) min (C+N) 0.025 |
| S44800 | ... | 0.010 | 0.30 | 0.025 | 0.020 | 0.20 | 28.0–30.0 | 2.00–2.50 | 3.5–4.2 | 0.020 | 0.15 | Ti 0.07–0.30 |
| S46800 | ... | 0.030 | 1.00 | 0.040 | 0.030 | 1.00 | 18.0–20.0 | 0.50 | ... | 0.030 | ... | Nb 0.10–0.60 (Ti+Nb) [0.20+4 (C+N)] min, 0.80 max |

^A Maximum, unless range or minimum is indicated. Where ellipses (. . .) appear in this table, there is no requirement and the element need not be determined or reported.

^B Designation established in accordance with Practice E527 and SAE J 1086.

^C Unless otherwise indicated, a grade designation originally assigned by the American Iron and Steel Institute (AISI).

^D Carbon analysis shall be reported to nearest 0.01 % except for the low-carbon types, which shall be reported to nearest 0.001 %.

^E The terms columbium (Cb) and niobium (Nb) both refer to the same element.

^F When two minimums or two maximums are listed for a single type, as in the case of both a value from a formula and an absolute value, the higher minimum or lower maximum shall apply.

^G Common name, not a trademark, widely used, not associated with any one producer.

^H Iron shall be determined arithmetically by difference of 100 minus the sum of the other specified elements.

^I (Al + Ti) 0.85–1.20.

^J Naming system developed and applied by ASTM.

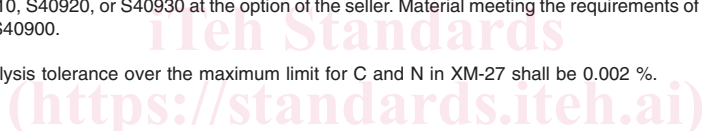
^K Cr + 3.3 (Mo + ½ W) + 16 N = 41 min.

^L S40900 (Type 409) has been replaced by S40910, S40920, and S40930. Unless otherwise specified in the ordering information, an order specifying S40900 or Type 409 shall be satisfied by any one of S40910, S40920, or S40930 at the option of the seller. Material meeting the requirements of S40910, S40920, or S40930, may at the option of the manufacturer be certified as S40900.

^M Plate version of CA-6NM.

^N Product (check or verification) analysis tolerance over the maximum limit for C and N in XM-27 shall be 0.002 %.

^O Cr + 3.3 Mo + 16 N = 41 min.


<https://standards.iteh.ai>
 Document Preview

ASTM A240/A240M-22

<https://standards.iteh.ai/catalog/standards/sist/cda7262c-ad3b-4c64-98d5-8280dcf988b8/astm-a240-a240m-22>

TABLE 2 Mechanical Test Requirements

| UNS Designation | Type ^A | Tensile Strength, min | | Yield Strength, ^B min | | Elongation in 2 in. or 50 mm, min, % | Hardness, max ^C | | Cold Bend ^D |
|-----------------|--------------------|------------------------------|-----|----------------------------------|------------------|--|----------------------------|----------|------------------------|
| | | ksi | MPa | ksi | MPa | | Brinell, HBW | Rockwell | |
| | | Austenitic (Chromium-Nickel) | | (Chromium-Manganese-Nickel) | | | | | |
| N08020 | ... | 80 | 550 | 35 | 240 | 30 ^F | 217 | 95 HRBW | not required |
| N08367 | | | | | | | | | |
| Sheet and Strip | | 100 | 690 | 45 | 310 | 30 | ... | 100 HRBW | not required |
| Plate | | 95 | 655 | 45 | 310 | 30 | 241 | ... | not required |
| N08700 | ... | 80 | 550 | 35 | 240 | 30 | 192 | 90 HRBW | not required |
| N08800 | 800 ^F | 75 | 520 | 30 ^G | 205 ^G | 30 ^H | ... | ... | not required |
| N08810 | 800H ^F | 65 | 450 | 25 ^G | 170 ^G | 30 | ... | ... | not required |
| N08811 | ... | 65 | 450 | 25 | 170 | 30 | ... | ... | not required |
| N08904 | 904L ^F | 71 | 490 | 31 | 220 | 35 | ... | 90 HRBW | not required |
| N08925 | ... | 87 | 600 | 43 | 295 | 40 | ... | ... | not required |
| N08926 | ... | 94 | 650 | 43 | 295 | 35 | ... | ... | not required |
| S20100 | 201-1 ^I | 75 | 515 | 38 | 260 | 40 | 217 | 95 HRBW | ... |
| S20100 | 201-2 ^I | 95 | 655 | 45 | 310 | 40 | 241 | 100 HRBW | ... |
| S20103 | 201L ^F | 95 | 655 | 38 | 260 | 40 | 217 | 95 HRBW | not required |
| S20153 | 201LN ^F | 95 | 655 | 45 | 310 | 45 | 241 | 100 HRBW | not required |
| S20161 | ... | 125 | 860 | 50 | 345 | 40 | 255 | 25 HRC | not required |
| S20200 | 202 | 90 | 620 | 38 | 260 | 40 | 241 | ... | ... |
| S20400 | ... | 95 | 655 | 48 | 330 | 35 | 241 | 100 HRBW | not required |
| S20431 | ... | 90 | 620 | 45 | 310 | 40 | 241 | 100 HRBW | not required |
| S20432 | ... | 75 | 515 | 30 | 205 | 40 | 201 | 92 HRBW | not required |
| S20433 | ... | 80 | 550 | 35 | 240 | 40 | 217 | 95 HRBW | not required |
| S20910 | XM-19 ^J | | | | | | | | |
| Sheet and Strip | | 105 | 725 | 60 | 415 | 30 | 241 | 100 HRBW | not required |
| Plate | | 100 | 690 | 55 | 380 | 35 | 241 | 100 HRBW | not required |
| S21600 | XM-17 ^J | | | | | | | | |
| Sheet and Strip | | 100 | 690 | 60 | 415 | 40 | 241 | 100 HRBW | not required |
| Plate | | 90 | 620 | 50 | 345 | 40 | 241 | 100 HRBW | not required |
| S21603 | XM-18 ^J | | | | | | | | |
| Sheet and Strip | | 100 | 690 | 60 | 415 | 40 | 241 | 100 HRBW | not required |
| Plate | | 90 | 620 | 50 | 345 | 40 | 241 | 100 HRBW | not required |
| S21640 | ... | 95 | 650 | 45 | 310 | 40 | ... | ... | not required |
| S21800 | ... | 95 | 655 | 50 | 345 | 35 | 241 | 100 HRBW | not required |
| S21904 | XM-11 ^J | | | | | | | | |
| Sheet and Strip | | 100 | 690 | 60 | 415 | 40 | 241 | 100 HRBW | not required |
| Plate | | 90 | 620 | 50 | 345 | 45 | 241 | 100 HRBW | not required |
| S24000 | XM-29 ^J | | | | | | | | |
| Sheet and Strip | | 100 | 690 | 60 | 415 | 40 | 241 | 100 HRBW | not required |
| Plate | | 100 | 690 | 55 | 380 | 40 | 241 | 100 HRBW | not required |
| S30100 | 301 | 75 | 515 | 30 | 205 | 40 | 217 | 95 HRBW | not required |
| S30103 | 301L ^F | 80 | 550 | 32 | 220 | 45 | 241 | 100 HRBW | not required |
| S30153 | 301LN ^F | 80 | 550 | 35 | 240 | 45 | 241 | 100 HRBW | not required |
| S30200 | 302 | 75 | 515 | 30 | 205 | 40 | 201 | 92 HRBW | not required |
| S30400 | 304 | 75 | 515 | 30 | 205 | 40 | 201 | 92 HRBW | not required |
| S30403 | 304L | 70 | 485 | 25 | 170 | 40 | 201 | 92 HRBW | not required |
| S30409 | 304H | 75 | 515 | 30 | 205 | 40 | 201 | 92 HRBW | not required |
| S30415 | ... | 87 | 600 | 42 | 290 | 40 | 217 | 95 HRBW | not required |
| S30435 | ... | 65 | 450 | 23 | 155 | 45 | 187 | 90 HRBW | ... |
| S30441 | ... | 75 | 515 | 30 | 205 | 40 | 201 | 92 HRBW | not required |
| S30451 | 304N | 80 | 550 | 35 | 240 | 30 | 217 | 95 HRBW | not required |
| S30452 | XM-21 ^J | | | | | | | | |
| Sheet and Strip | | 90 | 620 | 50 | 345 | 30 | 241 | 100 HRBW | not required |
| Plate | | 85 | 585 | 40 | 275 | 30 | 241 | 100 HRBW | not required |
| S30453 | 304LN | 75 | 515 | 30 | 205 | 40 | 217 | 95 HRBW | not required |
| S30500 | 305 | 70 | 485 | 25 | 170 | 40 | 183 | 88 HRBW | not required |
| S30530 | ... | 75 | 515 | 30 | 205 | 40 | 201 | 92 HRBW | not required |
| S30600 | ... | 78 | 540 | 35 | 240 | 40 | ... | ... | ... |
| S30616 | ... | 86 | 590 | 36 | 245 | 40 | 241 | 100 HRBW | not required |
| S30601 | ... | 78 | 540 | 37 | 255 | 30 | ... | ... | not required |
| S30615 | ... | 90 | 620 | 40 | 275 | 35 | 217 | 95 HRBW | not required |
| S30815 | ... | 87 | 600 | 45 | 310 | 40 | 217 | 95 HRBW | ... |
| S30908 | 309S | 75 | 515 | 30 | 205 | 40 | 217 | 95 HRBW | not required |
| S30909 | 309H ^F | 75 | 515 | 30 | 205 | 40 | 217 | 95 HRBW | not required |
| S30940 | 309Cb ^F | 75 | 515 | 30 | 205 | 40 | 217 | 95 HRBW | not required |