



Designation: ~~D4216–17~~ D4216 – 22

## Standard Specification for Rigid Poly(Vinyl Chloride) (PVC) and Related PVC and Chlorinated Poly(Vinyl Chloride) (CPVC) Building Products Compounds<sup>1</sup>

This standard is issued under the fixed designation D4216; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

*This standard has been approved for use by agencies of the U.S. Department of Defense.*

### 1. Scope\*

1.1 This specification covers rigid plastic PVC and CPVC Exterior compounds composed of poly(vinyl chloride), chlorinated poly(vinyl chloride), vinyl chloride copolymers or vinyl chloride blends, and the necessary compound ingredients intended for use in making building products. The compounding ingredients are permitted to consist of lubricants, stabilizers, nonpoly(vinyl chloride) resin modifiers, colorants or pigments, or both, and inorganic fillers.

1.2 This specification is intended to provide classification of base compounds used to manufacture PVC and CPVC exterior building products. It is acceptable to determine physical properties by evaluating compounds of any color.

NOTE 1—Two year weathering studies, without specific requirements for color change and physical property change, are recommended for all colors of new compounds and compounds for new applications to provide the basis for agreement between producer and buyer on the suitability of the compound for the intended application.

1.3 The requirements in this specification are intended for qualification, as well as for quality control of compounds used to manufacture building products. They are not applicable to finished building products.

1.4 It will be necessary, in special cases, to select specific compounds for unusual applications that require consideration of other properties not covered in this specification.

1.5 The rate of burning test, Test Method **D635**, is used in this specification only as a screening test for identification of certain properties of the PVC compound; there is no flammability test or flammability requirement for the compound.

1.6 The values stated in SI units are to be regarded as standard. The values given in parentheses are for information only.

1.7 The following safety hazards caveat pertains only to the test methods portion, Section **11**, of this specification: *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

<sup>1</sup> This specification is under the jurisdiction of ASTM Committee **D20** on Plastics and is the direct responsibility of Subcommittee **D20.15** on Thermoplastic Materials (Section D20.15.08).

Current edition approved Dec. 1, 2017; May 1, 2022. Published January 2018; May 2022. Originally approved in 1983. Last previous edition approved in 2013 as ~~D4216–13~~ D4216 – 17. DOI: ~~10.1520/D4216-17~~ 10.1520/D4216-22.

\*A Summary of Changes section appears at the end of this standard

NOTE 2—There is no known ISO equivalent to this standard.

1.8 The text of this standard references notes and footnotes, which provide explanatory material. These notes and footnotes (excluding those in tables and figures) shall not be considered as requirements of this standard.

1.9 It is possible that rigid PVC recycle plastic meeting the requirements of this specification will be usable in some applications. Refer to the specific requirements in the Materials and Manufacture Section of the applicable product standard.

1.10 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

## 2. Referenced Documents

### 2.1 ASTM Standards:<sup>2</sup>

[D256 Test Methods for Determining the Izod Pendulum Impact Resistance of Plastics](#)

[D618 Practice for Conditioning Plastics for Testing](#)

[D635 Test Method for Rate of Burning and/or Extent and Time of Burning of Plastics in a Horizontal Position](#)

[D638 Test Method for Tensile Properties of Plastics](#)

[D648 Test Method for Deflection Temperature of Plastics Under Flexural Load in the Edgewise Position](#)

[D696 Test Method for Coefficient of Linear Thermal Expansion of Plastics Between –30°C and 30°C with a Vitreous Silica Dilatometer](#)

[D883 Terminology Relating to Plastics](#)

[D1435 Practice for Outdoor Weathering of Plastics](#)

[D1600 Terminology for Abbreviated Terms Relating to Plastics](#)

[D3892 Practice for Packaging/Packing of Plastics](#)

[D4226 Test Methods for Impact Resistance of Rigid Poly\(Vinyl Chloride\) \(PVC\) Building Products](#)

[D5260 Classification for Chemical Resistance of Poly\(Vinyl Chloride\) \(PVC\) Homopolymer and Copolymer Compounds and Chlorinated Poly\(Vinyl Chloride\) \(CPVC\) Compounds](#)

## 3. Terminology

### 3.1 Definitions:

3.1.1 ~~General—Definitions are in accordance with~~ For definitions of terms pertaining to plastics used in this standard, refer to Terminology [D883](#) and ~~.~~ For abbreviations used in this test method, refer to Terminology [D1600](#), unless otherwise indicated.

### 3.2 Definitions of Terms Specific to This Standard:

3.2.1 ~~temperate northern climate~~—*climate, n*—in weather testing, a North American metropolitan area testing site located within 73° to 100°W longitude and 37° to 45°N latitude.

## 4. Classification

4.1 The means for classifying and identifying rigid PVC building products compounds are provided in [Table 1](#). The properties enumerated in this table and the tests defined are expected to provide identification of the compounds selected. They are not necessarily suitable for direct application in design because of differences in shape of part, size, loading, environmental conditions, etc.

4.2 Classes are designated by the cell number for each property in the order in which they are listed in [Table 1](#).


NOTE 3—Because of the large number of property requirements, the properties of classes are divided into groups for easy identification of the selected materials. The groups are the following: kind of resin in compound, strength properties, and dimensional stability. The class numbers are grouped as shown by the following example:

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.


**TABLE 1 Class Requirements for Rigid Poly(Vinyl Chloride) and Related PVC and CPVC Compounds for Building Products**

NOTE 1—The minimum property value will determine the cell number, although it is possible that the maximum expected values may fall within the next higher cell.

Designation Order No.	Property and Unit	Cell Limits								
		0	1	2	3	4	5	6	7	
1	Kind of resin in compound	Unspecified	poly(vinyl chloride) (PVC)	chlorinated poly(vinyl chloride) (CPVC)	vinyl chloride copolymer	vinyl chloride blend				
2	Impact resistance, J/m of notch (ft · lbf/in. of notch)	Unspecified	>34.7 (>0.65)	>53.4 (>1.0)	>107 (>2.0)	>267 (>5.0)				
3	Impact resistance, drop dart, Procedure A, Test Method D4226, J/m (in.-lb/mil)	Unspecified	>4450 (>1.0)	>6675 (>1.5)	>8900 (>2.0)	>13 350 (>3.0)				
4	Impact resistance, drop dart, Procedure B, Test Method D4226, J/m (in.-lb/mil)	Unspecified	>4450 (>1.0)	>6675 (>1.5)	>8900 (>2.0)	>13 350 (>3.0)				
5	Tensile strength, MPa (psi)	Unspecified	>34 (>5000)	>37.7 (>5500)	>41.4 (>6000)	>44.9 (>6500)	>48.3 (>7000)			
6	Modulus of elasticity in tension, MPa (psi)	Unspecified	>2000 (>290 000)	>2400 (>348 000)	>2600 (>377 000)	>2800 (>406 000)				
7	Deflection temperature under load, 1.82 MPa (264 psi) °C (°F)	Unspecified	>60 (>140)	>65 (>149)	>70 (>158)	>75 (>167)	>80 (>176)	>85 (>185)		
8	Coefficient of linear expansion, cm/cm/°C (in/in/°F)	Unspecified	<4 × 10 <sup>-5</sup> (<2.2 × 10 <sup>-5</sup> )	<6 × 10 <sup>-5</sup> (<3.3 × 10 <sup>-5</sup> )	<8 × 10 <sup>-5</sup> (<4.4 × 10 <sup>-5</sup> )	<10 × 10 <sup>-5</sup> (<5.5 × 10 <sup>-5</sup> )				

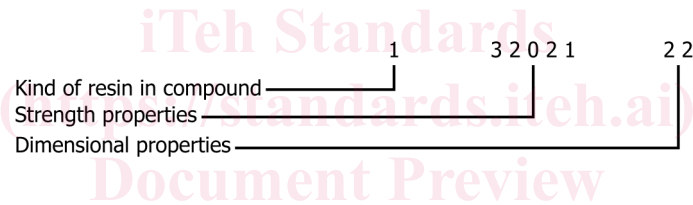

NOTE 4—The manner in which selected materials are identified by this classification system is illustrated by a Class 1-32021-22 PVC building products compound having the following requirements (see Table 1):

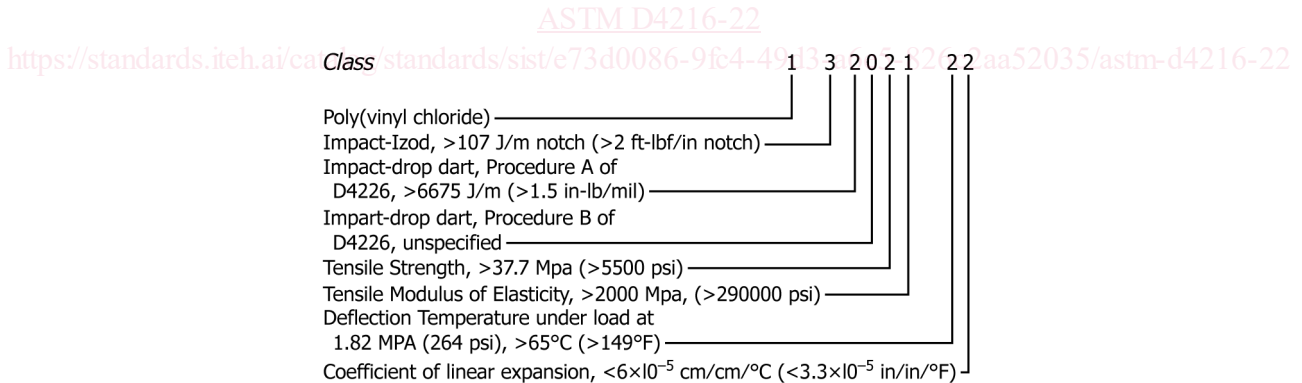

NOTE 5—The cell-type format provides the means for classification and close characterization and specification of material properties, alone or in combination, for a broad range of materials. This type format, however, is subject to possible misapplication since unobtainable property combinations can be selected if the user is not familiar with commercially available materials. The manufacturer should be consulted.

4.3 Product application chemical resistance when specified shall be classified according to the Classification Section of Classification D5260.

### 5. Ordering Information

5.1 The purchase order, or inquiry, for these materials shall state this specification number and identify the class selected; for example, D4216, Class 1-32021-22.

5.2 Further definition, as potentially required for the following, shall be on the basis of agreement between the purchaser and the seller.

5.2.1 Physical form and particle size (see 6.2 and 6.3).

5.2.2 Contamination level (see 6.4).

5.2.3 Other supplementary definition, if necessary.

## 6. Materials and Manufacture

### 6.1 Resin (Polymer) Requirements:

6.1.1 Poly(vinyl chloride) (PVC) resin (polymer) meeting Cell 1 in Designation Order 1 shall have a polymerized vinyl chloride content not less than 99.0 %.

6.1.2 Unless otherwise stated, vinyl chloride copolymer resin (polymer) meeting Cell 3 in Designation Order 1 shall contain not less than polymerized 80 % vinyl chloride content.

6.1.3 Vinyl chloride resin (polymer) blends with non-PVC polymers meeting Cell 4 of Designation Order 1 shall have not less than 50 % PVC content.

6.2 Materials supplied under this specification shall be PVC compound in the form of cubes, pellets, granules, free-flowing powder blends, or compacted powder blends.

6.3 Materials shall be of uniform composition and size.

6.4 Materials shall be free of foreign matter to a level that is not expected to affect processability, serviceability, or finished product appearance adversely.

6.5 Color and transparency or opacity of molded or extruded articles formed under the conditions recommended by the seller shall be comparable, within commercial match tolerances, to the color and transparency or opacity of standard molded or extruded samples of the same thickness supplied in advance by the seller of the material.

## 7. Sampling

7.1 A batch or lot shall be considered as a unit of manufacture and is permitted to consist of a blend of two or more production runs of material.

7.2 Samples shall be taken from either a product or process in statistical control.

## 8. Physical Requirements

8.1 Test values for specimens of the material prepared as specified in Section 10 and tested in accordance with Section 11 shall conform to the requirements given in Table 1 for the class selected.

8.2 The compound, when tested in accordance with Test Method D635, shall not exceed an average extent of burn of 100 mm (4 in.) with an average time of burn not to exceed 10 s. A sample thickness of 1 mm (0.040 in.)  $\pm$  10 % is recommended.

8.3 *Stability*—The compound shall be adequately stabilized against thermal degradation without sacrificing weathering performance.

NOTE 6—The type and amount of stabilizer may vary with the compound formulation, the equipment on which the compound is processed, the temperatures during processing steps, and the amount of regrind (reworked) material or rigid PVC recycled plastic employed. To date, no test procedure