



Designation: C1303/C1303M – 22

Standard Test Method for Predicting Long-Term Thermal Resistance of Closed-Cell Foam Insulation¹

This standard is issued under the fixed designation C1303/C1303M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reappraisal.

1. Scope

1.1 This test method covers a procedure for predicting the long-term thermal resistance (LTTR) of unfaced or permeably faced rigid gas-filled closed-cell foam insulations by reducing the specimen thickness to accelerate aging under controlled laboratory conditions (1-5).²

NOTE 1—See Terminology, 3.2.1, for the meaning of the word *aging* within this standard.

1.2 Rigid gas-filled closed-cell foam insulation includes all cellular plastic insulations manufactured with the intent to retain a blowing agent other than air.

1.3 This test method is limited to unfaced or permeably faced, homogeneous materials. This method is applied to a wide range of rigid closed-cell foam insulation types, including but not limited to: extruded polystyrene, polyurethane, polyisocyanurate, and phenolic. This test method does not apply to impermeably faced rigid closed-cell foams or to rigid closed-cell bun stock foams.

NOTE 2—See Note 8 for more details regarding the applicability of this test method to rigid closed-cell bun stock foams.

1.4 This test method utilizes referenced standard test procedures for measuring thermal resistance. Periodic measurements are performed on specimens to observe the effects of aging. Specimens of reduced thickness (that is, thin slices) are used to shorten the time required for these observations. The results of these measurements are used to predict the long-term thermal resistance of the material.

1.5 The test method is given in two parts. The Prescriptive Method in Part A provides long-term thermal resistance values on a consistent basis that can be used for a variety of purposes, including product evaluation, specifications, or product comparisons. The Research Method in part B provides a general relationship between thermal conductivity, age, and product thickness.

¹ This test method is under the jurisdiction of ASTM Committee C16 on Thermal Insulation and is the direct responsibility of Subcommittee C16.30 on Thermal Measurement.

Current edition approved June 1, 2022. Published July 2022. Originally approved in 1995. Last previous edition approved in 2019 as C1303/C1303M – 19. DOI: 10.1520/C1303_C1303M-22.

² The boldface numbers in parentheses refer to the list of references at the end of this standard.

1.5.1 To use the Prescriptive Method, the date of manufacture must be known, which usually involves the cooperation of the manufacturer.

1.6 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system are not necessarily exact equivalents; therefore, to ensure conformance with the standard, each system shall be used independently of the other, and values from the two systems shall not be combined.

1.7 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.8 Table of Contents:

	Section
Scope	1
Reference Documents	2
Terminology	3
Summary of Test Method	4
Significance and Use	5
Part A: The Prescriptive Method	6
Applicability	6.1
Qualification Requirements	6.1.1
Facing Permeability	6.1.2
Apparatus	6.2
Sampling	6.3
Schedule	6.3.1
Specimen Preparation	6.4
Goal	6.4.1
Schedule	6.4.2
Replicate Test Specimen Sets	6.4.3
Specimen Extraction	6.4.4
Slice Flatness	6.4.5
Slice Thickness	6.4.6
Stack Composition	6.4.7
Storage Conditioning	6.5
Test Procedure	6.6
Thermal Resistance Measurement Schedule	6.6.1
Thermal Resistance Measurements	6.6.2
Product Density	6.6.3
Calculations	6.7
Part B: The Research Method	7
Background	7.1
TDSL Apparatus	7.2
Sampling Schedule	7.3
Specimen Preparation	7.4
Storage Conditioning	7.5
Test Procedure	7.6
Calculations	7.7



Reporting
 Reporting for Part A, the Prescriptive Method
 Reporting for Part B, the Research Method
 Precision and Bias
 Keywords
 Mandatory Information – Qualification

Specimen Preparation
 Homogeneity Qualification
 Thermal Conductivity Equivalence Test Procedure
 Alternate Product Thickness Qualification
 Example Calculations
 Mandatory Information-Preparation of Test Specimens for Spray-Foam Products
 Effect Of TDSL

8
 8.1
 8.2
 9
 10
 Annex
 A1
 A1.1
 A1.2
 A1.3
 A1.4
 A1.5
 Annex
 A2
 Appendix
 X1
 Appendix
 X2
 Appendix
 X3

History of the Standard

Theory of Foam Aging

References

1.9 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 *ASTM Standards:*³

- C168 Terminology Relating to Thermal Insulation
- C177 Test Method for Steady-State Heat Flux Measurements and Thermal Transmission Properties by Means of the Guarded-Hot-Plate Apparatus
- C518 Test Method for Steady-State Thermal Transmission Properties by Means of the Heat Flow Meter Apparatus
- C578 Specification for Rigid, Cellular Polystyrene Thermal Insulation
- C591 Specification for Unfaced Preformed Rigid Cellular Polyisocyanurate Thermal Insulation
- C1029 Specification for Spray-Applied Rigid Cellular Polyurethane Thermal Insulation
- C1045 Practice for Calculating Thermal Transmission Properties Under Steady-State Conditions
- C1126 Specification for Faced or Unfaced Rigid Cellular Phenolic Thermal Insulation
- C1289 Specification for Faced Rigid Cellular Polyisocyanurate Thermal Insulation Board
- D1622 Test Method for Apparent Density of Rigid Cellular Plastics
- D6226 Test Method for Open Cell Content of Rigid Cellular Plastics

2.2 *Other Standards:*

- CAN/ULC S770 Standard Test Method for Determination of Long-Term Thermal Resistance of Closed-Cell Thermal Insulation Foams⁴

2.3 *ASTM Adjuncts:*

- Test Method for Predicting Long-Term Thermal Resistance of Closed-Cell Foam Insulation⁵

3. Terminology

3.1 *Definitions*—For definitions of terms and symbols used in this test method, refer to Terminology C168.

3.2 *Definitions of Terms Specific to This Standard:*

3.2.1 *aging, v*—the change in thermophysical properties of rigid closed-cell plastic foam with time, primarily due to changes in the composition of the gas contained within the closed cells.

3.2.2 *bias, n*—a generic concept related to a consistent or systematic difference between a set of test results from the process (that is, the predicted thermal conductivity at 5 years) and an accepted reference value of the property being measured (that is, the actual thermal resistance after 5 years of full-thickness products taken from the same lot as the source of the thin slices).

3.2.3 *core slice, n*—a thin-slice foam specimen that was taken at least 5 mm [0.2 in.] or 25 % of the product thickness, whichever is greater, away from the surface of the full-thickness product.

3.2.4 *effective diffusion thickness, n*—one-half of the geometric thickness minus the total thickness of damaged surface layer(s) (TDSL).

3.2.5 *facing, n*—a material adhered to the surface of foam insulation, including any foam product that has been suffused into the facing material, but not inclusive of any skin formed by the foam insulation itself.

3.2.6 *homogeneous material, n*—sufficiently uniform in structure and composition to meet the requirements of this test method (see A1.2).

3.2.7 *long-term, adj*—for the purposes of the Prescriptive Method, long term refers to five years.

3.2.8 *normalized service life, n*—product service life divided by the square of the full product thickness, units of time/length².

3.2.9 *scaled time, n*—time divided by the square of the specimen thickness.

3.2.10 *scaled service life, n*—time necessary for a thin specimen to reach the same thermal conductivity that a full thickness specimen would reach at the end of its service life, equals the product service life multiplied by the square of the ratio of the average slice thickness to the full product thickness, value has units of time.

3.2.11 *service life, n*—the anticipated period of time that the material is expected to maintain claimed thermophysical properties, may be dependent on the specific end-use application.

3.2.12 *surface slice, n*—a thin-slice foam specimen that was originally adjacent to the surface of the full-thickness product

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard’s Document Summary page on the ASTM website.

⁴ Underwriters Laboratory of Canada, 333 Pflingsten Road, Northbrook, IL 60062-2096 USA, www.ulc.ca

⁵ Available from ASTM International Headquarters. Order Adjunct No. ADJC1303.

and that includes any facing that was adhered to the surface of the original full-thickness product.

3.2.13 *thickness of damaged surface layer (TDSL), n* —the average thickness of surface cells, on one surface, that are either destroyed (ruptured or opened) during the preparation of test specimens or were originally open due to the manufacturing process.

3.3 Symbols:

$F_{surface}$	= fraction of the product thickness represented by surface slice
i	= counter used in a summation
k	= thermal conductivity, W/(m·K)
L	= thickness, m
n	= counter used in a summation
N	= number of cut planar surfaces
n_{SL}	= counter in a time series that corresponds to the service life.
R	= thermal resistance, (m ² ·K)/W
$TDSL$	= average thickness of damaged surface layer, m
ΔX	= insulation thickness, m
ΔX_{eff}	= effective diffusion thickness of thermal resistance specimen, m

4. Summary of Test Method

4.1 Rigid gas-filled closed-cell foam insulation is thin-sliced to reduce the gas diffusion path length which accelerates the aging process. The resulting temporal acceleration is proportional to the square of the ratio of the product use thickness to the slice thickness.

4.2 Careful and precise slice preparation is necessary and the process is described in detail in 6.4.

4.3 In Part A, the Prescriptive Method, specific test dates are calculated and the thermal resistance of the thin slices is measured on those dates.

4.3.1 Qualification tests are included to determine whether this method is applicable to a given material.

4.4 In Part B, the Research Method, thermal conductivity is measured for a series of time periods and extensive data analysis is possible.

5. Significance and Use

5.1 Rigid gas-filled closed-cell foam insulations include all cellular plastic insulations which rely on a blowing agent (or gas), other than air, for thermal resistance values. At the time of manufacture, the cells of the foam usually contain their highest percentage of blowing agent and the lowest percentage of atmospheric gases. As time passes, the relative concentrations of these gases change due primarily to diffusion. This results in a general reduction of the thermal resistance of the foam due to an increase in the thermal conductivity of the resultant cell gas mixture. These phenomena are typically referred to as foam aging.

5.1.1 For some rigid gas-filled closed-cell foam insulation products produced using blowing agent gases that diffuse very rapidly out of the full-thickness foam product, such as expanded polystyrene, there is no need to accelerate the aging process.

5.1.2 Physical gas diffusion phenomena occur in three dimensions. The one-dimensional form of the diffusion equations used in the development of this practice are valid only for planar geometries, that is, for specimens that have parallel faces and where the thickness is much smaller than the width and much smaller than the length.

NOTE 3—Please see Appendix X3 for a discussion of the theory of accelerated aging via thin slicing.

NOTE 4—Theoretical and experimental evaluations of the aging of insulation in radial forms, such as pipe insulation, have been made. (6) However, these practices have not evolved to the point of inclusion in the test standard.

5.2 The change in thermal resistance due to the phenomena described in 5.1 usually occurs over an extended period of time. Information regarding changes in the thermal resistance of these materials as a function of time is required in a shorter period of time so that decisions regarding formulations, production, and comparisons with other materials can be made.

5.3 Specifications C578, C591, C1029, C1126 and C1289 on rigid closed-cell foams measure thermal resistance after conditioning at $23 \pm 1^\circ\text{C}$ [$73 \pm 2^\circ\text{F}$] for 180 ± 5 days from the time of manufacture or at $60 \pm 1^\circ\text{C}$ [$140 \pm 2^\circ\text{F}$] for 90 days. This conditioning can be used for comparative purposes, but is not sufficient to describe long-term thermal resistance. This requirement demonstrates the importance of the aging phenomena within this class of products.

5.4 The Prescriptive Method in Part A provides long-term thermal resistance values on a consistent basis for a variety of purposes, including product evaluation, specifications, or product comparisons. The consistent basis for these purposes is provided by a series of specific procedural constraints, which are not required in the Research Method described in Part B. The values produced by the Prescriptive Method correspond to the thermal resistance at an age of five years, which corresponds closely to the average thermal resistance over a 15-year service life (7, 8).

5.4.1 It is recommended that any material standard that refers to C1303 to provide a product rating for long-term thermal resistance specify the Part A Test Method of C1303.

5.5 The Research Method in Part B provides a relationship between thermal conductivity, age, and product thickness. The calculation methods given in Part B can be used to predict the resistance at any specific point in time as well as the average resistance over a specific time period.

NOTE 5—The 5-year aged values produced in Part A can be derived from the Part B data only if all other Part A requirements are met.

5.6 This test method addresses three separate elements relating to the aging of rigid closed-cell plastic foams.

5.6.1 *Specimen Preparation*—Techniques for the preparation of thin flat specimens, including their extraction from the “as manufactured” product, and the measurement of specimen thickness are discussed.

5.6.2 *Measurement of the Thermal Resistance*—Thermal resistance measurements, taken at scheduled times, are an integral part of the test method.

5.6.3 *Interpretation of Data*—Procedures are included to properly apply the theory and techniques to achieve the desired goals.

6. Part A: The Prescriptive Method

6.1 Applicability:

6.1.1 *Qualification Requirements*—Before reporting the results from a C1303 Part A aging test, the material must be qualified using the procedures given in [Annex A1](#).

6.1.1.1 The qualification requirement tests must be performed whenever a significant change that would affect the thermal resistance properties is made to the product.

6.1.1.2 The qualification is valid for a period not to exceed two years.

NOTE 6—This test method is founded upon gas diffusion physical laws that apply to homogeneous materials with free surface exposure to the atmosphere as discussed more fully in [Appendix X3 \(2-4\)](#) and [\(9-11\)](#). Although rigid closed-cell foam insulation may not rigorously meet these homogeneity and exposure criteria, this test method has been shown to provide useful information for a wide range of products. Recognizing that none of the foam insulation products available today is perfectly homogeneous, the qualification requirements determine whether the product is sufficiently homogeneous for this test method to produce meaningful results. The user should also be aware that the material characteristics of the thin specimens must approximate those of the material under investigation. The material characteristics that are of most importance are gas diffusion coefficients and initial cell gas content. One-dimensional diffusion must dominate in the full use thickness material; by design, one-dimensional diffusion dominates in the thin slice.

NOTE 7—If two thicknesses of a particular foam product are manufactured from identical components and have identical foam morphology, then thin slices from one specimen will accurately predict the long-term aging behavior of the other. However, due to possible differences in the foam morphology, the applicability of data derived from specimens taken from one product thickness to a different thickness of the same product is currently a subject of research. The “alternate product equivalence test” qualification in [Annex A1](#) is provided in Part A to allow this type of data generalization.

NOTE 8—The age acceleration test method applies when one-dimensional diffusion dominates in the full-use thickness material. In bun-stock products, this condition does not exist during the time period between the initial foam production and the manufacturing process that cuts the buns into flat sheets. Because this time is variable, it is not possible to define a consistent initial time for the Prescriptive Method. Also, because the sheets may be cut from the bun stock in different orientations, the foam morphology may vary from one product sheet to another.

6.1.2 Facing Permeability:

6.1.2.1 Unfaced foam insulation meets the criteria of a free exposure to the atmosphere so the test method is applicable.

6.1.2.2 Faced products, with the exception of those foil-faced products that are Type 1 in Specification [C1289](#), that pass the homogeneity qualification test in [Annex A1](#) meet the criteria of this test method.

6.2 Apparatus:

6.2.1 Thermal resistance test apparatus used for this test method shall conform to all of the requirements of Test Method [C518](#).

6.2.2 Specimen preparation equipment must produce slices that are consistent in dimension and surface morphology.

6.2.2.1 *Surface Damage*—Equipment for preparing thin specimens shall be selected based on the ability of the equipment to consistently limit the amount of surface damage (open cells) that occurs during the preparation process.

6.2.2.2 *Thickness Uniformity*—The equipment used to prepare specimens shall be capable of producing uniform thickness slices able to meet the requirements of [6.4.5](#).

6.2.2.3 The following two types of equipment have successfully been used to prepare thin slice specimens. Reference [\(12\)](#) summarizes these techniques and compares their effectiveness.

(1) High Speed Band-saw, with a fine-tooth 1 tooth/mm [14 teeth/in.] blade, 0.6 mm [0.025 in.] blade thickness, and blade speed of about 6 m/s [1185 ft/min].

(2) Combination Lathe/Motor-driven Meat Slicer.

6.2.2.4 Use of a hot-wire cutter is prohibited because it can produce a surface skin. For further discussion, please see [9.3](#) and [Note 31](#).

6.3 Sampling:

6.3.1 *Schedule*—Specimens shall be collected between 7 and 20 days after production. The specimen collection schedule must be coordinated with the specimen preparation time requirement of [6.4.2](#).

6.4 Specimen Preparation:

6.4.1 *Goal*—The goal of this section is to produce thin slices, that when aged, are representative of the aged performance of the full-thickness product.

6.4.2 *Schedule*—The specimens shall be prepared between 14 and 21 days after the production date.

6.4.3 *Replicate Test Specimen Sets*—The minimum number of replicate specimens, referred to as stacks, to be tested shall be selected so that there is confidence that the average results from these sliced specimens are representative of the material undergoing testing. Depending upon the material, as described in [6.4.7](#), one, two, or three stacks shall be prepared.

6.4.4 *Specimen Extraction*—Test specimens shall be extracted either from full size product sheets or from specially prepared spray-product constructions.

6.4.4.1 Extraction of test specimens from full size product sheets:

(1) Cut 300 by 300 mm \pm 6 mm [12 by 12 in. \pm 0.25 in.] full-thickness sections from two full-size product sheets. In no case shall these sections be taken within 15 cm [6 in.] of the product edge. The number of full-thickness sections needed will depend upon the equipment used to prepare the thin slices and the number of replicate sets tested, as discussed in [6.4.3](#).

(2) Slice the 300 by 300 mm \pm 6 mm [12 by 12 in. \pm 0.25 in.] full-thickness specimens prepared in [6.4.4.1\(1\)](#) to produce stacks of thin slices. Surface slices shall include the product skin or facing.

6.4.4.2 The preparation and extraction of test specimens from spray-foam product is described in [Annex A2](#).


6.4.5 Slice Flatness:

6.4.5.1 During the slicing process, the thickness of each individual slice shall be measured in eight locations distributed evenly over the surface of the slice as shown in [Fig. 1](#).

(1) These measurements shall be made using a digital caliper or a digital length meter. Care shall be taken so that the contact between the caliper jaws or the length meter’s pressure foot does not indent the foam surface.

6.4.5.2 Each of these eight measurements must be within $\pm 5\%$ of the average of the eight measurements.

6.4.5.3 The average of these eight measurements shall be used to represent the thickness of the slice for the purposes of [6.4.6.3](#).

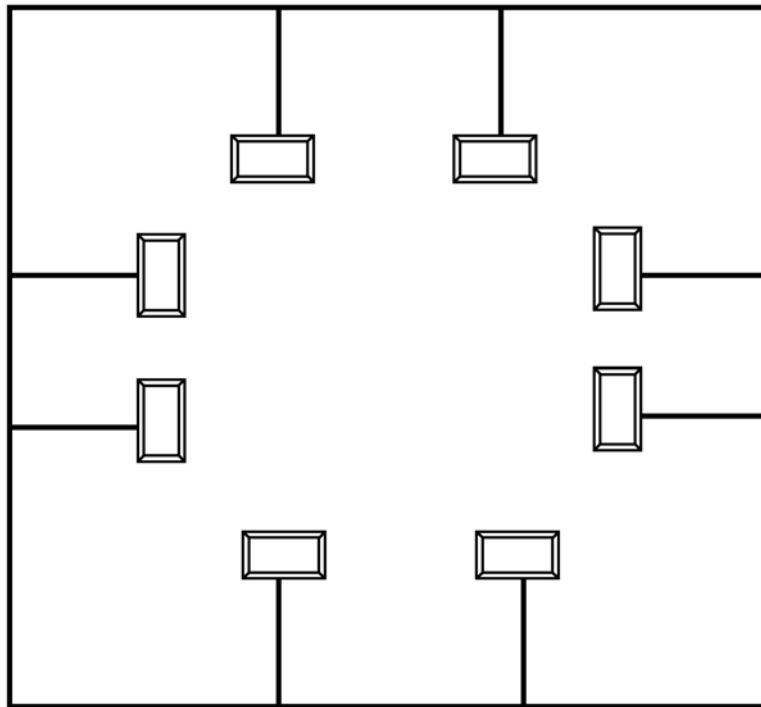

NOTE 1—Lines show position of caliper jaws.

FIG. 1 Location of Eight Measuring Points for Slice Thickness on a 300 by 300 mm [12 by 12 in.] Slice

6.4.5.4 It is possible that a apparatus and cutting technique adjustments will be necessary to meet the requirements of this section and those of 6.4.6.3. Practice is recommended.

6.4.6 *Slice Thickness:*

6.4.6.1 Each core slice shall be a minimum of 8 mm [0.32 in.] thick.

6.4.6.2 The foam portion of each surface slice shall be a minimum of 8 mm [0.32 in.] thick. The total thickness of each surface slice shall be a minimum of 8 mm [0.32 in.] plus the thickness of any facing material. If the facing thickness is not known, the facing shall be removed from an edge portion of the product sheet and the thickness measured with a caliper or digital length meter to the nearest 0.1 mm [0.004 in.]. If the facing thickness is less than 2 % of the total slice thickness, it shall be considered negligible in all succeeding calculations and the total slice thickness shall be used to represent the thickness of the foam portion of the surface slice.

6.4.6.3 Slice uniformity within each stack: The thickness of the foam portion of every slice (from 6.4.5.3) must be within $\pm 5\%$ of the average of the foam portion of all the slices used within that stack.

6.4.6.4 The average of the foam portion of the slice thickness within the stack will be used later in 6.7.1 to determine appropriate testing periods. This is called the Average Slice Thickness in Eq 1 in 6.7.1.

NOTE 9—The presence of a damaged layer of cells on every cut surface introduces errors into both the calculated testing period (causing it to be overestimated) and the thermal resistance (causing the measured value to be less than the true value). The 8 mm [0.32 in.] minimum thickness was selected based upon the magnitude of these errors (discussed in Appendix X1) and a desire to limit the controllable error sources associated with this test method to no more than the uncertainty of Test Method C518. There have been numerous experiments that show results from accelerated aging with 10 mm [0.39] slices are in good agreement with full-thickness aged values, as discussed more fully in Section 9. The C1303/C1303M ruggedness test established good agreement between full-thickness aged values and the accelerated aging predictions for slices between 8 mm [0.32 in.] and 12 mm [0.47 in.] for PIR and XPS boardstock products.

NOTE 10—If foam product morphology is changed by the introduction of new materials or manufacturing processes, the manufacturer may wish to pursue the TDSL investigation described in the Part B test method to determine whether the slice thickness should be increased to keep the TDSL errors within the uncertainty of Test Method C518.

NOTE 11—Errors in both the calculated testing period and the measured thermal resistance have the greatest effect for thermal resistance measurements made in the earlier portion of the aging curve. Therefore, when predicting aged values for thicker products, for example, 75 or 100 mm [3 or 4 in.] products, users may wish to elect slice thicknesses greater than the 8 mm [0.32 in.] minimum to extend the test time interval. This will improve the accuracy by: (1) reducing the effect of any small variation in the test time period and (2) reducing the magnitude of errors introduced into the calculated testing period due to the smaller relative fraction of TDSL (as discussed more fully in Appendix X1).

6.4.7 Stack Composition:

6.4.7.1 All thermal resistance measurements are made using stacks of slices in order to avoid errors (often referred to as the “thickness effect”) introduced by radiation heat transfer phenomena at small specimen thicknesses (13).

6.4.7.2 Depending upon the material, as described in 6.4.8, one, two, or three stacks shall be prepared. These three stack types are: four core slices, four surface slices, and a mixed stack of core and surface slices.

NOTE 12—For background and rationale regarding the use of these three stacks, please see X2.2.

(1) Slice uniformity among multiple stacks: The average slice thickness of each of the multiple stacks (that value calculated in 6.4.6.4 and used in 6.7.1 for each stack) must agree within ±1 mm [±0.04 in.].

6.4.7.3 For a stack of surface slices, the slices shall be organized so that every skin or facing faces upward, as shown in Fig. 2.

6.4.7.4 For the mixed stack, the core and surface slices shall be prepared at a uniform slice thickness that represents the reassembled full cross-section of the product except for small amounts destroyed in the slice-cutting process and excluding any remainder less than 8 mm [0.32 in.] in thickness. The slicing shall be organized so that any such remainder comes from a non-surface section of the foam and both surfaces shall be included as the outward facing layers of the stack. The number of core sections in the mixed stack will vary according to the product thickness, as shown in Fig. 2.

6.4.7.5 Each stack shall be marked to assure that the specimens are placed in the same top to bottom order for every thermal measurement. Each stack shall be marked to assure that the stacks are oriented in the thermal measurement apparatus in the same direction for every measurement. Fig. 3 is one example of an effective marking scheme.

6.4.7.6 A mathematical equivalent stack is constructed using the results from the core and surface stacks as described in 6.7.4.

6.4.8 Stack Type Selection:

6.4.8.1 The stack types allowed for PIR and XPS boardstock are based upon the results of a ruggedness test described in 9.5(14). Similar data are not yet available for other insulation products; so all three physical stack types are required for all other insulation products. That is, prepare three stacks using: four core slices, four surface slices, and a mixed stack of core and surface slices.

6.4.8.2 For PIR boardstock, select one of the five options listed here:

(1) If a product less than 75 mm [3 in.] thick is used to predict the long-term aged value for products of that same thickness, prepare a mixed stack.

(2) If a product less than 75 mm [3 in.] thick is used to predict the long-term aged value for products of that same thickness, prepare a core stack.

(3) If a product less than 75 mm [3 in.] thick is used to predict the long-term aged value for products of that same thickness, prepare both core and surface stacks. These will provide data required to evaluate the results for a mathematical equivalent stack.

(4) If a product with an original thickness between 45 and 55 mm [1.8 and 2.2 in.] is used to predict the long-term aged value for products between 22 and 103 mm [0.9 and 4.1 in.], prepare a core stack.

(5) If a product with an original thickness between 45 and 55 mm [1.8 and 2.2 in.] is used to predict the long-term aged value for products between 22 and 103 mm [0.9 and 4.1 in.], prepare both core and surface stacks. These will provide data needed to evaluate the results for a mathematical equivalent stack.

6.4.8.3 For XPS boardstock, select one of the three options listed here:

(1) If a product is used to predict the long-term aged value for products of that same thickness, prepare a mixed stack.

(2) If a product is used to predict the long-term aged value for products of that same thickness, prepare both core and surface stacks. These will provide data required to evaluate the results for a mathematical equivalent stack.

(3) If a product with an original thickness between 45 and 55 mm [1.8 and 2.2 in.] is used to predict the long-term aged value for products between 22 and 103 mm [0.9 and 4.1 in.], prepare both core and surface stacks. These will provide data required to evaluate the results for a mathematical equivalent stack.

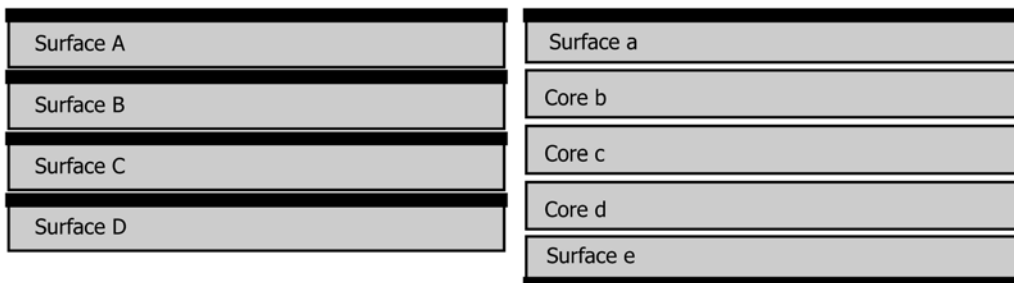


FIG. 2 Surface Stack Arrangement (left) and Mixed Stack Arrangement (right)

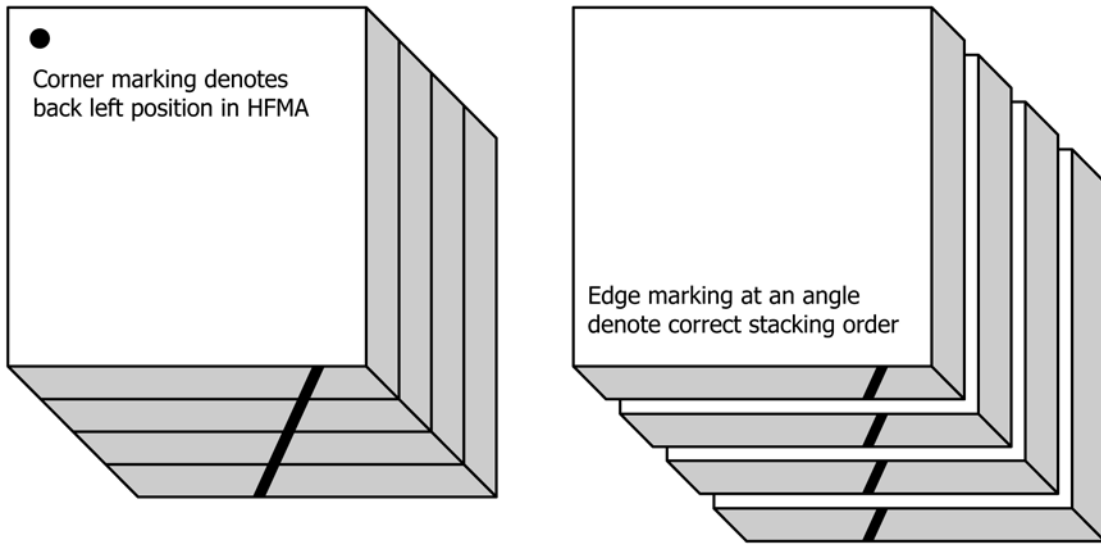


FIG. 3 Examples of Useful Specimen Stack Marking Techniques

6.5 Storage Conditioning:

6.5.1 Specimens shall be stored during the extended time periods between thermal conductivity measurements in a conditioned space, at a temperature of 22°C [72°F] (±5°C [10°F]) and relative humidity between 40 and 70 %.

NOTE 13—The long-term storage conditioning requirements defined here are separate from the specimen conditioning requirements of Test Methods C518 and C177.

6.5.2 Specimens shall be stored so that each surface of each slice is exposed to free air circulation.

NOTE 14—One method used to assure such exposure is to stand the slices like books on a shelf with small spaces between each adjacent slice.

6.6 Test Procedure:

6.6.1 Thermal Resistance Measurement Schedule:

6.6.1.1 Calculate the testing period(s) corresponding to the desired product thickness(es), as described in 6.7. Add the testing period to the slicing date to determine the test date for each product thickness.

6.6.1.2 Measure the thermal resistance of the stack on the test dates determined in 6.6.1.1 within ±24 h. If the test cannot be performed within that 3-day period (test date minus 24 h to test date plus 24 h), make a linear interpolation between two test measurements made before and after the test date. Each measurement used for interpolation shall be taken within a time interval before and after the test date determined in 6.6.1.1, corresponding to the lesser of 7 days or 15% of the calculated testing period. The linear interpolation shall be based on the number of days the first test was made before the calculated test date, the number of days between the two tests, and the measured thermal conductivity on both days.

NOTE 15—Linear interpolation example: Slice date July 30, 2010, calculated test date December 25, 2010. 15 % of the calculated test period of 148 days is 22 days, so the 7-day limit on interpolation test dates would apply.

First test date	December 20, 2010 (5 days before) (check, 5 < 7)	Measured thermal conductivity = 0.0307 W/m-K
Calculated test date	December 25, 2010	Interpolated thermal conductivity = 0.0307+(5/9).(0310-.0307) = 0.0309
Second test date	December 29, 2010 (4 days after, 9 days after the first test)(check, 4 < 7)	Measured thermal conductivity = 0.0310 W/m-K

6.6.2 Thermal Resistance Measurements—All thermal conductivity and resistance measurements shall be made according to Test Method C518 or C177, used in conjunction with Practice C1045. Of these test methods, the heat flow meter apparatus, Test Method C518, is recommended.

6.6.2.1 The mean test temperature shall be 24 ± 2°C [75 ± 4°F] with a temperature difference of 22 ± 2°C [40 ± 4°F].

6.6.2.2 It is important to eliminate any air gaps between slices within the stack and between the stack and the controlled temperature plates. Therefore, if the apparatus offers the option of automatically positioning the plates and determining the specimen thickness, that option shall be used.

6.6.2.3 If the apparatus does not include an automatic positioning feature, the user must ensure that there are no air gaps within the specimen stack or between the stack and the controlled temperature plates.

NOTE 16—The thermal conductivity reported by Test Method C518 or C177 apparatus is directly proportional to the distance between the controlled-temperature plates. If the apparatus reports the temperature difference and heat flux rather than the thermal conductivity, then the stack thickness used to calculate the thermal conductivity must equal the distance between the plates. This is not likely to be the sum of the individual slice thicknesses because of the pressure applied by the plate positioning apparatus within the device.

6.6.3 Product Density—For product identification and reporting purposes, the product apparent density shall be measured in accordance with Test Method D1622.

6.6.3.1 The density of interest is that of the foam. Therefore, for faced products, the facing shall be removed before the product density is measured.

6.7 Calculations:

6.7.1 The equation used to determine each testing period (in days) is shown in Eq 1.

$$\text{TestTime} = \left[\frac{\text{AverageSliceThickness}}{\text{ProductThickness}} \right]^2 \times 1826 \quad (1)$$

6.7.1.1 The Average Slice Thickness is that value calculated in 6.4.6.4. The constant 1826 represents the number of days in a 5-year period. Be sure to state the Average Slice Thickness and the Product Thickness in the same set of units.

6.7.2 Use Eq 1 to determine the test time for each product thickness of interest, subject to the limitations of Annex A1 and 6.4.8.

6.7.3 For the purpose of this calculation, the average slice thickness for surface slices shall not include the thickness of any facing material.

6.7.4 The results for a mathematical equivalent stack described in 6.4.8 are calculated using the standard series resistance expression to weight the measured values from the core and surface stacks to represent the overall product structure, as shown in Eq 2.

$$R_{\text{total}} = \frac{L_{\text{product}}}{k_{\text{effective}}} = \sum R = \sum \frac{\Delta x}{k} = \left(\frac{2L_{\text{surface}}}{k_{\text{surface}}} \right) + \left(\frac{L_{\text{product}} - 2L_{\text{surface}}}{k_{\text{core}}} \right) \quad (2)$$

$$\text{for } F_{\text{surface}} = \frac{2L_{\text{surface}}}{L_{\text{product}}}$$

$$R_{\text{effective}} = \frac{1}{k_{\text{effective}}} = \left(\frac{F_{\text{surface}}}{k_{\text{surface}}} \right) + \left(\frac{1 - F_{\text{surface}}}{k_{\text{core}}} \right)$$

7. Part B: The Research Method

7.1 *Background*—In general, the prescriptive procedure described in Section 6 shall be followed. Modifications made to meet research needs must be carefully documented when reporting the results and must be based on a clear understanding of the gas diffusion physics that form the foundation of the accelerated aging theory. (See Appendix X3.)

7.1.1 Data taken using the Research Method shall not be used for product rating purposes unless all the requirements of the Prescriptive Method in Section 6 are satisfied.

7.1.2 The qualification tests of Annex A1 are not required, but are recommended.

NOTE 17—For research purposes, such as to benchmark numerical analysis methods, it may be desirable to perform thin slicing age acceleration of specimens known to be highly non-homogeneous.

NOTE 18—This method applies when one-dimensional diffusion dominates in the full-use thickness material. In bun-stock products, this condition does not exist during the time period between the initial foam production and the manufacturing process that cuts the buns into flat sheets. Also, because the sheets may be cut from the bun stock in different orientations, the foam morphology may vary from one sheet to another. Therefore, if this type of product is tested using the Research Method, extensive information regarding the specimen source and extraction must be provided.

7.2 *TDSL Apparatus*—Apparatus used to measure the effective diffusion thickness of the specimen shall be as specified in Test Method D6226 or shall have demonstrated equivalent performance. See Ref (15) for a description of an acceptable alternative apparatus.

NOTE 19—Test Method D2856 has been withdrawn. However, laboratories that have the apparatus described in that test method are allowed to use that apparatus following the withdrawn test method.

7.3 *Sampling Schedule*—It is acceptable to prepare the specimens from products where the production date is unknown, but every effort must be made to acquire the foam soon after its production.

7.3.1 Data analysis must address the question of initial age using the aging theory found in Appendix X3 and Refs (4, 8).

7.3.2 Other resources, including data from the manufacturer and the pertinent material standard, shall be consulted to determine whether the estimated initial age is reasonable.

7.4 Specimen Preparation:

7.4.1 *Stack Composition*—The choice of core, surface, mixed, or mathematical equivalent stacks, or a combination thereof is acceptable in the Research Method. However, data for each stack shall be kept independent from data for any other stack.

NOTE 20—The effects of facers and density gradients on the accuracy and applicability of the accelerated aging test method are of great interest. Researchers may select alternative stacking compositions in order to investigate these phenomena.

7.4.2 It is acceptable to vary the extraction of specimens described in 6.4.4 if necessary to meet research goals. In no case shall these sections be taken within 15 cm [6 in.] of the product edge.

7.4.3 It is acceptable to reduce the slice thickness below the minimum specified for Part A in 6.4.6. See 7.6.5 and Appendix X1.

7.4.4 If the TDSL is measured, prepare the TDSL test specimens using the same slicing equipment as was used for the thermal test specimens. Prepare test specimens with dimensions that are required for the closed-cell volume measurement apparatus described in Test Method D6226. Prepare these specimens from sample material taken adjacent to the thermal specimen sections.

7.5 *Storage Conditioning*—In order to investigate the effect of environmental conditions on product aging, it is acceptable to use environmental conditions other than those specified in 6.5. If other conditions are used, they shall be recorded on a monthly basis.

7.6 Test Procedure:

7.6.1 Start an initial thermal conductivity measurement as soon as possible but no more than 6 h after the slicing procedure begins. Record the time elapsed between this measurement and the slicing procedure to the nearest hour.

7.6.2 A series of subsequent thermal conductivity measurements shall be adequate to provide data for the integration calculation procedure described in 7.7. The precise timing on these measurements is flexible, but it is important that the test schedule recognize that the foam aging progresses at a more

rapid rate in the earliest portion of the aging period. Measurements need to continue until a steady state condition has been reached. Steady state conditions can be recognized when thermal conductivity measurements, taken over a period of at least 100 days, agree within $\pm 2\%$, and show no trend. See [7.7.2](#).

NOTE 21—A suggested test schedule for 10 mm [0.4 in.] thick slices from a 25 mm [1 in.] product would include measurements at 5 days, 10 days, 30 days, 60 days, 100 days, 150 days, 210 days, 365 days, and 480 days.

NOTE 22—If a more accurate representation of the earliest aging period is desired, slice thickness should be increased to extend the time period over which this phenomenon occurs.

7.6.3 It is acceptable to make thermal conductivity measurements at other mean test temperatures and temperature differences.

NOTE 23—Gas diffusion rates increase at elevated temperatures. Repeated thermal conductivity measurements made at elevated mean temperatures may therefore change the very aging behavior that is the subject of the study. The thin slice adjacent to the hottest surface during the thermal conductivity measurement is the most likely to be affected. It may be necessary to rotate the slice stacking order, or to use a smaller number of measurements on a larger number of specimen stacks, in order to limit the exposure of any particular specimen to the higher temperatures.

7.6.4 It is acceptable to make the apparent specimen density in accordance with Test Method [D1622](#) on the same test schedule as the thermal conductivity.

7.6.5 Use Test Method [D6226](#) to measure the TDSL and effective diffusion thickness if necessary.

NOTE 24—The accuracy of the measured TDSL from either method is strongly influenced by the proportion of closed cells in the body, because any open cells that are connected to the surface will be counted in the TDSL volume.

7.6.5.1 The slice thickness, slice preparation method, and foam morphology shall be considered in making this determination. If the foam morphology varies from foam products previously tested, or if the slice thickness is decreased such that the TDSL will potentially comprise more than 4 % of the slice thickness, the TDSL shall be measured.

NOTE 25—The specimen preparation techniques employed by this test method destroy the closed cell integrity of the surface cells. For thinner specimens, these damaged surface cells may account for an appreciable percentage of the total specimen thickness. See [Appendix XI](#) for more information about the effect of the thickness of the destroyed surface layer on the test results.

NOTE 26—The accuracy of Test Method [D6226](#) may be insufficient when used to determine the effective diffusion thickness of some thin specimens. The uncertainty associated with this procedure shall be considered when selecting the geometric thickness of the thin test specimen.

NOTE 27—When using Test Method [D6226](#), it is recommended that an average of the half-atmosphere and two-atmosphere methods be used. The two-atmosphere method is likely to cause cell damage in low density materials; for these materials, the half-atmosphere method should be used exclusively.

NOTE 28—At a minimum, equivalency between Test Method [D6226](#) and the proposed alternative shall be demonstrated by direct comparison of the two procedures.

7.7 Calculations:

7.7.1 A functional relationship between thermal conductivity, time, and product thickness is developed using

simple interpolation and trapezoidal integration techniques. Note that thermal conductivity is used throughout this section. The thermal resistance is calculated only after all other calculation steps are complete. All the necessary equations are given here and are also available in an Excel spreadsheet.⁵

7.7.2 Extrapolate data with the greatest caution. These products typically reach a steady-state value at some point in time. However, if the last two data points are unequal, any extrapolation using the linear data analysis methods given here will falsely show a product eventually reaching infinite or zero thermal conductivity.

7.7.3 Organize the data in two columns, the first showing the test date and the second the measured thermal conductivity. Convert the test dates to elapsed test time periods in days, measured from the day of slicing. Create a column of normalized test times corresponding to each elapsed test time period according to [Eq 3](#).

7.7.3.1 The Average Slice Thickness comes from [6.4.6.4](#) and does not include the facing thickness for surface slices. See [7.7.6](#) for adjustments related to slice thickness and TDSL.

7.7.4 The average effective thermal conductivity of a given product over a projected service life can be determined by performing an integration of thermal conductivity versus time, and then dividing by the service life. The time scale used in this equation is real, not normalized, time. The concept is shown in [Eq 4](#).

7.7.5 Several time scales are used in this section. The Scaled Service Life has units of time, usually days, and is comparable to the “elapsed time period” scale in the thin-slice test data. The integration is accomplished in this time scale. The Normalized Service Life has units of time per length², usually days/cm², and is comparable to the normalized test time scale. The interpolation is accomplished in this normalized time scale. The normalized time scale is also used to determine the thermal conductivity of a given thickness product at any specific point in time.

7.7.5.1 The service life integral can be approximated using a numerical trapezoidal integration based upon thin-slice test data taken over a much shorter time period. This shorter time period corresponds to the Scaled Service Life. (Other integration techniques were tested and found to offer results very similar to this simple method [\(16\)](#).) See [Eq 5](#).

7.7.5.2 The final time in this series, or time(n_{SL}), is by definition the Scaled Service Life, which is determined using [Eq 6](#).

7.7.5.3 It is possible that the thin slice data will not include a data point corresponding to the scaled service life (where $n = n_{SL}$ in [Eq 5](#)). In that case, it is necessary to interpolate to obtain the thermal conductivity corresponding to that point, as shown in [Fig. 4](#). This value becomes the last thermal conductivity value in the series in [Eq 5](#).

(1) Because the diffusive aging process is an exponential function, this interpolation is more accurate if it is based on the normalized time defined in [7.7.3](#). Determine the Normalized Service Life corresponding to the full-thickness product and projected service life according to [Eq 7](#). Be sure to use the same set of units that were used in [7.7.3](#), for example, days per cm².

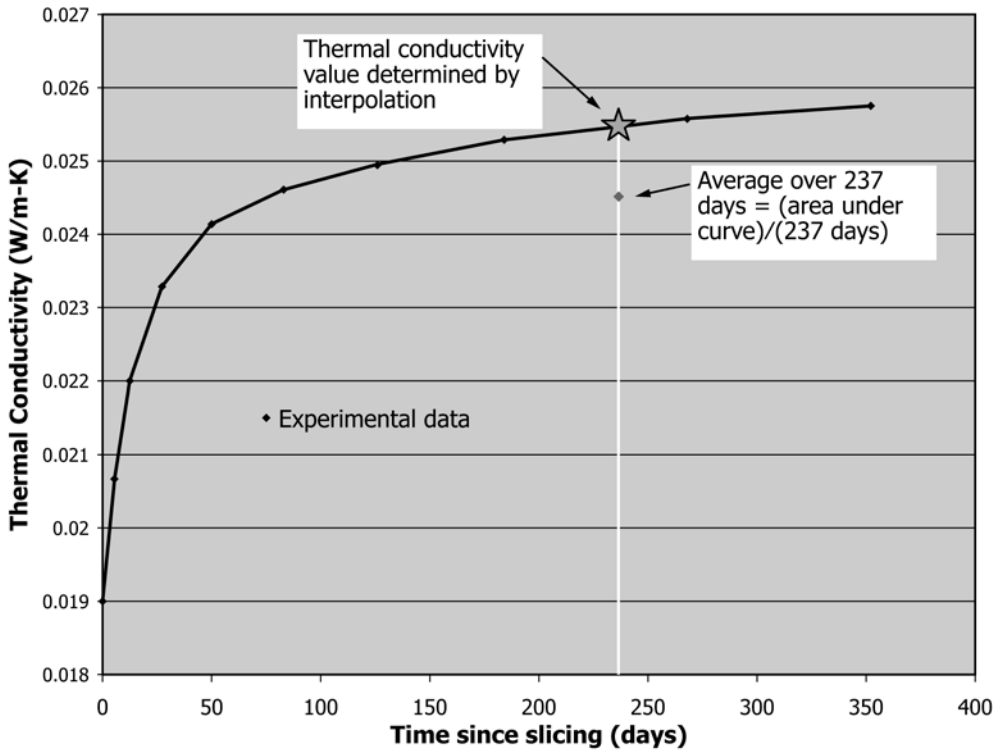


FIG. 4 Illustration of the Integration and Interpolation Methods Used in the Research Method

(2) Comparing the Normalized Service Life from 7.7.5.3(1) to the Normalized Test Time column of values from 7.7.3, select the two test data points that bracket the Normalized Service Life, as shown in Table 1.

(3) Interpolate the values shown in 7.7.5.3(2) to obtain the instantaneous thermal conductivity corresponding to the service life according to Eq 8.

7.7.6 Measured thermal conductivity values include the effect of the TDSL, as discussed in Appendix X1. When the researcher considers that the TDSL represents a significant

TABLE 1 Time Scale Interpolation

Normalized Test Time (i)	k(i)
Normalized Service Life	k(n _{SL})
Normalized Test Time (i+1)	k(i+1)
[Normalized Test Time(i) < Normalized Service Life < Normalized Test Time(i+1)]	

fraction (typically greater than 4 %) of the average slice thickness, then adjustments (given in the remainder of this section) to the above equations to account for the TDSL shall be made.

$$\text{Normalized Test Time}(i) = \frac{\text{Test Time}(i)}{(\text{Average Slice Thickness})^2} \quad (3)$$

$$k_{\text{avg, service life}} = \frac{\int_{\text{service life}} k \times d(\text{time})}{\text{Service Life}} \quad (4)$$

$$k_{\text{avg, predicted}} = \frac{\sum_{n=2}^{n=N_{SL}} \frac{k_{n-1} + k_n}{2} \times (\text{time}_n - \text{time}_{n-1})}{\text{Scaled Service Life}} \quad (5)$$

$$\text{Scaled Service Life} = \text{Service Life} \times \left[\frac{\text{Average Slice Thickness}}{\text{Full Product Thickness}} \right]^2 = \text{time}(n_{SL}) \quad (6)$$

$$\text{Normalized Service Life} = \frac{\text{Projected Service Life}}{(\text{Full Product Thickness})^2} \quad (7)$$

$$k(N S L) = k(i) + \left[\frac{\text{Normalized Service Life} - \text{Normalized Test Time}(i)}{(\text{Normalized Test Time}(i+1) - \text{Normalized Test Time}(i))} \right] \times \{k(i+1) - k(i)\} \quad (8)$$

$$\Delta X_{eff} = \frac{1}{2} \times [(\text{Geometric Thickness}) - (N \times TDSL)] \quad (9)$$

7.7.6.1 Determine the effective diffusion thickness of the thermal resistance specimen, ΔX_{eff} , where N is the number of cut planar surfaces. Usually $N=2$ for a core specimen and $N=1$ for a surface slice. The TDSL was measured in 7.6.5. The Geometric Thickness corresponds to the average slice thickness from 6.4.6.4. See Eq 9.

7.7.6.2 Use two times the effective diffusion thickness as the average slice thickness for the purposes of 7.7.3 and 7.7.5.3.

7.7.6.3 Depending upon the proportion of the average slice thickness represented by the TDSL, in some circumstances it will also be necessary to correct the thermal conductivity measurements. See Appendix X1.

8. Report

8.1 Reporting for Part A, the Prescriptive Method:

8.1.1 Report the following, including references to applicable test methods.

8.1.2 The name, address, and any other identification of the test laboratory and the date of the report. State that Part A: The Prescriptive Method was used.

8.1.3 The name and any other identification of the material tested.

8.1.3.1 Report the ASTM material specification designation, type, class, and grade (as applicable).

8.1.3.2 Report the density of the test specimen.

8.1.4 The manufacturer of the material, the date obtained and the date of manufacture.

8.1.5 The method of slice specimen preparation and the date(s) of specimen preparation.

8.1.6 The environmental conditions at which the specimens were aged.

8.1.7 Mean test temperature and temperature difference for the thermal resistance measurements. State the test method used for thermal resistance measurements, Test Method C177 or C518.

8.1.8 The results of qualification tests in Annex A1, if required.

8.1.9 For each stack tested, report:

8.1.9.1 The type of stack prepared and measured.

8.1.9.2 The average slice thickness for each stack.

8.1.9.3 The test periods calculated in 6.7 for each product thickness, the calculated test dates, and the actual test dates.

8.1.9.4 The thermal resistance corresponding to the resistance at 5 years for each product thickness as measured in 6.6.2.

NOTE 29—The application of these results for product rating purposes is beyond the scope of this test method. See the pertinent material specification for guidance.

8.1.10 The most recent precision and bias for the Part A test method are discussed in 9.5.

NOTE 30—Precision and bias for previous editions of C1303 are described in Section 9.

8.2 Reporting for Part B, the Research Method:

8.2.1 The composition of the test stacks used for the test measurements. This shall include a description of any facer material present on the original product, and whether or not the facer was included in the test specimens.

8.2.2 The average slice thickness for each stack.

8.2.3 A table showing the test dates and the measured thermal conductivity for each test, along with the mean test temperature and temperature difference.

8.2.4 Other analysis results pertinent to the objectives of the research project. It is possible that this will include graphical representations of functional relationships between product thickness, product service life, thermal conductivity, and average effective thermal conductivity.

8.2.5 The precision and bias for this test method, and the expected effect of any differences between the research tests and those used to define the method's precision and bias.

8.2.6 State explicitly whether the Qualification tests of Annex A1 were performed, and if so, give the results of the homogeneity qualification in A1.2.

8.2.7 Other values listed in 8.1.

9. Precision and Bias

9.1 The precision of this test method is significantly influenced by the specimen preparation techniques and the dimension measurement procedures, as well as the precision of the thermal test method used. Precision data on these combined procedures are not yet available for all material types. All precision and bias data reported before 2005 was collected under the conditions specified in the version of C1303 published in 2000.

9.2 A round robin was conducted between 1993 and 1994, and employed unfaced, rigid closed-cell polyisocyanurate (PIR) foam specimens from 7.6 to 33-mm [0.3 to 1.3-in.] thick (8). The PIR boardstock was blown with hydrochlorofluorocarbon 141b and CO₂. Thirteen laboratories were involved in this study. The ratios of predicted lifetime thermal resistance to initial thermal resistance for the seven data sets on board Set 1 had a coefficient of variation of 1.1 % for 10-year lifetimes and 1.3 % for 20-year lifetimes for a thickness of 38 mm [1.5 in.] The results for Set 2 are not pertinent here because there was a significant and variable delay between the slicing and the initial thermal conductivity measurement.

9.3 A round robin was conducted 1995, and employed a selected extruded polystyrene (XPS) foam insulation (12). The specimens varied from 7.9 to 41 mm [0.31 to 1.6 in.] in thickness. Three laboratories participated in this study. The XPS foam insulation used in the round robin was produced in January 1995 using HCFC-142b as the blowing agent. The board stock was nominally 50 mm [2 in.] thick. Each laboratory prepared their own slices using different slice preparation methods including hot-wire, planer, slicer, and band saw. This comparison of slicing/scaling thermal resistance data for extruded polystyrene foamboard insulation resulted in a variability of no more than ±2.5 % in average thermal resistance