



Designation: ~~D4396 – 15~~ D4396 – 22

Standard Specification for Rigid Poly(Vinyl Chloride) (PVC) and Chlorinated Poly(Vinyl Chloride) (CPVC) Compounds for Plastic Pipe and Fittings Used in Nonpressure Applications¹

This standard is issued under the fixed designation D4396; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope*

1.1 This specification covers the classification and identification of rigid plastic compounds intended for use in making nonpressure piping products composed of (1) poly(vinyl chloride) polymer, (2) chlorinated poly(vinyl chloride) polymer, or (3) vinyl chloride copolymers, and the necessary compound ingredients. Compounding ingredients consist of lubricants; stabilizers; non-poly(vinyl chloride) resin modifiers; colorants or pigments, or both; fibrous or nonfibrous reinforcements; or fillers.

1.2 The requirements in this specification are intended for the quality control of compounds used to manufacture pipe or fittings intended for nonpressure use. They Specific properties are not directly applicable to finished pipe and finished fittings products. When specified in a product or application standard, the series of classification properties in this standard form a basis for a material specification. See the applicable ASTM standards or requirements for finished products.

1.3 In special cases, specific compounds for unusual piping applications that require consideration of other properties not covered in this specification, such as service temperature, sag resistance, special chemical resistance, weather resistance, bending forces, and electrical properties, shall be considered.

1.4 Rigid PVC-type compounds for building applications other than piping are covered in Specification [D4216](#).

1.5 Rigid PVC compounds for general purpose extrusion, molding, fitting, and pipe are covered in Specification [D1784](#).

1.6 The rate of burning test, Test Method [D635](#), is used in this specification as a test for identification of certain properties of the compound.

1.7 It is acceptable for rigid PVC and CPVC recycle plastics meeting the requirements of this specification to be used in some applications. Refer to the specific requirements in the Material and Manufacture section of the applicable product standard.

1.8 The values stated in SI units are to be regarded as standard. The values given in parentheses are for information only.

1.9 The following safety hazards caveat pertains only to the test methods portion, Section 10, of this specification: *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

¹ This specification is under the jurisdiction of ASTM Committee [D20](#) on Plastics and is the direct responsibility of Subcommittee [D20.15](#) on Thermoplastic Materials. Current edition approved Oct. 1, 2015; Sept. 1, 2022. Published October 2015; September 2022. Originally approved in 1984. Last previous edition approved in 2006 as [D4396 – 06](#); [D4396 – 15](#), which was withdrawn January 2015 and reinstated in October 2015. DOI: 10.1520/D4396-15; DOI: 10.1520/D4396-22.

*A Summary of Changes section appears at the end of this standard

NOTE 1—There is no known ISO equivalent to this standard.

1.10 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 ASTM Standards:²

- D256 Test Methods for Determining the Izod Pendulum Impact Resistance of Plastics
- D618 Practice for Conditioning Plastics for Testing
- D635 Test Method for Rate of Burning and/or Extent and Time of Burning of Plastics in a Horizontal Position
- D638 Test Method for Tensile Properties of Plastics
- D648 Test Method for Deflection Temperature of Plastics Under Flexural Load in the Edgewise Position
- D883 Terminology Relating to Plastics
- D1600 Terminology for Abbreviated Terms Relating to Plastics
- D1784 Classification System and Basis for Specification for Rigid Poly(Vinyl Chloride) (PVC) Compounds and Chlorinated Poly(Vinyl Chloride) (CPVC) Compounds
- D3892 Practice for Packaging/Packing of Plastics
- D4216 Specification for Rigid Poly(Vinyl Chloride) (PVC) and Related PVC and Chlorinated Poly(Vinyl Chloride) (CPVC) Building Products Compounds
- D5260 Classification for Chemical Resistance of Poly(Vinyl Chloride) (PVC) Homopolymer and Copolymer Compounds and Chlorinated Poly(Vinyl Chloride) (CPVC) Compounds
- F412 Terminology Relating to Plastic Piping Systems

3. Terminology

3.1 *Definitions*—General definitions are in accordance with Terminologies. For definitions of terms that appear in this specification relating to plastics, refer to Terminology D883, F412, and D1600, unless otherwise noted. For abbreviations D1600, unless otherwise noted, that appear in this specification, refer to Terminology D1600.

4. Classification

4.1 The means for classifying and identifying PVC pipe compounds are provided in Table 1. The properties enumerated in this table and the tests defined provide identification of the compounds selected. They are not necessarily suitable for direct application in design because of differences in shape or part, size, loading, environmental conditions, method of processing, etc.

TABLE 1 Class Requirements for Rigid Poly(Vinyl Chloride) (PVC) and Chlorinated Poly(Vinyl Chloride) (CPVC) Pipe Compounds for Nonpressure Piping Products


Designation Order No.	Property and Unit	Cell Limits ^A								
		0	1	2	3	4	5	6	7	8
1	Kind of resin in compound	...	poly(vinyl chloride) (PVC)	chlorinated poly (vinyl chloride) (CPVC)	vinyl chloride copolymer					
2	Impact resistance, min, (J/m) of notch (ft-lbf/in.)	Unspecified	40.0 (0.65)	80.1 (1.5)	266.9 (5.0)	533.8 (10.0)	800.7 (15.0)			
3	Tensile strength, min, (MPa) psi	Unspecified	21 (3000)	27.5 (4000)	34.4 (5000)	44.7 (6500)	48.3 (7000)	55.2 (8000)		
4	Modulus of elasticity in tension, min, (MPa) psi	Unspecified	1930 (280 000)	2344 (340 000)	2620 (380 000)	2758 (400 000)	3034 (440 000)	3171 (460 000)	3585 (520 000)	4275 (620 000)
5	Deflection temperature under load, 264 psi (1.82 MPa), min, °C (°F)	Unspecified	60 (140)	70 (158)	80 (176)	100 (212)	110 (230)	120 (248)	130 (266)	140 (284)

^AThe property value per Section 8 determines the cell number.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For Annual Book of ASTM Standards volume information, refer to the standard's Document Summary page on the ASTM website.

4.2 Classes are designated by the cell number for each property in the order in which they are listed in [Table 1](#).

NOTE 2—The manner in which selected materials are identified by this classification system is illustrated by a cell Class 13452 PVC nonpressure pipe compound having the following requirements (see [Table 1](#)):

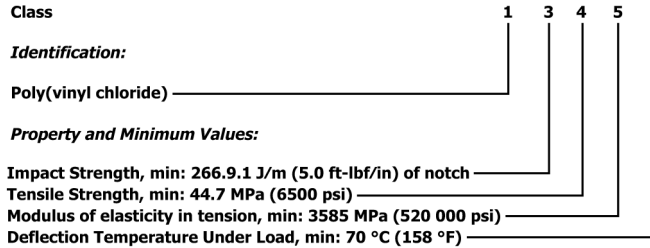

NOTE 3—The cell-type format provides the means for classification and close characterization and specification of compound properties, alone or in combination, for a broad range of compounds. This type format, however, is subject to possible misapplication since unobtainable property combinations can be selected if the user is not familiar with commercially available compounds. The manufacturer should be consulted.

4.3 Product application chemical resistance when specified shall be classified in accordance with the Classification Section of Classification [D5260](#).

5. Materials and Manufacture

5.1 Resin (Polymer) Requirements:

5.1.1 Poly(vinyl chloride) (PVC) resin (polymer) meeting Cell 1 in Designation Order 1 shall have a vinyl chloride homopolymer content not less than 99.0 %.

5.1.2 Chlorinated Poly(vinyl chloride) (CPVC) resin (polymer) meeting Cell 2 in Designation Order 1 shall have a chlorine content not less than 63 %.

5.1.3 Vinyl chloride copolymer resin (polymer) meeting Cell 3 in Designation Order 1 shall contain not less than 80 % vinyl chloride content.

5.2 Compounds supplied under this specification shall be in the form of cubes, granules, pellets, ~~free-flowing powder blends, or compacted or~~ powder blends.

5.3 Compounds shall be of uniform composition and size. Color and transparency or opacity shall be within applicable commercial tolerances.

5.4 Compounds shall be free of foreign matter to a level that will not affect processability, serviceability, or finished product appearance adversely.

6. Physical Requirements

6.1 Test values for specimens of the compound prepared as specified in Section 9 and tested in accordance with Section 11, shall conform to the requirements given in [Table 1](#) for the cell class selected.

6.2 The compound, when tested in accordance with Test Method [D635](#), shall not exceed an average extent of burn of 4 in. (100 mm) nor an average time of burn to exceed 10 s.