



Designation: **D6874–22** D6874 – 22a

Standard Test Methods for Nondestructive Evaluation of the Stiffness of Wood and Wood-Based Materials Using Transverse Vibration or Stress Wave Propagation¹

This standard is issued under the fixed designation D6874; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

INTRODUCTION

Nondestructive testing methods are used to determine the physical and mechanical properties of wood and wood-based materials. These test methods help ensure structural performance of products manufactured from a variety of wood species and quality levels of raw materials. These test methods also assist in evaluating the influence of environmental conditions on product performance.

Dynamic test methods based on the transverse vibration of a simply or freely supported beam, or the propagation of a longitudinal stress wave are methods used to nondestructively evaluate wood-based materials. These methods yield results comparable to traditional static test methods, permitting standardization of results, interchange and correlation of data, and establishment of a cumulative body of information on wood species and products of the world.

1. Scope

1.1 These test methods cover the non-destructive determination of the following dynamic properties of wood and wood-based materials from measuring the fundamental frequency of vibration:

1.1.1 Flexural (see Refs **(1-3)**)² stiffness and apparent modulus of elasticity (E_{tv}) properties using simply or freely supported beam transverse vibration in the vertical direction, and

1.1.2 Axial stiffness and apparent longitudinal modulus of elasticity (E_{sw}) using stress wave propagation time in the longitudinal direction.

1.2 The test methods can be used for a broad range of wood-based materials and products ranging from logs, timbers, lumber, and engineered wood products.

1.2.1 The two flexural methods can be applied to flexural products such as glulam beams and I-joists.

1.2.2 The longitudinal stress wave methods are limited to solid wood and homogeneous grade glulam (for example, columns but not products with distinct subcomponents such as wood I-joists).

¹ These test methods are under the jurisdiction of ASTM Committee D07 on Wood and is the direct responsibility of Subcommittee D07.01 on Fundamental Test Methods and Properties.

Current edition approved Aug. 1, 2022/Oct. 1, 2022. Published October 2022/November 2022. Originally approved in 2003. Last previous edition approved in 2021/2022 as ~~D6874 – 21~~D6874 – 22. DOI: ~~10.1520/D6874-22~~10.1520/D6874-22A.

² The boldface numbers in parentheses refer to the list of references at the end of this standard.

1.3 The standard recognizes three implementation classes for each of these test methods.

1.3.1 *Class I*—Defines the fundamental method to achieve the highest degree of repeatability and reproducibility that can be achieved under laboratory conditions.

NOTE 1—Testing should follow Class I methods to develop training and validation data sets for method conversion models (see [Annex A2](#)).

1.3.2 *Class II*—Method with permitted modifications to the Class I method that can be used to address practical issues found in the field, and where practical deviations from the Class I protocol are known and their effects can be accounted.

NOTE 2—Practical deviations include, for example, environmental and test boundary conditions. Class II methods allow for corrections to test results to account for quantifiable effect such as machine frame deflections.

1.3.3 *Class III*—Method permitting the broadest range of application, with permitted modifications to suit a wider range of practical needs with an emphasis on repeatability.

NOTE 3—Online testing machines implemented to grade/sort lumber may be treated as Class III.

1.4 The standard provides guidance for developing a model for estimating a non-destructive test method result (for example, static modulus of elasticity obtained in accordance with Test Methods [D198](#)) from another non-destructive test method result (for example, dynamic longitudinal modulus of elasticity from measurement of longitudinal stress wave propagation time).

1.4.1 The standard covers only models developed from test data obtained directly from non-destructively testing a representative sample using one test method, and retesting the same sample following a second test method.

1.4.2 Results used for model development shall not be estimated from a model.

1.5 The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.

1.6 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.7 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 ASTM Standards:³

[D9 Terminology Relating to Wood and Wood-Based Products](#)

[D198 Test Methods of Static Tests of Lumber in Structural Sizes](#)

[D1990 Practice for Establishing Allowable Properties for Visually-Graded Dimension Lumber from In-Grade Tests of Full-Size Specimens](#)

[D2395 Test Methods for Density and Specific Gravity \(Relative Density\) of Wood and Wood-Based Materials](#)

[D2915 Practice for Sampling and Data-Analysis for Structural Wood and Wood-Based Products](#)

[D3043 Test Methods for Structural Panels in Flexure](#)

[D4442 Test Methods for Direct Moisture Content Measurement of Wood and Wood-Based Materials](#)

[D4444 Test Method for Laboratory Standardization and Calibration of Hand-Held Moisture Meters](#)

[D4761 Test Methods for Mechanical Properties of Lumber and Wood-Based Structural Materials](#)

[D7438 Practice for Field Calibration and Application of Hand-Held Moisture Meters](#)

[E4 Practices for Force Calibration and Verification of Testing Machines](#)

[E2655 Guide for Reporting Uncertainty of Test Results and Use of the Term Measurement Uncertainty in ASTM Test Methods](#)

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

2.2 ISO Standards:⁴

ISO 7626/1 Mechanical vibration and shock—Experimental determination of mechanical mobility—Part 1: Basic terms and definitions, and transducer specifications

ISO 7625/5 Vibration and shock—Experimental determination of mechanical mobility—Part 5: Measurements using impact excitation with an exciter which is not attached to the structure

3. Terminology

3.1 Definitions—See Terminology D9 and Test Methods D198.

3.2 Definitions of Terms Specific to This Standard:

3.2.1 calibration, *v*—the determination of the relationship between the response of a standardized instrumentation to properties determined by a standard method of a reference material in order to obtain comparable results between different instruments.

3.2.2 fundamental mode of vibration, *n*—the simplest mode of vibration for the given support condition.

3.2.2.1 Discussion—

For a simply supported beam, the fundamental mode has the mode shape with a half-sine wave form (see Fig. 1).

3.2.2.2 Discussion—

For a freely supported beam, the fundamental mode has the mode shape shown in Fig. 2.

3.2.3 longitudinal stress wave, *n*—the wave induced in a specimen by the transmission and attenuation of speed-of-audible sound generated by an excitation in the specimen’s longitudinal direction.

3.2.3.1 Discussion—

Resonant frequency (Fig. 3) is the frequency of the stress wave that reflects off the ends of the specimen following an end impact. The frequency may be determined from time-signal data collected by a single accelerometer, or by a microphone detecting sound waves emitted by the specimen following the impact. Higher frequencies will be present in the signal. Therefore, the signal will need to be analyzed to extract the fundamental frequency.

3.2.3.2 Discussion—

Time of flight (Fig. 4) is the time required for stress wave to travel a known distance through the specimen. This method is excluded from this standard. Because there are many frequencies excited in this manner, the signal needs to be analyzed to find the same wave that passes the first and second transducers. This is further complicated by the fact that higher frequencies attenuate faster than lower frequencies, and that these may vary depending on the specimen size and test configuration.

3.2.4 modal analysis, *v*—the process of determining the natural frequencies, modal damping ratios, and mode shapes of an object such as a beam for the vibration modes in the frequency range of interest from the Frequency Response Function (see Appendix X3).

3.2.5 modal testing, *v*—measurement of the Frequency Response Function (see Appendix X3).

3.2.6 mode shape, *n*—pattern of movement (that is, dynamic displacement, velocity, or acceleration) of an object for a vibration mode.

3.2.7 oscillation, *n*—the periodic movement of the specimen about a central position that includes both the rigid movement and the vibration of the specimen.

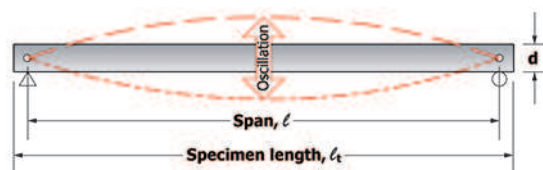


FIG. 1 Mode Shape of Simply Supported Beam Under Transverse Vibration in the Fundamental Mode

⁴ Available from American National Standards Institute (ANSI), 25 W. 43rd St., 4th Floor, New York, NY 10036, <http://www.ansi.org>.

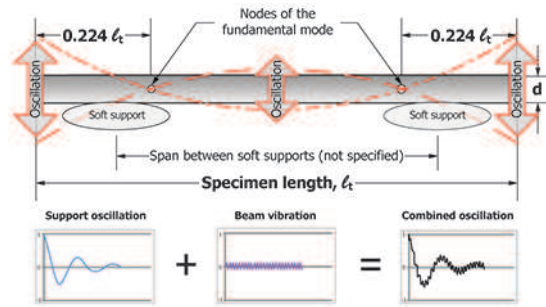


FIG. 2 Mode Shape of Freely Supported Beam Under Transverse Vibration in the Fundamental Mode



FIG. 3 Stress Wave Transmission in a Specimen (Resonant Frequency)

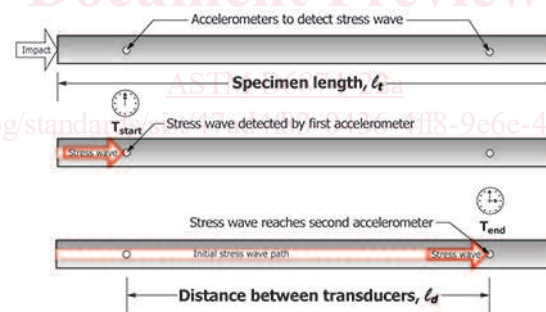


FIG. 4 Stress Wave Transmission in a Specimen (Time of Flight)

3.2.8 *standardization, v*—the determination of the response of the instrumentation to a reference material to demonstrate consistency of results from instruments of the same type.

3.2.9 *training test sample, n*—a test sample that provides results for establishing the statistical model to convert from one non-destructive test method to another non-destructive test method.

3.2.10 *transverse vibration, n*—the oscillation of a specimen in flexure that results from causing an initial displacement of the specimen at its mid-span or another other means of exciting the fundamental mode of vibration.

3.2.11 *validation test sample, n*—a test sample separate from the training test sample that provides results for checking the model’s ability to accurately represent the relationship between the two non-destructive test methods established by the training test sample.

3.2.12 *vibration, n*—the component of the specimen’s oscillation that results in an elastic strain in the specimen.

3.2.12.1 *Discussion*—

The oscillation that remains after the periodic rigid body motion is removed.

3.2.13 *vibration mode, n*—the vibration behavior of a specimen that is characterized by its natural frequency, modal damping, and mode shape.

3.2.13.1 *Discussion*—

The free vibration of a continuous object such as a beam or a log contains a summation of an infinite number of vibration modes. The free vibration from which the modulus of elasticity is computed shall not include any periodic rigid body motion, or oscillating motion that does not result in any elastic strain in the specimen.

4. Summary of Test Methods

4.1 Two dynamic modulus of elasticity methods are covered:

4.1.1 *Transverse Vibration Methods*—The specimen is deflected at its mid-span and allowed to oscillate in a transverse bending mode. Observations of the frequency of oscillation are used to calculate a flexural stiffness or apparent modulus of elasticity.

4.1.2 *Longitudinal Stress Wave Method*—A longitudinal stress wave is induced by impacting the end of a specimen. Indirect observation of the transmission time from measuring resonant frequency is used to calculate an axial stiffness or apparent longitudinal modulus of elasticity.

NOTE 4—The dynamic modulus of elasticity is determined when the specimen's stress state is changing. The static modulus of elasticity is the traditional method where the modulus of elasticity is determined at two different stress states where the stresses are not changing or changing at a slow rate as defined in the static test method. Examples of static test methods for wood and wood-based products are standard Test Methods [D198](#), [D4761](#), and [D3043](#).

5. Significance and Use

5.1 The dynamic modulus of elasticity provided by these test methods is a fundamental property for the configuration tested.

5.1.1 The rapidity and ease of application of these test methods facilitate their use as a substitute for static measurements.

5.1.2 Dynamic modulus of elasticity is often used for surveys, for segregation of lumber for test purposes, for quality assessment of engineered wood products, and to provide indication of environmental or processing effect.

<https://standards.iteh.ai/catalog/standards/sist/47ad4f83-0436-4ff8-9e6e-4b0a9def8eba/astm-d6874-22a>

5.2 The modulus of elasticity, whether measured statically or dynamically, is often a useful predictor variable to suggest or explain property relationships.

5.3 Results from these test methods can be related to other measurements of modulus of elasticity, such as static methods (see [Annex A1](#) and [Appendix X4](#)).

5.4 These methods use calculations that assume specimens are prismatic in cross-section and are uniform in modulus of elasticity and density.

5.4.1 As a result of the above assumptions, the obtained values of modulus of elasticity are dependent on how the specimen is stressed (see [Commentary](#)).

5.4.2 Transverse vibration and longitudinal stress wave modulus of elasticity are correlated but not necessarily equal.

5.4.3 These methods provide a means to establish a model to predict one dynamic modulus of elasticity from another dynamic method or a static method (that is, [D198](#), [D4761](#), etc.).

5.4.4 The methods can also be used to estimate the Class I or Class II modulus of elasticity from the Class III method, or the Class I from the Class II method.

5.5 Testing specified to be undertaken in accordance with this Method shall include any requirements regarding the following for each Class:

- 5.5.1 Grades and species permitted to be combined to form the training and validation test sample.
- 5.5.2 Selection and positioning of manufacturing or growth characteristics to be included or permitted in the test sample.
- 5.5.3 Moisture content conditioning undertaken prior to testing.
- 5.5.4 Acceptable moisture content adjustment models.
- 5.5.5 Any other sampling and data adjustment requirements to obtain a representative sample of the population under consideration.

NOTE 5—Guidance or requirements from applicable product standards or specifications for representative sampling should be considered. See [Annex A2](#).

NOTE 6—See Commentary [Appendix X4](#) for additional information (for example, blocking parameter and blocking limits) that may need to be provided for generating a test sample suitable for developing the test method conversion model.

6. Precision and Bias

- 6.1 The precision and bias of these test methods have not yet been established.

TRANSVERSE VIBRATION METHODS

7. Apparatus

- 7.1 The testing equipment shall consist of four essential elements:

- 7.1.1 Support apparatus,

- 7.1.2 Excitation system,

- 7.1.3 Response and weight measurement devices, and [ASTM D6874-22a](#)

<https://standards.iteh.ai/catalog/standards/sist/47ad4f83-0436-4ff8-9e6e-4b0a9def8eba/astm-d6874-22a>

- 7.1.4 Time signal processing algorithm.

8. Test Procedure

8.1 *Standardization and Calibration*—The testing system shall be standardized and calibrated using standard reference materials. The procedures of [Annex A1](#) shall be followed. The results of this test method are conditional upon proper standardization and appropriate choice of calibration method.

NOTE 7—It has been a practice to use aluminum bars or lumber specimens as standardization materials and also for calibration against a standard static test results.

8.2 *Excitation*—The procedures of excitation listed under each Class shall be followed. Repetitions and inter-laboratory testing are recommended to assess test procedures and to reduce the chance of bias caused by improper excitation.

8.3 *Calculation of Dynamic Modulus of Elasticity and Stiffness:*

8.3.1 *Basic Equations*—The following formulas, [Eq 1](#) and [Eq 2](#), shall be used to calculate apparent dynamic modulus of elasticity and bending stiffness from the measured oscillation in the fundamental mode for either the simply supported ([Fig. 1](#)) or freely supported ([Fig. 2](#)) beams:

$$E_w = \frac{f^2 w \ell^3}{KIg \left(\frac{\ell_r}{\ell} \right)} \quad (1)$$

$$(EI)_{rv} = \frac{f^2 w \ell^3}{Kg \left(\frac{\ell_r}{\ell} \right)} \quad (2)$$

where:

- E_{rv} = modulus of elasticity determined using transverse vibration, psi (MPa),
- $(EI)_{rv}$ = bending stiffness determined using transverse vibration method, lb-in² (N-mm²),
- ℓ_r = specimen length, in. (mm),
- ℓ = span, in. (mm) for simply-supported beams,
= ℓ_r , for freely supported beams,
- w = total specimen weight, lbf (N),
- f = fundamental vibration mode frequency, Hz (s⁻¹),
- I = specimen moment of inertia, in⁴ (mm⁴); for example, $bh^3/12$, for a rectangular cross-section,
- b = horizontal breadth (width), in. (mm),
- d = vertical depth, in. (mm),
- g = acceleration due to gravity, 386 in./s² (9807 mm/s²), and
- K = constant for free vibration of a beam (see Ref (4))
= 2.47, if simply supported,
= 12.48, if freely supported.

9. Class I—Laboratory Use

9.1 Apparatus

9.1.1 Support Apparatus:

9.1.1.1 Simply Supported Beams—Vertical support is provided at the ends of the beam while rotation is unrestrained.

NOTE 8—The supporting material should be sufficiently stiff so that the vertical stiffness of the support is much greater than the flexural stiffness of the specimen. If the stiffness of the support is not sufficiently high compared to the stiffness of the specimen, the measured fundamental frequency will be affected. See Refs. (5) and (6). Even support on carpet with a pad can affect the fundamental frequency.

(1) *Reactions*—The specimen shall be supported in a manner to prevent damage to the specimen at the point of contact between it and the reaction support.

NOTE 9—Dimension lumber specimens are typically light enough to enable them to be supported on knife edges or the load button of a load cell. Where flat bearing plates are required, ensure the plate does not impede free rotation of the specimen.

(2) The reactions shall be such that rotation of the specimen about the reaction due to deflection will be unrestricted.

(3) Transverse vibration that results in a large mid-span deflection (for example, when the vibration amplitude exceeds approximately half the specimen depth, d) shall have at least one support configured to provide unrestricted longitudinal movement of the specimen relative to the support (for example, a roller).

(4) *Reaction Alignment*—Provision shall be made at the reactions to allow for initial twist in the length of the specimen. If the bearing surfaces of the specimen at its reaction are not parallel to the bearing surface of the reactions, the specimen shall be shimmed or the bearing surfaces shall be permitted to rotate about an axis parallel to the span to provide adequate contact across the width of the specimen.

(5) *Lateral Support*—No lateral support shall be applied. Specimens unstable in this mode shall not be tested using this method.

(6) *Lengthwise Positioning and Overhang of the Specimen*—The specimen shall be positioned with an equal portion of the length overhanging each support. If basic equation (Eq 1) is used, then the span (ℓ) to length (ℓ_r) ratio shall equal or exceed 0.98 (for example, an overhang of 1 in. (25 mm) at each end of an 8-ft (2400-mm) long member).

NOTE 10—Excessive or unequal overhang may alter results obtained. Overhang that differs by one specimen depth (d , as defined in 8.3.1) or less may be neglected.

NOTE 11—When developing data for method conversion (see Annex A2), it is recommended that the span not be varied to meet the maximum overhang criteria. Doing so may introduce additional measurement errors associated with setting the test span. If possible, samples should be cut to a common length so that the test can be carried out at the same span.

9.1.1.2 *Freely Supported Beams*—The free support condition (soft supports, such as by air bags) shall provide vertical support when the specimen is at rest, and permit rotation and vertical movement when the specimen is excited and vibrating in the

fundamental mode. The stiffness of the supports shall be identical and sufficiently flexible at both support points to permit the specimen to oscillate at a frequency that is less than approximately one-tenth of the fundamental vibration frequency of the specimen.

NOTE 12—The frequency of oscillation of the specimen contains the movement of the specimen relative to the fixed ground and will depend on the stiffness of the supports and the specimen. The fundamental vibration frequency of the specimen contains only movement of the specimen relative to the nodes of the fundamental mode (see Fig. 2) and is dependent on the stiffness of the specimen.

NOTE 13—In order to accurately isolate and not affect the measured vibration frequency of the specimen, the supporting material should be sufficiently flexible so that the vertical stiffness of the support is much smaller than the stiffness of the specimen. If the stiffness of the support is not sufficiently low compared to the stiffness of the specimen, the measured fundamental vibration frequency of the specimen will be affected. The support may be a spring, elastic string, elastic mat, or air bag selected or adjusted to have the desired compliance. See commentary.

(1) *Reactions and Lateral Support*—The specimen shall be supported in a manner as specified in 9.1.1.1(1) to 9.1.1.1(5).

(2) *Lengthwise Positioning and Overhang of the Specimen*—The specimen shall be positioned such that the length of overhang at each support is approximately equal. The supports shall be positioned to minimize rigid body rotation of the specimen.

NOTE 14—The freely supported beam method is not as susceptible as the simply supported beam method to measurement errors arising from unequal overhangs. A large unequal overhang is likely to result in rigid body rotation of the specimen.

NOTE 15—Ideally, the supports should be placed at the nodes of the fundamental mode. Supports located far from the node, particularly when they are not sufficiently flexible, or at mid-length may alter the beam vibration frequency. As the supports are moved closer together, the specimen becomes susceptible to rigid body rotation (that is, downward movement at one support and upward movement at the other support) which should be avoided or minimized. Such rotation effects can be assessed by applying a downward impact at only one end and observing if significant oscillation due to rigid body rotation occurs.

9.1.2 *Excitation System*—The specimen shall be excited so as to produce a vertical oscillation in a repeatable and reproducible manner in the fundamental mode. The method of analysis is based on oscillation in this mode (Fig. 2).

NOTE 16—It is recommended to measure the time signals of the excitation.

9.1.2.1 *Manual Method*—A manual deflection and release of the specimen will provide sufficient impetus for oscillation for many products. The initial deflection shall be vertical with an effort to exclude lateral components; neither excessive impact nor prolonged contact with the specimen are recommended.

NOTE 17—For example, a manual tap on a 16-foot 2-by-12, supported flat-wise having a modulus of elasticity of 2.0×10^6 psi will result in a vertical fundamental vibration frequency of between 3 and 4 Hz in either of the two transverse vibration methods.

NOTE 18—A manual tap with a hammer instrumented with an integrated load cell is preferred.

9.1.2.2 *Mechanical Methods*—Use of a mechanical exciter to cause a deflection as noted in 9.1.2.1 is permitted. Caution shall be exercised to limit the excitation forces to avoid exciting a non-linear response.

9.1.3 *Response and Weight Measurement Devices*—Measurement of the frequency of oscillation shall be obtained by either a force transducer installed at one or both supports; or a displacement, velocity, or acceleration transducer installed at mid-span. The time signals from the transducers shall be recorded in analog or digital form that preserves the accuracy as specified in the applicable standards in 2.2.

NOTE 19—Displacement sensors are normally not used to measure the vibration signals. In practice, accelerometers, which are both cost effective and rugged, are the most common.

NOTE 20—The minimum speed and resolution of the data acquisition system, and the minimum sampling rates used must anticipate the frequency to be measured.

9.1.3.1 *Force Transducer*—Changes in the force in response to the vibration at one or both of the supports is one method used to obtain the vibration time signal. Force transducers shall be selected and calibrated to ensure accuracy in accordance with Practices E4 and shall be sufficiently stiff to not affect the fundamental frequency of the system. Test procedures shall include steps to eliminate transient force readings.

NOTE 21—If the stiffness of load transducers is not sufficiently high, it will alter the natural transverse vibration frequency of the specimen and produce erroneous results. This issue is normally not related to the transducer calibration.

9.1.3.2 *Deflection, Velocity, or Acceleration Transducer*—Measurement of the mid-span displacement, velocity, or acceleration in response to the initial displacement are alternative methods to obtain the vibration time signal. Displacement, velocity or acceleration transducers shall meet the requirements of ISO 7626/1.

9.1.4 *Time Signal Processing Algorithm*—A procedure implemented manually, or in hardware and software for processing the time signals to obtain the fundamental natural frequency shall be established.

9.1.4.1 The standardization procedure shall include the time signal processing algorithm and all calibrated transducers.

9.1.4.2 Changes to the time signal processing algorithm or any of the transducers shall be subject to the standardization procedures.

9.1.5 *Determining the Fundamental Mode*—Document the procedures used to identify the frequency associated with the fundamental vertical oscillation mode, and to ensure that the data acquired is only related to the fundamental vertical mode (Fig. 1).

NOTE 22—Appendix X3 and Ref (7) provide the procedure to determine the mode shape.

NOTE 23—When validated for a specific flexural stiffness and span-to-depth ratio, a short delay before acquiring the data may also be used to ensure the data acquired is only related to the fundamental vertical mode.

9.2 Test Specimen

9.2.1 Specimens shall be solid and prismatic (uniform in cross-section area along the length). Deviations in shape and uniformity in dimension from end-to-end and side-to-side incidental to sampling, such as wane included in a lumber grade description, shall be noted as part of the sample or specimen description.

9.2.2 *Span to Depth Ratio*—Specimens shall be tested at the permitted span-to-depth ratio.

9.2.2.1 Except as permitted in 9.2.2.2, the span-to-depth ratio shall be greater than or equal to 20.

9.2.2.2 Where the span-to-depth is less than 20, modal analysis shall be conducted on tests on a representative sample to show that the procedures used will determine the vibration frequency corresponding to the fundamental frequency.

9.2.3 *Specimen Dimensions*—Specimen dimensions (for example, diameter, width, depth, length, etc.) shall be measured to at least three significant figures. Sufficient measurements of the cross-section shall be made to establish the number of measurements needed to determine the average dimensions along the length.

NOTE 24—The cross-section size of Surfaced Dry (S-Dry) dimension lumber can typically be established by measuring the cross-section at one location along the length.

9.2.4 *Moisture Content*—Moisture content (MC) of specimens shall be measured in accordance with Test Methods D4442 or Practice D7438, or both. Specific reference to the current moisture status of the specimens shall be made; for example, equilibrated, recently kiln dried containing gradients, air dried, packaged specimens of unknown drying history, and so forth. Identification of MC gradients caused by drying or surface wetting is recommended.

NOTE 25—MC gradients within a piece may affect the dynamic modulus of elasticity (see X1.1.23).

9.2.5 *Specimen Weight*—The specimen weight used in Eq 1 or Eq 2 shall be determined to at least 3 significant figures.

10. Class II—Field Use

10.1 Apparatus

10.1.1 Support Apparatus:

10.1.1.1 *Simply Supported Beams*—The support apparatus shall meet the requirements of 9.1.1.1.

10.1.1.2 *Lengthwise Positioning and Overhang of the Specimen*—The specimen shall be positioned such that an equal portion of the length overhangs each support. If basic equation (Eq 1) is used, then the span (ℓ) to length (ℓ_t) ratio shall equal or exceed 0.85. If other ℓ/ℓ_t ratios are used, more exacting analysis and equations shall be used; see Ref (8).

NOTE 26—Excessive or unequal overhang may alter results obtained. Overhang that differs by one specimen depth (d , as defined in 8.3.1) or less may be neglected.

10.1.1.3 *Freely Supported Beams*—The support apparatus shall meet the requirements of 9.1.1.2.

10.1.2 *Excitation System*—The excitation system shall meet the requirements of 9.1.2.

10.1.3 *Response and Weight Measurement Devices*—The response and weight measurement devices shall meet the requirements of 9.1.3.

10.1.4 *Time Signal Processing Algorithm*—The time signal processing algorithm shall meet the requirements of 9.1.4.

10.2 Test Specimen

10.2.1 Specimens shall be solid and prismatic (uniform in cross-section area along the length). Deviations in shape and uniformity in dimension from end-to-end and side-to-side incidental to sampling, such as wane included in a lumber grade description, shall be noted as part of the sample or specimen description.

10.2.2 *Span-to-Depth Ratio*—The span-to-depth ratio used shall meet the requirements of 9.2.2.

10.2.3 *Specimen Dimensions*—The specimen dimensions used to compute the modulus of elasticity shall be recorded.

10.2.3.1 Unless the effect of cross-section modification is a test evaluation objective, test the specimens without modifying the dimensions of the commercial cross-section.

10.2.3.2 Where the average dimensions of the sample are used, a representative sub-sample of specimens shall be selected and measured for specimen dimension in accordance with 9.2.3. The sub-sample size shall be sufficient to estimate the 95% confidence limits of each average dimension.

NOTE 27—Where the sample consists of specimens produced at different facilities or at different times, the average dimension of the sample may not be representative of the combined population. Measuring the dimensions of each specimen is recommended.

10.2.3.3 Where the average dimensions of the sample are not used, specimen dimensions shall be measured in accordance with 9.2.3.

10.2.4 *Moisture Content*—A sample representative of the moisture content of the test population shall be measured for moisture content in accordance with Test Methods D4442, Practice D7438, or both.

10.2.4.1 Where the 95% confidence interval for the average moisture content is 2% or greater, the moisture content shall be determined as specified in 9.2.4.

10.2.4.2 Where the 95% confidence interval for the average moisture content is less than 2%, it is permitted to report only the average and 95% confidence interval for the average moisture content.

10.2.5 *Specimen Weight*—The specimen weight used in Eq 1 or Eq 2 shall be determined to at least two significant figures.

NOTE 28—For the simply supported method, the specimen weight may be estimated from a force reading at one support (that is, the “half-weight”). It is recommended to verify that the test population tested in this manner provides a weight reading within the tolerance specified in 10.2.5.

11. Class III—Other Applications

11.1 Apparatus

11.1.1 Support Apparatus:

11.1.1.1 *Simply Supported Beams*—The support apparatus shall meet the requirements of 9.1.1.1.

11.1.1.2 *Lengthwise Positioning and Overhang of the Specimen*—The lengthwise positioning and overhang of the specimen shall meet the requirements of 10.1.1.2.

11.1.1.3 *Freely Supported Beams*—The support apparatus shall meet the requirements of 9.1.1.2.

11.1.2 *Excitation System*—The excitation system shall meet the requirements of 9.1.2.

11.1.3 *Response and Weight Measurement Devices*—The response and weight measurement devices shall meet the requirements of 9.1.3.

11.1.4 *Time Signal Processing Algorithm*—The time signal processing algorithm shall meet the requirements of 9.1.4.

11.2 Test Specimen

11.2.1 Specimens shall meet the requirements of 10.2.1.

11.2.2 *Span-to-Depth Ratio*—The span-to-depth ratio used shall meet the requirements of 10.2.2.

11.2.3 *Specimen Dimensions*—The specimen dimensions used to compute the modulus of elasticity shall be recorded.

11.2.3.1 Where a dimension monitoring program is not in effect or is not able to provide specimen dimension information on the sample, a sample representative of the dimensions of the test population shall be measured in accordance with 9.2.3.

NOTE 29—Monitoring programs include measurements for quality assurance.

11.2.4 *Moisture Content*—The specimen moisture content shall be within the range of moisture content permitted for the protocol established in accordance with Annex A1.

11.2.4.1 Where a moisture monitoring program is not in effect or is not able to provide specimen moisture content information on the sample, a sample representative of the dimensions of the test population shall be measured in accordance with 10.2.4.

11.2.5 *Specimen Weight*—The specimen weight shall be determined as required by the protocol evaluated in accordance with Annex A1.

11.2.5.1 The accuracy of the method for estimating the specimen weight used in Eq 1 or Eq 2 shall be recorded.

11.2.5.2 The specimen weight, when measured for each specimen, shall be recorded to at least two significant figures.

STRESS WAVE METHOD

12. Apparatus

12.1 The testing equipment shall consist of three essential elements:

12.1.1 A support apparatus,

12.1.2 An excitation system, and

12.1.3 A measurement system to determine the stress wave transmission time, or a time signal processing algorithm.

13. Test Procedure

13.1 *Standardization and Calibration*—The testing system shall be standardized and calibrated using standard reference materials. The procedures of **Annex A1** shall be followed. The results of this test method are conditional upon proper standardization and appropriate choice of calibration method.

NOTE 30—It has been a practice to use aluminum bars or standardization materials and, often, also for calibration against a standard static test results.

13.2 *Excitation*—The procedures of excitation listed under each Class shall be followed. Repetitions and inter-laboratory testing are recommended to assess test procedures and to reduce the chance of bias caused by improper excitation.

13.2.1 To quantify measurement uncertainty for precision and bias estimates, specific data sets shall be taken during the test sequence to allow calculation of this contribution to measurement tolerances.

13.3 *Calculation of Dynamic Modulus of Elasticity and Stiffness:*

13.3.1 The following equations, **Eq 3** or **Eq 4**, shall be used to calculate the longitudinal modulus of elasticity and axial stiffness from the measured frequency of the reflected stress wave (**Fig. 3**):

$$E_{sw} = \frac{4\ell_t w f^2}{gA} \quad (3)$$

$$(EA)_{sw} = \frac{4\ell_t w f^2}{g} \quad (4)$$

where:

E_{sw} = modulus of elasticity determined using longitudinal stress wave, psi (MPa),
 EA_{sw} = axial stiffness determined using longitudinal stress wave, lb (N),
 ℓ_t = specimen length, in. (mm),
 f = frequency of the first mode of the longitudinal vibration, s^{-1} (Hz) (see **Fig. 3**), and
 A = cross-section area of the specimen, $in.^2$ (mm^2).

14. Class I—Laboratory Use

14.1 Apparatus

14.1.1 Support Apparatus:

14.1.1.1 The support apparatus shall provide vertical support yet permit longitudinal movement.

NOTE 31—A thick elastic mat or air bag are examples of suitable supports.

(1) *Lateral Support*—No lateral support shall be applied. Specimens unstable in this mode shall not be tested using this method.

14.1.2 *Excitation System*—The specimen shall be excited as to produce a stress wave that propagates through the length of a specimen in a repeatable and reproducible manner (**Fig. 4**). The magnitude of the impact force, and the duration of contact with the specimen shall be kept to a minimum.

NOTE 32—A mechanical exciter, such as a hammer, is preferred.

14.1.3 *Measurement System*—A transducer shall be used to obtain the time-signal data of the longitudinal stress wave reflected off the ends of the specimen. Analysis of the time-signal data shall be used to determine the resonant frequency. The dynamic modulus of elasticity or dynamic axial stiffness shall be calculated in accordance with **13.3.1**.

14.1.4 *Time Signal Processing Algorithm*—A procedure implemented manually, or in hardware and software for processing the time signals shall be established.

14.1.4.1 The standardization procedure shall include the time signal processing algorithm and all calibrated transducers.

14.1.4.2 Changes to the time signal processing algorithm or any of the transducers shall be subject to the standardization procedures.

14.1.5 *Determining the Resonant Frequency*—Document the procedures used to identify the frequency associated with the fundamental frequency, and to ensure that the data acquired is only related to the fundamental frequency of the longitudinal stress wave.

14.2 Test Specimen

14.2.1 Specimens shall be uniform along the length. Deviations in shape and uniformity in dimension from end-to-end and side-to-side incidental to sampling, such as wane included in a lumber grade description, shall be noted as part of the sample or specimen description.

14.2.2 *Specimen Dimensions*—Specimen dimensions (for example, diameter, width, depth, length, etc.) shall be measured as specified in 9.2.3.

NOTE 33—The cross-section size of Surfaced Dry (S-Dry) dimension lumber can typically be established by measuring the cross-section at one location along the length.

14.2.3 *Moisture Content*—The MC shall be determined as specified in 9.2.4.

14.2.4 *Specimen Weight*—The specimen weight used in Eq 3 or Eq 4 shall be recorded as specified in 9.2.5.

15. Class II—Field Use

15.1 Apparatus

15.1.1 Support Apparatus:

15.1.1.1 The support apparatus shall meet the requirements of 14.1.1.

15.1.2 *Excitation System*—The excitation system shall meet the requirements of 14.1.2.

15.1.3 *Measurement System*—The measurement system shall meet the requirements of 14.1.3.

15.1.4 *Determining the Resonant Frequency*—The signal processing system shall meet the requirements of 14.1.4.

15.2 Test Specimen

15.2.1 The characteristic specimen shape shall be as defined in the model and validated in accordance with Annex A1.

15.2.2 *Specimen Dimensions*—The specimen dimensions used to compute the modulus of elasticity shall be recorded.

15.2.2.1 Unless the effect of cross-section modification is a test evaluation objective, test the specimens without modifying the dimensions of the commercial cross-section.

15.2.2.2 Where dimensions used are the average dimensions of the sample, a representative sub-sample of specimens shall be selected and measured for specimen dimension in accordance with 14.2.2. The sub-sample size shall be sufficient to estimate the 95% confidence limits of each dimension.

NOTE 34—Where the sample consists of specimens produced at different facilities or at different times, the average dimension of the sample may not be representative and measuring the dimensions of each specimen is recommended.

15.2.2.3 Where the average dimensions of the sample are not used, specimen dimensions shall be measured in accordance with 14.2.2.