



**Designation: D5344–99 (Reapproved 2017) D5344 – 22**

## Standard Test Method for Extension Force of Partially Oriented Yarn<sup>1</sup>

This standard is issued under the fixed designation D5344; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope

1.1 This test method covers the measurement of extension force developed while drawing a partially oriented filament yarn between pairs of draw rolls of different surface speeds.

1.2 Extension force provides an estimate of the yarn orientation.

1.3 This test method applies to partially oriented filament yarns less than 33.3 tex (300 denier), but it can be used for higher deniers by applying the test conditions as directed in **Appendix X1**.

1.4 The values stated in SI units are to be regarded as standard. The values given in parentheses are provided for information only.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.6 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

<https://standards.iteh.ai/catalog/standards/sist/0984fd96-740d-479e-bfe3-abe933574077/astm-d5344-22>

### 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

[D123 Terminology Relating to Textiles](#)

[D1776 Practice for Conditioning and Testing Textiles](#)

[D2258 Practice for Sampling Yarn for Testing](#)

[D2904 Practice for Interlaboratory Testing of a Textile Test Method that Produces Normally Distributed Data](#) (Withdrawn 2008)<sup>3</sup>

[D2906 Practice for Statements on Precision and Bias for Textiles](#) (Withdrawn 2008)<sup>3</sup>

[D4849 Terminology Related to Yarns and Fibers](#)

### 3. Terminology

3.1 For terminology related to yarn test methods refer to Terminology **D4849**.

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee **D13** on Textiles and is the direct responsibility of Subcommittee **D13.58** on Yarns and Fibers. Current edition approved July 1, 2017; Nov. 1, 2022. Published July 2017/December 2022. Originally approved in 1993. Last previous edition approved in 2011 as **D5344-99(2011); D5344-99** (2017). DOI: [10.1520/D5344-99R17.10.1520/D5344-22](https://doi.org/10.1520/D5344-99R17.10.1520/D5344-22).

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> The last approved version of this historical standard is referenced on [www.astm.org](http://www.astm.org).

3.2 The following terms are relevant to this standard: drawing; draw ratio (DR); draw texturing; extension; extension force; partially oriented yarn.

3.3 For definitions of other textile terms used in this test method refer to Terminology **D123**.

#### 4. Summary of Test Method

4.1 Partially oriented filament yarn withdrawn from a package is pretensioned, heated, and drawn on an instrument under conditions similar to those used in the draw-texturing process. A tension measuring head senses the force required to draw the running yarn a specified amount of its original length under given conditions.

#### 5. Significance and Use

5.1 This test method is considered satisfactory for acceptance testing of commercial shipments because current estimates of between-laboratory precision are acceptable and the method is used extensively in the trade for acceptance testing.

5.1.1 If there are differences or practical significance between reported test results for two laboratories (or more), comparative tests should be performed to determine if there is a statistical bias between them, using competent statistical assistance. As a minimum, the test samples to be used are as homogeneous as possible, are drawn from the material from which the disparate test results are obtained, and are assigned randomly in equal numbers to each laboratory for testing. Other materials with established test values may be used for this purpose. The test results from the two laboratories should be compared using a statistical test for unpaired data, at a probability level chosen prior to the testing series. If a bias is found, either its cause must be found and corrected, or future test results must be adjusted in consideration of the known bias.

5.2 Elapsed time between spinning and testing has a marked effect on the results of the draw tension test, especially during the first 24 h. Therefore, if tested within 24 h of spinning, specimens should be compared only if tested after the same elapsed time. No specimen should be tested within 4 h of spinning because the aging process is at its most rapid rate during this period, and the differences in rate due to fiber structure are most pronounced.

5.3 The extension force of manufactured filament yarns is related to the alignment of the molecules in the yarn filaments, which influences the yarn processing behavior. Knowledge of this property of partially oriented yarn is useful to determine processing conditions. <https://standards.iteh.ai/catalog/standards/sist/0984fd96-740d-479e-bfe3-abe933574077/astm-d5344-22>

#### 6. Apparatus

6.1 An Extension Force Measuring Instrument, ~~Instrument~~<sup>4</sup>, which will perform the test on a running threadline. ~~This~~The instrument should include the following: (1) an input section to withdraw the yarn from a package and position the yarn for delivery to the drawing section and establish constant tension, (2) a drawing section that should include a constant heat source to provide for the extension of the yarn, and (3) a means of recording the force required to draw the yarn.

#### 7. Sampling and Test Specimens

7.1 *Primary Sampling Unit*—Consider shipping containers of yarns to be the primary sampling unit.

7.2 *Laboratory Sampling Unit*—From the combined number of primary sampling units in a designated lot, take ten randomly selected packages as directed in Practice **D2258** as laboratory sampling units.

7.3 *Test Specimens*—For acceptance testing, take one test specimen from each laboratory sampling unit. For nylon and polyester, use a 50-m test length. For polypropylene, use a ~~100-m~~ 100 m test length.

<sup>4</sup> DYNAFIL, available from Lawson-Hemphill 1658 G A R Highway, Suite 6, Swansea, MA 02777, has been found suitable. Texttechno Herbert Stein GmbH & Co. KG, Dohrweg 65, 41066 Mönchengladbach, Germany. Commercial Draw Force Test Instruments are available.

<sup>5</sup> DTL, available from W. Fritz Mezger, Inc., 155 Hall Street, Spartanburg, SC 29302-1523, has been found suitable. Lenzing Instruments GmbH & Co KG, Bundesstrasse 1a, A-4860, Lenzing, Austria.

## 8. Conditioning

8.1 Prior to conditioning, prepare the test packages by removing at least 100 m (10 yds) of yarn from the outside of each test package to avoid testing nonrepresentative yarn. No preconditioning is required.

NOTE 1—Preconditioning is generally not advisable because it prolongs the time required for conditioning.

8.2 Bring the specimens in package form to moisture equilibrium for testing in the standard atmosphere for testing textiles  $21 \pm 1^\circ\text{C}$  ( $70 \pm 2^\circ\text{F}$ ) and  $65 \pm 2\%$  relative humidity in accordance with Practice D1776. A 24-h period is usually sufficient.

## 9. Procedure

9.1 Perform all tests in the standard atmosphere for testing textiles, which is  $21 \pm 1^\circ\text{C} \pm 1^\circ\text{C}$  or  $70 \pm 2^\circ\text{F} \pm 2^\circ\text{F}$  and  $65 \pm 2\%$  relative humidity.

9.2 Calibrate the test instrument as specified by the manufacturer. Test certified control packages and evaluate them using statistical procedures to verify calibration.

### 9.3 Test Conditions:

9.3.1 Use the test conditions as specified in Table 1 for to the instrument being used. The use of these conditions will allow for the direct comparison of test results from the two instruments.

NOTE 2—Due to the difference in heater length on the two commercially available test instruments, the draw roll speed is different to maintain the same dwell time of the yarn in the heater. It is important to maintain the same dwell time in the heater at a given heat to assure reproducible data for extension force test.

NOTE 3—For conditions other than those given in 9.3.1, see Appendix X1 for test condition optimization, which provides for direct comparison between users.

### 9.4 Procedure for Testing Specimens:

9.4.1 Remove surface yarn from the outside of each package immediately before the test is run to remove damaged or disturbed yarn.

9.4.2 Mount the test package on a suitable holder.

**TABLE 1 Test Conditions**

| Polymer Type  | DYNAFIL, 7.62-cm Heater  |                                    | Heat,<br>°C | Draw<br>Ratio      |
|---------------|--------------------------|------------------------------------|-------------|--------------------|
|               | Pretension<br>cN/tex     | Draw Roll Speed,<br>g/den<br>m/min |             |                    |
| Polyester     | 0.90                     | 0.10                               | 150         | 1.60               |
| Nylon         | 0.90                     | 0.10                               | 150         | 1.40               |
| Polypropylene | 0.90                     | 0.10                               | 140         | 1.60               |
| Polymer Type  | DTI, 104-cm Heater       |                                    |             | Heat-Draw<br>Ratio |
|               | Draw Roll Speed<br>m/min |                                    | °C          |                    |
| Polyester     | 68.2                     |                                    | 150         | 1.60               |
| Nylon         | 68.2                     |                                    | 150         | 1.40               |
| Polypropylene | 136.5                    |                                    | 140         | 1.60               |

**TABLE 1 Test Conditions**

| Polymer Type  | Pretension |       | Heat,<br>°C | Draw<br>Ratio | Heater Length (Note 2)               |                                     |                                    |
|---------------|------------|-------|-------------|---------------|--------------------------------------|-------------------------------------|------------------------------------|
|               | cN/tex     | g/den |             |               | Instrument 1                         | Instrument 2                        | Instrument 3                       |
|               |            |       |             |               | 76.2 cm<br>Draw Roll Speed,<br>m/min | 104 cm<br>Draw Roll Speed,<br>m/min | 98 cm<br>Draw Roll Speed,<br>m/min |
| Polyester     | 0.9        | 0.1   | 150         | 1.6           | 50                                   | 68.2                                | 64.3                               |
| Nylon         | 0.9        | 0.1   | 150         | 1.4           | 50                                   | 68.2                                | 64.3                               |
| Polypropylene | 0.9        | 0.1   | 140         | 1.6           | 100                                  | 136.5                               | 128.6                              |

9.4.3 Turn the instrument on.

9.4.4 Feed the yarn through the instrument as specified by the instrument operator's manual (see Fig. 1, Fig. 2 and Fig. 23).

9.4.5 Set the yarn test speed.

9.4.6 Check the yarn pretension, if applicable.

9.4.7 Run the test for a minimum of 1 min.

## 10. Calculation

10.1 Calculate the average extension force of each package in the laboratory sample from the chart recorder or input signal to the microprocessor.

10.2 Calculate the average extension force and coefficient of variation for the lot.

## 11. Report

11.1 State that the test was performed as directed in this test method.

11.2 Report the following information for the laboratory sampling unit and for the lot as applicable to a material specification or contract order.

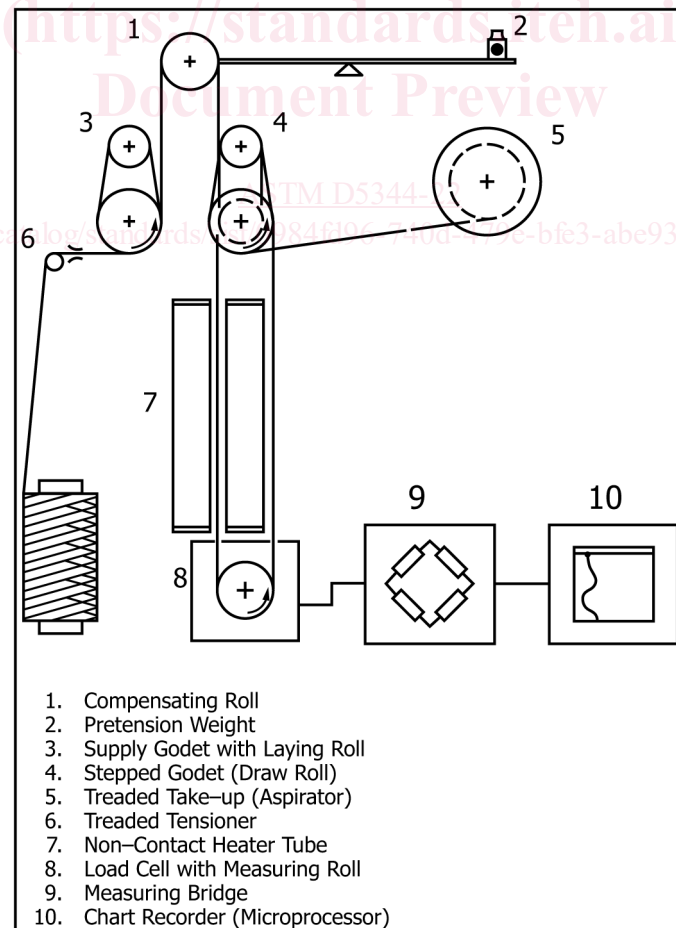


FIG. 1 Layout of Extension Force Measuring Unit—DYNAFIL Unit—Instrument 1

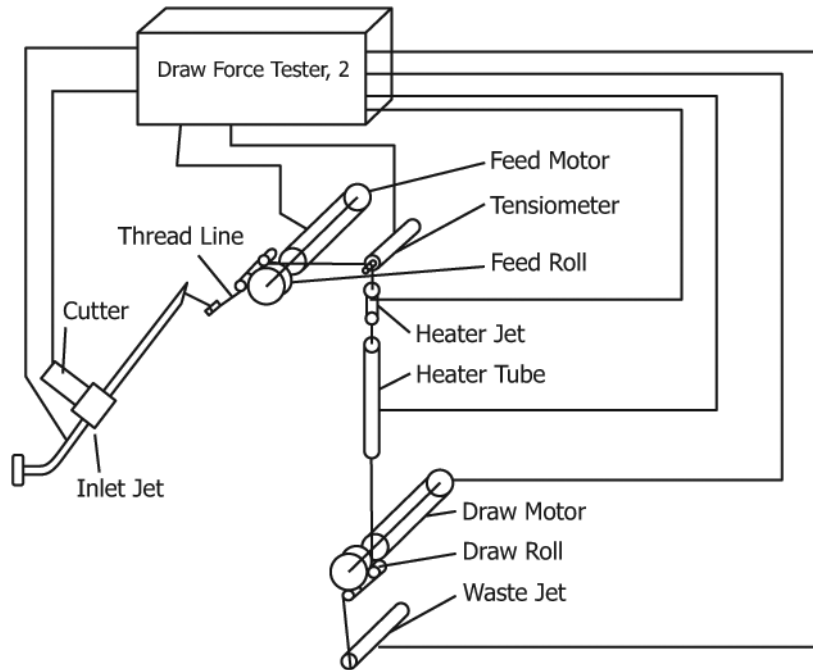


FIG. 2 Layout of Extension Force Measuring Unit—DTI Unit—Instrument 2

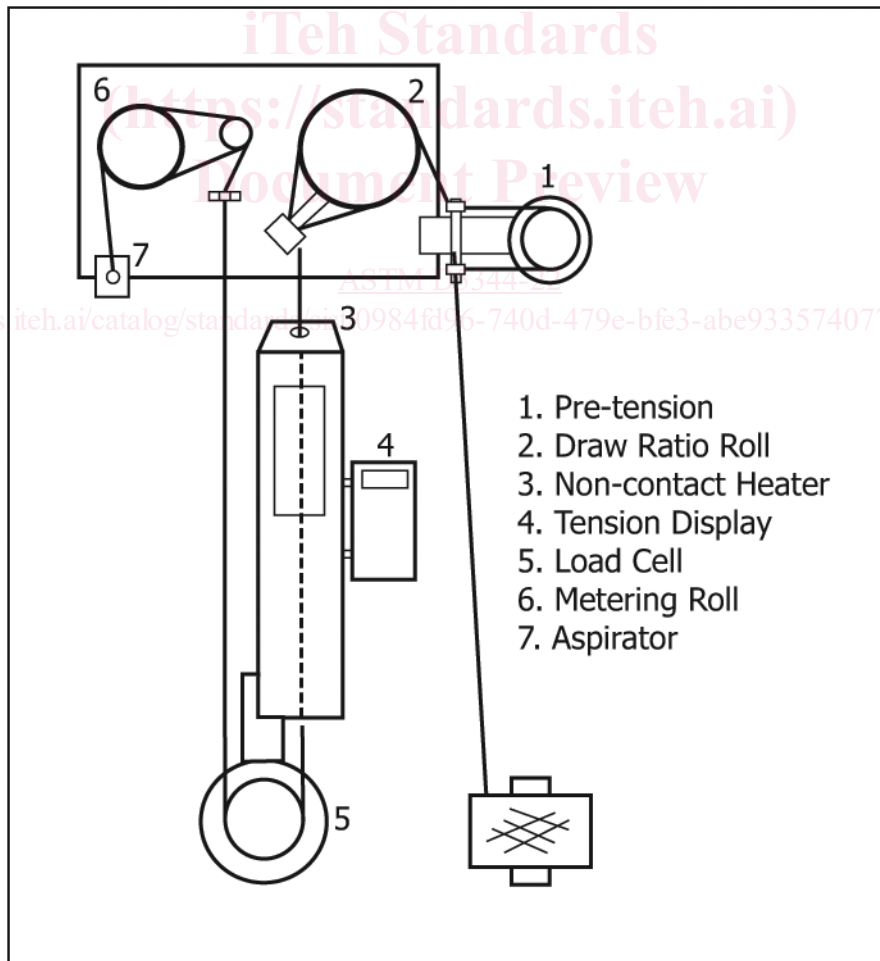


FIG. 3 Layout of Extension Force Measuring Unit—Instrument 3