



Designation: **B946 – 11 (Reapproved 2016) B946 – 23**

Standard Test Method Methods for Surface Finish Roughness of Powder Metallurgy (PM) Products¹

This standard is issued under the fixed designation B946; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. ~~Scope~~ Scope*

1.1 ~~This test method covers~~ These test methods cover measuring the surface finish roughness of powder metallurgy (PM) products at all stages of manufacturing from green compact to fully hardened finished component.

1.2 ~~This test method provides~~ These test methods provide the definition and schematic of some common surface finish roughness parameters (R_a , R_p , and R_{zISO})

1.3 This standard specifies two different standardized procedures for measuring the surface roughness of PM parts.

1.3.1 Method 1 uses a conical stylus and a Gaussian filter.

1.3.2 Method 2 uses a chisel (knife) edge stylus.

1.3.3 Each test method results in a different measure of surface roughness and the results are not directly comparable.

1.4 The values stated in ~~inch-pound~~ SI units are to be regarded as standard. The values given in parentheses are ~~mathematical conversions to~~ after SI units that are provided for information only and are not considered standard.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and to safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.6 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 ASTM Standards:²

[E456 Terminology Relating to Quality and Statistics](#)

[E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method](#)

¹ ~~This test method is~~ These test methods are under the jurisdiction of ASTM Committee B09 on Metal Powders and Metal Powder Products and is the direct responsibility of Subcommittee B09.05 on Structural Parts.

Current edition approved April 1, 2016 Feb. 1, 2023. Published April 2016 February 2023. Originally approved in 2006. Last previous edition approved in 2014 as B946 – 11. DOI: 10.1520/B0946-11R16.11 (2016). DOI: 10.1520/B0946-23.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For Annual Book of ASTM Standards volume information, refer to the standard's Document Summary page on the ASTM website.

*A Summary of Changes section appears at the end of this standard

2.2 *MPIF Standard:*³

[MPIF Standard 58 Method for Determination of Surface Finish of Powder Metallurgy Products](#)

2.3 *ASME Standard:*⁴

[ASME B46.1 Surface Texture \(Surface Roughness, Waviness, and Lay\)](#)

2.4 *ISO Standard:*⁵

[ISO 16610-21 Geometric Product Specifications \(GPS\) – Filtration–Part 21: Linear Profile Filters: Gaussian Filters](#)

3. Significance and Use

3.1 ~~The surface finish of a component may be critical for certain applications, affecting properties such as wear resistance, fatigue strength, and coefficient of friction.~~ roughness of PM parts is an important characteristic in relation to factors such as their load-bearing, wear, sealing, sliding, adhesion, electrical contact, and lubricant retention properties.

3.2 ~~Surface finish~~ roughness may also be critical for component assembly or system performance. Dimensional fit and mating surface interaction may require certain surface ~~finish~~ roughness requirements to meet performance specifications.

4. Interferences

4.1 ~~Because many conventional PM materials contain open porosity at the surface, special consideration should be taken when measuring surface finish.~~ roughness. As most roughness parameters are defined by measuring the microscopic peaks and valleys, the porosity in sintered powder metallurgy products will negatively influence this value.

4.2 ~~The use of a conical point stylus may result in inaccurate or inconsistent surface finish results because the sharper point of the stylus may drop into open porosity on the surface of the component.~~

4.3 ~~A chisel point stylus may be used for better accuracy and consistency.~~

4.2 ~~Because the direction of pressing may cause directionality in surface finish~~ roughness values, the direction of measurement should be specified and reported.

5. Apparatus

5.1 ~~Surface Finish Measuring Instrument—Method 1 (Conical Stylus):~~

5.1.1 ~~Surface Finish Measuring Instrument—~~Suitable for complying with ASME B46.1.

5.1.2 ~~A profiling, contact, skidless instrument for measuring displacements of a stylus relative to an external datum.~~

5.1.3 ~~Stylus with an appropriate radius (for example, 2 μm, 5 μm, or 10 μm (0.00008 in., 0.0002 in., or 0.0004 in.)).~~

NOTE 1—Because the stylus tip is subject to wear and mechanical damage, even when made of diamond, regular checks of the stylus are recommended. Techniques for checking the stylus condition are discussed in ASME B46.1.

5.2 ~~Stylus—Method 2 (Chisel (Knife) Edge Stylus): Chisel point, 0.050 in. (1.27 mm) length and 0.0004 in. ± 30 % (0.010 mm ± 30 %) tip radius as shown in Fig. 1. To limit the possibility of the stylus dropping into open surface porosity, a chisel point stylus is recommended. If a cone stylus is used, filtering software shall also be used to remove the influence of open surface porosity.~~

5.2.1 ~~Surface Finish Measuring Instrument—~~Suitable for complying with ASME B46.1.

5.2.2 ~~Stylus—Chisel (knife) edge, 1.27 mm (0.050 in.) length and 0.010 mm ± 30 % (0.0004 in. ± 30 %) tip radius as shown in Fig. 1. The chisel tip shall be oriented so that its long edge is perpendicular to the direction of travel of the probe.~~

³ Available from Metal Powder Industries Federation (MPIF), 105 College Rd. East, Princeton, NJ 08540, <http://www.mpif.org>.

⁴ Available from American Society of Mechanical Engineers (ASME), ASME International Headquarters, Two Park Ave., New York, NY 10016-5990, <http://www.asme.org>.

⁵ Available from International Organization for Standardization (ISO), ISO Central Secretariat, Chemin de Blandonnet 8, CP 401, 1214 Vernier, Geneva, Switzerland, <https://www.iso.org>.

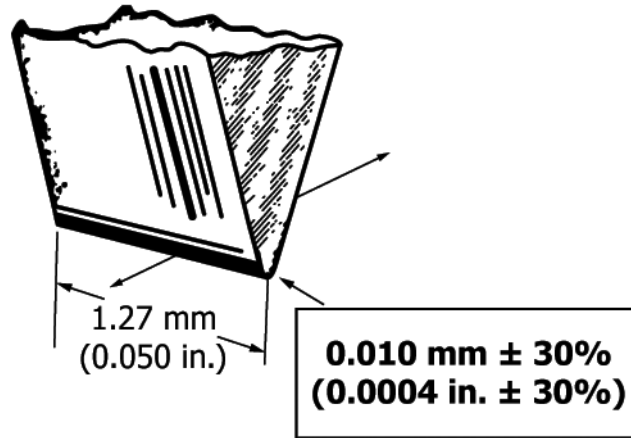


FIG. 1 Chisel (Knife) Edge Stylus for Surface Finish Roughness Measurement

6. Sampling, Test Specimens, and Test Units

- 6.1 The test surface shall be clean and free of any oil, dirt, debris, or foreign material.
- 6.2 Sufficient surface area shall be available to permit multiple traverses by the measuring instrument.
- 6.3 The test surface shall be flat over a sufficient length (in accordance with instrument instructions) to allow proper movement of the stylus.

7. Procedure

- 7.1 The PM parts manufacturer and purchaser shall agree on the desired location and direction for surface finish measurement.
- 7.2 Place the surface finish instrument in a position suitable for measuring the test sample.
- 7.3 Zero and verify the instrument over the surface finish range expected for the test sample.

7.1 Place the test sample under the stylus and then lower the stylus to the measuring position in accordance with the instrument instructions. Method 1 (Conical Stylus):

7.1.1 Measure the surface roughness in accordance with ASME B46.1 by using the following parameters:

7.1.2 The surface roughness parameter to be measured should be agreed upon by the producer and purchaser; for example, R_a, R_p, R_z .

NOTE 2— R_a is the arithmetic average value of the filtered roughness profile determined from deviations about the centerline within the evaluation length L_m as shown in Fig. 2. R_p is the maximum peak-to-valley height over the tested length (absolute value between the highest peak and lowest valley) as shown in Fig. 3. R_z is the ten-point height, or the absolute value of the five highest peaks and five lowest valleys over the evaluation length as shown in Fig. 4. R_z is also known as the ISO 10-point height parameter.

7.1.3 Use a stylus with a tip radius of either 2 μm , 5 μm , or 10 μm [0.00008 in., 0.0002 in., or 0.0004 in.] as agreed between the producer and purchaser.

7.1.4 Use a Gaussian filtered profile (for example, ISO 16610-21) with a cut-off agreed between the producer and the purchaser.

7.1.5 Use a total evaluation length that is five times the cut-off value. For example, if the cut-off is 0.8 mm (0.03 in.), the total evaluation length shall be 4 mm (0.16 in.).

7.1.6 The PM parts producer and the purchaser shall agree on the desired location and direction for the surface roughness measurement.

$$R_a = \frac{1}{l_m} \int_{x=0}^{x=l_m} |y| dx$$

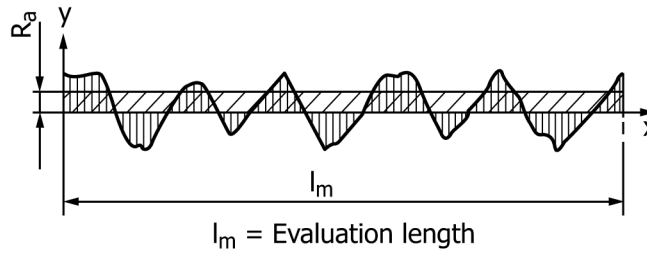


FIG. 2 R_a Arithmetic Mean Roughness Value

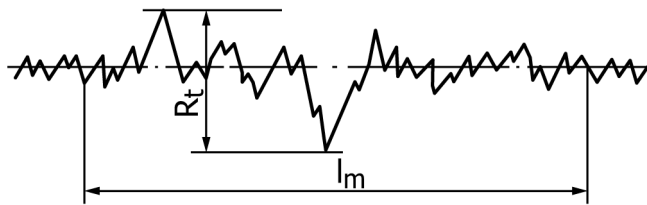


FIG. 3 R_t Maximum Peak-to-Valley Height

NOTE 3—If the roughness is higher than $4.0 R_a$, increase the cut-off so that the evaluation length is longer. This is because the surface is so irregular that a longer evaluation length is necessary to obtain a real statistical approach.

7.1.7 Place the surface finish instrument in a position suitable for measuring the test sample.

7.1.8 Zero and verify the instrument over the surface roughness range expected for the test sample.

7.1.9 Place the test sample under the stylus and then lower the stylus to the measuring position in accordance with the instrument instructions.

<https://standards.iteh.ai/catalog/standards/sist/147d9c6d-8deb-41fa-bc78-e0a1b291f706/astm-b946-23>

7.1.10 Measure the surface roughness of the test surface. A minimum of three traverses at different locations is recommended.

7.2 Measure the surface finish of the test surface. A minimum of three traverses at different locations is recommended. *Method 2 (Chisel (Knife) Edge Stylus):*

7.2.1 The surface roughness parameter to be measured should be agreed upon by the producer and purchaser; for example, R_a, R_p, R_z . In addition, the traverse length to be used should be agreed upon.

NOTE 4— R_a is the arithmetic average value of the filtered roughness profile determined from deviations about the centerline within the evaluation length l_m , as shown in Fig. 2. R_p is the maximum peak-to-valley height over the tested length (absolute value between the highest peak and lowest valley) as shown in Fig. 3. R_z is the ten-point height, or the absolute value of the five highest peaks and five lowest valleys over the evaluation length as shown in Fig. 4. R_z is also known as the ISO 10-point height parameter.

7.2.2 The PM parts producer and the purchaser shall agree on the desired location and direction for the surface roughness measurement.

7.2.3 Place the surface finish instrument in a position suitable for measuring the test sample.

7.2.4 Calibrate the instrument over the surface roughness range expected for the test sample prior to testing.

7.2.5 Place the test sample under the stylus and then lower the stylus to the measuring position per the instrument instructions.

7.2.6 Measure the surface roughness of the test surface. A minimum of three traverses at different locations is recommended.