



# SLOVENSKI STANDARD

## SIST EN 13364:2002

01-maj-2002

---

### Preskušanje naravnega kamna – Ugotavljanje lomne obremenitve ob sidrni izvrtini

Natural stone test methods - Determination of the breaking load at dowel hole

Prüfung von Naturstein - Bestimmung der Ausbruchlast am Ankerdornloch

Méthodes d'essai pour pierre naturelle - Détermination de l'effort de rupture au niveau du goujon de l'agrafe

iTeh STANDARD PREVIEW  
(standards.itih.ai)

[SIST EN 13364:2002](https://standards.itih.ai/catalog/standards/sist/685c52d-b55f-4b64-9c91-100fcd05f06/sist-en-13364-2002)

Ta slovenski standard je istoveten z: EN 13364:2001

---

#### ICS:

73.020	Rudarstvo in kamnolomsko izkopavanje	Mining and quarrying
91.100.15	Mineralni materiali in izdelki	Mineral materials and products

**SIST EN 13364:2002**

**en**

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST EN 13364:2002

<https://standards.iteh.ai/catalog/standards/sist/68f5c52d-b55f-4b64-9c91-1001e5d03f06/sist-en-13364-2002>

EUROPEAN STANDARD  
NORME EUROPÉENNE  
EUROPÄISCHE NORM

**EN 13364**

November 2001

ICS 73.020; 91.100.15

English version

**Natural stone test methods - Determination of the breaking load  
at dowel hole**

Méthodes d'essai pour pierre naturelle - Détermination de  
l'effort de rupture au niveau du goujon de l'agrafe

Prüfung von Naturstein - Bestimmung der Ausbruchlast am  
Ankerdornloch

This European Standard was approved by CEN on 29 September 2001.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)  
<https://standards.iteh.ai/catalog/standards/sist/68f5c52d-b55f-4b64-9c91-1001e5d03f06/sist-en-13364-2002>



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**Management Centre: rue de Stassart, 36 B-1050 Brussels**

## Contents

	page
Foreword .....	3
1 Scope .....	5
2 Normative references .....	5
3 Principle .....	5
4 Symbols .....	5
5 Apparatus .....	5
6 Preparation of the specimens .....	6
6.1 Sampling and position of bedding .....	6
6.2 Test specimens .....	6
6.2.1 General .....	6
6.2.2 Number of specimens .....	6
6.2.3 Surface finish of the specimens .....	9
6.2.4 Dimensions of the specimens .....	9
6.2.5 Location of the holes .....	10
6.2.6 Dimensions and tolerances of the holes .....	10
6.2.7 Drilling the holes .....	10
6.2.8 Planes of anisotropy .....	10
6.2.9 Conditioning .....	10
6.2.10 Measuring $d$ and $d_1$ .....	10
7 Dowels .....	11
7.1 Dimensions and tolerances .....	11
7.2 Material .....	11
7.3 Placing the dowels .....	11
8 Test procedure .....	11
9 Expression of the results .....	12
10 Test report .....	12
Annex A (normative) Statistical evaluation of the test results .....	14
A.1 Scope .....	14
A.2 Symbols and definitions .....	14
A.3 Statistical evaluation of test results .....	15
Bibliography .....	18

## Foreword

This European Standard has been prepared by Technical Committee CEN/TC 246, "Natural Stone", the secretariat of which is held by UNI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by May 2002, and conflicting national standards shall be withdrawn at the latest by December 2002.

This European Standard is one of the series of standards for tests on natural stone.

Test methods for natural stone consist of the following parts:

EN 1925, *Natural stone test methods - Determination of water absorption coefficient by capillarity.*

EN 1926, *Natural stone test methods - Determination of compressive strength.*

EN 1936, *Natural stone test methods - Determination of real density and apparent density and of total open porosity.*

EN 12370, *Natural stone test methods - Determination of resistance to salt crystallisation.*

EN 12372, *Natural stone test methods - Determination of flexural strength under concentrated load.*

EN 12407, *Natural stone test methods - Petrographic description.*

prEN 12371, *Natural stone test methods - Determination of frost resistance.*

prEN 13161, *Natural stone test methods - Determination of flexural strength under constant moment.*

prEN 13373, *Natural stone test methods - Determination of geometric characteristics on units.*

prEN 13755, *Natural stone test methods - Determination of water absorption at atmospheric pressure.*

prEN 13919, *Natural stone test methods - Determination of resistance to ageing by SO<sub>2</sub> action in the presence of humidity.*

prEN 14066, *Natural stone test methods - Determination of thermal shock resistance.*

prEN ....(WI 00246011), *Natural stone test methods - Determination of thermal dilatation coefficient.*

prEN ....(WI 00246012), *Natural stone test methods - Determination of sound - speed propagation.*

prEN 14157, *Natural stone test methods - Determination of abrasion resistance.*

prEN 14205, *Natural stone test methods - Determination of Knoop hardness.*

prEN 14231, *Natural stone test methods - Determination of slip resistance by means of the pendulum tester.*

prEN ....(WI 00246018), *Natural stone test methods - Determination of static elastic modulus.*

prEN 14158, *Natural stone test methods - Determination of rupture energy.*

prEN 14147, *Natural stone test methods - Determination of resistance to ageing by salt mist.*

It is intended that other ENs should call up this EN 13364 as the basis of evaluation of conformity. (Nevertheless it is not intended that all natural stones products should be subjected regularly to all the listed tests. Specifications in other standards should call up only relevant test methods).

This European Standard has an annex A (normative).

**EN 13364:2001 (E)**

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

**iTeh STANDARD PREVIEW  
(standards.iteh.ai)**

SIST EN 13364:2002

<https://standards.iteh.ai/catalog/standards/sist/68f5c52d-b55f-4b64-9c91-1001e5d03f06/sist-en-13364-2002>

## 1 Scope

This European Standard specifies a test method to determine the breaking load at the dowel hole of natural stones used for cladding or lining in building.

## 2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text, and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies (including amendments).

EN 10088-1, *Stainless steels – Part 1: List of stainless steels*.

EN 12390-4, *Testing hardened concrete – Part 4: Compressive strength - Specification for testing machines*.

EN 197-1, *Cement - Part 1: Composition, specifications and conformity criteria for common cements*.

## 3 Principle

This test consists of applying a force in a direction perpendicular to the face of a specimen through a dowel previously placed in an hole drilled in one of its sides and measuring the breaking load of the specimen.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

## 4 Symbols

- $d$  is the thickness of the test specimen, in millimetres
- $d_1$  is the distance from the hole wall to the face where fracture occurs, in millimetres
- $b_A$  is the maximum distance of the centre of the hole to the fracture edge on the face, in millimetres
- $F$  is the individual breaking load, in newtons
- $\bar{d}_1$  is the mean value of  $d_1$ , in millimetres
- $\bar{F}$  is the mean value of  $F$ , in newtons
- $\bar{b}_A$  is the mean value of  $b_A$ , in millimetres

## 5 Apparatus

**5.1** A balance capable of weighing the specimens with an accuracy of 0,01 % of their mass.

**5.2** A ventilated oven capable of maintaining a temperature of  $(70 \pm 5) ^\circ\text{C}$ .

**5.3** A linear measuring device with an accuracy of 0,05 mm.

**5.4** A rotary drilling machine equipped with a diamond or tungsten carbide tipped bit.

**5.5** A testing machine of appropriate force in accordance with EN 12390-4 and calibrated according to this standard.

**5.6** A clamping device consisting of two metal plates having the shape and sizes shown in Figure 1.

**5.7** A device for applying loads perpendicular to the axis of the dowel (see Figure 2).

**EN 13364:2001 (E)**

5.8 A room or chamber in which the temperature of the air can be maintained at  $(20 \pm 5) ^\circ\text{C}$ .

**6 Preparation of the specimens****6.1 Sampling and position of bedding**

The sampling is not the responsibility of the test laboratory except where specially requested.

The position of any bedding or anisotropy shall be indicated on each specimen by means of at least two parallel lines.

**6.2 Test specimens****6.2.1 General**

The test can be carried out as an identification test or as a technological test.

Identification tests are tests carried out when the use of the stone with respect to the position of the planes of anisotropy and the thickness and surface finish of the elements in the cladding are not known.

Technological tests are those carried out when the use of the stone with respect to the position of the planes of anisotropy and the thickness and surface finish of the elements in the cladding are known. In this case the major faces of the specimens shall have the same orientation of the face that will be loaded during use.

**6.2.2 Number of specimens**

The minimum number of test specimens depends on the presence of planes of anisotropy.


If the stone does not show planes of anisotropy 10 tests of Type 0 (see Figure 3) shall be made on three specimens.

If the stone shows planes of anisotropy:

- 10 tests of Type I (see Figure 4) shall be made on three specimens cut parallel to the planes of anisotropy;
- 10 tests of Type IIa (see Figure 5) and 10 tests of Type IIb (see Figure 6) shall be made on five specimens cut perpendicular to the planes of anisotropy.



## a) General view

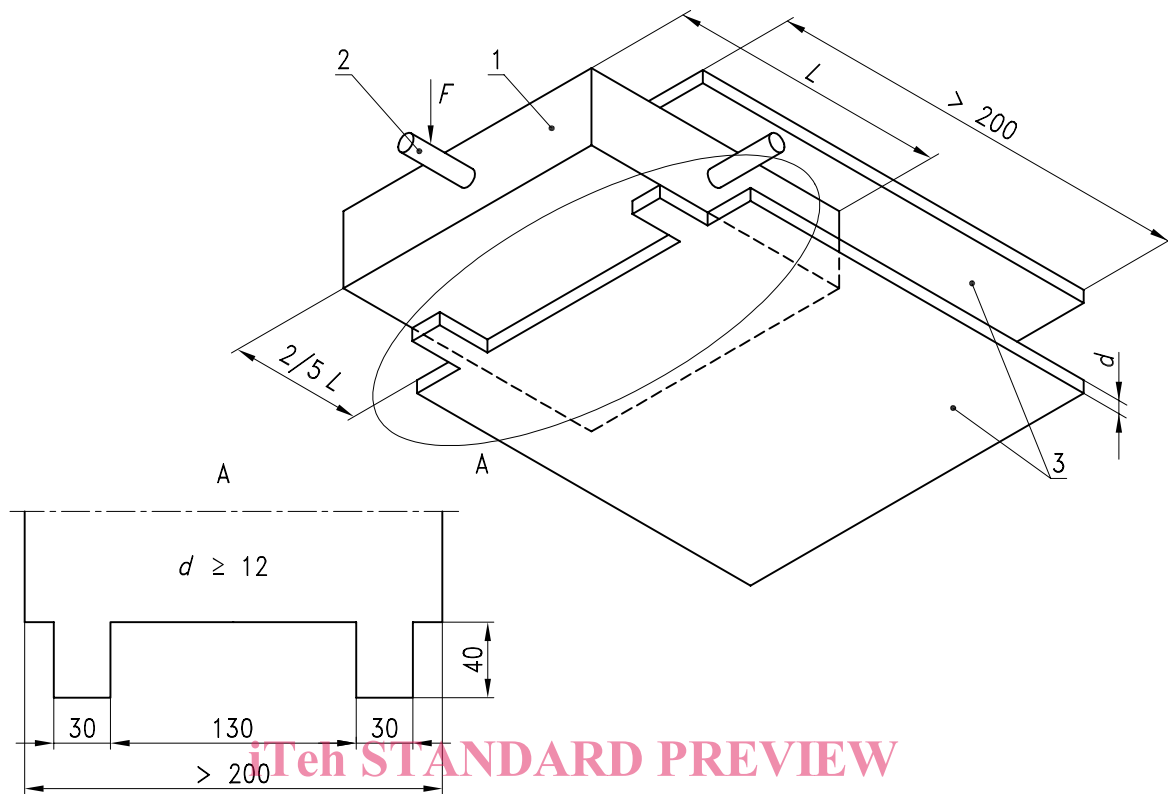

b) Detail of a plate suitable for tests on specimens having dimensions of 200 mm × 200 mm


[SIST EN 13364:2002](https://standards.iteh.ai/catalog/standards/sist/68f5c52d-b55f-4b64-9c91-1001e5d03f06/sist-en-13364-2002)

<https://standards.iteh.ai/catalog/standards/sist/68f5c52d-b55f-4b64-9c91-1001e5d03f06/sist-en-13364-2002>

**Key**

- 1 Specimen
- 2 Dowel
- 3 Metal plate
- $F$  Force applied on the specimen
- $L$  Length of the specimen
- $d$  Thickness of the metal plate

**Figure 1 – Clamping device to hold the specimen in place**

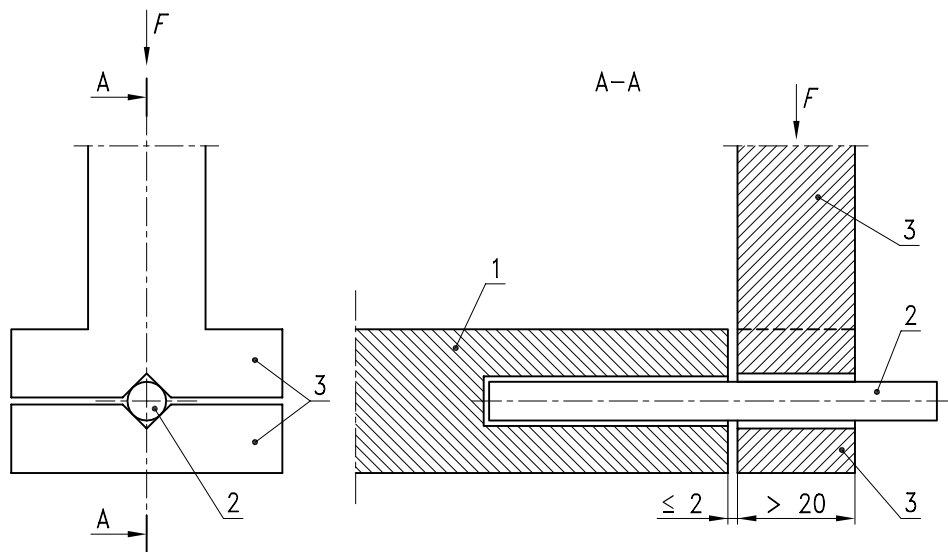**Key**

- 1 Specimen
- 2 Dowel
- 3 Device for applying load


$F$  Force applied on the specimen

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)


[SIST EN 13364:2002](#)

[standards.iteh.ai/catalog/standards/sist/68f5c52d-b55f-4b64-9c91-1001e5d03f06/sist-en-13364-2002](#)

**Figure 2 – Device for applying loads perpendicular to the axis of the dowel**

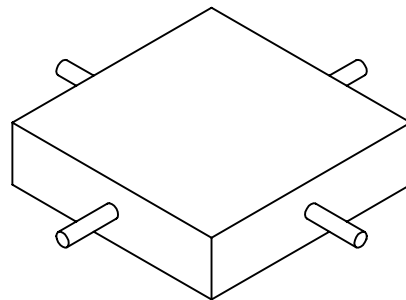

**Figure 3 - Test arrangement for a specimen without planes of anisotropy (type 0)**

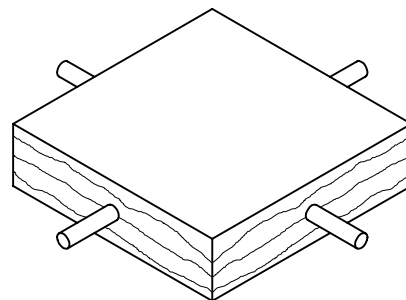

**Figure 4 – Test arrangement for a specimen with the load applied perpendicular to the planes of anisotropy (type I)**

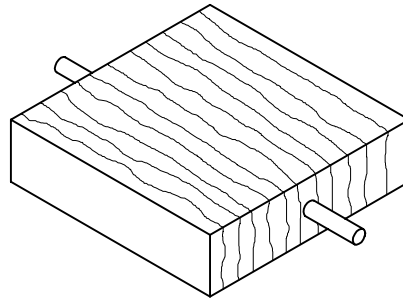


Figure 5 - Test arrangement for a specimen with the load applied parallel to the planes of anisotropy (type IIa)

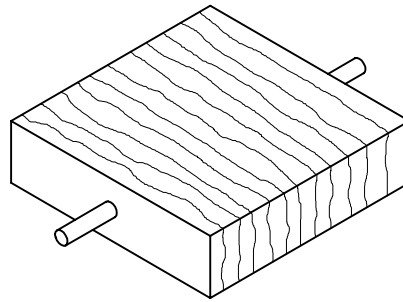


Figure 6 - Test arrangement for a specimen with the load applied parallel to the edges of the planes of anisotropy (type IIb)

### 6.2.3 Surface finish of the specimens

#### a) identification test

The surface finish on the faces and sides of the specimens shall be sawn, honed or polished.

[SIST EN 13364:2002](https://standards.iteh.ai/catalog/standards/sist/68f5c52d-b55f-4b64-9c91-1001e5d03f06/sist-en-13364-2002)

#### b) technological test

<https://standards.iteh.ai/catalog/standards/sist/68f5c52d-b55f-4b64-9c91-1001e5d03f06/sist-en-13364-2002>

The surface finish on the faces and sides of the specimens shall be carried out according to the application (for example sawn, honed, polished, sanded, rubbed, flamed, bushhammered, riven).

### 6.2.4 Dimensions of the specimens

#### a) identification test

The specimens are square slabs with faces  $(200 \pm 1)$  mm and a thickness of  $(30 \pm 3)$  mm. The permissible deviation on the squareness is a maximum of 2 mm.

#### b) technological test

The specimens are square slabs with the following dimensions:

Thickness	Dimensions
20 mm to 65 mm	200 mm × 200 mm
> 65 mm to 80 mm	300 mm × 300 mm