
Preskušanje naravnega kamna - Ugotavljanje odpornosti proti kristalizaciji soli

Natural stone test methods - Determination of resistance to salt crystallisation

Prüfverfahren für Naturstein - Bestimmung des Widerstandes gegen Kristallisation von Salzen

Méthodes d'essai pour pierres naturelles - Détermination de la résistance par un essai de cristallisation des sels

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Ta slovenski standard je istoveten z: EN 12370:1999

SIST EN 12370:2000
<https://standards.iteh.ai/catalog/standards/sist/8218a418-a8bc-4b08-b57a-7160ea7c8b61/sist-en-12370-2000>

ICS:

73.020	Rudarstvo in kamnolomsko izkopavanje	Mining and quarrying
91.100.15	Mineralni materiali in izdelki	Mineral materials and products

SIST EN 12370:2000**en**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 12370:2000

<https://standards.iteh.ai/catalog/standards/sist/82f8a4f8-a8be-4b08-b57a-7160ea7c8b61/sist-en-12370-2000>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN 12370

March 1999

ICS 73.020; 91.100.15

English version

Natural stone test methods - Determination of resistance to salt
crystallisation

Méthodes d'essai pour pierres naturelles - Détermination
de la résistance par un essai de cristallisation des sels

Prüfverfahren für Naturstein - Bestimmung des
Widerstandes gegen Kristallisation von Salzen

This European Standard was approved by CEN on 12 February 1999.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

SIST EN 12370:2000

<https://standards.iteh.ai/catalog/standards/sist/82f8a4f8-a8be-4b08-b57a-7160ea7c8b61/sist-en-12370-2000>



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG


Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Contents	Page
Foreword	3
Introduction	4
1 Scope	4
2 Normative references	4
3 Principle	4
4 Symbols	4
5 Apparatus	4
6 Preparation of specimens	5
7 Procedure	5
8 Expression of results	6
9 Test report	6

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 12370:2000

<https://standards.iteh.ai/catalog/standards/sist/82f8a4f8-a8be-4b08-b57a-7160ea7c8b61/sist-en-12370-2000>

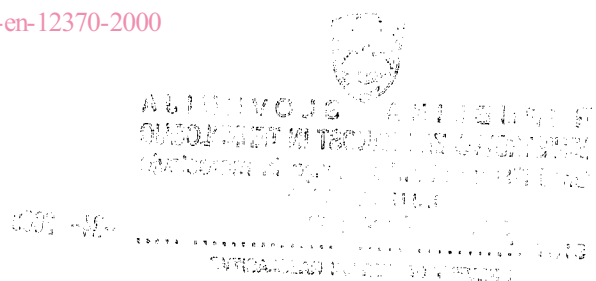

Foreword

This European Standard has been prepared by Technical Committee CEN/TC 246 "Natural stones", the secretariat of which is held by UNI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by September 1999, and conflicting national standards shall be withdrawn at the latest by September 1999.

This draft standard is one of the series of draft standards for tests on natural stone.
Test methods for natural stone consist of the following parts:

- EN 1925 Natural stone test methods - Determination of water absorption coefficient by capillarity
- EN 1926 Natural stone test methods - Determination of compressive strength
- EN 1936 Natural stone test methods - Determination of real density and apparent density and of total and open porosity
- prEN 12371 Natural stone test methods - Determination of frost resistance
- EN 12372 Natural stone test methods - Determination of flexural strength under concentrated load
- prEN 12407 Natural stone test methods - Petrographic description
- prEN 13161 Natural stone test methods - Determination of flexural strength under constant moment
- prEN 13364 Natural stone test methods - Determination of the breaking load at a dowel hole
- prEN(WI 00246011) Natural stone test methods - Determination of thermal dilatation coefficient
- prEN(WI 00246012) Natural stone test methods - Determination of sound - speed propagation
- prEN(WI 00246014) Natural stone test methods - Determination of abrasion resistance
- prEN(WI 00246015) Natural stone test methods - Determination of Knoop hardness
- prEN(WI 00246016) Natural stone test methods - Determination of thermal shock resistance
- prEN(WI 00246017) Natural stone test methods - Determination of slip coefficient
- prEN(WI 00246018) Natural stone test methods - Determination of static elastic modulus
- prEN(WI 00246019) Natural stone test methods - Determination of rupture energy
- prEN(WI 00246030) Natural stone test methods - Determination of surface finishes (rugosity)
- prEN 13373 Natural stone test methods - Determination of geometric characteristics on units
- prEN(WI 00246032) Natural stone test methods - Determination of resistance to ageing by salt mist
- prEN(WI 00246033) Natural stone test methods - Determination of resistance to ageing by humidity, temperature, SO₂ action
- prEN(WI 00246035) Natural stone test methods - Determination of dynamic elastic modulus (by fundamental resonance frequency)
- prEN(WI 00246036) Natural stone test methods - Determination of water absorption at atmospheric pressure

It is intended that other ENs should call up this EN 12370 as the basis of evaluation of conformity. (Nevertheless it is not intended that all natural stones products should be subjected regularly to all the listed tests. Specifications in other standards should call up only relevant test methods).

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Introduction

This test is designed to assess the salt crystallisation resistance of natural stones where it is considered relevant. The test can not be used in isolation and results will be considered with other physical tests to indicate durability, these include prEN 12371 "Determination of frost resistance".

1 Scope

This European Standard specifies a test method to assess the relative resistance of natural stones with an open porosity of greater than 5%, measured in accordance with EN 1936, to damage caused by the crystallisation of salts. The test is not necessary for low porosity stones.

2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

EN 1936 Natural stone test methods - Determination of real density and apparent density and of total and open porosity

prEN 12371 Natural stone test methods - Determination of frost resistance

prEN 12440 Denomination of natural stone

3 Principle

After drying to constant mass, the specimen is immersed in a solution of sodium sulphate, dried and allowed to cool to room temperature. This cycle is carried out 15 times and the percentage mass change measured.

4 Symbols

M_d is the mass of the dried specimen, in grams

M_{d1} is the mass of the dried specimen with label before first cycle, in grams

M_f is the mass of the dried specimen with label, after 15 cycles, in grams

ΔM is the relative difference of masses before and after testing (mass loss or mass gain), in percent.

5 Apparatus

5.1 A ventilated oven capable of maintaining a temperature of $(105 \pm 5)^\circ\text{C}$

5.2 A weighing instrument capable of weighing the specimens to $\pm 0,001\text{g}$

5.3 A room or water bath capable of maintaining the temperature of the specimens and solution to $(20 \pm 0,5)^{\circ}\text{C}$

5.4 A 14% solution of sodium sulphate decahydrate (i.e. 14g of $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$ for every 86g de-ionised water). The density of this solution at 20°C is 1055 kg/m^3 .

6 Preparation of specimens

6.1 Sampling

The sampling is not the responsibility of the test laboratory except where specially requested. At least six test specimens, which are considered representative of the body of stone being tested, shall be selected.

6.2 Dimensions of test specimens

Cubes of $(40 \pm 1)\text{mm}$ sides shall be prepared. Specimens shall be wet diamond sawn and any surface irregularities removed by grinding.

6.3 Washing

All loose material shall be washed from the surface of the specimen using potable water.

6.4 Drying

The specimens are to be dried in an oven at a temperature $(105 \pm 5)^{\circ}\text{C}$ until a constant mass is reached. This is assumed to have been attained when the difference between two weighings at an interval of $(24 \pm 2) \text{ h}$ is not greater than 0,1% of the first weighing. They are then allowed to cool to room temperature and weighed to $\pm 0,01 \text{ g}$ (M_d). Each specimen is then labelled with a durable tag that is wired on to the cube. The specimen is then re-weighed to $\pm 0,01 \text{ g}$ (M_{d1}).

7 Procedure

The procedure entails the use of a 14% solution of sodium sulphate decahydrate. The density of the solution shall be checked prior to use. The solution shall only be used for one test cycle.

Each of the dried specimens is placed in a 250 ml container and covered with the sodium sulphate solution to a depth of $(8 \pm 2) \text{ mm}$ above the top of the specimen and the container covered to reduce evaporation. Alternatively, the specimens may be placed in a single container provided that there is a minimum of 10 mm between specimens and at least 20 mm between the specimens and the sides of the container. The specimens are then left to soak for 2 h at $(20 \pm 0,5)^{\circ}\text{C}$.

NOTE: Changing the soaking temperature can markedly affect the results.

After immersion the specimens are removed from the solution and dried in an oven. The oven shall be arranged to provide a high relative humidity in the early stages of drying and to raise the temperature of the specimens to $(105 \pm 5)^{\circ}\text{C}$ in not less than 10 h and not more than 15 h. The initial high relative humidity may be obtained by placing a tray of water in the cold oven, and switching on the heater for $(30 \pm 5) \text{ min}$ before putting in the specimens; $(300 \pm 25)\text{ml}$ has been found to be adequate in an oven capable of holding 48 specimens, for example a 125 l capacity.

The specimens are left in the oven for at least 16 h and then they are cooled at room temperature for $(2,0 \pm 0,5)$ h before resoaking in fresh sodium sulphate solution. The cycle of operation is carried out 15 times in all, except when the specimens break up before this. After the 15th cycle the specimens are removed from the oven and stored for (24 ± 1) h in water at $(23 \pm 5)^{\circ}\text{C}$, finally, they are washed thoroughly with flowing water. The specimens are weighed after drying to constant mass (as in 6.4) if they are sufficiently coherent. If the test is to be interrupted at any time, the specimens are to be left in the oven at $(105 \pm 5)^{\circ}\text{C}$.

8 Expression of results

The results are expressed as relative mass difference ΔM (mass loss or gain) as a percentage of the initial dry mass M_d or as the number of cycles required to induce failure if the specimen is too shattered to weigh after the final drying.

$$\Delta M = \frac{M_f - M_{d1}}{M_d} \cdot 100$$

If failure has occurred or the specimen has fractured during testing, then this shall be recorded together with the number of completed cycles of testing.

A photographic record of the initial and final condition shall be made.

iTeh STANDARD PREVIEW (standards.iteh.ai)

9 Test report

The test report shall contain the following information:

- a) unique identification number for the report;
- b) the number, title and date of issue of this European standard;
- c) the name and address of the test laboratory and the address of where the test was carried out if different from the test laboratory;
- d) the name and address of the client;
- e) it is the responsibility of the client to supply the following information:
 - the petrographic name of the stone
 - the commercial name of the stone in accordance with prEN 12440
 - the country and region of extraction
 - the name of the supplier
 - the direction of any existing plane of anisotropy (if relevant to the test) to be clearly indicated on the sample or on each specimen by means of two parallel lines
 - the name of the person or organization which carried out the sampling;
 - the surface finish of the specimens (if relevant to the test);
- f) the date of delivery of the sample or of the specimens;
- g) the date when the specimens were prepared (if relevant) and the date of testing;
- h) the number of specimens in the sample;