



Designation: ~~D8044~~ – 16 D8044 – 23

Standard Test Method for Evaluation of Asphalt Mixture Cracking Resistance using ~~Using~~ the Semi-Circular Bend Test (SCB) at Intermediate Temperatures¹

This standard is issued under the fixed designation D8044; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the procedures for preparation, testing, and measurement of asphalt mixture cracking resistance at ~~Long Term Pavement Performance (LTTP) database~~ intermediate temperatures using semi-circular bend (SCB) geometry ~~laboratory prepared~~ of laboratory-prepared or pavement core asphalt ~~mixture~~ samples tested monotonically. The SCB sample is a half-disk with a notch cut ~~parallel to the loading and vertical axis, aligned vertically in parallel with the testing loading.~~ The test method describes the determination of the critical strain energy release ~~rate, rate parameter, J_c ,~~ and other parameters determined from the load-displacement curve. These parameters can be used to rank the resistance of asphalt mixtures to cracking.

1.2 The text of this standard references notes and footnotes which provide explanatory material. These notes and footnotes (excluding those in tables and figures) shall not be considered as requirements of the standard.

1.3 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.4 ~~This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use. Since a complete Precision and Bias statement for this standard has not been developed, the test method is to be used for research and informational purposes only. Therefore, this standard should not be used for acceptance or rejection of a material for purchasing purposes.~~

1.5 This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.

1.6 This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.

2. Referenced Documents

2.1 ASTM Standards:²

¹ This test method is under the jurisdiction of ASTM Committee D04 on Road and Paving Materials and is the direct responsibility of Subcommittee D04.26 on Fundamental/Mechanistic Tests.

Current edition approved July 1, 2016; May 15, 2023. Published August 2016; May 2023. Originally approved in 2016. Last previous edition approved in 2016 as D8044 – 16. DOI: 10.1520/D8044-16.10.1520/D8044-23.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

- [D979/D979M Practice for Sampling Asphalt Mixtures](#)
[D2041/D2041M Test Method for Theoretical Maximum Specific Gravity and Density of Asphalt Mixtures](#)
[D2726/D2726M Test Method for Bulk Specific Gravity and Density of Non-Absorptive Compacted Asphalt Mixtures](#)
[D3203/D3203M Test Method for Percent Air Voids in Compacted Asphalt Mixtures](#)
[D3666 Specification for Minimum Requirements for Agencies Testing and Inspecting Road and Paving Materials](#)
[D5361/D5361M Practice for Sampling Compacted Asphalt Mixtures for Laboratory Testing](#)
[D6373 Specification for Performance-Graded Asphalt Binder](#)
[D6857/D6857M Test Method for Maximum Specific Gravity and Density of Asphalt Mixtures Using Automatic Vacuum Sealing Method](#)
[D6925 Test Method for Preparation and Determination of the Relative Density of Asphalt Mix Specimens by Means of the Superpave Gyration Compactor](#)
[E4 Practices for Force Calibration and Verification of Testing Machines](#)
[E29 Practice for Using Significant Digits in Test Data to Determine Conformance with Specifications](#)
[E178 Practice for Dealing With Outlying Observations](#)
[E399 Test Method for Linear-Elastic Plane-Strain Fracture Toughness of Metallic Materials](#)
[E2309/E2309M Practices for Verification of Displacement Measuring Systems and Devices Used in Material Testing Machines](#)
[E3029 Practice for Determining Relative Spectral Correction Factors for Emission Signal of Fluorescence Spectrometers](#)
 2.2 *AASHTO Standards*:³
[R30R 30 Practice for Mixture Conditioning of Hot Mix Asphalt \(HMA\)](#)
[M320M 320 Standard Specification for Performance-Graded Asphalt Binder](#)
[M332M 332 Standard Specification for Performance-Graded Using Multiple Stress Creep Recovery \(MSCR\) Test](#)

3. Terminology

3.1 Definitions:

- 3.1.1 J_c —critical strain energy release rate (kJ/m^2), value used to evaluate mixture resistance to cracking.
- 3.1.2 U —strain energy to failure (kJ) is the area under the loading portion of the load versus deflection curves, up to the maximum load measured for each notch depth.

4. Summary of Test Method

4.1 A semi-circular specimen is loaded monotonically until fracture failure occurs under a constant rate of deformation in a three-point bending load configuration. The load and deformation are continuously recorded and are used to compute the strain energy for a given notch depth. The test is repeated at multiple notch depths to compute the critical strain energy release rate, rate parameter, J_c . High J_c values are desirable for fracture-resistant mixtures. A minimum J_c value ranging from 0.50 to 0.60 kJ/m^2 is typically recommended to ensure adequate fracture resistance of the mixture.

4.2 This test procedure considers the elasto-plastic/visco-elastic relationship of asphalt mixtures and fracture mechanics (Mull, et al., 2006, Anderson 2005)(Mull et al., 2006; Anderson, 2005; and suggested by Wu et al., 2005).

5. Significance and Use

5.1 The critical strain energy release rate, rate parameter, J_c , is used to compare the cracking resistance of asphalt mixtures prepared with different asphalt binder and aggregate types prepared to meet the volumetric requirements of differing traffic levels tested at intermediate temperatures.

5.2 ~~This~~—The critical strain energy release rate parameter, J_c , is an engineering property is and a performance indicator of at intermediate temperature cracking.

NOTE 1—The quality of the results produced by this standard are dependent on the competence of the personnel performing the procedure and the capability, calibration, and maintenance of the equipment used. Agencies that meet the criteria of Specification **D3666** are generally considered capable of competent and objective ~~testing/sampling/inspection/etc.~~ testing, sampling, inspection, etc. Users of this standard are cautioned that compliance with Specification **D3666** alone does not completely assure reliable results. Reliable results depend on many factors; following the suggestions of Specification **D3666** or some similar acceptable guideline provides a means of evaluating and controlling some of those factors.

³ Available from American Association of State Highway and Transportation Officials (AASHTO), 444 N. Capitol St., NW, Suite 249, Washington, DC 20001, <http://www.transportation.org>.

6. Apparatus

6.1 *Load Test System*—A load test system consisting of an axial loading device, environmental chamber, and control and data acquisition system. The test system shall meet the minimum requirements specified in **Table 1**. (See Practices **E2309/E2309M**.)

6.1.1 *Axial Loading Device*—The load apparatus shall be capable of maintaining a constant deformation rate of 0.5 ± 0.02 mm/min.

6.1.2 *Environmental Chamber*—A chamber capable of maintaining $\pm 0.3 \pm 0.5$ °C of the climatic intermediate temperature calculated in **8.4**.

6.1.3 *Control and Data Acquisition System*—The system shall include a data acquisition system comprising analog to digital conversion or digital input, or both, for storage and analysis on a computer. The system shall be capable of measuring and recording three signals during the test including load, displacement, and chamber temperature at a sampling rate of 10 Hz. The minimum resolution of the measurements is provided in **Table 1**.

6.2 *Measurement Devices:*

6.2.1 *Load Measuring Device*—The load measuring device shall consist of an electronic load cell, designed for placement between the load platen and piston, with the minimum capacity and sensitivity stated in **Table 1**. The load cell shall be calibrated in accordance with Practices **E4**.

6.2.2 *Axial Deformations*—Axial deformations shall be measured with linear variable differential transformers (~~LVD~~)(LVDTs) or other devices capable of measuring displacement within the range and tolerance provided in **Table 1**. The LVDT shall be calibrated in accordance with Practice **E3029**, Class B.

6.2.3 *Temperature*—Chamber temperature shall be measured with Resistance Temperature Detectors (~~RTD~~)(RTDs) or other suitable devices accurate to within ± 0.3 °C; ± 0.5 °C.

6.3 *Gyratory Compactor*—A gyratory compactor and associated equipment for preparing laboratory specimens in accordance with Test Method **D6925** shall be used.

6.4 *Saw*—The saw shall be capable of producing three different notch sizes ranging from 0 to 50 mm. The width of the saw blade shall be ~~<3.5mm;~~ <3.5 mm.

6.5 *Test Fixture*—The loading frame shall consist of a loading rod and two sample support rods. The schematic of the test apparatus is shown in **Fig. 1**. The diameters of the loading and supports rods shall be 25 mm and the anvil span shall be 127 mm.

6.6 *Reaction Surface Treatment*—Polytetrafluoroethylene (PTFE) strips are used to reduce friction between the specimen and the lower two support rollers.

TABLE 1 Test System Minimum Requirements

| Measurement | Range | Accuracy |
|---|------------|----------|
| Load Measurement and Control | 0 to 10 kN | ± 1 % |
| Load Measurement and Control | 0 to 10 kN | ± 1 % |
| Displacement Measurement and Control | 0 to 30 mm | ± 0.5 % |
| Displacement Measurement and Control | 0 to 30 mm | ± 0.5 % |
| Temperature Measurement and Control Range | 5 to 35 °C | ± 0.3 °C |
| Temperature Measurement and Control Range | 5 to 35 °C | ± 0.5 °C |

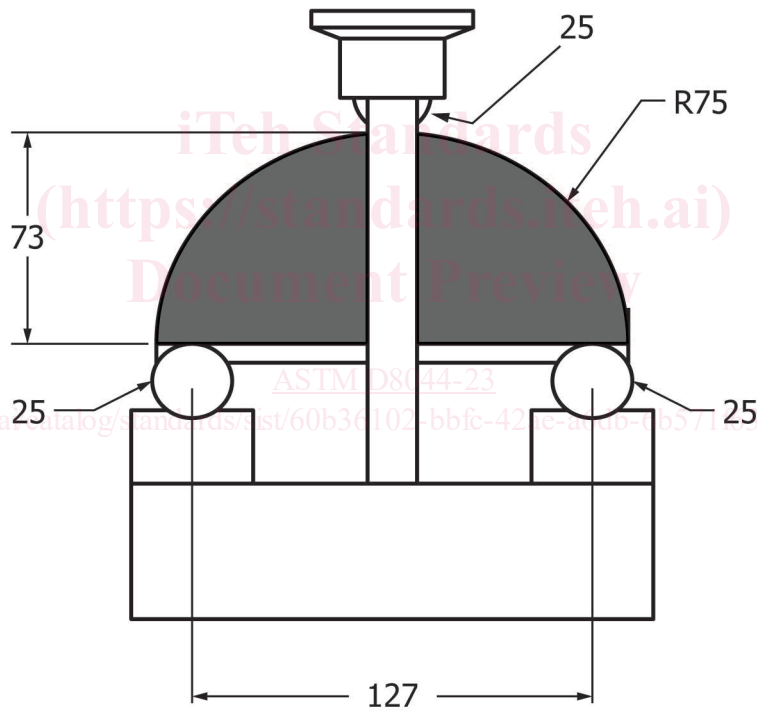
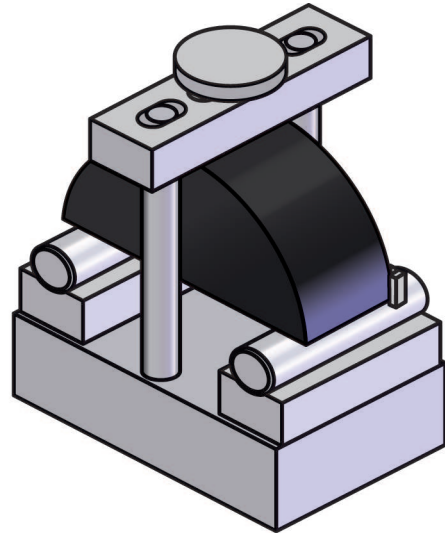


FIG. 1 Shop Drawing of SCB Test Fixture

7. Sampling, Test Specimens, and Test Units

7.1 Semi-circular bend testing may be performed on field cores or ~~laboratory-prepared~~ laboratory-prepared test specimens. (See Practices [D5361/D5361M](#) and [D979/D979M](#).)

7.2 ~~Laboratory-compacted asphalt mixture samples:~~ Laboratory-Compacted Asphalt Mixture Samples:

7.2.1 *Specimen Size*—The specimens shall be 150 mm in diameter by 120 mm thick.

7.2.2 *Air Void Content*—Prepare a minimum of three gyratory specimens at the target air void content using the Superpave Gyratory Compactor (SGC) according to Test Method **D6925** at the target air void content $\pm 0.5\%$ – $\pm 1\%$. The typical air void target for the test specimens is 7.0 %.

NOTE 2—The specimen air voids are calculated using Test Methods **D2041/D2041M**, **D2726/D2726M**, **D3203/D3203M**, and **D6857/D6857M**.

7.2.3 The semi-circular shaped specimens are prepared by first cutting a 150 mm diameter by 120 mm thick specimen into two equal circular test samples 57 ± 2 mm thick. These samples are cut along its central axis into two equal semi-circular samples. The height of the semi-circular specimen shall be 73.5 ± 2 mm. The height (radius) of the two samples halves shall be within 1 mm of each other.

NOTE 3—Some practitioners believe that the test should be conducted on specimens with two cut faces. If this approach is used, increase the compacted sample height by approximately 15 ± 5 mm such that the semi-circular shaped specimens with two cut faces have a final thickness of 57 ± 1 mm.

7.3 *Samples Cored from Asphalt Pavement:*

7.3.1 Roadway cores can be used if pavement layer thickness is between 38 and ~~60 mm~~–60 mm. Cores shall be taken full depth so that no prying action is needed to extract the cores from the pavement. Care shall be taken to avoid stress or damage to the interface during coring, handling, and transportation. The cores shall be trimmed such that only a single layer is tested.

7.3.2 Roadway core specimens shall be approximately 150 mm diameter with all surface of the perimeter perpendicular to the surface of the core within 6 mm. If the thickness of the core being tested is greater than 57 ± 2.0 mm, it shall be trimmed with a wet masonry saw to a height of 57 ± 2.0 mm.

7.3.3 The semi-circular shaped specimens are prepared by slicing the 150 mm diameter specimen prepared in 7.2.3 or 7.3.2 along its central axis into two equal semi-circular samples. The height (radius) of the two halves shall be within 1 mm of each other.

7.4 *Notching*—A straight vertical notch is cut along the symmetrical axis of each semi-circular specimen. The location of the notch shall be in the center of the specimen within 0.3 mm. maximum allowable offset between the center of notch and the axis of symmetry of the specimen is 2 mm. The three nominal notch depths are 25 mm, 32 mm, and 38 mm. The notch depth tolerance is $\pm 1.0 \pm 2.0$ mm. The width of the notch shall be ~~<3.5 mm~~–less than

NOTE 4—Ruggedness testing between four laboratories has shown the J_c for split samples to have a within laboratory COV of 9.9 % for specimens with notch widths between 1.3 mm and 3.4 mm. The specimens should be symmetrical about the cut notch. 3.5 mm.

NOTE 4—Ruggedness testing between four laboratories has shown the J_c for split samples to have a within-laboratory COV of 9.9 % for specimens with notch widths between 1.3 mm and 3.4 mm. The specimens should be symmetrical about the cut notch.

7.5 *Aging*—Laboratory-prepared test specimens shall be ~~long term temperature conditioned~~–long-term temperature conditioned in according to AASHTO R30:R 30. Roadway cores need not be aged prior to testing.

7.6 A minimum of four semi-circular specimens shall be tested at each of the following notch depths: 25 ± 2.0 mm, 32 ± 2.0 mm, and 38 mm – \pm

NOTE 5—A loose mix aging method is under development that may be able to achieve the AASHTO R30 level of aging in 12 to 24 h, NCHRP 9-54 Long Term Aging of Asphalt Mixtures for Performance Testing and Prediction. The long-term temperature aging is needed to account for binder source, RAP, RAS and rejuvenators on mix performance (Reinke, et al., 2009, 2015; Cooper, et al. 2014, 2015)–2.0 mm.

NOTE 5—A loose mix aging method is under development that may be able to achieve the AASHTO R 30 level of aging in 12 to 24 h, NCHRP 9-54 Long Term Aging of Asphalt Mixtures for Performance Testing and Prediction. The long-term temperature aging is needed to account for binder source, RAP, RAS and rejuvenators on mix performance (Reinke et al., 2009, 2015; Cooper et al., 2014, 2015).

8. Procedure

8.1 Inspect the fixture to ensure all contact surfaces are clean and free of debris. Place the PTFE tape or pads to reduce friction caused by interactions between the specimen and testing fixture during loading. The PTFE pads can be placed between the specimen and the bottom support rollers.

8.2 Load the specimen in the fixture, ensuring the specimen is centered and making uniform contact (level) on the support rollers (as shown in Fig. 2).

8.3 Set the environmental chamber temperature and allow it to stabilize to the test temperature $\pm 0.3^\circ\text{C}$, $\pm 0.5^\circ\text{C}$. A dummy specimen with a temperature sensor mounted to its center can be monitored to determine when the specimen reaches the test temperature $\pm 0.3^\circ\text{C}$, $\pm 0.5^\circ\text{C}$. In the absence of a dummy specimen, the specimens should be placed in the environmental chamber set at the test temperature for a minimum of 2 ± 0.5 h to reach the required temperature equilibrium.

NOTE 6—Dummy specimens are typically the same material as the test specimens.

8.4 Select test temperature based on the climatic intermediate temperature performance grade temperature as defined in Specification **D6373**, AASHTO **M320**, or **M332-M 320**, or **M 332** and provided below in Eq 1:

$$PGIT = \frac{PGHT + PGLT}{2} + 4 \quad (1)$$

where:

PGIT = Intermediate performance grade temperature ($^\circ\text{C}$);
PGHT = Climatic high performance grade temperature, and
PGLT = Climatic low performance grade temperature.

PGIT \equiv intermediate performance grade temperature ($^\circ\text{C}$),
PGHT \equiv climatic high performance grade temperature, and
PGLT \equiv climatic low performance grade temperature.

8.5 After temperature equilibrium is reached, apply a preload of 45 ± 10 N for a maximum duration of 30 s to specimen to ensure the sample is seated properly. After ensuring the sample is level, release the load.

8.6 Begin to apply load to specimen in displacement control at a rate of 0.5 ± 0.02 mm/min ensuring that time, force, and displacement are measured and recorded at a sampling rate of 10 Hz. Test may be terminated when the applied load decreases to 25 % of the peak load.


9. Calculation or Interpretation of Results

9.1 The critical value of J-integral (J-strain energy release rate (J_c)) is determined/computed using Eq 2:


$$J_c = \frac{-1}{b} \left(\frac{dU}{da} \right) \quad (2)$$

where:

J_c = critical strain energy release rate (kJ/m^2),
b = sample thickness (m),
a = notch depth (m),
U = strain energy to failure (kJ), and
dU/da = change of strain energy with notch depth (kJ/m).

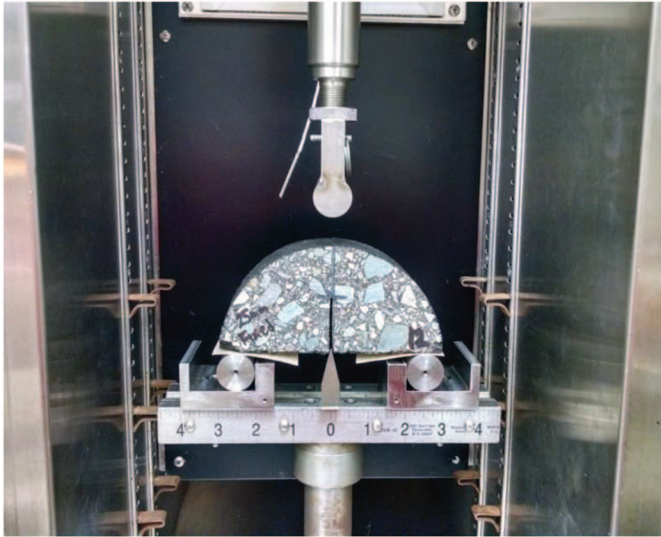


(a)

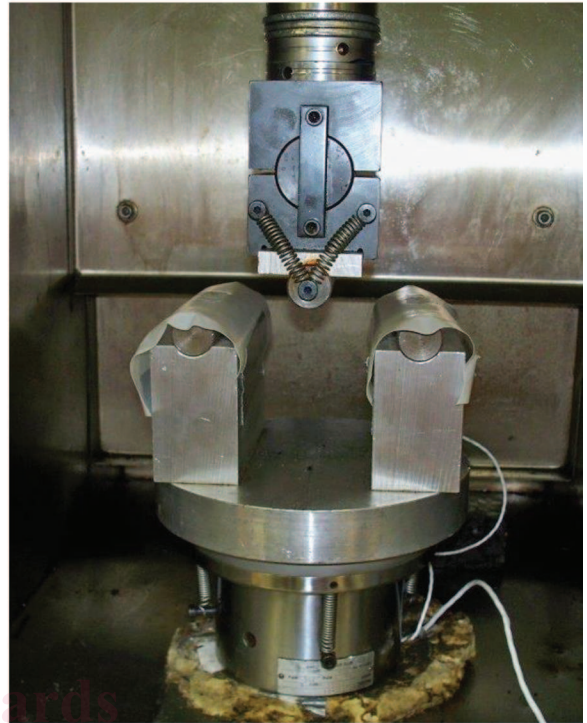

(b)



(c) Sample Placed in Marshall Fixture

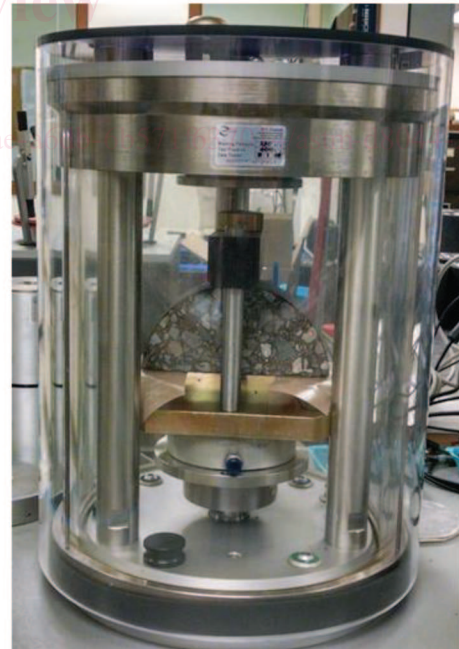

(d) Fixture in AMPT

FIG. 2 Examples of SCB Test Fixtures for a Universal Testing Machine (a and b) and a Marshall Press (c) or AMPT (d)