



Designation: D7864/D7864M – 15 (Reapproved 2023)

## Standard Test Method for Determining the Aperture Stability Modulus of Geogrids<sup>1</sup>

This standard is issued under the fixed designation D7864/D7864M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope

1.1 This test method covers the procedure for measuring the Aperture Stability Modulus of a geogrid. (The terms “Secant Aperture Stability Modulus,” “Torsional Rigidity Modulus,” “In-plane Shear Modulus,” and “Torsional Stiffness Modulus” have been used in the literature to describe this same property.)

1.2 This test method is intended to determine the in-plane stability of a geogrid by clamping a center node and measuring the stiffness over an area of the geogrid. This test method is applicable for various types of geogrid.

1.3 This test method is intended to provide characteristic properties for design. The test method was developed for pavement and subgrade improvement calibrated design methods requiring input of aperture stability modulus.

1.4 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system are not necessarily exact equivalents; therefore, to ensure conformance with the standard, each system shall be used independently of the other, and values from the two systems shall not be combined.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.6 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D35 on Geosynthetics and is the direct responsibility of Subcommittee D35.01 on Mechanical Properties.

Current edition approved June 1, 2023. Published June 2023. Originally approved in 2015. Last previous edition approved in 2015 as D7864/D7864M – 15. DOI: 10.1520/D7864\_D7864M-15R23.

### 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

D4354 Practice for Sampling of Geosynthetics and Rolled Erosion Control Products (RECPs) for Testing  
D4439 Terminology for Geosynthetics

2.2 *FHWA Document:*<sup>3</sup>

FHWA Geosynthetic Design and Construction Guidelines (2008)

### 3. Terminology

3.1 *Definitions:*

3.1.1 For definitions of general terms used in this test method, refer to Terminology D4439.

3.1.2 *geogrid, n*—a geosynthetic formed by a regular network of integrally connected elements with apertures greater than 6.35 mm [ $\frac{1}{4}$  in.] to allow interlocking with surrounding soil, rock, earth, and other surrounding materials to primarily function as reinforcement.

3.1.3 *index test, n*—a test procedure which may contain a known bias but which may be used to establish an order for a set of specimens with respect to property of interest.

3.2 *Definitions of Terms Specific to This Standard:*

3.2.1 *aperture*—the openings between adjacent ribs forming an angle which enable soil interlocking to occur.

3.2.2 *aperture stability modulus*—a measure of the in-plane torsional stiffness of a geogrid. This is defined as torque divided by the rotation at that torque.

3.2.3 *geosynthetic, n*—a product manufactured from polymeric material used with soil, rock, earth, or other geotechnical engineering material as integral part of a man-made project, structure, or system.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> Available from U.S. Department of Transportation, Federal Highway Administration, 1200 New Jersey Ave., SE, Washington, DC 20590, <http://www.fhwa.dot.gov>.

3.2.4 *initial aperture stability modulus,  $n$* —the change in moment at 0.5 and 1.0 N-m [4.4 and 8.8 lbf-in.], respectively, divided by the change in angular rotation at these two moment values.

3.2.5 *junction,  $n$* —the point where geogrid ribs are interconnected to provide structure and dimensional stability.

3.2.6 *offset aperture stability modulus*—the change in moment at 2.0 and 2.5 N-m [17.7 and 22.1 lbf-in.], respectively, divided by the change in angular rotation at these two moment values.

3.2.7 *rib,  $n$* —for geogrids, the continuous oriented elements of a geogrid which are interconnected to a node or junction.

#### 4. Summary of Test Method

4.1 A geogrid sample is placed over a square, horizontal opening and the edges are anchored just outside the opening. A rod is clamped vertically on the single center node or junction. A torque is applied to the rod, which twists the clamped node or junction and the geogrid rib matrix, thereby applying a moment causing bending to each of the ribs that intersects the single clamped center node or junction. The torque divided by the angle of rotation is termed the Aperture Stability Modulus expressed in units of N-m/degree [lbf-in./degree].

#### 5. Significance and Use

5.1 The aperture stability modulus is a measure of the in-plane shear modulus, which is a function of other geogrid characteristics, most notably junction stability, flexural rib stiffness, and rib tensile modulus.

5.2 The test data can be used in conjunction with interpretive methods to evaluate the geogrid aperture stability at various traffic loads and base/subgrade conditions.

NOTE 1—Aperture stability modulus is referenced in the FHWA Geosynthetics Design and Construction Guidelines (2008) as an input parameter for the design of geogrid-reinforced unpaved roads using punched and drawn biaxial geogrids. Geogrids of different manufacturing process and material composition may use this property in calibration and validation of their material within the associated design.

5.3 This test method is not intended for routine acceptance testing of geogrid. This test method should be used to characterize geogrid intended for use in applications in which aperture stability is considered relevant.

#### 6. Apparatus

6.1 The apparatus consists of a table, table clamps for the edges of the geogrid, a rod with a center clamp that attaches to the ribs around a node or junction, a loading mechanism, and a method of measuring the moment and the angle of rotation of

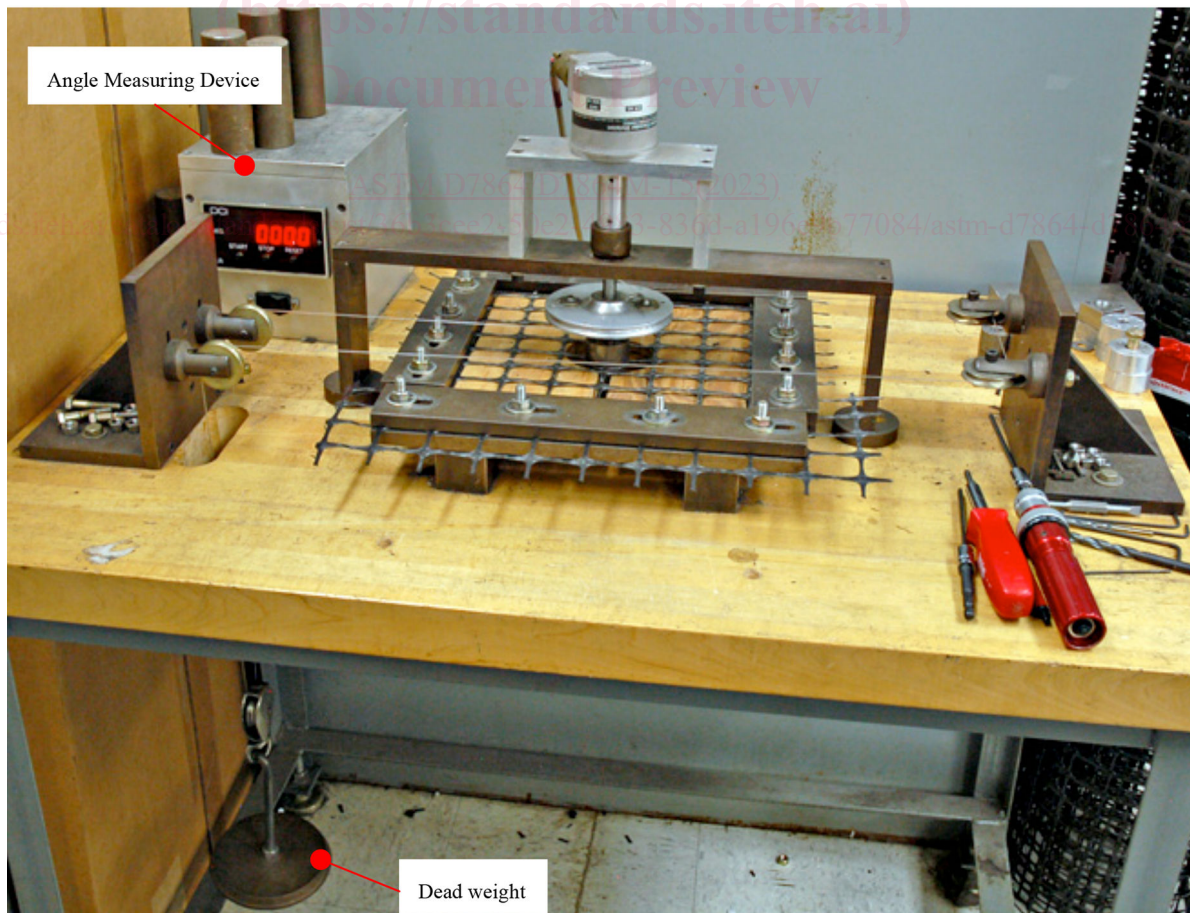


FIG. 1 Test Apparatus During Test (loading plates and weights not shown)



the rod. A cross section of the apparatus used originally to develop the test method is shown in Figs. 1-4. Other methods of clamping, applying a moment, loading, and measuring have been used by others and are acceptable, subject to the constraints discussed in the following subsections. Details of each part follow.

6.1.1 *Table*—The table shall be constructed so that the geogrid can be laid over a 229 mm [9 in.] square hole and anchored in place. The geogrid must be placed as it would be in the field, flat but not stretched. This requires a supporting plate beneath the geogrid and a loading plate over the geogrid to keep it flat while it is being laid over the table and clamped around the edges with table clamps. The plate must be large enough to support every node or junction and any part of the geogrid that tends to protrude above or below the planes of the tops and bottoms of the nodes or junction. The loading plate must cover the same nodes or junctions and be weighted with not less than 100 N [22.5 lbf] to sufficiently maintain the geogrid flat during clamping. These plates must be removed before test loads are applied and the sample inspected to ensure that it is completely flat. No additional tensioning of the geogrid should be done.

6.1.2 *Table Clamps*—Clamps for the outside edges of the geogrid. The table clamps should have smooth surfaces and be rectangular in shape (Fig. 2). The table clamps hold the geogrid ribs firmly in place with respect to lateral movement at a distance of 8 mm [0.31 in.] ± 6 mm [0.24 in.] from the edge of the hole. If the node or junction is more than 12.7 mm

[0.5 in.] outside the hole then the rib must be clamped between the node or junction and the edge of the hole. If the node or junction is within 12.7 mm [0.5 in.] of the edge of the hole, the node or junction must be clamped. Each rib must be held so that it does not move laterally more than 0.1 mm [0.004 in.] during the test. The tension in some ribs may be very high, perhaps on the order of several thousand N [several hundred lbf] for geogrids with high modulus values and large aperture sizes. The higher the aperture stability modulus, the more important it is that the clamps do not allow lateral movement. The direction of maximum movement will be in the general direction of the rib. If the clamped point moves more than 0.1 mm [0.004 in.], the test should be discarded. Once confidence has been developed in a particular clamping technique with a particular geogrid, it will not be necessary to measure the potential movement in every test. However, while developing the clamping technique for a particular geogrid, the clamping efficiency must be checked. One method of doing this is to measure the distance from the edge of the clamp to a point close to the clamp on the rib. The clamping technique used to develop this test method was determined to be adequate for the geogrids tested and is shown in Figs. 1 and 2. The table clamps are made of steel bars with 9.5 mm [3/8 in.] bolts with 16 threads per 25 mm [1 in.] on about 50 mm [2 in.] spacing. The bolts were torqued to 13.5 N·m [120 lbf·in.].

6.1.3 *Torquing Rod*—The torquing rod must have a clamp at one end to attach it to the ribs around the single center node or junction of the geogrid. The rod must be supported so that

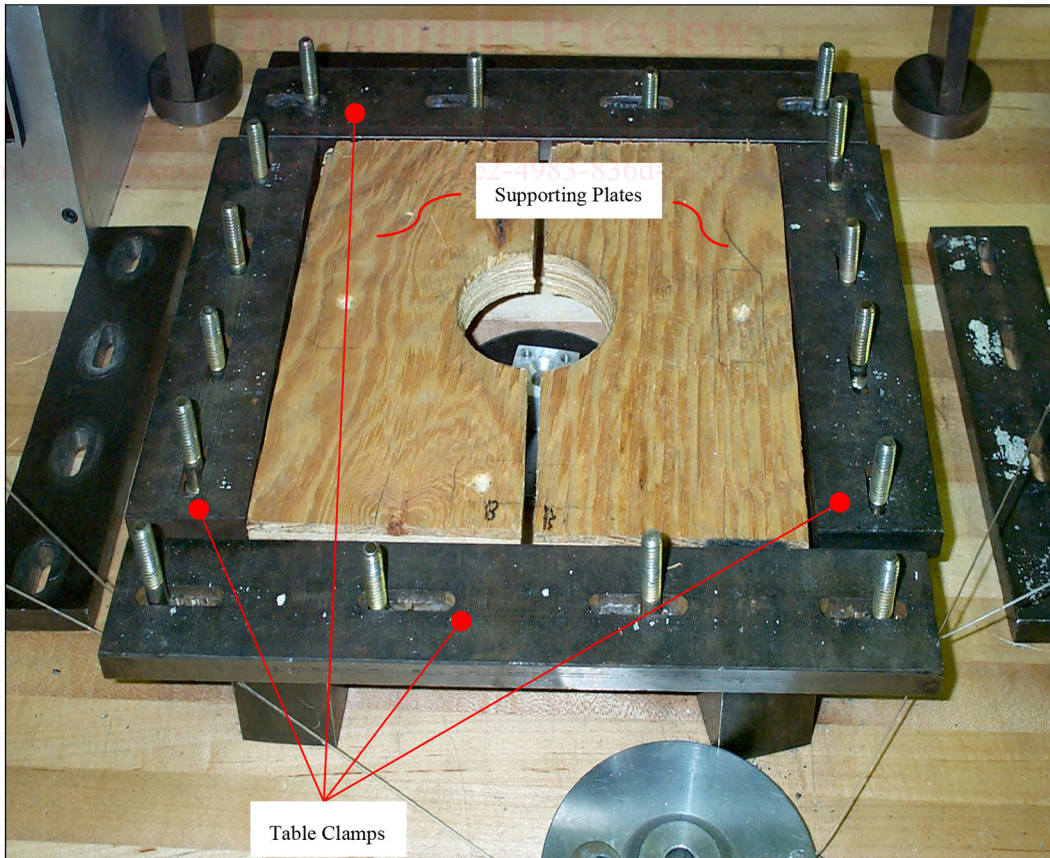


FIG. 2 Details of Table Clamps and Supporting Plates





FIG. 3 Loading Plates and Weights Applied Prior to Clamping Specimens on Table Clamps

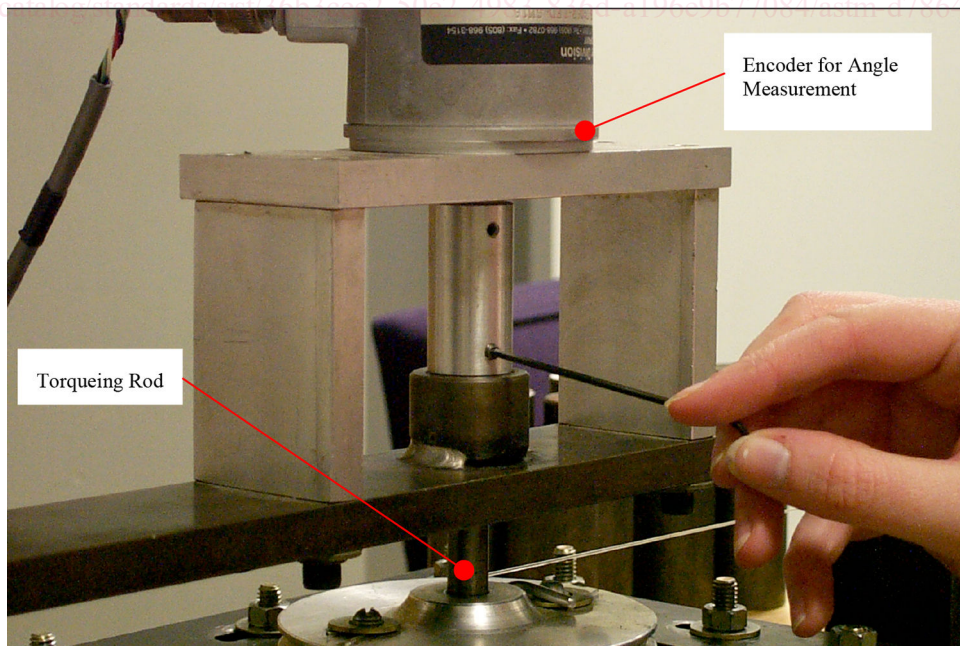


FIG. 4 Torquing Rod with Encoder Being Locked in Place