



Designation: E3107/E3107M – 23

Standard Test Method for Resistance to Penetration and Backface Deformation for Ballistic-resistant Torso Body Armor and Shoot Packs¹

This standard is issued under the fixed designation E3107/E3107M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method addresses resistance to ballistic penetration and to backface deformation (BFD) for ballistic-resistant torso body armor and shoot packs.

1.2 This test method is intended for testing of soft body armor, hard armor plates, in conjunction with armor, and shoot packs mounted on a clay block as the backing assembly.

NOTE 1—This test method does not apply to ballistic helmets, inserts, trauma packs, trauma plates, or accessories.

1.3 The test method does not specify performance criteria or usage of the test results.

1.4 This test method does not address conditioning of test items.

1.5 It is anticipated that this test method will be referenced by certifiers, purchasers, or other users in order to meet their specific needs.

1.5.1 Purchasers and other users will specify the ballistic test threats to be used. Within this test method, the reference defining the ballistic test threats is called the “test threats document.”

1.5.2 In this test method, “other standards and specifications” and “unless specified elsewhere” refer to documents (for example, military standards, purchase specifications) that require the use of this test method. Purchasers and other users are responsible for the “other standards and specifications” and for specifying any requirements that supersede those of this test method.

1.6 *Units*—The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system are not necessarily exact equivalents; therefore, to ensure conformance with the standard, each system shall be used independently of the other, and values from the two systems shall not be combined.

¹ This test method is under the jurisdiction of ASTM Committee E54 on Homeland Security Applications and is the direct responsibility of Subcommittee E54.04 on Public Safety Equipment.

Current edition approved May 1, 2023. Published June 2023. Originally approved in 2017. Last previous edition approved in 2022 as E3107/E3107M – 22. DOI: 10.1520/E3107_E3107M-23.

1.6.1 The user of this standard will identify the system of units to be used, and it is critical to ensure that any cross-referenced standards maintain consistency of units between standards.

1.7 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.8 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 ASTM Standards:²

E3004 Specification for Preparation and Verification of Clay Blocks Used in Ballistic-Resistance Testing of Torso Body Armor

E3005 Terminology for Body Armor

E3062/E3062M Specification for Indoor Ballistic Test Ranges for Small Arms and Fragmentation Testing of Ballistic-resistant Items

E3068 Test Method for Contact Measurement of Backface Deformation in Clay Backing During Body Armor Testing

2.2 ISO Standard:³

ISO/IEC 17025:2005 General Requirements for the Competence of Testing and Calibration Laboratories

2.3 NIJ Standard:⁴

NIJ Standard-0101.06 Ballistic Resistance of Body Armor

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard’s Document Summary page on the ASTM website.

³ Available from International Organization for Standardization (ISO), ISO Central Secretariat, BIBC II, Chemin de Blandonnet 8, CP 401, 1214 Vernier, Geneva, Switzerland, <http://www.iso.org>.

⁴ Available from National Institute of Justice (NIJ), 810 7th St., NW, Washington, DC 20531, <http://nij.gov>.

3. Terminology

3.1 For terms not defined in this test method, the following definitions of Terminology E3005 apply: *accessories, angle of incidence, applique, backface deformation, backing assembly, backing material, backing fixture, body armor, complete penetration, fair hit, hard armor, in conjunction with armor, obliquity, partial penetration, plate, shoot pack, shot-to-edge distance, shot-to-shot distance, soft body armor, stop, strike face, striking device, test item, test series, unfair hit, warmer round, witness panel, and yaw.*

4. Summary of Test Method

4.1 This test method specifies the methods for assessing penetration resistance and backface deformation for ballistic-resistant torso soft body armor, hard armor plates, in conjunction with armor, and shoot packs.

4.2 Individual test items are subjected to ballistic tests with specified test threats. The type and velocity of the test threats are specified in a test threats document, and the number of shots and shot pattern are specified in other standards or specifications, or both.

5. Significance and Use

5.1 U.S. Department of Defense and U.S. Department of Justice standards and specifications require assessing the penetration resistance and backface deformation of ballistic-resistant body armor.

5.2 This test method may be used by private-sector and government laboratories, manufacturers, research and development organizations, and others assessing the ballistic resistance of body armor or performing research and development of new materials.

5.3 It is intended that this test method be referenced by other standards, specifications, or test methods.

6. Test Equipment and Apparatus

6.1 Test threats shall be specified in a separate test threats document.

6.2 The ballistic test range shall meet the requirements of Specification E3062/E3062M.

6.3 The method of measuring yaw may be with a yaw card, flash radiography, high speed video, or photography and shall be capable of determining, at the point of measurement, whether the angle of yaw was greater or less than 5°.

6.4 Clay blocks shall be used as backing assemblies behind test items and shall meet the requirements of Specification E3004.

6.5 Measurement of BFD may be performed using contact or non-contact measurement instruments, and other standards and specifications will specify which method to use.

6.5.1 When the contact method for BFD measurement is used, the equipment shall be as specified in Test Method E3068.

7. Hazards

7.1 The ballistic tests described in this test method have inherent hazards. Adequate safeguards for personnel and property shall be employed when conducting these tests.

8. Sampling and Test Items

8.1 The test items shall be individual soft armor panels, hard armor plates, in conjunction with systems, or shoot packs.

8.2 Test item details, including quantity, size, and conditioning, shall be specified in other standards and specifications.

NOTE 2—It is recommended that spare test items be provided.

8.3 When the use of a spare test item is required, details about selecting the appropriate spare item shall be specified in other standards and specifications.

9. Test Requirements

9.1 The intended angle of incidence, obliquity, or other shot direction details, if any, for all shots shall be specified in other standards and specifications.

NOTE 3—Typical angles of incidence are 0°, 30°, and 45°, with most testing at an angle of incidence of 0°.

9.2 When warmer rounds are necessary, a number of test threats shall be fired through the projectile firing system.

NOTE 4—Examples of when warmer rounds may be necessary include, but are not limited to, at the start of a new day of testing and upon reconfiguration of the test range.

9.3 Unless specified elsewhere, each ballistic impact shall meet the requirements listed below to be considered a fair hit. See Annex A1 for flowchart showing the decision logic for determination of fair hit.

9.3.1 The test threat shall impact the test item at an angle of incidence or obliquity within 5° from the intended angle.

9.3.2 The test threat shall have yaw verified using a yaw card, flash radiography, high speed video, or photography. Yaw shall be checked for every test threat shot and shall be $\leq 3^\circ$ for rifle threats or $\leq 5^\circ$ for fragment and handgun threats.

9.3.2.1 The yaw measurement equipment shall be positioned perpendicular to the projectile line of flight. The yaw measurement equipment shall be securely mounted and anchored to maintain its required position and alignment.

9.3.2.2 When photographic means are used to assess the projectile yaw angle, the assessment shall be made as close as practical to the strike face of the test item but not more than 305 mm [12 in.] from the front of the strike face.

9.3.2.3 When yaw cards are used to assess the projectile yaw angle, unless specified elsewhere, the cards shall be positioned between 91 cm and 152 cm [3 ft to 5 ft] from the front of the strike face of the test item.

9.3.3 The test threat shall impact the test item no closer to the edge of the test item than the minimum shot-to-edge distance. The measurement for shot-to-edge distance shall be taken from the center of the projectile impact to the nearest edge of the ballistic material in the test item. When not specified elsewhere, the minimum shot-to-edge distance shall be 51 mm [2 in.].

NOTE 5—Procedures for determining the edge of the test item should be specified in other standards or specifications.

9.3.4 For intended edge shots, the test threat shall impact the test item no further from the edge than the maximum shot-to-edge distance.

9.3.5 The test threat shall impact the test item no closer to a prior impact than the minimum shot-to-shot distance. The measurement for shot-to-shot distance shall be taken from the center of one projectile impact to the center of another. When the minimum shot-to-shot distance is not specified, the minimum shot-to-shot distance shall be 51 mm [2 in.].

NOTE 6—When assessing whether a particular impact location meets the minimum shot-to-shot distance requirements, the shot-to-shot distances should be measured from that impact location to all prior impact locations.

9.3.6 For grouped shots, the test threat impacts shall be within the specified spacing or pattern.

9.3.7 The test threat shall impact the clay block no closer than 106 mm [4.2 in.] from the inside edge of the clay block frame.

9.3.8 The test threat velocity shall conform to the requirements given in the test threats document. If no specification is given, the test threat velocity shall be within ± 9.1 m/s [± 30 ft/s] of the required velocity.

9.3.9 The velocity difference requirements of Specification E3062/E3062M shall apply.

9.3.10 Details for specifying a shot outcome as a complete penetration or a partial penetration shall be specified in other standards and specifications.


10. Mounting and Positioning of Soft Armor Test Items on a Clay Block

10.1 The testing of nonplanar soft armor test items intended for females requires the use of appliques that are specified in other standards and specifications.


NOTE 7—Appliques that may be needed for testing nonplanar soft armor test items are specified in other standards and specifications. Testing of planar soft armor test items does not require the use of appliques.

10.2 The test item shall be positioned on a clay block such that the entire test item is supported. When the test item exceeds the size of the clay block, install backing fixture extensions coplanar with the backing material surface to allow the test item to be fully supported.

10.3 The test item, and its applique(s) for nonplanar test items, shall be held in contact with the clay block and secured using approximately 50 mm [2.0 in.] wide elastic straps, held closed by hook-and-loop fasteners. Unless specified elsewhere, two vertical and three horizontal straps shall be positioned such that they do not interfere with the impact points on the test item. Fig. 1 shows examples of strapping arrangements.

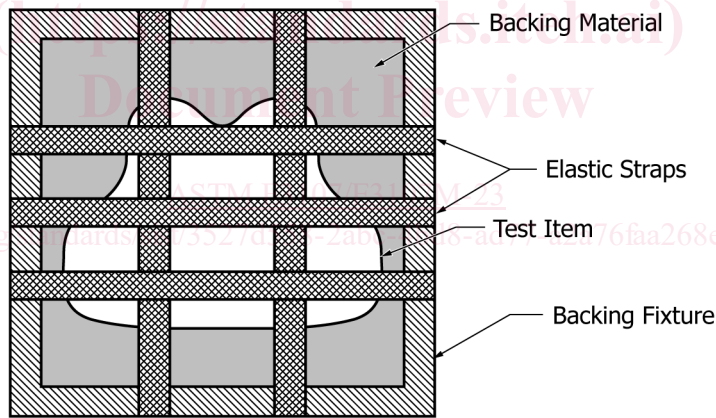

A. Strapping Arrangement for Smaller Test Items

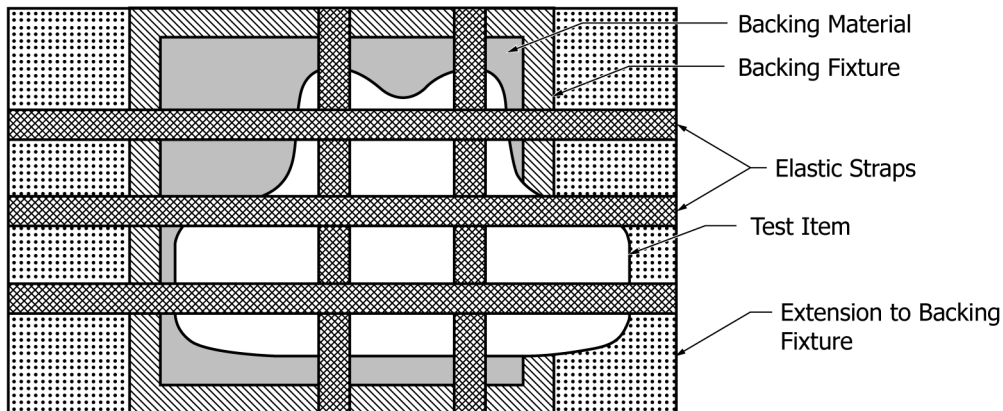

B. Strapping Arrangement for Larger Test Items Requiring Extension to Backing Fixture

FIG. 1 Examples of Strapping Arrangements

10.4 The clay block shall be positioned to achieve proper bullet impact location and angle (for example, angle of incidence, obliquity) of the test threat. For any shots requiring a nonzero angle of incidence, the clay block shall be rotated to achieve the appropriate angle.

10.5 Between test threat impacts, the test item shall be manipulated by hand so that any wrinkles or bunching in the test item (caused by a previous shot) are smoothed out. No effort shall be made to recover any bullets trapped in the test item until the test series is complete.

NOTE 8—Manipulation of a bullet is allowed if the bullet will interfere with subsequent shots. The test item may be removed if necessary to smooth it out.

10.5.1 The test item shall be repositioned on the backing material such that the test item is supported by smooth backing material for a distance of no less than 76 mm [3.0 in.] in all directions around the next shot location.

NOTE 9—Instructions related to striking the backing material between shots shall be specified by other standards and specifications.

11. Ballistic Test Procedure for Soft Armor Test Items

11.1 A complete test series for the assessment of penetration resistance and backface deformation consists of individual ballistic tests being conducted on a number of individual test items, of specified size(s), as specified in other standards and specifications.

11.2 Unless specified in other standards or specifications, the shot placement, pattern, and angles of incidence shall be as specified below.

11.2.1 All test items shall be marked to indicate the intended fair hit locations prior to taking any shots.

11.2.2 Shots 1, 2, 3, and 7 shall meet the shot-to-edge distance requirements but shall not be located more than the shot-to-edge distance plus 19 mm [0.75 in.] from the edge of the test item.

11.2.2.1 Shots 1, 2, and 3 shall not be placed close to each other and shall be arbitrarily moved to different locations on different test items within the test series.

11.2.3 Shots 4, 5, 6, and 7 shall meet the minimum shot-to-shot distance requirements.

11.2.3.1 Shots 4, 5, and 6 shall be located within a 100 mm [3.94 in.] diameter circle.

(1) For test items with sufficient area, the locations of shots 4, 5, and 6 shall be arbitrarily moved to different areas on different test items within the test series.

(2) Unless specified in other standards and specifications, when the test item is too small to allow all six shots with the required spacing, an additional test item may be used for shots 4, 5, and 6.

11.2.4 Shot 7 is only required to be taken on test items representing front panels that have a neck scoop.

11.2.4.1 Shot 7 shall be placed at the center of the neck scoop.

11.2.4.2 Shot 7 shall be placed on the same test item as shots 4, 5, and 6.

11.2.5 Fig. 2 shows example shot locations and patterns. Placement of shots is not restricted to locations shown in Fig. 2.

11.2.5.1 Fig. 2a and Fig. 2b are for a test item too small to allow all shots on one test item. Fig. 2a shows example locations for shots 1, 2, and 3 on one test item, and Fig. 2b shows locations for shots 4, 5, 6, and 7 on another test item.

11.2.5.2 Fig. 2c is for a test item having sufficient area to fit all 7 shots.

11.2.6 Shots 1, 2, 3, and 6 shall be taken at 0° angle of incidence.

11.2.6.1 Shots 4 and 5 shall be taken at 30° and 45° angle of incidence, with the angular rotation of the backing assembly in the same direction for both shots on an individual test item.

(1) The order of angles shall be alternated between test items. For example, on the first test item, if shot 4 is taken at 30°, then shot 5 shall be taken at 45°; then, on test item 2, shot 4 shall be taken at 45°, and shot 5 shall be taken at 30°. This shall continue until the test series is complete.

(2) For test items with no seams or discontinuities, the direction of the angles shall be alternated between sets of shots 4 and 5. For example, on the first test item, if the backing assembly is rotated clockwise for shots 4 and 5, then on test item 2, the backing assembly shall be rotated counter-clockwise. This rotation sequence shall continue until the test series is complete.

(3) For test items with seams or discontinuities (for example, nonplanar), the direction of the angles shall be specified in other standards or specifications.

11.2.7 Shot 7 shall be taken on test items representing front panels that have a neck scoop and shall be taken on the same test items used for shots 4, 5, and 6.

11.2.7.1 For planar test items, shot 7 shall be placed such that the shot impacts towards the test item edge at a 45° angle of incidence (which may be achieved by rotating the panel 90° on surface of the clay block and then rotating the clay block 45° about its vertical axis).

11.2.7.2 For nonplanar test items, shot 7 shall be placed at the center of the neck scoop such that the shot impacts towards the edge at a 45° angle of incidence.

NOTE 10—It is expected that the nonplanar armor applique will have approximately a 15° angle with respect to the surface of the clay block. Using a 30° angle of obliquity results in a shot taken at approximately 45° angle of incidence.

11.3 The steps below shall be followed for each test series:

11.3.1 Mount and position the test item on the clay block as specified in Section 10 of this test method.


11.3.2 Fire the test threat at the test item.

11.3.3 Verify that the shot was a fair hit (per Section 9 of this test method), taking the following steps:


11.3.3.1 The velocity shall be checked to determine whether it was within the specified range.

11.3.3.2 The difference between the velocity readings from each independent instrument shall be compared as specified in Specification E3062/E3062M.


11.3.3.3 The shot spacing shall be assessed to determine if shot-to-edge, shot-to-shot, and shot-to-clay block edge were within specified requirements.

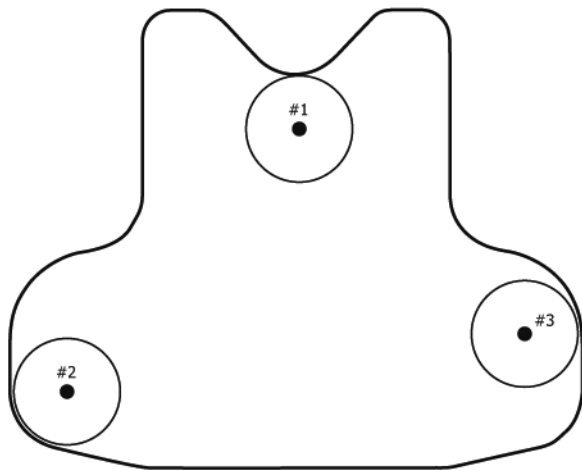

2a. Small Test Item with Shots 1, 2, and 3

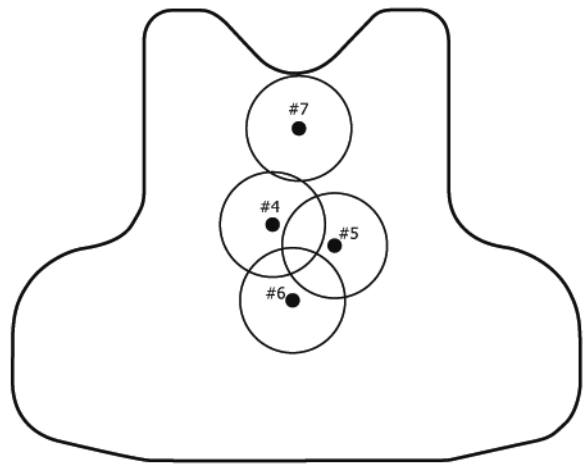

2b. Small Test Item with Shots 4, 5, 6, and 7

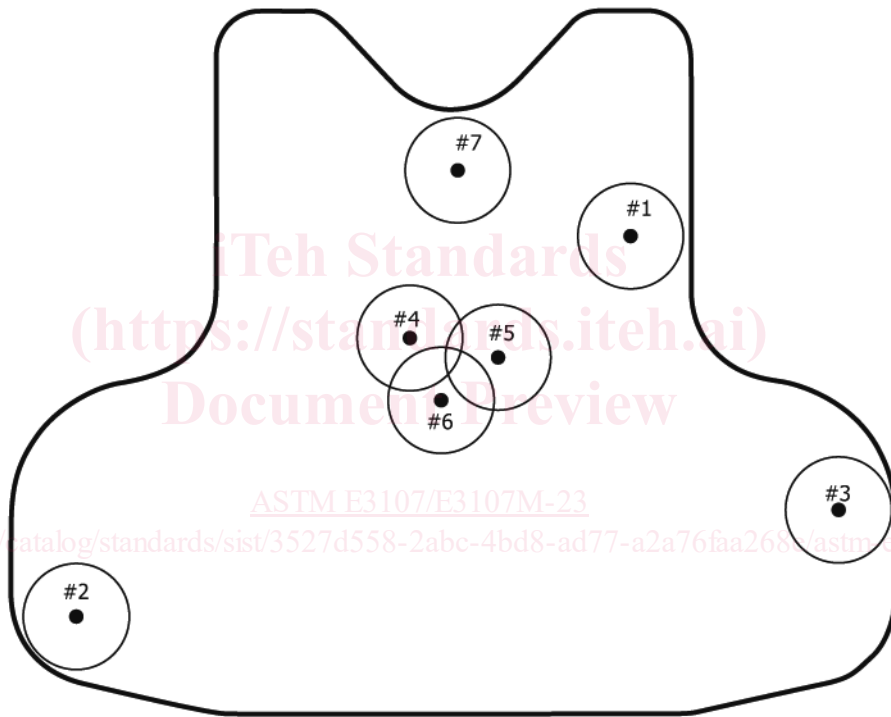

2c. Larger Test Item with All Shots

FIG. 2 Example of Soft Armor Test Item Shot Position and Pattern

11.3.3.4 When not specified elsewhere, if the shot is determined to be unfair, another shot shall be taken on that test item in a location that meets shot spacing requirements. If there is not sufficient room on the test item for another shot, all required shots shall be repeated on a spare test item. The spare test item shall be of the same size, if available.

11.3.4 Determine whether the shot outcome is a partial or complete penetration.

11.3.5 When required, measure the BFD for partial penetrations.

11.3.6 Reposition and smooth the test item as specified in Section 10 of this test method.

11.3.7 Repeat relevant steps until all required shots on the test item are complete.

11.3.8 Repeat relevant steps until the test series is complete.

12. Mounting and Positioning of Hard Armor Test Items on a Clay Block

12.1 The test item shall be positioned on a clay block such that the entire test item is supported.

12.2 The testing of nonplanar hard armor test items requires the use of appliques between the test item and the clay block.

NOTE 11—Testing of planar hard armor test items does not require the use of appliques. The applique details of this section may also apply for nonplanar soft armor that requires the use of appliques between the test item and the clay block.

12.3 A clay applique shall be created for each individual test item and shall meet the following requirements: