



Designation: **D5457–21a** D5457 – 23

# Standard Specification for Computing Reference Resistance of Wood-Based Materials and Structural Connections for Load and Resistance Factor Design<sup>1</sup>

This standard is issued under the fixed designation D5457; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reappraisal.

## INTRODUCTION

Load and resistance factor design (LRFD) is a structural design method that uses concepts from reliability theory and incorporates them into a procedure usable by the design community. The basic design equation requires establishing a reference resistance based on several material property parameters. A standard method for calculating the required material property input data is critical so that all wood-based structural materials can be treated equitably. This specification provides the procedures that are format conversion procedure that is required for the generation of reference resistance for LRFD. A non-mandatory appendix of this specification provides broad guidance for users who wish to pursue the test-based approach for the generation of reference resistance for LRFD.

## 1. Scope

1.1 This specification covers procedures the format conversion procedure for computing the reference resistance of wood-based materials and structural connections for use in load and resistance factor design (LRFD). The format conversion procedure is outlined in Section 4. The test-based derivation procedure is outlined in Annex A1. The reference resistance derived from this specification applies to the design of structures addressed by the load combinations in ASCE 7-16.

1.2 A commentary to this specification is provided in [Appendix X1](#).

1.3 Guidance for users considering test-based derivation of reference resistance is provided in [Appendix X2](#).

1.4 The values stated in inch-pound units are to be regarded as the standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

<sup>1</sup> This specification is under the jurisdiction of ASTM Committee D07 on Wood and is the direct responsibility of Subcommittee D07.02 on Lumber and Engineered Wood Products.

Current edition approved May 1, 2021; May 1, 2023. Published May 2021; June 2023. Originally approved in 1993. Last previous edition approved in 2021 as D5457–21; D5457 – 21a. DOI: 10.1520/D5457-21A; 10.1520/D5457-23.

## 2. Referenced Documents

### 2.1 ASTM Standards:<sup>2</sup>

- D9 Terminology Relating to Wood and Wood-Based Products
- D143 Test Methods for Small Clear Specimens of Timber
- D198 Test Methods of Static Tests of Lumber in Structural Sizes
- D1037 Test Methods for Evaluating Properties of Wood-Base Fiber and Particle Panel Materials
- D1761 Test Methods for Mechanical Fasteners in Wood and Wood-Based Materials
- D1990 Practice for Establishing Allowable Properties for Visually-Graded Dimension Lumber from In-Grade Tests of Full-Size Specimens
- D2718 Test Methods for Structural Panels in Planar Shear (Rolling Shear)
- D2719 Test Methods for Wood Structural Panels in Shear Through-the-Thickness
- D2915 Practice for Sampling and Data-Analysis for Structural Wood and Wood-Based Products
- D3043 Test Methods for Structural Panels in Flexure
- D3500 Test Methods for Wood Structural Panels in Tension
- D3501 Test Methods for Wood-Based Structural Panels in Compression
- D3737 Practice for Establishing Allowable Properties for Structural Glued Laminated Timber (Glulam)
- D4761 Test Methods for Mechanical Properties of Lumber and Wood-Based Structural Materials
- D5055 Specification for Establishing and Monitoring Structural Capacities of Prefabricated Wood I-Joists
- D5456 Specification for Evaluation of Structural Composite Lumber Products
- E105 Guide for Probability Sampling of Materials

### 2.2 ASCE Standard:<sup>3</sup>

- ASCE 7-16 Minimum Design Loads and Associated Criteria for Buildings and Other Structures

## 3. Terminology

### 3.1 Definitions:

3.1.1 For general definitions of terms related to wood, refer to Terminology D9.

### 3.2 Definitions of Terms Specific to This Standard:

3.2.1 *ASD reference design value,  $F_x$* —the design value at reference conditions used in allowable stress design (ASD) prior to application of the load duration factor ( $C_D$ ).

3.2.2 *coefficient of variation,  $CV_w$* —the standard deviation divided by the mean of a 2-parameter Weibull distribution.

#### 3.2.2.1 Discussion—

Coefficient of variation,  $CV_w$ , can be calculated three ways: the traditional method of moments; method of maximum likelihood; and method of least squares. The method of moments calculates the mean and standard deviation directly from the data of a complete data set. The methods of maximum likelihood and least squares calculate the Weibull parameters from complete or incomplete data sets. An incomplete data set includes suspended data (for example, data from proof loading.) Mean and standard deviation (and  $CV_w$ ) are then calculated from the Weibull parameters.

3.2.3 *data confidence factor,  $\Omega$* —a factor that is used to adjust member reference resistance for sample variability and sample size.

3.2.4 *distribution percentile,  $R_p$* —the value of the distribution associated with proportion,  $p$ , of the cumulative distribution function.

3.2.3 *factored resistance*—the product of the resistance factor ( $\phi$ ) and the reference or nominal resistance ( $R_n$ ).

3.2.4 *format conversion factor,  $K_F$* —a factor applied to convert resistance from the allowable stress design (ASD) format to the LRFD format, equal to the ratio  $R_n/F_x$ .

3.2.5 *lower tail*—a portion of an ordered data set consisting of all test specimens with the lowest property values (for example, lowest strengths).

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> Available from The American Society of Civil Engineers (ASCE), 1801 Alexander Bell Dr., Reston, VA 20191.

3.2.6 *nominal resistance*—a term equivalent to the reference resistance used in reliability analysis and LRFD standards.

3.2.7 *reference conditions*—the design basis for which all applicable adjustment factors are equal to unity, except for the load duration factor in ASD or the time effect factor in LRFD.

3.2.8 *reference resistance,  $R_n$* —the design value at reference conditions used in LRFD to represent member resistance prior to application of the resistance factor ( $\phi$ ) and the time effect factor ( $\lambda$ ).

3.2.8.1 *Discussion*—

The reference value represents member resistance at 10-minute load duration.

3.2.9 *reliability normalization factor,  $K_R$* —a factor used to establish the reference resistance ( $R_n$ ) to achieve a target reliability index for a specific set of conditions.

3.2.10 *resistance factor,  $\phi$* —a factor applied to the resistance side of the LRFD equation.

#### 4. Reference Resistance for LRFD

4.1 Reference resistance for LRFD shall be determined using ~~one of the following procedures:~~ the format conversion procedure per 4.2.

NOTE 1—Appendix X2 discusses considerations that should be addressed by users considering test-based approaches for the generation of reference resistance for LRFD. Appendix X5 provides discussion of alternative methods to determine reference resistance for LRFD.

4.1.1 Format conversion per Section 4.2; or

4.1.2 Test-based derivation per Annex A1.

#### 4.2 Format Conversion Procedure:

4.2.1 Resistance values for LRFD ~~are permitted to shall~~ be based on format conversion from code-recognized allowable stress design (ASD). It shall not be claimed that reference resistance values generated in this manner achieve a stated reliability index. Resistance factors for determining LRFD factored resistance,  $\phi R_n$ , are given in Table 1.

NOTE 2—Examples of standards that are used to generate code-recognized ASD values include Test Methods D143, D198, D1037, D1761, D2718, D2719, D3043, D3500, D3501, and D4761; Practices D1990 and D3737; and Specifications D5055 and D5456.

4.2.2 For standardization purposes, format conversion reference resistance values shall be based on the arithmetic conversion for a specific design case that results from the calibration of basic ASD and LRFD equations. Here, the calibration means providing an identical required section modulus, cross-sectional area, allowable load capacity, and so forth. The specific design case was chosen such that changes in design capacity over the range of expected load cases and load ratios were minimized.

4.2.3 Values of the format conversion factor,  $K_F$ , are given in Table 2.

4.2.4 The format conversion reference resistance is computed by multiplying the ASD resistance by  $K_F$ . For members and

**TABLE 1 Specified LRFD Resistance Factors,  $\phi_s$**

Application	Property	$\phi_s$
Members	compression <sup>A</sup>	0.90
	bending, lateral buckling (stability)	0.85
	tension parallel	0.80
	shear, radial tension	0.75
Connections	all	0.65
Shear Walls, diaphragms	shear (wind)	0.80
	shear (seismic)	0.50

<sup>A</sup> Compression parallel-to-grain, compression perpendicular-to-grain, and bearing.

**TABLE 2 Format Conversion Factor,  $K_F$** 

Property	$K_F$
Compression Parallel to Grain	2.40
Bending	2.54
Tension Parallel to Grain	2.70
Shear	2.88 <sup>A</sup>
Radial Tension	2.88
Connections	3.32
Lateral Buckling (Stability)	1.76
Compression Perpendicular to Grain	1.67
Shear Wall and Diaphragm Shear (wind)	2.00 <sup>B</sup>
Shear Wall and Diaphragm Shear (seismic)	2.80 <sup>B</sup>

<sup>A</sup> The value of the format conversion factor is 2.00 where shear is not subject to load duration or time effect adjustments (e.g., for example, rolling shear in cross-laminated timber).

<sup>B</sup> The format conversion factor for shear wall and diaphragm shear is only intended to be applied to the design capacity of shear wall or diaphragm assemblies, not to the design of individual members or subcomponents of these assemblies.

connections, the ASD resistance is based on a normal (10-year) load duration. For shear walls and diaphragms, the ASD resistance is based on a ~~10-minute~~ 10-min load duration.

4.2.5 For lateral buckling (stability), compression perpendicular to grain, and rolling shear that is not subject to load duration or time effect adjustments, the value of  $K_F$  is based on the assumption that neither the ASD nor LRFD resistance values are modified by duration of load or time effect adjustments.

4.2.6 *Format Conversion Example*—An ASD bolt design value for a single shear connection,  $F_x$ , is 800 lbf (3.56 kN) (based on normal 10-year load duration). From **Table 2**, the format conversion factor,  $K_F$ , is 3.32. The corresponding LRFD bolt reference resistance value is as follows:

$$R_n = (K_F)(F_x) = (3.32)(800) = 2658 \text{ lbf}(11.82 \text{ kN}) \quad (1)$$

4.2.7 *Format Conversion Example for Shear Walls and Diaphragms*—An ASD shear wall design value,  $F_x$ , is 350 lb/ft (5.11 kN/m) for seismic design, and 490 lb/ft (7.15 kN/m) for wind design. From **Table 2**, the format conversion factor,  $K_F$ , is 2.8 for seismic design and 2.0 for wind design. The corresponding LRFD shear wall reference resistance values for seismic and wind are as follows:

For seismic:

$$R_n = (K_F)(F_x) = (2.8)(350) = 980 \text{ lb/ft}(14.30 \text{ kN/m}) \quad (2)$$

For wind:

$$R_n = (K_F)(F_x) = (2.0)(490) = 980 \text{ lb/ft}(14.30 \text{ kN/m}) \quad (3)$$

## 5. Keywords

5.1 format conversion; load and resistance factor design (LRFD); reference resistance; structural connections; test-based derivation; wood-based materials

**ANNEX**
**(Mandatory Information)**
**A1. TEST-BASED DERIVATION OF REFERENCE RESISTANCE FOR LRFD**

A1.1 Parameters required for the derivation of reference resistance are presented in this Annex. These parameters include the distribution percentile,  $R_p$ , coefficient of variation,  $CV_w$ , data confidence factor,  $\Omega$ , and reliability normalization factor,  $K_R$ . An example derivation of reference resistance is provided in **X1.8.5**.

**A1.2 Sampling:**

A1.2.1 Samples selected for analysis and implementation with this specification shall be representative of the population about which inferences are to be made. Both manufacturing and material source variability shall be considered. The principles of Practice **E105** shall be maintained. Practice **D2915** provides methods for establishing a sampling plan. Special attention is directed to sampling procedures in which the variability is low and results can be influenced significantly by manufacturing variables. It is essential that the sampling plan addresses the relative magnitude of the sources of variability.

A1.2.1.1 Data generated from a quality control program shall be acceptable if the criteria of **A1.2.1** are maintained.

A1.2.1.2 *Multiple Data Sets*—When data from multiple data sets are compiled or grouped, the criteria used to group such data shall be in accordance with the provisions of **A1.2.1**. When such procedures are available in applicable product standards, they shall be used.

**A1.2.2 Sample Size:**

A1.2.2.1 For data sets in which all specimens are tested to failure, the minimum sample size shall be 30.

**NOTE A1.1**—The confidence with which population properties can be estimated decreases with decreasing sample size. For sample sizes less than 60, extreme care must be taken during sampling to ensure a representative sample.

A1.2.2.2 For lower tail data sets, a minimum of 60 failed observations is required for sample sizes of  $n = 600$  or less. This represents at least the lower 10 % of the distribution. For sample sizes greater than 600, a minimum of the lowest 10 % of the distribution is required. For example, sample size,  $n = 720$ ,  $0.10 (720) = 72$  failed test specimens in the lower tail. Only parameter estimation procedures designed specifically for lower tail data sets shall be used (see **Appendix X2**).

**A1.3 Testing:**

A1.3.1 Testing shall be conducted in accordance with appropriate standard testing procedures. The intent of the testing shall be to develop data that represent the capacity of the product under standard conditions.

A1.3.2 *Periodic Property Assessment*—Periodic testing is recommended to verify that the properties of production material remain representative of published properties.

**A1.4 Reference Resistance,  $R_n$** —The following equation establishes reference resistance for LRFD:

$$R_n = (R_p)(\Omega)(K_R) \quad (\text{A1.1})$$

where:

- $R_p$  = distribution percentile estimate,
- $\Omega$  = data confidence factor, and
- $K_R$  = reliability normalization factor.

**A1.4.1 Distribution Percentile Estimate,  $R_p$** :

**A1.4.2 Eq A1.2** is intended to be used to calculate any percentile of a two-parameter Weibull distribution. The percentile of interest depends on the property being estimated:

$$R_p = \eta[-\ln(1-p)]^{1/\alpha} \quad (\text{A1.2})$$

where:

- $\eta$  = Weibull scale parameter,
- $p$  = percentile of interest expressed as a decimal (for example, 0.05), and
- $\alpha$  = Weibull shape parameter.

**A1.4.3** The shape ( $\alpha$ ) and scale ( $\eta$ ) parameters of the two-parameter Weibull distribution shall be established to define the distribution of the material resistance **(1)**.<sup>4</sup> Algorithms for common estimation procedures are provided in **Appendix X2**.

**A1.4.4 Coefficient of Variation,  $CV_w$** —The coefficient of variation of the material is necessary when determining the data confidence factor,  $\Omega$ , and the reliability normalization factor,  $K_R$ . The  $CV_w$  can be estimated from the shape parameter of the Weibull distribution as follows:

$$CV_w \cong \alpha^{-0.97} \quad (\text{A1.3})$$

**NOTE A1.2**—The above approximation is within 1 % of the exact solution for  $CV_w$  values between 0.09 and 0.50. An exact relationship of  $CV_w$  and  $\alpha$  is shown in **Appendix X3**.

**A1.5 Data Confidence Factor,  $\Omega$** —The data confidence factor accounts for uncertainty associated with data sets **(2)**. This factor, which is a function of coefficient of variation, sample size, and specified percentile, is applied as a multiplier on the distribution estimate. **Table A1.1** provides data confidence factors appropriate for lower fifth-percentile estimates.

**NOTE A1.3**—When a distribution tolerance limit is developed on a basis consistent with  $\Omega$ , the data confidence factor is taken as unity.

**A1.6 Reliability Normalization Factor,  $K_R$** —The reliability normalization factor,  $K_R$ , which is a function of  $CV_w$  and is generated for specific target reliability indices, is used to adjust the distribution estimate (for example,  $R_{0.05}$ ) to achieve a target reliability index. The reliability normalization factor is the ratio of the computed resistance factor,  $\phi_c$  (**X1.8.5**), to the specified resistance factor,  $\phi_s$  (**Table 1**), adjusted by a scaling factor, which is a function of  $CV_w$  and is generated for specific target reliability indices.

<sup>4</sup> The boldface numbers in parentheses refer to a list of references at the end of this standard.

The  $K_R$  values presented in [Table A1.2](#) were computed at a live-to-dead load ratio of 3. Computations (FORTRAN code listings reflecting 1980's methodologies) for determining reliability indices are contained in Refs (3) and (4). Calculations to derive input parameters for reliability analyses are outlined in Ref (5).

#### *A1.7 Presentation of Results:*

A1.7.1 Report the sampling plan and testing in accordance with applicable standards. When lower tail data sets are used, report the sample size and data used in the calculations. Report the estimated shape and scale parameters along with the calculated coefficient of variation. When appropriate, also report the mean and standard deviation (derived from the calculated coefficient of variation). Include a plot showing the data points and fitted Weibull distribution. In addition to these basic parameters, also report the data confidence factor,  $\Omega$ , calculated percentile estimate,  $R_p$ , reliability normalization factor,  $K_R$ , and reference resistance,  $R_m$ .

## APPENDIXES

### (Nonmandatory Information)

#### X1. COMMENTARY TO THE TEXT

##### X1.1 *Commentary to the Introduction:*

X1.1.1 Load and resistance factor design (LRFD) is a design format. LRFD is a subset of a broader design methodology known as reliability-based design (RBD). The distinction between the two design procedures is significant. RBD implies, and often calculates, quantities related to the reliability of a member under a given set of conditions. A higher reliability corresponds to a lower probability of failure. One practical concern that arises when one attempts to apply RBD to real structural applications is that the calculations must idealize both the loads and the structural system response to reduce it to a mathematically tractable problem. This idealization process reduces the final calculation to a theoretically interesting, but often inapplicable, number. LRFD was developed by selecting a few of the basic concepts of RBD and using them to develop a format that is similar in many ways to current (allowable stress) design. LRFD provides incremental improvements in the design process in this way. The improvements provided by LRFD include the following: allowable stress design.

X1.1.1.1 Consideration of the variability of various types of loads when assessing safety factors.

X1.1.1.2 Consideration of the consequences of various potential failure modes in a structure.

X1.1.1.3 Material resistance values that relate more closely to test data (member capacities).

X1.1.1.4 Consideration of resistance variability.

X1.1.2 Previous standards for developing allowable properties for many types of wood-based products directed the user to various ways of computing a population lower fifth-percentile estimate. This single number was the basis for an allowable strength property assignment. At the other extreme, a realistic RBD would require an accurate definition of a large portion of the lower tail of the material distribution and a large portion of the upper tail of the load distribution. LRFD requires somewhat more information than current procedures (for example, reference values and variability) but substantially less than RBD. In the most advanced LRFD procedures in use today, procedures, one needs only a distribution type and the parameters that describe that distribution. Refinements of these procedures suggest that estimates of the distribution and its parameters give the most accurate reliability



estimates when they represent a tail portion of the distribution rather than the full distribution. This reflects the fact that, for common building applications, only the lower tail of the resistance and upper tail of the load distribution contribute to failure probabilities.

X1.1.3 Simulations have shown that the assumed distribution type can have a strong effect on computed LRFD resistance factors. However, much of this difference is due to the inability of standard distribution forms to fit the tail data precisely. By standardizing the distribution type, this procedure provides a consistent means for deriving these factors. In addition, by permitting tail fitting of the data, it provides a way of fitting data in this important region that is superior to full-distribution types.

X1.1.4 While the two-parameter Weibull distribution is the underlying basis for these calculations, the user of this specification is not burdened with applying statistical decisions. For LRFD purposes, the user must calculate the shape and scale parameters for the fitted Weibull distribution using the equations in the specification. All remaining steps in the calculations of a reference resistance are spelled out in the equations of the specification.

X1.2 *Commentary to Section 1, Scope*—The calculation procedures identified Format conversion per 4.2 in this specification are common statistical procedures. This specification gives the user a document for all calculations necessary to develop LRFD reference resistances. Format conversion per Section is the standard method for determination of reference resistance for LRFD. The 4.2 and test-based derivation approach per Annex A1 Appendix X2 represent two separate approaches for determination provides broad guidance for users who wish to pursue the test-based approach for the generation of reference resistance for LRFD. Due to the sensitivity of reliability to changes in some of the parameters, these procedures offer a limited set of options to ensure that LRFD reference resistances are generated in a consistent manner. Other methods for computing reference resistance that are beyond the scope of this standard are discussed in Appendix X4X5.

X1.3 *Commentary to Section 3, Terminology:*

X1.3.1 Numerical simulations show that, for complete data sets from an underlying 2-parameter Weibull distribution, all three methods: method of moments; method of maximum likelihood; and, method of least squares; will estimate mean, standard deviation, and coefficient of variation with little difference. Reliability analyses benefit from fitting the distribution parameters to a lower tail subset of the data:

X1.3.1 The term “factored resistance” is specifically defined as the product of the resistance factor ( $\phi$ ) and the nominal resistance ( $R_n$ ) to differentiate it from the nominal (reference) resistance. Users are cautioned to include all applicable adjustment factors when determining the LRFD adjusted design value.

X1.3.2 The term “nominal resistance” is the most widely used term in reliability analysis and material specifications. As described in Ref (61),<sup>4</sup> users are cautioned that the term “nominal” has been defined in various ways over the years. This standard focuses on the term “reference resistance,” used in the NDS.

X1.3.3 The term “reference conditions” is added to clarify that the design checking equations presented in this specification do not include notations for the myriad of potential end-use adjustment factors that might be applicable to specific designs. The rationale is that all end-use adjustment factors, with the notable exceptions of the load duration factor in ASD and the time effect factors in LRFD, are identical in both design formats and will mathematically cancel in the calculation of the ratio  $R_n / F_x$ . Users are cautioned to include all applicable adjustment factors when determining the LRFD adjusted design value.

X1.3.4 The term “reference resistance” is retained as the primary terminology in this version of the standard for continued



compatibility with the NDS (72) and other design documents, but its definition is clarified to indicate that it does not include the resistance factor ( $\phi$ ), the time-effect factor ( $\lambda$ ) and other adjustments for end-use conditions that will be subsequently applied in the design checking equation.

X1.3.5 As discussed in Ref (83), an underlying assumption in virtually all reliability analyses is that every adjustment factor applied in the design checking equation applies equally across the entire resistance population. From an analysis standpoint, this results in identical reliability indices for the reference and adjusted design cases.

X1.3.6 Ref (83) also describes the difficulty of applying the same judgment to the time effect factor ( $\lambda$ ). The time effect factor is different from other design adjustment factors in two respects. First, it represents an interaction between the load side and the resistance side of the design equation. This fact leads to a dilemma regarding the format of the design checking equation: should the time effect factor be expressed separately (that is,  $\lambda\phi_s R_n$ ) or embedded into the adjusted resistance like other adjustment factors? Second, test specimens at the lower tail of the strength distribution exhibit shorter times to failure under constant load than those higher in the distribution, while most of those at the upper end don't fail at all, because they are effectively loaded at a lower stress ratio.

X1.4 *Commentary to Section 4.2, Format Conversion*—Format conversion is the method used to develop format conversion factors to adjust reference ASD design values (based on normal 10-year load duration) to LRFD reference resistances (based on 10-minute load duration). Format conversion factors in Table 2 are developed to provide similar member and connection sizes when considering specific ASD and LRFD load cases and specified values of the resistance factor,  $\phi$ , for LRFD as provided in Table 1.

X1.5 *Commentary to Table 2, Format Conversion Factor,  $K_F$ , for Compression Parallel to Grain, Bending, Tension Parallel to Grain, Shear, Radial Tension and Connections:*

X1.5.1 The format conversion factors for compression parallel to grain, bending, tension parallel to grain, shear, radial tension and connections that are subject to load duration or time effect adjustments, can be obtained from Eq X1.2.

X1.5.2 The factor of 2.16 is the algebraic solution at the calibration point, the ratio of  $R_n / F_x$  for  $S/D = 3$ ,  $\lambda = 0.80$ , and  $C_D = 1.15$ .

$$\text{LRFD: } \lambda\phi R_n \geq 1.2D + 1.6(L \text{ or } S) \quad (\text{X1.1})$$

$$\text{ASD: } C_D F_x \geq D + (L \text{ or } S) \quad (\text{X1.2})$$

where:

- $\lambda$  = time effect factor (LRFD),
- $\phi$  = specified resistance factor (LRFD),
- $R_n$  = reference resistance value (LRFD),
- $D, L, S$  = dead, live, and snow load effects, respectively,
- $C_D$  = load duration factor (ASD), and
- $F_x$  = ASD design value (ASD).

Substituting and solving for  $K_F$  ( $= R_n/F_x$ ):

$$K_F = 2.16/\phi_s \quad (\text{X1.3})$$

X1.5.3 Use of a single constant for the format conversion factor,  $K_F$ , is appropriate, based on the judgment of the committee, over a broad range of design cases. As shown in Fig. X1.1, this judgment produces exact calibration between ASD and LRFD for one specific design case ( $S/D = 3$ ,  $C_D = 1.15$ ,  $\lambda = 0.8$ ). Differences between ASD and LRFD designs will result for other design cases. The algebraic format conversion solution for the precise constant in the numerator of Eq X1.3 is not to be confused as the RBD

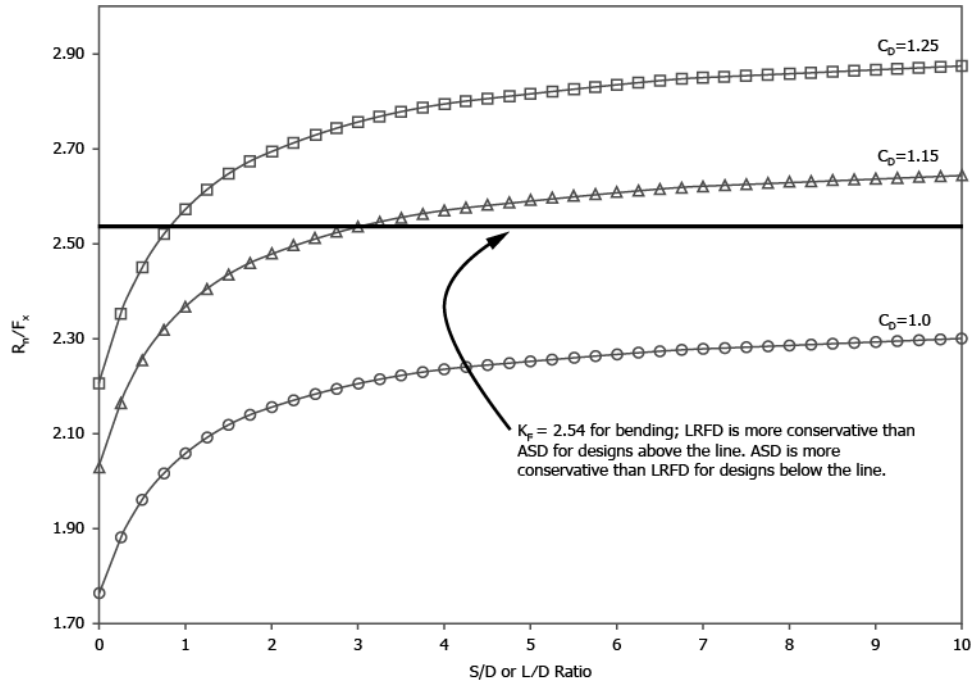


FIG. X1.1  $R_n/F_x$  Producing Exact Calibration Between ASD and LRFD for Bending ( $\phi_s = 0.85$ ;  $K_F = 2.16/\phi_s = 2.54$ )

basis supporting Eq X1.3 (see Commentary to Annex A1 Appendix X2). The RBD basis of the format conversion factor involved first order, second moment reliability methods to graph  $R_n/F_x$  across a range of load ratios for three distinct live-load cases (occupancy floor, snow roof, and non-snow roof), where  $R_n$  and  $F_x$  come directly from the LRFD and ASD design equations. The factor in the numerator of Eq X1.3 is in the range from 2.1 to 2.2 and resulted from the application of engineering judgment as a balance of increases for floors at low L/D ratios versus decreases for non-snow roofs at higher L/D ratios.

X1.6 Commentary to Table 2, Format Conversion Factor,  $K_F$ , for Lateral Buckling (Stability), Compression Perpendicular to Grain, and Rolling Shear not subject to load duration or time effect adjustments:

X1.6.1 The format conversion factors for lateral buckling (stability), compression perpendicular to grain, and rolling shear values that are not subject to load duration or time effect adjustments, can be obtained from Eq X1.4:

$$K_F = 1.5/\phi_s \tag{X1.4}$$

X1.6.2 The  $K_F$  of  $1.5/\phi$  is the algebraic solution at the point of calibration - the ratio of  $R_n/F_x$  for  $L/D = 3$ . Terms  $\lambda$  and  $C_D$  do not appear in the design checking equations because they are not applicable for modulus of elasticity for beam and column stability ( $E_{min}$ ), compression perpendicular to grain, and rolling shear in accordance with the NDS.

$$\text{LRFD: } \phi_s R_n \geq 1.2D + 1.6(LorS) \tag{X1.5}$$

$$\text{ASD: } F_x \geq D + (LorS) \tag{X1.6}$$

Substituting and solving for  $K_F$  ( $= R_n/F_x$ ):

$$K_F = 1.5/\phi_s$$

X1.6.3 Format Conversion for Lateral Buckling (Stability)—The format conversion factor of 1.76 for stability is applied to  $E_{min}$  which is the modulus of elasticity used in ASD for beam stability and column stability calculations (not to the average modulus of elasticity,  $E$ , used for deflection calculations). Using the format conversion factor of 1.76,  $E_{min}$  for LRFD can be calculated from  $E_{05}$  as follows:

For ASD:  $E_{min} = E_{05}/1.66$  (X1.7)

where:

$E_{05}$  = fifth percentile shear-free  $E$  value, and  
 1.66 = safety factor for beam and column stability calculations.

For LRFD: Multiply by  $K_F = 1.5/\phi_s$  (X1.8)

$$E_{min} = (E_{05}/1.66)(1.76)$$

$$= (1.06)(E_{05})$$

X1.6.4 Equations for  $K_{bE}$  and  $K_{cE}$  contained in the 2001 NDS beam and column stability provisions adjust tabulated average modulus of elasticity,  $E$ , values to fifth percentile shear-free  $E$  values divided by a 1.66 safety factor. In the 2005 NDS,  $K_{bE}$  and  $K_{cE}$  equations were replaced with a reference to tabulated  $E_{min}$  values (fifth percentile shear-free  $E$  values divided by a 1.66 safety factor) to simplify design equations for beam and column stability and to enable use of the same equations for both ASD and LRFD.

X1.6.4.1  $E_{min}$  values tabulated in the NDS Design Value Supplement for sawn lumber are estimated in accordance with Eq X1.9 where for sawn lumber  $E_{05} = 1.03E(1-1.645(COV_E))$ :

$$E_{min} = \frac{1.03E(1-1.645(COV_E))}{1.66}$$
 (X1.9)

X1.6.5 *Format Conversion for ASD Deformation-Based Compression Perpendicular to Grain Values*—Wood compression perpendicular to grain stresses are based on serviceability criteria from testing of small specimens (Test Methods D143, square cross-section block, 2 in. loading block). However, in many cases, these allowable stresses are being applied more broadly. In some compression perpendicular to grain applications, especially where laterally unsupported tall/narrow sections are used, failure modes, such as instability or splitting, can occur. These failure modes have been demonstrated in short-term tests to occur at compression perpendicular to grain stress levels as low as 1.5 times the ASD value for compression perpendicular to grain. Designers must be certain to check the failure modes of buckling or splitting that may now control the design. Alternatively, the designer may choose to brace the tall/narrow member at the bearing to prevent this mode from occurring.

X1.6.6 One method to compute buckling capacity in the perpendicular to grain direction for ASD may be done by using an elastic-buckling (Euler) type formula similar to that now used for visually graded lumber. This calculation could supplement the standard ASD compression perpendicular to grain calculation. In the calculation, the relevant modulus of elasticity is the transverse modulus (often assumed to be  $E/20$ ) and the relevant dimensions (relative to buckling direction) would also be substituted.

X1.7 *Commentary to Table 2, Format Conversion Factor,  $K_F$ , for Shear Walls and Diaphragms:*

X1.7.1 The format conversion factor,  $K_F = 2.0$  for wind and  $K_F = 2.8$  for seismic, for shear walls and diaphragms has been derived as the algebraic solution (with rounding) at specific points of calibration. The ratio of  $R_r/F_x$  for  $\phi_s = 0.80$  for wind design, and the ratio of  $R_r/F_x$  for  $\phi_s = 0.50$  for seismic design, and where  $F_x$  is determined in accordance with SDPWS in Ref (94). Terms  $\lambda$  and  $C_D$  do not appear in the design checking equations because design values for wind and seismic load cases in accordance with SDPWS Ref (94) are tabulated based on a ~~10-minute~~ 10-min load duration and require no further designer adjustment for short duration wind or seismic loading.

X1.7.2 Design equations for wind load effects based on wind load factors from ASCE 7–16 are as follows:

LRFD:  $\phi_s R_r \geq 1.0 W$  (X1.10)