



Designation: E2603 – 15 (Reapproved 2023)

Standard Practice for Calibration of Fixed-Cell Differential Scanning Calorimeters¹

This standard is issued under the fixed designation E2603; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This practice covers the calibration of fixed-cell differential scanning calorimeters over the temperature range from $-10\text{ }^{\circ}\text{C}$ to $+120\text{ }^{\circ}\text{C}$.

1.2 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.* Specific precautionary statements are given in Section 7.

1.4 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 *ASTM Standards:*²

[E473 Terminology Relating to Thermal Analysis and Rheology](#)

[E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method](#)

[E967 Test Method for Temperature Calibration of Differential Scanning Calorimeters and Differential Thermal Analyzers](#)

[E968 Practice for Heat Flow Calibration of Differential Scanning Calorimeters \(Withdrawn 2023\)](#)³

[E1142 Terminology Relating to Thermophysical Properties](#)

¹ This practice is under the jurisdiction of ASTM Committee E37 on Thermal Measurements and is the direct responsibility of Subcommittee E37.09 on Microcalorimetry.

Current edition approved Aug. 1, 2023. Published August 2023. Originally approved in 2008. Last previous edition approved in 2015 as E2603 – 15. DOI: 10.1520/E2603-15R23.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ The last approved version of this historical standard is referenced on www.astm.org.

3. Terminology

3.1 Specific technical terms used in this practice are defined in Terminologies [E473](#) and [E1142](#), including *differential scanning calorimeter*, *enthalpy*, *Kelvin*, and *transformation temperature*.

4. Summary of Practice

4.1 This practice covers calibration of fixed-cell differential scanning calorimeters. These calorimeters differ from another category of differential scanning calorimeter in that the former have generally larger sample volumes, slower maximum temperature scan rate capabilities, provision for electrical calibration of heat flow, and a smaller range of temperature over which they operate. The larger sample cells, and their lack of disposability, make inapplicable the calibration methods of Practices [E967](#) and [E968](#).

4.2 This practice consists of heating the calibration materials in aqueous solution at a controlled rate through a region of known thermal transition. The difference in heat flow between the calibration material and a reference material, both relative to a heat reservoir, is monitored and continuously recorded. A transition is marked by the absorption or release of energy by the specimen resulting in a corresponding peak in the resulting curve.

4.3 The fixed-cell calorimeters typically, if not always, have electrical heating facilities for calibration of the heat-flow axis. Despite the use of resistance heating for calibration, a chemical calibration serves to verify the correct operation of the calibration mechanism and the calorimeter. The thermal denaturation of chicken egg white lysozyme is used in this practice for verification of the proper functioning of the instrument's systems. The accuracy with which the denaturation enthalpy of chicken egg white lysozyme is currently known, $\pm 5\%$, is such that it should be rare that a calorimeter provides a value outside that established in the literature for this reference material.

5. Significance and Use

5.1 Fixed-cell differential scanning calorimeters are used to determine the transition temperatures and energetics of materials in solution. For this information to be accepted with confidence in an absolute sense, temperature and heat calibration of the apparatus or comparison of the resulting data to that of known standard materials is required.

5.2 This practice is useful in calibrating the temperature and heat flow axes of fixed-cell differential scanning calorimeters.

6. Apparatus

6.1 Apparatus shall be:

6.1.1 *Differential Scanning Calorimeter (DSC)*, capable of heating a test specimen and a reference material at a controlled rate and of automatically recording the differential heat flow between the sample and the reference material to the required sensitivity and precision.

6.1.2 *DSC Test Chamber*, composed of:

6.1.2.1 A device(s) to provide uniform controlled heating or cooling of a specimen and reference to a constant temperature or at a constant rate within the applicable temperature range of this method.

6.1.2.2 A temperature sensor to provide an indication of the specimen temperature to ± 0.01 K.

6.1.2.3 Differential sensors to detect a heat flow (power) difference between the specimen and reference with a sensitivity of ± 0.1 μ W.

6.1.3 A *Temperature Controller*, capable of executing a specific temperature program by operating the furnace(s) between selected temperature limits at a rate of temperature change of 0.01 K/min to 1 K/min constant to ± 0.001 K/min or at an isothermal temperature constant to ± 0.001 K.

6.1.4 A *Data Collection Device*, to provide a means of acquiring, storing, and displaying measured or calculated signals, or both. The minimum output signals required for DSC are heat flow, temperature, and time.

6.1.5 *Containers*, that are inert to the specimen and reference materials and that are of suitable structural shape and integrity to contain the specimen and reference in accordance with the specific requirements of this test method. These containers are not designed as consumables. They are either an integral part of the instrument, whether or not user-removable for replacement or, in some implementations, are removable and reusable. Container volumes generally range from 0.1 ml to 1 ml, depending on the instrument's manufacture.

6.2 *Analytical Balance*, capable of weighing to the nearest 0.1 mg, for preparation of solutions.

6.3 *UV spectrophotometer or UV/Vis spectrophotometer*, capable of scanning the UV spectrum in a region about 280 nm.

6.4 *Reagents*:

6.4.1 *Phosphatidylcholines*, 1,2-ditridecanoyl-*sn*-glycero-3-phosphocholine (DTPC) CAS Number 71242-28-9 and 1,2-ditetradecanoyl-*sn*-glycero-3-phosphocholine (DLPC) CAS Number 91742-11-9 are the minimum required.

6.4.2 *Aqueous buffer solutions*, 0.01 Molar, pH 7 aqueous solution of $\text{Na}_2\text{HPO}_4 - \text{NaH}_2\text{PO}_4$ and 0.1 Molar, pH (2.4 \pm 0.1) aqueous solution of HCl + glycine.

6.4.3 *Chicken egg white lysozyme*.

7. Precautions

7.1 This practice assumes linear temperature indication. Care must be taken in the application of this practice to ensure

that calibration points are taken sufficiently close together so that linear temperature indication may be approximated.

8. Calibration Materials

8.1 Phosphatidylcholines: 1,2-ditridecanoyl-*sn*-glycero-3-phosphocholine (DTPC) CAS Number 71242-28-9; and 1,2-ditetradecanoyl-*sn*-glycero-3-phosphocholine (DLPC) CAS Number 91742-11-9. Purities are to be 0.99 or better. Additional calibration materials are listed in **Table 1**.

8.1.1 Aqueous suspensions of the phosphatidylcholines are prepared as follows. Weighed amounts of a 0.01 Molar, pH 7 solution of the buffer $\text{Na}_2\text{HPO}_4 - \text{NaH}_2\text{PO}_4$ and DTPC are combined so to give a solution of 1 mass percent of the phosphatidylcholine. This procedure is repeated for DLPC. The solutions are heated in a hot water bath to 5 K above the transition temperatures. A vortex mixer is used to shake the solutions at their respective temperatures until the lipid appears to have been completely suspended. The solutions may be stored in a refrigerator until use for up to a week.

8.2 Chicken egg white lysozyme with purity of at least 95 % mass percent.

8.2.1 Weighed amounts of the lysozyme and of a 0.1 M HCl – glycine buffer at pH = (2.4 \pm 0.1) are combined to obtain a solution of approximately 3 mass percent.

8.2.2 The concentration of lysozyme in this solution is calculated from UV absorbance at a wavelength of 280 nm, using a 1 cm cell and the optical density of 2.65 for a 1 mg mL⁻¹ solution.

8.2.2.1 Fill a 1 cm optical cell with buffer solution and another 1 cm cell with the lysozyme solution. Follow the instrument's directions for establishing baseline, and if needed, calibration of the absorbance scale. Insert both of the filled cells in the UV spectrometer if the spectrometer is a dual beam instrument. Scan through the 280 nm region and note the absorbance at 280 nm. If the spectrometer is a single beam instrument, the buffer is measured first, then the lysozyme solution is measured and the difference in the recorded absorbances is used to calculate the concentration. Concentration is calculated as:

$$c = A/(2.65 \text{ mL mg}^{-1})$$

where:

A = absorbance, and

c = concentration in mg mL⁻¹.

NOTE 1—Different concentrations may be used between 1 and 10 mass percent, the concentration used shall be included in the report.

TABLE 1 Melting Temperature of Calibration Material

NOTE 1—The uncertainties for the temperatures are ± 0.1 K.

Calibration Material	Melting Temperature	
	°C	K
1,2-ditridecanoyl- <i>sn</i> -glycero-3-phosphocholine (DTPC)	13.25	286.4
1,2-ditetradecanoyl- <i>sn</i> -glycero-3-phosphocholine (DMPC)	23.75	296.9
1,2-dihexadecanoyl- <i>sn</i> -glycero-3-phosphocholine (DPPC)	41.45	314.6
1,2-dioctadecanoyl- <i>sn</i> -glycero-3-phosphocholine (DSPC)	54.85	328.0
1,2-dieicosanoyl- <i>sn</i> -glycero-3-phosphocholine (DAPC)	65.05	338.2
1,2-didocosanoyl- <i>sn</i> -glycero-3-phosphocholine (DBPC)	73.35	346.5
1,2-ditetradecanoyl- <i>sn</i> -glycero-3-phosphocholine (DLPC)	80.55	353.7

9. Procedure

9.1 Two Point Temperature Calibration:

9.1.1 Determine the apparent transition temperature for each calibration material, as described in [Table 1](#).

9.1.1.1 Fill the clean specimen cell with the phosphatidylcholine suspension, according to the usual method specified for the instrument. Fill the reference cell with buffer solution that was used to prepare the phosphatidylcholine suspension.

9.1.1.2 Equilibrate the calorimeter approximately 10 K to 15 K below the expected transition temperature from [Table 1](#).

9.1.1.3 Heat each calibration material at the desired scan rate through the transition until the baseline is reestablished above the transition. Record the resulting thermal curve.

NOTE 2—Temperature scale calibration may be affected by temperature scan rate and by the time-constant of the instrument.

9.1.2 From the resultant curve, measure the temperature for the maximum of the heat flow, T_p . See [Fig. 1](#).

9.1.3 Using the apparent transition temperatures thus obtained, calculate the slope (S) and intercept (I) of the calibration [Eq 1](#) (see [Section 10](#)). The slope and intercept values reported should be mean values from duplicate determinations based on separate specimens.

9.2 One-Point Temperature Calibration:

9.2.1 If the slope value (S) previously has been determined in [9.1](#) (using the two-point calibration calculation in [10.2](#)) to be sufficiently close to 1.0000, a one-point calibration procedure may be used.

NOTE 3—If the slope value differs by only 1 % from linearity (that is, $S < 0.9900$ or $S > 1.0100$), a 0.5 K error will be produced if the test temperature differs by 50 K from the calibration temperature.

9.2.2 Select a calibration material from [Table 1](#). The calibration temperature should be centered as close as practical within the temperature range of interest.

9.2.3 Determine the apparent transition temperatures of the calibration material using steps [9.1.1.1](#) – [9.1.1.3](#).

9.2.4 Using the apparent transition temperature thus obtained, calculate the intercept (I) of the calibration equation using all available decimal places. The value reported should be a mean value based upon duplicate determinations on separate specimens.

9.3 Enthalpy Calibration:

9.3.1 If recommended by the instrument manufacturer, perform an electrical calibration per the manufacturer's directions.

9.3.2 Determine the enthalpy of transition for the lysozyme solution.

9.3.2.1 Fill the sample cell with the lysozyme + buffer solution and fill the reference cell with the HCl-glycine buffer solution—taking care that no air bubbles are retained in either of the cells.

9.3.2.2 Equilibrate the calorimeter near room temperature, following equilibration the temperature of the calorimeter is ramped at 60 K/h until a sufficient baseline is established beyond the transition peak.

NOTE 4—Slower scan rates shall not be used in this step due to potential aggregation of the denatured protein.

9.3.2.3 The enthalpy of the denaturation is calculated by integration, using a two-state transition baseline. This enthalpy is then divided by the mass of sample in the cell. The mass of sample in the cell, m , is calculated as:

$$m = v c$$

where:

v = the volume of the measuring cell in milliliters.

NOTE 5—A two state model refers to a model that assumes the denaturation reaction proceeds from a single native state to a single denatured state. Although the denaturation reaction involves a transition between one manifold of states to another manifold of states, the two-state model adequately represents the average behavior for this protein. The heat capacity of the solution with the native state protein is often significantly different from the heat capacity of the solution with the denatured protein. A two-state transition baseline is one that employs a heat capacity calculated from the thermodynamic progression from one state to the next and the heat capacities of the aqueous solution of the two states of the protein.

9.3.2.4 A second enthalpy of denaturation is calculated using a two-state model and the van't Hoff equation, which is built into the software packages of most fixed-cell calorimeters.

NOTE 6—Using the two state model, the equations: $Q(T) = \Delta H \cdot x(T)$ $K(T) = x/(1-x)$ define the temperature dependence of the observed curve, if the enthalpy is defined by the van't Hoff relation: $d \ln K / dT = \Delta H / RT^2$. where Q is the integrated enthalpy observed, ΔH is the enthalpy change for the two-state reaction, K is the equilibrium constant for the reaction, R is the gas constant, x is the fraction of reactant converted to product and T is temperature. The model can be fitted to the curve of apparent heat capacity against temperature. Failure of the two state model occurs from precipitation reactions or other reactions that inhibit a reverse reaction in the thermodynamic equilibrium.

9.4 If practical, adjustment to the temperature scale of the instrument should be made so that temperatures are accurately indicated directly.

10. Calculation

10.1 For the purposes of this procedure, it is assumed that the relationship between observed temperature (TO) and actual specimen temperature (T) is a linear one governed by the following equation:

$$T = TO \times S + I \quad (1)$$

where:

S and I = the slope and intercept, respectively. (See [10.2](#) for the values for S and I , used in [Eq 1](#).)

NOTE 7—For some instruments, the assumption of a linear relation between observed and actual specimen temperature may not hold. Under such conditions, calibration temperatures sufficiently close together shall be used so that the instrument calibration is achieved with a series of linear relations.

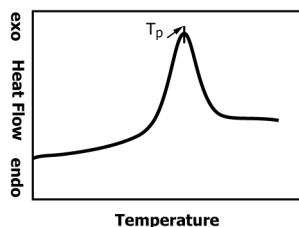


FIG. 1 Example Showing the Temperature of Maximum Heat Flow