



Designation: D6484/D6484M – 23

# Standard Test Method for Open-Hole Compressive Strength of Polymer Matrix Composite Laminates<sup>1</sup>

This standard is issued under the fixed designation D6484/D6484M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reappraisal.

## 1. Scope

1.1 This test method determines the open-hole compressive strength of multidirectional polymer matrix composite laminates reinforced by high-modulus fibers. The composite material forms are limited to continuous-fiber or discontinuous-fiber (tape or fabric, or both) reinforced composites in which the laminate is balanced and symmetric with respect to the test direction. The range of acceptable test laminates and thicknesses are described in 8.2.1.

1.2 Several related ASTM standards reference the procedures and apparatus described within this test method. In particular, the support fixture described in 7.2 is used by several other standards to stabilize compression-loaded test specimens. These include Practice D6742/D6742M, which covers filled-hole compression testing; Practice D7615/D7615M, which covers open-hole fatigue testing; and Practice D8066/D8066M, which covers unnotched laminate compression testing.

1.3 *Units*—The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system are not necessarily exact equivalents; therefore, to ensure conformance with the standard, each system shall be used independently of the other, and values from the two systems shall not be combined.

1.3.1 Within the text, the inch-pound units are shown in brackets.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

*mentations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

## 2. Referenced Documents

### 2.1 ASTM Standards:<sup>2</sup>

- D792 Test Methods for Density and Specific Gravity (Relative Density) of Plastics by Displacement
- D883 Terminology Relating to Plastics
- D2584 Test Method for Ignition Loss of Cured Reinforced Resins
- D2734 Test Methods for Void Content of Reinforced Plastics
- D3039/D3039M Test Method for Tensile Properties of Polymer Matrix Composite Materials
- D3171 Test Methods for Constituent Content of Composite Materials
- D3878 Terminology for Composite Materials
- D5229/D5229M Test Method for Moisture Absorption Properties and Equilibrium Conditioning of Polymer Matrix Composite Materials
- D5687/D5687M Guide for Preparation of Flat Composite Panels with Processing Guidelines for Specimen Preparation
- D6742/D6742M Practice for Filled-Hole Tension and Compression Testing of Polymer Matrix Composite Laminates
- D7615/D7615M Practice for Open-Hole Fatigue Response of Polymer Matrix Composite Laminates
- D8066/D8066M Practice Unnotched Compression Testing of Polymer Matrix Composite Laminates
- D8509 Guide for Test Method Selection and Test Specimen Design for Bolted Joint Related Properties
- E4 Practices for Force Calibration and Verification of Testing Machines
- E6 Terminology Relating to Methods of Mechanical Testing
- E83 Practice for Verification and Classification of Extensometer Systems
- E122 Practice for Calculating Sample Size to Estimate, With Specified Precision, the Average for a Characteristic of a Lot or Process

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D30 on Composite Materials and is the direct responsibility of Subcommittee D30.05 on Structural Test Methods.

Current edition approved Sept. 1, 2023. Published October 2023. Originally approved in 1999. Last previous edition approved in 2020 as D6484/D6484M – 20. DOI: 10.1520/D6484\_D6484M-23.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

[E177 Practice for Use of the Terms Precision and Bias in ASTM Test Methods](#)

[E456 Terminology Relating to Quality and Statistics](#)

[E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method](#)

### 3. Terminology

3.1 *Definitions*—Terminology [D3878](#) defines terms relating to high-modulus fibers and their composites. Terminology [D883](#) defines terms relating to plastics. Terminology [E6](#) defines terms relating to mechanical testing. Terminology [E456](#) and Practice [E177](#) define terms relating to statistics. In the event of a conflict between terms, Terminology [D3878](#) shall have precedence over the other terminologies.

3.2 *Definitions of Terms Specific to This Standard*—Refer to Guide [D8509](#).

#### 3.3 Symbols:

- $A$ —cross-sectional area of a specimen
- $CV$ —coefficient of variation statistic of a sample population for a given property (in percent)
- $B_z$ —edgewise percent bending
- $D$ —hole diameter
- $h$ —specimen thickness
- $n$ —number of specimens per sample population
- $N$ —number of plies in laminate under test
- $F_x^{ohcu}$ —ultimate open hole (notched) compressive strength in the test direction
- $P_{max}$ —maximum force carried by test specimen before failure
- $r$ —95 % repeatability confidence limit, equal to 2.8 times the repeatability standard deviation
- $R$ —95 % reproducibility confidence limit, equal to 2.8 times the reproducibility standard deviation
- $S_{n-1}$ —standard deviation statistic of a sample population for a given property
- $S_r$ —repeatability (within laboratory precision) standard deviation, calculated in accordance with Practice [E691](#)
- $S_R$ —reproducibility (between laboratory precision) standard deviation, calculated in accordance with Practice [E691](#)
- $w$ —specimen width
- $x_i$ —test result for an individual specimen from the sample population for a given property
- $\bar{x}$ —mean or average (estimate of mean) of a sample population for a given property
- $\sigma$ —normal stress

### 4. Summary of Test Method

4.1 A uniaxial compression test of a balanced, symmetric laminate is performed with a centrally located hole. Edge-mounted extensometer displacement transducers are optional. Refer to Guide [D8509](#) for additional test details.

4.2 The test specimen is face-supported in a multi-piece bolted support fixture. Two acceptable test procedures are provided. In Procedure A, the specimen/fixture assembly is clamped in hydraulic wedge grips. The force is transmitted by shear into the support fixture and then is transmitted by shear into the test specimen. In Procedure B, the specimen/fixture assembly is placed between flat platens, such that the specimen

and fixture are end-loaded. The portion of the force initially transferred into the support fixture is transmitted by shear into the test specimen.

### 5. Significance and Use

5.1 Refer to Guide [D8509](#).

### 6. Interferences

6.1 Refer to Guide [D8509](#).

### 7. Apparatus

7.1 *Micrometers and Calipers*—A micrometer with a 4 mm to 8 mm [0.16 in. to 0.32 in.] nominal diameter ball interface or a flat anvil interface shall be used to measure the specimen thickness. A ball interface is recommended for thickness measurements when at least one surface is irregular (for example, a coarse peel ply surface which is neither smooth nor flat). A micrometer or caliper with a flat anvil interface shall be used for measuring length, width, and other machined surface dimensions. The use of alternative measurement devices is permitted if specified (or agreed to) by the test requestor and reported by the testing laboratory. The accuracy of the instruments shall be suitable for reading to within 1 % of the specimen dimensions. For typical specimen geometries, an instrument with an accuracy of  $\pm 0.0025$  mm [ $\pm 0.0001$  in.] is adequate for the thickness measurement, while an instrument with an accuracy of  $\pm 0.025$  mm [ $\pm 0.001$  in.] is adequate for measurement of length, width, and other machined surface dimensions. Additionally, a micrometer or gauge capable of determining the hole diameter to  $\pm 0.025$  mm [ $\pm 0.001$  in.] shall be used.

7.2 *Support Fixture*—The fixture is a face-supported compressive test fixture as shown in [Fig. 1](#). The fixture consists of two short-grip/long-grip assemblies, two support plates, and steel shims as required to maintain a nominally zero (0.00 mm to 0.12 mm [0.000 in. to 0.005 in.] tolerance) gap between support plates and long grips. If this gap does not meet the minimum requirement, shim the contact area between the support plate and the short grip with steel shim stock. If the gap is too large, shim between the support plate and the long grip, holding the shim stock on the support plate with tape. [Fig. 2](#) shows shim requirements. The fixture should be checked for conformity to engineering drawings. Each short-grip/long-grip assembly is line-drilled as shown in [Figs. A2.1 and A1.1](#) and must be used as a matched set. The threading of the support plate is optional. Standard test specimens are 36 mm by 300 mm [1.5 in. by 12 in.]. In Procedure A, the fixture is hydraulically gripped on each end and the compressive force is transmitted by means of friction through the fixture and into the test specimen. In Procedure B, the fixture is placed between flat platens and loaded in compression at each end; force introduced into the fixture is transmitted by means of friction into the test specimen. A cutout exists on both faces of the fixture for a thermocouple, fastener, or extensometer, if required by the requesting organization. The long and short fixtures have an undercut along the corner of the specimen grip area so that specimens are not required to be chamfered and to avoid damage caused by the radius. The fixtures also allow a slight

**METRIC HARDWARE**  
 NA0036-060050 BOLT (4)  
 NA0179B-060 WASHER (8+)  
 (# AS REQ'D)  
 NA0033-060M NUT (4)  
 (OR EQUIVALENT)  
 OR  
 FOR THREADED PLATES  
 NA0036-060045 BOLT (4)  
 NA0179B-060 WASHER (4)  
 (OR EQUIVALENT)

**US CUSTOMARY HARDWARE**  
 NAS 6605-32 BOLT (4)  
 NAS 1587-5C WASHER (8+)  
 (# AS REQ'D.)  
 NAS 1804-5 NUT (4)  
 [OR EQUIVALENT]  
 OR  
 FOR THREADED PLATES  
 NAS6605-28 BOLT (4)  
 NAS 1587-5C WASHER (4)  
 [OR EQUIVALENT]

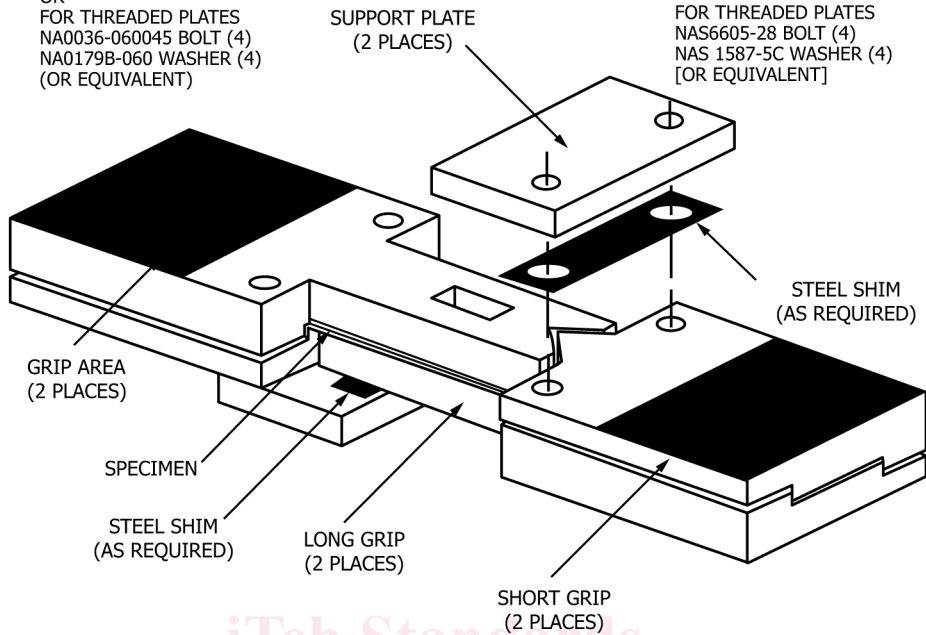


FIG. 1 Support Fixture Assembly

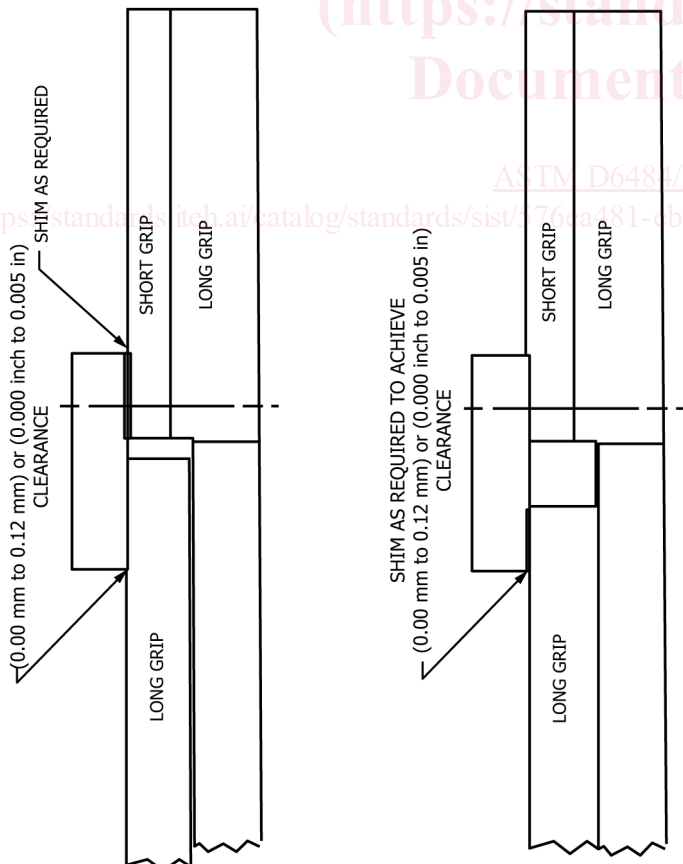


FIG. 2 Support Fixture—Shim Requirements

clearance between the fixture and the gauge section of the specimen, in order to minimize grip failures and friction effects.

7.2.1 *Support Fixture Details*—The detailed drawings for manufacturing the support fixture are contained in Figs. A2.2-A1.5. An optional threaded support plate is shown in Figs. A2.6 and A1.6, to be used instead of the support plate shown in Figs. A2.5 and A1.5 and the nuts called out in Fig. 1. Other fixtures that meet the requirements of this section may be used (for example, MTS Open Hole Compressive Fixture Model 605.21A or Wyoming Test Fixtures, Inc. Models CU-OH and WTF-OH). The following general notes apply to these figures:

7.2.1.1 Machine surfaces to a 3.2 [125] finish unless otherwise specified.

7.2.1.2 Break all edges.

7.2.1.3 Specimen-gripping area shall be thermal sprayed using high-velocity oxygen fueled (HVOF), electrospark deposition (ESD), or equivalent process.

7.2.1.4 The test fixture may be made of low-carbon steel for ambient temperature testing. For non-ambient environmental conditions, the recommended fixture material is a nonheat-treated ferritic or precipitation-hardened stainless steel (heat treatment for improved durability is acceptable but not required).

7.2.1.5 Additional fasteners may be installed in the gripping area (shown in Figs. A2.1 and A1.1) when using Procedure B. The presence of such fasteners is not required to perform an end-loaded test successfully. However, they can be beneficial

in suppressing unacceptable failure modes (such as end failures) in certain circumstances (high temperature testing, for example) by ensuring that the specimen is well-supported by the fixture.

NOTE 1—Experience has shown that fixtures may be damaged in use, thus periodic reinspection of the fixture dimensions and tolerances is important.

**7.3 Testing Machine**—The testing machine shall be in accordance with Practices **E4** and shall satisfy the following requirements:

**7.3.1 Testing Machine Configuration**—The testing machine shall have both an essentially stationary head and a movable head. A short loading train, and either rigidly mounted hydraulic grips or flat end-loading platens, shall be used.

**7.3.2 Grips**—If Procedure A is used, each head of the testing machine shall be capable of holding one end of the test assembly so that the direction of force applied to the specimen is coincident with the longitudinal axis of the specimen. Hydraulic wedge grips shall apply sufficient lateral pressure to prevent slippage between the grip face and the support fixture.

**7.3.3 Flat Platens**—If Procedure B is used, the test machine shall be mounted with well-aligned, fixed (as opposed to spherical seat) flat platens. The platen surfaces shall be parallel within 0.03 mm [0.001 in.] across the test fixture base length of 80 mm [3.0 in.]. If the platens are not sufficiently hardened, or simply to protect the platen surfaces, a hardened plate (with parallel surfaces) can be inserted between each end of the fixture and the corresponding platen. A rectangle should be drawn on the center of the lower platen, to help center the test fixture between the platens.

**7.3.4 Drive Mechanism**—The testing machine drive mechanism shall be capable of imparting to the movable head a controlled velocity with respect to the stationary head. The velocity of the movable head shall be capable of being regulated in accordance with **11.3**.

**7.3.5 Load Indicator**—The testing machine load-sensing device shall be capable of indicating the total force being carried by the test specimen. This device shall be essentially free from inertia lag at the specified rate of testing and shall indicate the force with an accuracy over the force range(s) of interest of within  $\pm 1\%$  of the indicated value.

**7.3.6 Extensometers**—The extensometer gauge length shall be 25 mm [1.0 in.]. Extensometers shall satisfy, at a minimum, Practice **E83**, Class B-1 requirements for the strain range of interest, and shall be calibrated over that range in accordance with Practice **E83**. The extensometers shall be essentially free of inertia lag at the specified speed of testing.

**7.4 Conditioning Chamber**—When conditioning materials at non-laboratory environments, a temperature/vapor-level controlled environmental conditioning chamber is required that shall be capable of maintaining the required temperature to within  $\pm 3\text{ }^{\circ}\text{C}$  [ $\pm 5\text{ }^{\circ}\text{F}$ ] and the required relative humidity level to within  $\pm 3\%$  RH. Chamber conditions shall be monitored either on an automated continuous basis or on a manual basis at regular intervals.

**7.5 Environmental Test Chamber**—An environmental test chamber is required for test environments other than ambient

testing laboratory conditions. This chamber shall be capable of maintaining the test specimen and fixture at the required test environment during the mechanical test. The test temperature shall be maintained within  $\pm 3\text{ }^{\circ}\text{C}$  [ $\pm 5\text{ }^{\circ}\text{F}$ ] of the required temperature, and the relative humidity level shall be maintained to within  $\pm 3\%$  RH of the required humidity level.

## 8. Sampling and Test Specimens

**8.1 Sampling**—Test at least five specimens per test condition unless valid results can be gained through the use of fewer specimens, as in the case of a designed experiment. For statistically significant data, consult the procedures outlined in Practice **E122**. Report the method of sampling.

### 8.2 Geometry:

**8.2.1 Stacking Sequence**—The standard tape and fabric laminates shall have multidirectional fiber orientations (fibers shall be oriented in a minimum of two directions) and balanced and symmetric stacking sequences. The nominal thickness shall be 4 mm [0.160 in.], with a permissible range from 3 mm to 5 mm [0.125 in. to 0.200 in.], inclusive. Fabric laminates containing satin-type weaves shall have symmetric warp surfaces, unless otherwise specified and noted in the report.

NOTE 2—Typically, a  $[45_i/-45_i/0_j/90_k]_{ms}$  tape or  $[45_i/0_j]_{ms}$  fabric laminate should be selected such that a minimum of 5% of the fibers lay in each of the four principal orientations. This laminate design has been found to yield the highest likelihood of acceptable failure modes.


**8.2.2 Specimen Configuration**—The geometry of the specimen is shown in **Figs. 3 and 4**.

**8.3 Specimen Preparation**—Guide **D5687/D5687M** provides recommended specimen preparation practices and should be followed where practical.

**8.3.1 Panel Fabrication**—Control of fiber alignment is critical. Improper fiber alignment will reduce the measured properties. The panel must be flat and of uniform thickness to ensure even loading. Erratic fiber alignment will also increase the coefficient of variation. Report the panel fabrication method.


**8.3.2 Machining Methods**—Specimen preparation is extremely important for this specimen. Take precautions when cutting specimens from plates to avoid notches, undercuts, rough or uneven surfaces, or delaminations due to inappropriate machining methods. Obtain final dimensions by water-lubricated precision sawing, milling, or grinding. The use of diamond tooling has been found to be extremely effective for many material systems. Edges should be flat and parallel within the specified tolerances. Holes should be drilled undersized and reamed to final dimensions. Take special care to ensure that creation of the specimen hole does not delaminate or otherwise damage the material surrounding the hole. Machining tolerances and surface finish requirements are as noted in **Figs. 3 and 4**. Record and report the specimen cutting and hole preparation methods.

**8.3.3** If specific gravity, density, reinforcement volume fraction, or void volume fraction are to be reported, then obtain these samples from the same panels being tested. Specific gravity and density may be evaluated by means of Test Method **D792**. Volume percent of the constituents may be evaluated by one of the matrix digestion procedures of Test Method **D3171**

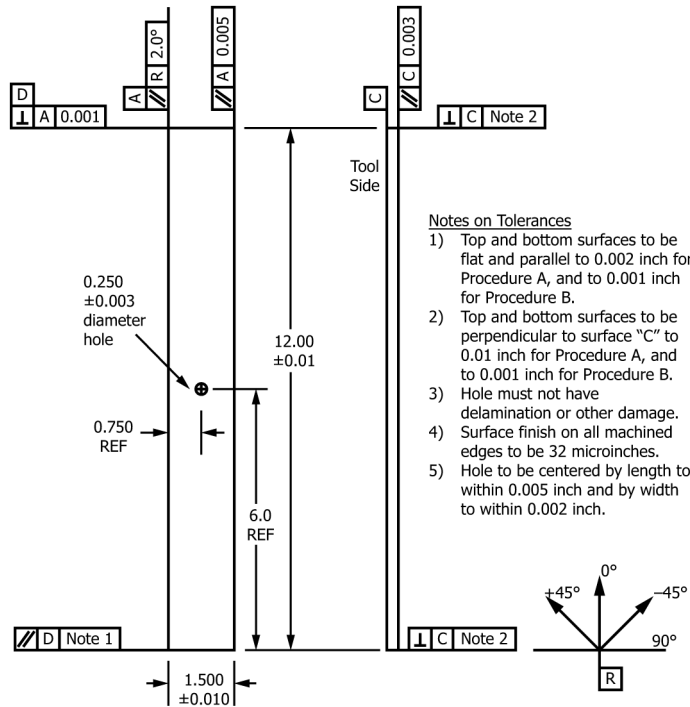

Note: All dimensions in inches

FIG. 3 Open Hole Compression Test Specimen (Inch-Pound Version)

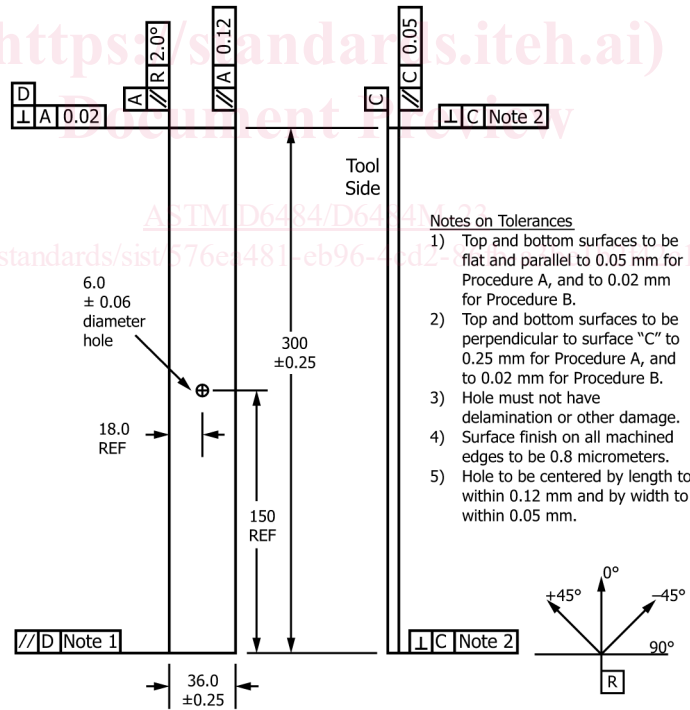

Note: All dimensions in millimeters

FIG. 4 Open Hole Compression Test Specimen (SI Version)

or, for certain reinforcement materials such as glass and ceramics, by the matrix burn-off technique of Test Method

**D2584.** The void content equations of Test Method **D2734** are applicable to both Test Method **D2584** and the matrix digestion procedures.

8.3.4 *Labeling*—Label the specimens so that they will be distinct from each other and traceable back to the raw material, and will neither influence the test nor be affected by it.

## 9. Calibration

9.1 The accuracy of all measuring equipment shall have certified calibrations that are current at the time of use of the equipment.

## 10. Conditioning

10.1 The recommended pre-test condition is effective moisture equilibrium at a specific relative humidity as established by Test Method **D5229/D5229M**; however, if the test requestor does not explicitly specify a pre-test conditioning environment, no conditioning is required and the test specimens may be tested as prepared.

10.2 The pre-test specimen conditioning process, to include specified environmental exposure levels and resulting moisture content, shall be reported with the test data.

NOTE 3—The term “moisture,” as used in Test Method **D5229/D5229M**, includes not only the vapor of a liquid and its condensate, but the liquid itself in large quantities, as for immersion.

10.3 If no explicit conditioning process is performed, the specimen conditioning process shall be reported as “unconditioned” and the moisture content as “unknown.”

## 11. Procedure

### 11.1 *Parameters to Be Specified Before Test:*

11.1.1 The specimen sampling method, specimen type and geometry, and conditioning travelers (if required).

11.1.2 The test procedure desired (A or B).

11.1.3 The compressive properties and data reporting format desired.

NOTE 4—Determine specific material property, accuracy, and data reporting requirements prior to test for proper selection of instrumentation and data recording equipment. Estimate the specimen strength to aid in transducer selection, calibration of equipment, and determination of equipment settings.

11.1.4 The environmental conditioning test parameters.

11.1.5 If performed, extensometry requirements and related calculations.

11.1.6 If performed, sampling method, specimen geometry, and test parameters used to determine density and reinforcement volume.

### 11.2 *General Instructions:*

11.2.1 Report any deviations from this test method, whether intentional or inadvertent.

11.2.2 Following final specimen machining, but before conditioning and testing, measure the specimen width,  $w$ , and the specimen thickness  $h$ , in the vicinity of the hole. Measure the hole diameter,  $D$ , distance from hole edge to closest specimen side,  $f$ , and distance from the hole edge to specimen end,  $g$ . Inspect the hole and areas adjacent to the hole for delaminations. Report the location and size of any delamination found. The accuracy of all measurements shall be within

1 % of the dimension. Record the dimensions to three significant figures in units of millimetres [inches].

NOTE 5—The test requester may request that additional measurements be performed after the machined specimens have gone through any conditioning or environmental exposure.

11.2.3 Condition the specimens as required. Store the specimens in the conditioned environment until test time, if the test environment is different than the conditioning environment.

11.3 *Speed of Testing*—Set the speed of testing so as to produce failure within 1 min to 10 min. If the ultimate strength of the material cannot be reasonably estimated, initial trials should be conducted using standard speeds until the ultimate strength of the material and the compliance of the system are known, and speed of testing can be adjusted. The suggested standard head displacement rate is 2 mm/min [0.05 in./min].

11.4 *Test Environment*—If possible, test the specimen under the same fluid exposure level used for conditioning. However, cases such as elevated temperature testing of a moist specimen place unrealistic requirements on the capabilities of common testing machine environmental chambers. In such cases, the mechanical test environment may need to be modified, for example, by testing at elevated temperature with no fluid exposure control, but with a specified limit on time to failure from withdrawal from the conditioning chamber. Record any modifications to the test environment.

NOTE 6—When testing a conditioned specimen at elevated temperature with no fluid exposure control, the percentage moisture loss of the specimen prior to test completion may be estimated by placing a conditioned traveler coupon of known weight within the test chamber at the same time the specimen is placed in the chamber. Upon completion of the test, the traveler coupon is removed from the chamber, weighed, and the percentage weight calculated and reported.

11.5 *Specimen Installation*—Install the test specimen into the open-hole compression fixture such that the machined ends of the specimen are flush with the ends of the fixture halves. This should result in the specimen hole being centered in the fixture cutout. Tighten the four bolts just enough to hold the specimen in place during fixture installation.

### 11.6 *Procedure A (Hydraulic Grip Loading):*

#### 11.6.1 *Fixture Insertion:*

11.6.1.1 Place the fixture in the grips of the testing machine (Fig. 5), taking care to align the long axis of the gripped fixture with the test direction. When inserting the fixture into the grip-jaws, grip the outer portion of the fixture up to the bolts, approximately 80 mm [3 in.].

11.6.1.2 Tighten the grips, recording the pressure used on the hydraulic grips. The ends of the grip-jaws on wedge-type grips should be even with each other following insertion to avoid inducing a bending moment which could result in premature failure of the specimen.

11.6.1.3 Retorque the four bolts to approximately 7 N-m [60 in.-lbf] after hydraulic gripping pressure is applied.

11.6.1.4 Check the gaps between the support plates and the long grip portion of the support fixture using a feeler gauge, and shim as required in Fig. 2.

11.6.1.5 Check that the gap between the gauge section of the specimen and the long grip portion of the support fixture is 0.05 mm  $\pm$  0.05 mm [0.002 in.  $\pm$  0.002 in.] using a feeler