



Designation: **D2103—15** **D2103 – 23**

## Standard Specification for Polyethylene Film and Sheeting<sup>1</sup>

This standard is issued under the fixed designation D2103; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

*This standard has been approved for use by agencies of the U.S. Department of Defense.*

### 1. Scope\*

1.1 This specification covers the classification of polyethylene film and sheeting up to 0.3 mm (0.012 in.) in thickness, inclusive. The film or sheeting ~~may~~can contain additives for the improvement of the surface properties, pigments, or stabilizers, or combinations thereof.

NOTE 1—Film is defined in Terminology **D883** as an optional term for sheeting having a nominal thickness no greater than 0.254 mm (0.010 in.).

1.2 The values stated in SI units are to be regarded as standard. The values given in parentheses are for information only.

1.3 The following precautionary caveat pertains only to the test method portion, Section 8, of this specification: *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate ~~safety and health~~safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.4 This specification allows for the use of recycled polyethylene film or resin as feedstock, in whole or in part, as long as all the requirements as governed by the producer and end user are also met (see **Note 2**).

<https://standards.iteh.ai/catalog/standards/sist/9cbcd76d-9720-4ed6-a072-195ce4cdcd82/astm-d2103-23>  
NOTE 2—Guide **D7209** describes terminology and definitions related to recycled plastics.

NOTE 3—There is no known ISO equivalent to this standard.

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

### 2. Referenced Documents

#### 2.1 ASTM Standards:<sup>2</sup>

- [D618 Practice for Conditioning Plastics for Testing](#)
- [D792 Test Methods for Density and Specific Gravity \(Relative Density\) of Plastics by Displacement](#)
- [D882 Test Method for Tensile Properties of Thin Plastic Sheeting](#)
- [D883 Terminology Relating to Plastics](#)

<sup>1</sup> This specification is under the jurisdiction of ASTM Committee **D20** on Plastics and is the direct responsibility of Subcommittee **D20.19** on Film, Sheeting, and Molded Products.

Current edition approved April 1, 2015 Nov. 15, 2023. Published April 2015 November 2023. Originally approved in 1962. Last previous edition approved in 2010 **D2103 – 10**; **D2103 – 15**. DOI: ~~10.1520/D2103-15~~ 10.1520/D2103-23.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

\*A Summary of Changes section appears at the end of this standard

- D1003 Test Method for Haze and Luminous Transmittance of Transparent Plastics
- D1004 Test Method for Tear Resistance (Graves Tear) of Plastic Film and Sheeting
- D1434 Test Method for Determining Gas Permeability Characteristics of Plastic Film and Sheeting
- D1505 Test Method for Density of Plastics by the Density-Gradient Technique
- D1709 Test Methods for Impact Resistance of Plastic Film by the Free-Falling Dart Method
- D1746 Test Method for Transparency of Plastic Sheeting
- D1894 Test Method for Static and Kinetic Coefficients of Friction of Plastic Film and Sheeting (Withdrawn 2023)<sup>3</sup>
- D1922 Test Method for Propagation Tear Resistance of Plastic Film and Thin Sheeting by Pendulum Method
- D1938 Test Method for Tear-Propagation Resistance (Trouser Tear) of Plastic Film and Thin Sheeting by a Single-Tear Method
- D2457 Test Method for Specular Gloss of Plastic Films and Solid Plastics
- D2578 Test Method for Wetting Tension of Polyethylene and Polypropylene Films
- D2839 Practice for Use of a Melt Index Strand for Determining Density of Polyethylene
- D3892 Practice for Packaging/Packing of Plastics
- D4321 Test Method for Package Yield of Plastic Film
- D4703 Practice for Compression Molding Thermoplastic Materials into Test Specimens, Plaques, or Sheets
- D4976 Specification for Polyethylene Plastics Molding and Extrusion Materials
- D5947 Test Methods for Physical Dimensions of Solid Plastics Specimens
- D6988 Guide for Determination of Thickness of Plastic Film Test Specimens
- D7209 Guide for Waste Reduction, Resource Recovery, and Use of Recycled Polymeric Materials and Products (Withdrawn 2015)<sup>3</sup>
- E96/E96M Test Methods for Gravimetric Determination of Water Vapor Transmission Rate of Materials
- F1249 Test Method for Water Vapor Transmission Rate Through Plastic Film and Sheeting Using a Modulated Infrared Sensor

### 3. Terminology

#### 3.1 Definitions:

3.1.1 ~~Unless otherwise specified, the For definitions of plastic terms used in this specification are in accordance with and associated with plastics issues refer to the terminology contained in Terminology D883.~~

#### 3.2 Definitions of Terms Specific to This Standard:

3.2.1 *treated*—surface characteristics of the sheet or film have been modified by flame, corona discharge, or other means to promote the adhesion of inks, etc.

3.2.2 *yield*—the area provided by a given weight of film or sheeting of specified thickness.

### 4. Classification

4.1 The film and sheeting covered in this specification shall be designated by a type number, composed by listing the desired cell limit for each of the five properties, in the order shown in **Table 1**.

**TABLE 1 Type Numbers**

Property Order Number	Property	0	1	2	3	4	5	Units
1	Density <sup>A</sup>	unspecified	0.910–<0.926	0.926–<0.941	0.941–0.965	<0.910	...	g/cm <sup>3</sup>
2	Impact strength	unspecified	<40	40–70	71–150	151–300	>300	grams
3	Coefficient of friction <sup>G</sup>	unspecified	<0.20	0.20–0.40	0.41–0.70	>0.70	...	...
4	Haze	unspecified	<5.0	5.0–9.0	>9.0	...	...	...
5	Nominal thickness	unspecified	<sup>B</sup>	<sup>C</sup>	<sup>D</sup>	<sup>E</sup>	<sup>F</sup>	mm (in.)

<sup>A</sup>Annealed density of molded plaques or Melt Index extrudates.

<sup>B</sup><0.0254 (<0.0010).

<sup>C</sup>0.0254–<0.0508 (0.0010–<0.0020)

<sup>D</sup>0.0508–<0.1016 (0.0020–<0.0040)

<sup>E</sup>0.1016–<0.1778 (0.0040–<0.0070)


<sup>F</sup>0.1778–≤0.3048 (0.0070–≤0.0120)

<sup>G</sup>Coefficient of friction listed in this table is based on the kinetic coefficient of friction.


<sup>3</sup> The last approved version of this historical standard is referenced on [www.astm.org](http://www.astm.org).

NOTE 4—Examples of this classification system are as follows:


(1) A high-clarity packaging film might be described as follows:

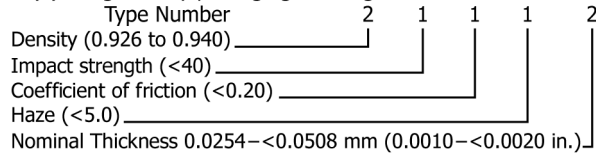


(2) A thin garment bag film might be described as follows:

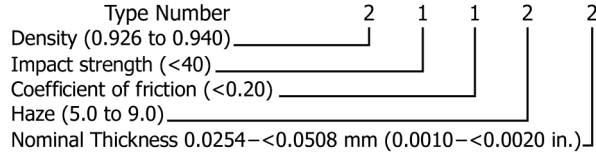


(3) A tough, thick, pigmented industrial film might be described as follows:

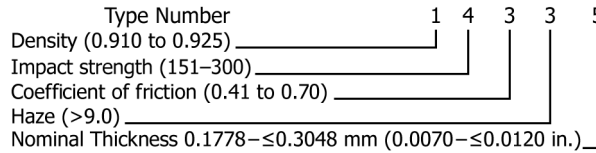


(1) A high-clarity packaging film might be described as follows:

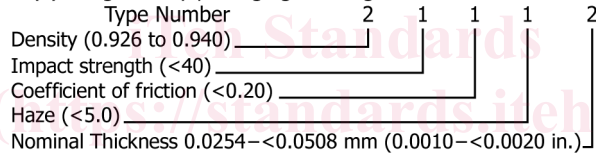

(2) A thin garment bag film might be described as follows:

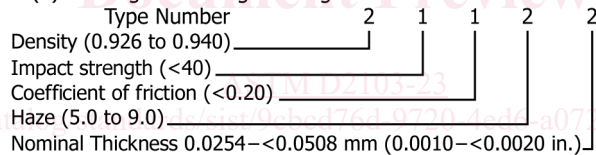

(3) A tough, thick, pigmented industrial film might be described as follows:

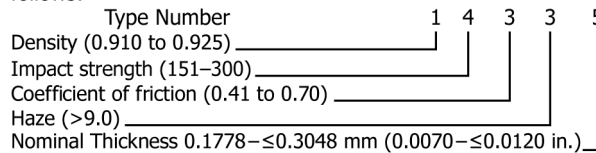

With this type of classification it is possible to assemble on paper a combination of properties that is impossible to obtain with the present state of technology. A purchaser using this specification for the first time will probably find it necessary to contact material suppliers to learn what materials are commercially available.

4.2 In cases where surface treatment is specified by the purchaser, the test method must be agreed upon between the purchaser and the seller. The recommended test to measure the degree of surface treatment is Test Method **D2578**.

**5. General Requirements**

5.1 *Appearance*—The material shall have appearance qualities conforming with those produced by good commercial practice. It shall be as free as commercially possible of gels, streaks, pinholes, particles of foreign matter, and undispersed raw material. Gels need to be kept as minimal as possible when recycled materials are used in the films. There shall be no other visible defects such as holes, tears, or blisters. The edges shall be free of nicks and cuts visible to the unaided eye. There shall be no visible evidence of damage from shipping.