



**Designation: D143 – 23**

## **Standard Test Methods for Small Clear Specimens of Timber<sup>1</sup>**

This standard is issued under the fixed designation D143; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### **INTRODUCTION**

The need to classify wood species by evaluating the physical and mechanical properties of small clear specimens has always existed. Because of the great variety of species, variability of the material, continually changing conditions of supply, many factors affecting test results, and ease of comparing variables, the need will undoubtedly continue to exist.

In the preparation of these methods for testing small clear specimens, consideration was given both to the desirability of adopting test methods that would yield results comparable to those already available and to the possibility of embodying such improvements as experience has shown desirable. In view of the many thousands of tests made under a single comprehensive plan by the U.S. Forest Service, the former Forest Products Laboratories of Canada (now FPInnovations), and other similar organizations, these test methods naturally conform closely to the methods used by those institutions. These test methods are the outgrowth of a study of both American and European experience and methods. The general adoption of these test methods will tend toward a world-wide unification of results, permitting an interchange and correlation of data, and establishing the basis for a cumulative body of fundamental information on the timber species of the world. Many of the figures in this standard use sample data and computation sheets from testing done in the 1950s and earlier. These figures remain in the standard because they are still valid depictions of the recording and plotting of test results and also provide a historical link to the large body of test data on small clear specimens already in existence for this long-standing test method.

Descriptions of some of the strength tests refer to primary methods and secondary methods. Primary methods provide for specimens of 2-in. by 2-in. (50 mm by 50 mm) cross section. This size of specimen has been extensively used for the evaluation of various mechanical and physical properties of different species of wood, and a large number of data based on this primary method have been obtained and published.

The 2-in. by 2-in. (50 mm by 50 mm) size has the advantage in that it embraces a number of growth rings, is less influenced by earlywood and latewood differences than smaller size specimens, and is large enough to represent a considerable portion of the sampled material. It is advisable to use primary method specimens wherever possible. There are circumstances, however, when it is difficult or impossible to obtain clear specimens of 2-in. by 2-in. cross section having the required 30 in. (760 mm) length for static bending tests. With the increasing incidence of smaller second growth trees, and the desirability in certain situations to evaluate a material which is too small to provide a 2-in. by 2-in. cross section, a secondary method which utilizes a 1-in. by 1-in. (25 mm by 25 mm) cross section has been included. This cross section is established for compression parallel to grain and static bending tests, while the 2-in. by 2-in. cross section is retained for impact bending, compression perpendicular to grain, hardness, shear parallel to grain, cleavage, and tension perpendicular to grain. Toughness and tension parallel to grain are special tests using specimens of smaller cross section.

The user is cautioned that test results between two different sizes of specimens are not necessarily directly comparable. Guidance on the effect of specimen size on a property being evaluated is beyond the scope of these test methods and should be sought elsewhere.

Where the application, measurement, or recording of load and deflection can be accomplished using electronic equipment and computerized apparatus, such devices are encouraged. It is important that all data measurement and recording equipment, whether electronic or mechanical, be accurate and reliable to the degree specified.

## 1. Scope

1.1 These test methods cover the determination of various strength and related properties of wood by testing small clear specimens.

1.1.1 These test methods represent procedures for evaluating the different mechanical and physical properties, controlling factors such as specimen size, moisture content, temperature, and rate of loading.

1.1.2 Sampling and collection of material is discussed in Practice **D5536**. Sample data, computation sheets, and cards have been incorporated, which were of assistance to the investigator in systematizing records.

1.1.3 The values stated in inch-pound units are to be regarded as the standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard. When a weight is prescribed, the basic inch-pound unit of weight (lbf) and the basic SI unit of mass (Kg) are cited.

1.2 The procedures for the various tests appear in the following order:

	Sections
Photographs of Specimens	5
Control of Moisture Content and Temperature	6
Record of Heartwood and Sapwood	7
Static Bending	8
Compression Parallel to Grain	9
Impact Bending	10
Toughness	11
Compression Perpendicular to Grain	12
Hardness	13
Shear Parallel to Grain	14
Cleavage	15
Tension Parallel to Grain	16
Tension Perpendicular to Grain	17
Nail Withdrawal	18
Specific Gravity and Shrinkage in Volume	19
Radial and Tangential Shrinkage	20
Moisture Determination	21
Permissible Variations	22
Calibration	23

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.4 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

<sup>1</sup> These test methods are under the jurisdiction of ASTM Committee **D07** on Wood and are the direct responsibility of Subcommittee **D07.01** on Fundamental Test Methods and Properties.

Current edition approved Nov. 15, 2023. Published December 2023. Originally approved in 1922. Last previous edition approved in 2022 as D143 – 22. DOI: 10.1520/D0143-23.

## 2. Referenced Documents

### 2.1 ASTM Standards:<sup>2</sup>

- D9 Terminology Relating to Wood and Wood-Based Products**
- D198 Test Methods of Static Tests of Lumber in Structural Sizes**
- D2395 Test Methods for Density and Specific Gravity (Relative Density) of Wood and Wood-Based Materials**
- D3043 Test Methods for Structural Panels in Flexure**
- D4442 Test Methods for Direct Moisture Content Measurement of Wood and Wood-Based Materials**
- D4761 Test Methods for Mechanical Properties of Lumber and Wood-Based Structural Materials**
- D5536 Practice for Sampling Forest Trees for Determination of Clear Wood Properties**
- E4 Practices for Force Calibration and Verification of Testing Machines**
- E2309 Practices for Verification of Displacement Measuring Systems and Devices Used in Material Testing Machines**

## 3. Summary of Test Methods

3.1 The mechanical tests are static bending, compression parallel to grain, impact bending toughness, compression perpendicular to grain, hardness, shear parallel to grain, cleavage, tension parallel to grain, tension-perpendicular-to-grain, and nail-withdrawal tests. These tests are permitted for both green and air-dry material as specified in these test methods. In addition, test methods for evaluating such physical properties as specific gravity, shrinkage in volume, radial shrinkage, and tangential shrinkage are presented.

NOTE 1—The test for shearing strength perpendicular to the grain (sometimes termed “vertical shear”) is not included as one of the principal mechanical tests since in such a test the strength is limited by the shearing resistance parallel to the grain.

## 4. Significance and Use

4.1 These test methods cover tests on small clear specimens of wood that are made to provide the following:

4.1.1 Data for comparing the mechanical properties of various species,

4.1.2 Data for the establishment of correct strength functions, which in conjunction with results of tests of timbers in structural sizes (see Test Methods **D198** and Test Methods **D4761**), afford a basis for establishing allowable stresses, and

4.1.3 Data to determine the influence on the mechanical properties of such factors as density, locality of growth, position in cross section, height of timber in the tree, change of properties with seasoning or treatment with chemicals, and change from sapwood to heartwood.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard’s Document Summary page on the ASTM website.

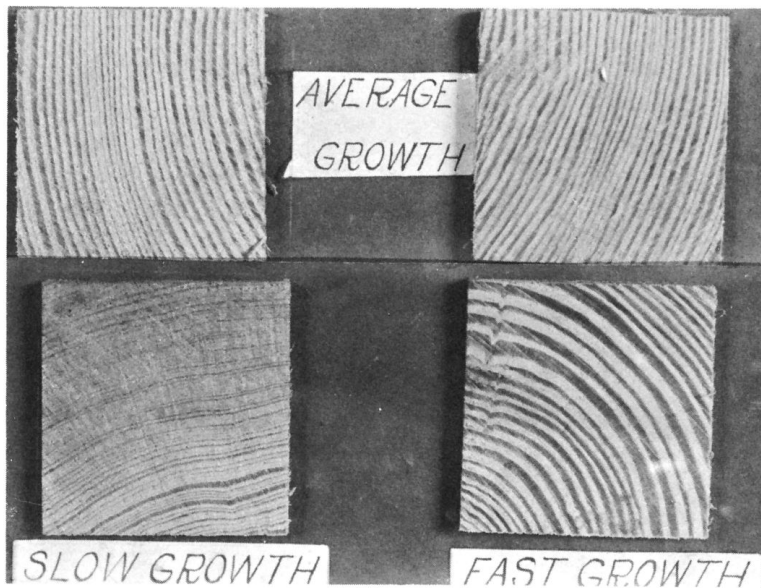


FIG. 1 Cross Sections of Bending Specimens Showing Different Rates of Growth of Longleaf Pine (2-in. by 2-in. (50 mm by 50 mm) Specimens)



FIG. 2 Tangential Surfaces of Bending Specimens of Different Rates of Growth of Jeffrey Pine 2-in. by 2-in. by 30-in. (50 mm by 50 mm by 760 mm) Specimens

## 5. Photographs of Specimens

5.1 Four of the static bending specimens from each species shall be selected for photographing, as follows: two average growth, one fast growth, and one slow growth. These specimens shall be photographed in cross section and on the radial and tangential surfaces. Fig. 1 is a typical photograph of a cross section of 2-in. by 2-in. (50 mm by 50 mm) test specimens, and Fig. 2 is the tangential surface of such specimens.

## 6. Control of Moisture Content and Temperature

6.1 In recognition of the significant influence of moisture content and temperature on the physical and mechanical properties of wood, these factors shall be controlled and reported to ensure comparable test results.

NOTE 2—It is desirable that the testing room and the room for preparation of test specimens are temperature- and humidity-controlled.

6.2 *Moisture Content*—Moisture content shall be managed based on the objective of the test: Specimens for tests in the green condition shall be stored and manipulated in such a manner that their moisture content remains above the fiber saturation point; specimens for in-situ tests shall be maintained at the in-situ moisture content; and specimens for tests in the air-dry condition shall be conditioned to approximately constant weight before the test. Tests shall be carried out in such a manner that influential changes in moisture content do not occur during the tests.



NOTE 3—USDA Technical Bulletin 479<sup>3,4</sup> describes the sensitivity of wood properties to moisture content changes. This reference may be useful when determining influential moisture content changes relative to the wood properties being tested.

6.3 *Temperature*—The temperature of the specimens shall be 68 °F ± 6 °F (20 °C ± 3 °C) except when the effects of other temperatures are to be evaluated. The conditioning temperature and the temperature at the time of test shall be recorded.

NOTE 4—Temperature and relative humidity affect the equilibrium moisture content and wood properties. Historically, when testing wood in the air-dry condition, the equilibrium moisture content is based on hygrothermal conditioning at a temperature of 68 °F ± 6 °F (20 °C ± 3 °C) and 65 % ± 5 % relative humidity.

**7. Record of Heartwood and Sapwood**

7.1 *Proportion of Sapwood*—If heartwood and sapwood present in the specimen can be distinguished by visual inspection, the proportion of sapwood present shall be estimated as required for the purposes of the test program and recorded for each test specimen.

**8. Static Bending**

8.1 *Size of Specimens*—The static bending tests shall be made on 2 in. by 2 in. by 30 in. (50 mm by 50 mm by 760 mm) primary method specimens or 1 in. by 1 in. by 16 in. (25 mm by 25 mm by 410 mm) secondary method specimens. The actual height and width at the center and the length shall be measured (see 22.2).

<sup>3</sup> Markwardt, L.J. and T.R.J. Wilson. 1935. Strength and related properties of woods grown in the United States. *Technical Bulletin No. 479*. Forest Products Laboratory, USDA, Washington, DC.

<sup>4</sup> Available from USDA National Agricultural Library Digital Collections (https://naldc.nal.usda.gov).

8.2 *Loading Span and Supports*—Use center loading and a span length of 28 in. (710 mm) for the primary method and 14 in. (360 mm) for the secondary method. These spans were established in order to maintain a minimum span-to-depth ratio of 14. Both supporting knife edges shall be provided with bearing plates and rollers of such thickness that the distance from the point of support to the central plane is not greater than the depth of the specimen (Fig. 3). The knife edges shall be adjustable laterally to permit adjustment for slight twist in the specimen.

NOTE 5—An example of laterally adjustable supports is provided in Figure 1 of Test Methods D3043.

8.3 *Bearing Block*—A rigid bearing block having a radius of 3 in. (76 mm) and a chord length of not less than 3<sup>13</sup>/<sub>16</sub> in. (97 mm) that is fixed from rotation shall be used for applying the load for primary method specimens. An example is provided in Fig. 4. A similar block having a radius of 1½ in. (38 mm) for a chord length of not less than 2 in. (50 mm) shall be used for secondary method specimens. The bearing block shall be fabricated with a material that will not appreciably deform under load.

8.4 *Placement of Growth Rings*—The specimen shall be placed so that the load will be applied through the bearing block to the tangential surface nearest the pith.

8.5 *Speed of Testing*—The load shall be applied continuously throughout the test at a rate of motion of the movable crosshead of 0.10 in. (2.5 mm)/min, for primary method specimens, and at a rate of 0.05 in. (1.3 mm)/min for secondary method specimens (see 22.3).

8.6 *Load-Deflection Curves:*

8.6.1 At a minimum, the load-deflection curves shall be recorded and the test continued up to the maximum load for all

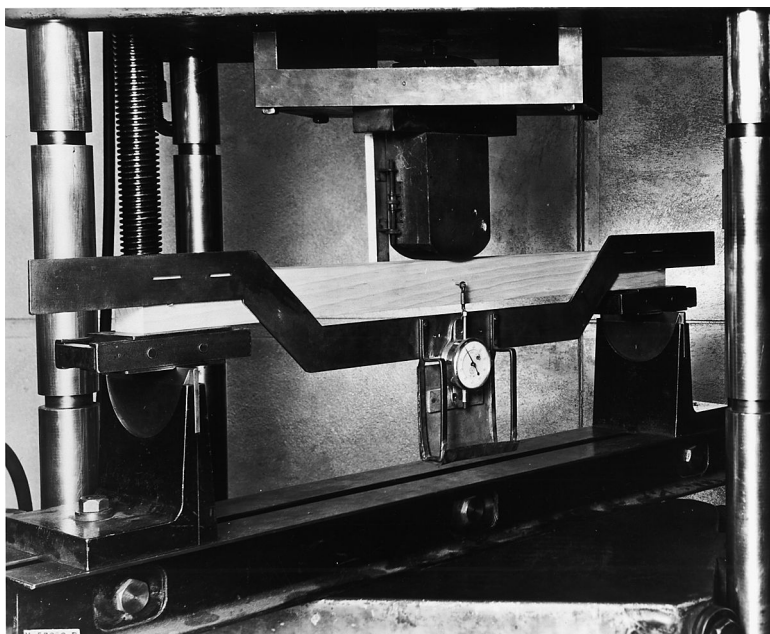


FIG. 3 Static Bending Test Assembly Showing Test Method of Load Application, Specimen Supported on Rollers and Laterally Adjustable Knife Edges, and Test Method of Measuring Deflection at Neutral Axis by Means of Yoke and Displacement Measurement Device

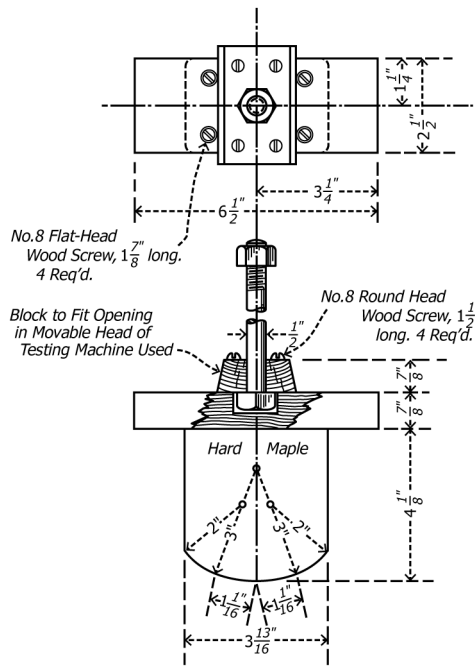


FIG. 4 Example of a Bearing Block for Static Bending Tests

static bending tests. If required for the purposes of the study, it shall be permitted to continue both loading and the load-deflection measurement beyond the maximum load.

NOTE 6—One situation where the user may choose to continue the test and the load-deflection measurements beyond the maximum load is if the total energy under the flexural load-deflection curve is a parameter of concern. In these instances for primary method specimens, it has been customary to continue the test and record the load-deflection curve beyond the maximum load to a 6 in. (152 mm) deflection or until the specimen fails to support a load of 200 lbf (890 N). For secondary method specimens, it has been customary to continue loading to a 3 in. (76 mm) deflection, or until the specimen fails to support a load of 50 lbf (222 N).

8.6.2 Deflections of the neutral plane at the center of the length shall be taken with respect to points in the neutral plane above the supports. Alternatively, deflection shall be permitted to be taken relative to the tension surface at midspan, provided that vertical displacements which occur at the reactions are taken into account.

8.6.3 Within the proportional limit, deflection readings shall be taken with a yoke-mounted displacement measurement device capable of at least a Class B rating when evaluated in accordance with Practice E2309. After the proportional limit is reached, less refinement is necessary in observing deflections. It shall be permissible to continue the deflection measurement beyond the proportional limit using an alternative means of deflection measurement capable of at least a Class C rating when evaluated in accordance with Practice E2309. To characterize the load-deflection curve, the load and deflection shall be measured and recorded at a maximum interval spacing of 0.10 in. (2.5 mm) and after abrupt changes in load. Continuous load and deflection data acquisition is preferred.

8.6.4 When data are recorded manually, the load and deflection of the first failure, the maximum load, and points of sudden change shall be read and shown on the curve sheet, even if they do not occur at one of the regular load or deflection

increments. When data are recorded electronically, the data recording rate shall be sufficient to capture the same points so that they can be similarly reported.

NOTE 7—See Fig. 5 for a sample static bending data sheet form.

8.7 Description of Failure—Static bending (flexural) failures shall be classified in accordance with the appearance of the fractured surface and the manner in which the failure develops (Fig. 6). Where appropriate, the fractured surfaces shall be roughly divided into “brash” and “fibrous,” the term “brash” indicating abrupt failure and “fibrous” indicating a fracture showing splinters. Each type of observed failure mode shall be photographed or sketched.

8.8 Weight and Moisture Content—The specimen shall be weighed immediately before test, and after the test a moisture section approximately 1 in. (25 mm) in length shall be cut from the specimen near the point of failure (see 21.1 and 22.1).

## 9. Compression Parallel to Grain

9.1 Size of Specimens—The compression-parallel-to-grain tests shall be made on 2 in. by 2 in. by 8 in. (50 mm by 50 mm by 200 mm) primary method specimens, or 1 in. by 1 in. by 4 in. (25 mm by 25 mm by 100 mm) secondary method specimens. The actual cross-sectional dimensions and the length shall be measured (see 22.2).

9.2 End Surfaces Parallel—Special care shall be used in preparing the compression-parallel-to-grain test specimens to ensure that the end grain surfaces will be parallel to each other and at right angles to the longitudinal axis. At least one platen of the testing machine shall be equipped with a spherical bearing to obtain uniform distribution of load over the ends of the specimen.

9.3 Speed of Testing—The load shall be applied continuously throughout the test at a rate of motion of the movable crosshead of 0.003 in./in. (mm/mm) of nominal specimen length/min (see 22.3).

### 9.4 Load-Compression Curves:

9.4.1 Load-compression curves shall be taken over a central gauge length not exceeding 6 in. (150 mm) for primary method specimens, and 2 in. (50 mm) for secondary method specimens. Load-compression readings shall be continued until the proportional limit is well passed, as indicated by the curve.

NOTE 8—See Fig. 7 for a sample compression-parallel-to-grain data sheet form.

9.4.2 Deformations shall be recorded using displacement measurement devices that are capable of a Class A rating when evaluated in accordance with Practice E2309.

9.4.3 Figs. 8 and 9 illustrate two types of compressometers that have been found satisfactory for wood testing. Similar apparatus is available for measurements of compression over a 2 in. (50 mm) gauge length.

9.5 Position of Failures—In order to obtain satisfactory and uniform results, it is necessary that the failures be made to develop in the body of the specimen. With specimens of uniform cross section, this result can best be obtained when the ends are at a very slightly lower moisture content than the body. With green material, it will usually suffice to close-pile

FILE NO. 124  
 COST CHARGE \_\_\_\_\_  
 LABORATORY NO. 100,831

U. S. DEPARTMENT OF AGRICULTURE  
 FOREST SERVICE

STATION - MADISON DATE - AUG. 24, 1914 SHIP NO. L-315 STICK NO. S-8  
 PIECE NO. 4 MARK d

MEASURED \_\_\_\_\_  
 TESTED \_\_\_\_\_  
 WEIGHED \_\_\_\_\_

SPECIES DOUGLAS-FIR  
 KIND OF TEST STATIC BENDING  
 LOADING CENTER  
 SPAN 28 IN.  
 GAGE LENGTH \_\_\_\_\_  
 WIDTH OF PLATE \_\_\_\_\_  
 MACHINE M 1037  
 SPEED OF MACH. 0.105 IN. PER MIN.  
 WEIGHT OF HAMMER \_\_\_\_\_  
 HEIGHT 2.02 IN.  
 WIDTH 2.00 IN.  
 LENGTH 30.10 IN.  
 CROSS-SECTION \_\_\_\_\_  
 WEIGHT 1,251 GRAMS  
 RINGS PER INCH 9  
 SAP 0%  
 SUMMERWOOD 40%  
 SEASONING GREEN  
 MOISTURE 31.4%  
 TESTED AT 75°F. TEMP. 64 % R. H.  
 KIND OF FAILURE COMPRESSION  
FOLLOWED BY SPLINT-  
ERING TENSION.  
 REMARKS \_\_\_\_\_

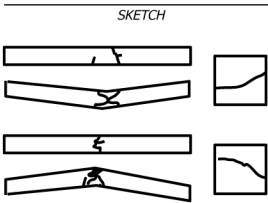
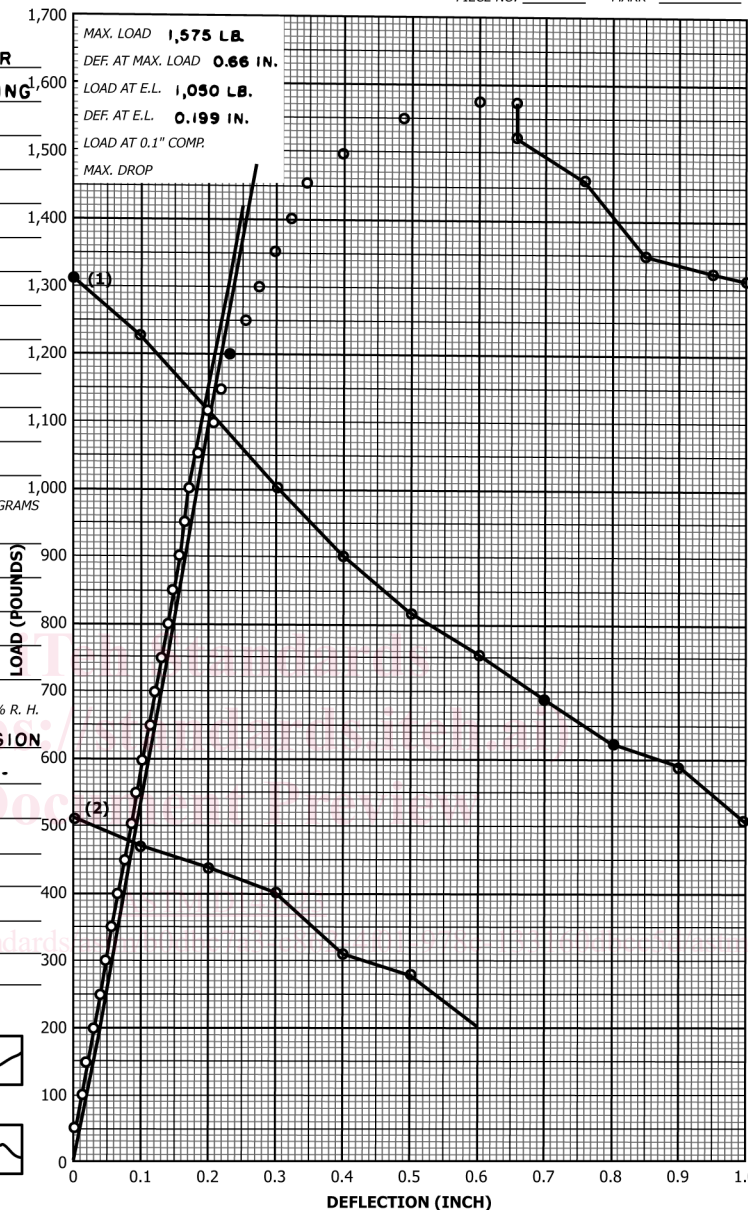


FIG. 5 Sample Data Sheet for a Manually Recorded Static Bending Test


the specimens, cover the body with a damp cloth, and expose the ends for a short time. For dry material, it shall be permitted to pile the specimens in a similar manner and place them in a desiccator, if failures in test indicate that a slight end-drying is necessary.

9.6 *Descriptions of Failure*—Compression failures shall be classified in accordance with the appearance of the fractured surface (Fig. 10). In case two or more kinds of failures develop, all shall be described in the order of their occurrence; for example, shearing followed by brooming. Each type of observed failure mode shall be photographed or sketched.

9.7 *Weight and Moisture Content*—See 8.8.

9.8 *Ring and Latewood Measurement*—When practicable, the number of rings per inch (average ring width in millimeters) and the proportion of summerwood shall be measured over a representative inch (centimeter) of cross section of the test specimen. In determining the proportion of summerwood, it is essential that the end surface be prepared so as to permit accurate latewood measurement. When the fibers are broomed over at the ends from sawing, a light sanding, planing, or similar treatment of the ends is recommended.



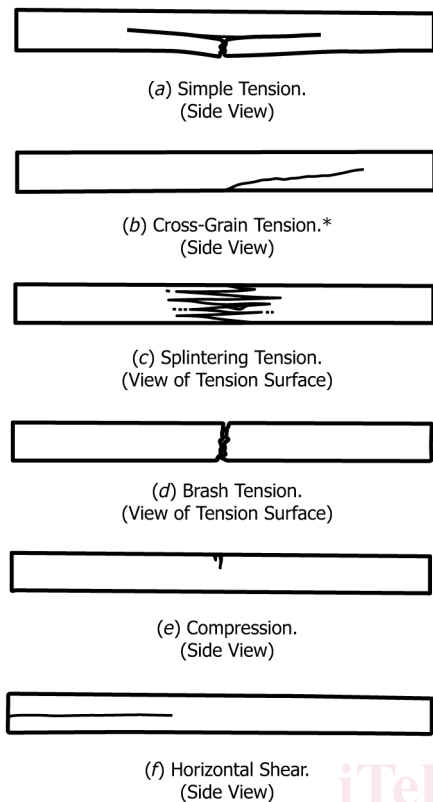

NOTE 1—The term “cross grain” shall be considered to include all deviations of grain from the direction of the longitudinal axis or longitudinal edges of the specimen. It should be noted that spiral grain may be present even to a serious extent without being evident from a casual observation.

NOTE 2—The presence of cross grain having a slope that deviates more than 1 in 20 from the longitudinal edges of the specimen shall be cause for culling the test.

**FIG. 6 Types of Failures in Static Bending** [ASTM D143](https://standards.iteh.ai/catalog/standards/astm/b0dbce7a3-c811-4242-9000-000000000000)

## 10. Impact Bending

10.1 *Size of Specimens*—The impact bending tests shall be made on 2 in. by 2 in. by 30 in. (50 mm by 50 mm by 760 mm) specimens. The actual height and width at the center and the length shall be measured (see 22.2).

10.2 *Loading and Span*—Use center loading and a span length of 28 in. (710 mm).

10.3 *Bearing Block*—A metal tup of curvature corresponding to the bearing block shown in Fig. 4 shall be used in applying the load.

10.4 *Placement of Growth Rings*—The specimen shall be placed so that the load will be applied through the bearing block to the tangential surface nearest the pith.

10.5 *Procedure*—Make the tests by increment drops in a Hatt-Turner or similar impact machine (see Fig. 11). The first drop shall be 1 in. (25 mm), after which increase the drops by 1 in. increments until a height of 10 in. (250 mm) is reached. Then use a 2 in. (50 mm) increment until complete failure occurs or a 6 in. (150 mm) deflection is reached.

10.6 *Weight of Hammer*—A 50 lbm (22.5 kg) hammer shall be used with drops up to the capacity of the machine provided

that complete failure or a 6 in. (150 mm) deflection will result for all specimens of a species. For all other cases, a 100 lbm (45 kg) hammer shall be used.

10.7 *Deflection Records*—When desired, records giving the deflection for each drop and the set, if any, shall be made until the first failure occurs. This record will also afford data from which the exact height of drop can be scaled for at least the first four falls.

NOTE 9—See Fig. 12 for a sample drum record.

10.8 *Drop Causing Failure*—The height of drop causing either complete failure or a 6 in. (150 mm) deflection shall be observed for each specimen.

10.9 *Description of Failure*—The failure shall be classified in accordance with the directions for static bending in 8.7. Each type of observed failure mode shall be photographed or sketched.

NOTE 10—See Fig. 13 for a sample of a manually recorded impact bending data sheet form. A sample data and computation card are shown in Fig. 14.

10.10 *Weight and Moisture Content*—See 8.8.

## 11. Toughness

11.1 A single-blow impact test on a small specimen is recognized as a valuable and desirable test. Several types of machines such as the Toughness, Izod and Amsler have been used, but insufficient information is available to decide whether one procedure is superior to another, or whether the results by the different test methods can be directly correlated. If the Toughness machine is used, the following procedure has been found satisfactory. To aid in standardization and to facilitate comparisons, the size of the toughness specimen has been made equal to that accepted internationally.

11.2 *Size of Specimen*—The toughness tests shall be made on 0.79 in. by 0.79 in. by 11 in. (20 mm by 20 mm by 280 mm) specimens. The actual height and width at the center and the length shall be measured (see 22.2).

11.3 *Loading and Span*—Center loading and a span length of 9.47 in. (240 mm) shall be used. The load shall be applied to a radial or tangential surface on alternate specimens.

11.4 *Bearing Block*—An aluminum tup (Fig. 15) having a radius of  $\frac{3}{4}$  in. (19 mm) shall be used in applying the load.

11.5 *Apparatus and Procedure*—Make the tests in a pendulum type toughness machine (See Fig. 15). Adjust the machine before test so that the pendulum hangs vertically, and adjust it to compensate for friction. Adjust the cable so that the load is applied to the specimen when the pendulum swings to 15° from the vertical, so as to produce complete failure by the time the downward swing is completed. Choose the weight position and initial angle (30°, 45°, or 60°) of the pendulum, so that complete failure of the specimen is obtained on one drop. Most satisfactory results are obtained when the difference between the initial and final angle is at least 10°.

NOTE 11—Many pendulum-type toughness machines are based on a design developed and used at the USDA Forest Products Laboratory in Madison, Wisconsin.


FILE NO. 124  
 COST CHARGE \_\_\_\_\_  
 LABORATORY NO. 871,902

U. S. DEPARTMENT OF AGRICULTURE  
 FOREST SERVICE

STATION - MADISON DATE - NOV. 5, 1943 SHIP NO. 1590 STICK NO. S-5  
 PIECE NO. 5 MARK d

MEASURED \_\_\_\_\_  
 TESTED \_\_\_\_\_  
 WEIGHED \_\_\_\_\_


SPECIES RED FIR  
 KIND OF TEST COMPRESSION  
 LOADING \_\_\_\_\_  
 SPAN \_\_\_\_\_  
 GAGE LENGTH 6 IN  
 WIDTH OF PLATE \_\_\_\_\_  
 MACHINE 4272  
 SPEED OF MACH. 0.0223 IN. PER MIN.  
 WEIGHT OF HAMMER \_\_\_\_\_  
 HEIGHT \_\_\_\_\_  
 WIDTH \_\_\_\_\_  
 LENGTH 8.02 IN  
 CROSS-SECTION 2.002 X 2.014 IN.  
 WEIGHT 198.9 GRAMS  
 RINGS PER INCH 7  
 SAP 0%  
 SUMMERWOOD \_\_\_\_\_  
 SEASONING KILN DRY  
 MOISTURE 11.5%  
 TESTED AT 75°F TEMP. 64 % R. H.  
 KIND OF FAILURE CRUSHING NEAR END

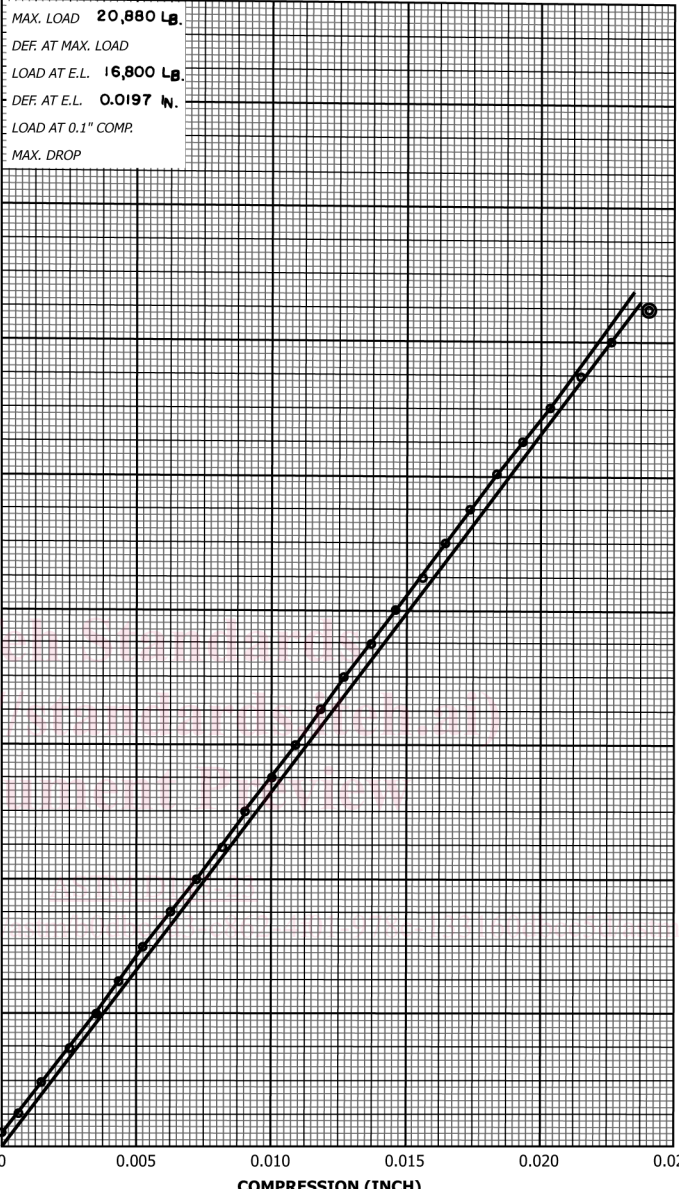

REMARKS \_\_\_\_\_  
 \_\_\_\_\_  
 \_\_\_\_\_  
 SKETCH


FIG. 7 Sample Data Sheet for a Manually Recorded Compression-Parallel-to-Grain Test



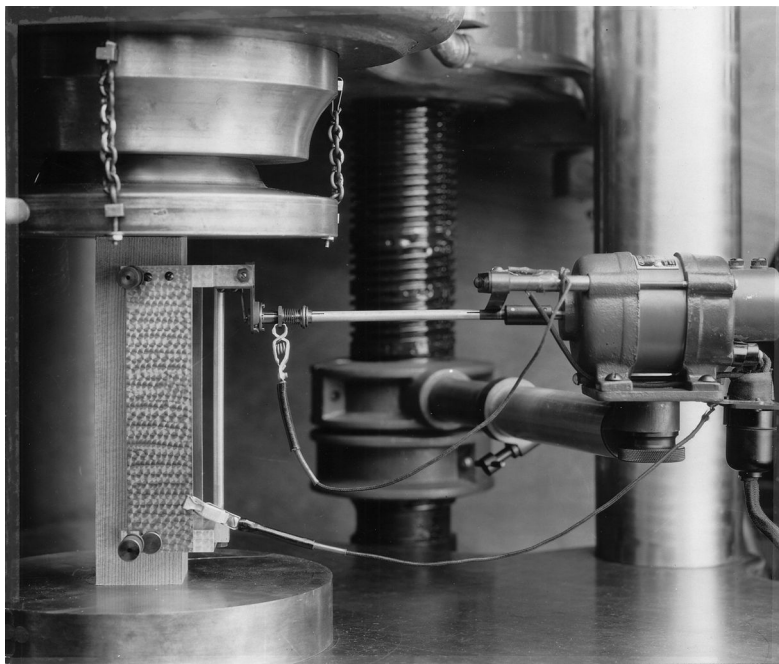

The wire in the lower right-hand corner connects the compressometer with the recording unit.

**FIG. 8 Compression-Parallel-to-Grain Test Assembly Using an Automatic Type of Compressometer to Measure Deformations**

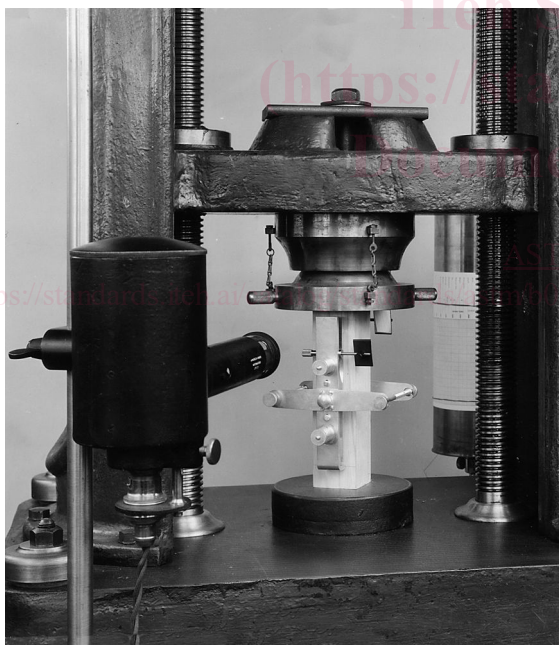

**FIG. 9 Compression-Parallel-to-Grain Test Assembly Showing Method of Measuring Deformations by Means of Roller-Type Compressometer**

where:

- $T$  = toughness (work per specimen), in. · lbf (N · m),
- $w$  = weight of pendulum, lbf (N),
- $L$  = distance from center of the supporting axis to center of gravity of the pendulum, in. (m),
- $A_1$  = initial angle, degrees, and
- $A_2$  = final angle the pendulum makes with the vertical after failure of the test specimen, degrees.

NOTE 12—See Fig. 16 for sample data and computation sheet for the toughness test.

NOTE 13—Since friction is compensated for in the machine adjustment, the initial angle may be regarded as exactly 30°, 45°, or 60°, as the case may be.

11.7 *Weight and Moisture Content*—The specimen shall be weighed immediately before test, and after test a moisture section approximately 2 in. (50 mm) in length shall be cut from the specimen near the failure (see 21.1 and 22.1).

**12. Compression Perpendicular to Grain**

12.1 *Size of Specimens*—The compression-perpendicular-to-grain tests shall be made on 2 in. by 2 in. by 6 in. (50 mm by 50 mm by 150 mm) specimens. The actual height, width, and length shall be measured (see 22.2).

12.2 *Loading*—The load shall be applied through a metal bearing plate 2 in. (50 mm) in width, placed across the upper surface of the specimen at equal distances from the ends and at right angles to the length (Fig. 17). The bearing plate surface that contacts the wood specimen shall be smooth and flat with edges that have not been rounded or chamfered. The actual width of the bearing plate shall be measured (see 22.2). The

11.6 *Calculation*—The initial and final angle shall be read to the nearest 0.1° by means of the vernier (Fig. 15) attached to the machine. The toughness shall then be calculated as follows:

$$T = wL(\cos A_2 - \cos A_1) \tag{1}$$

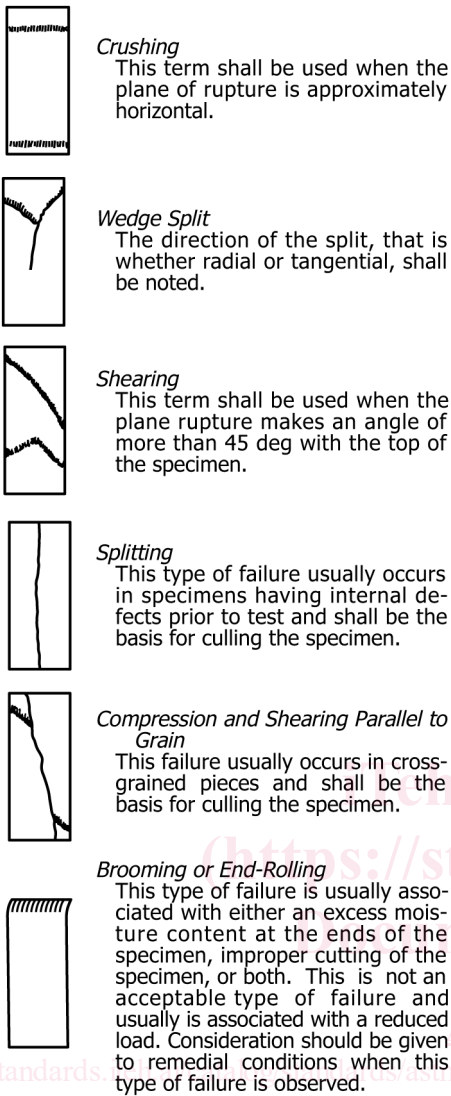


FIG. 10 Types of Failures in Compression

metal bearing plate shall be loaded in compression using a spherical bearing. The bottom of the specimen shall be fully supported by a smooth, fixed, and rigidly supported metal surface.

12.3 *Placement of Growth Rings*—The specimens shall be placed so that the load will be applied through the bearing plate to a radial surface.

12.4 *Speed of Testing*—The load shall be applied continuously throughout the test at a rate of motion of the movable crosshead of 0.012 in. (0.305 mm)/min (see 22.3).

12.5 *Load-Compression Curves:*

12.5.1 Load-compression curves shall be taken for all specimens up to 0.1 in. (2.5 mm) compression, after which the test shall be discontinued. Compression shall be measured between the loading surfaces.

NOTE 14—See Fig. 18 for a sample compression-perpendicular-to-grain data sheet form.

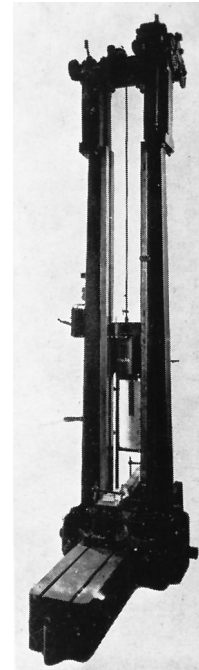


FIG. 11 Hatt-Turner Impact Machine, Illustrating Test Method of Conducting Impact Bending Test



FIG. 12 Sample Drum Record of Impact Bending Test

12.5.2 Deformations shall be recorded using displacement measurement devices that are capable of at least a Class A rating when evaluated in accordance with Practice E2309.

12.6 *Weight and Moisture Content*—The specimen shall be weighed immediately before test, and after test a moisture

FILE NO. 124  
 COST CHARGE \_\_\_\_\_  
 LABORATORY NO. 101,151

U. S. DEPARTMENT OF AGRICULTURE  
 FOREST SERVICE

MEASURED \_\_\_\_\_  
 TESTED \_\_\_\_\_  
 WEIGHED \_\_\_\_\_

STATION - MAOLSON DATE - AUG. 26, 1914 SHIP. NO. L-315 STICK NO. E-12  
 PIECE NO. 1 MARK C

SPECIES DOUGLAS-FIR  
 KIND OF TEST IMPACT BENDING  
 LOADING CENTER  
 SPAN 28 IN.  
 GAGE LENGTH \_\_\_\_\_  
 WIDTH OF PLATE \_\_\_\_\_  
 MACHINE HATT-TURNER  
 SPEED OF MACH. \_\_\_\_\_ IN. PER MIN.  
 WEIGHT OF HAMMER 50 LB.  
 HEIGHT 2.00 IN.  
 WIDTH 2.00 IN.  
 LENGTH 29.94 IN.  
 CROSS-SECTION \_\_\_\_\_  
 WEIGHT 1,370 GRAMS  
 RINGS PER INCH 8  
 SAP 100%  
 SUMMERWOOD 30%  
 SEASONING GREEN  
 MOISTURE 61.4%  
 TESTED AT 75°F TEMP. 64 % R. H.  
 KIND OF FAILURE COMPRESSION  
FOLLOWED BY SPLINTERING  
TENSION.  
 REMARKS \_\_\_\_\_

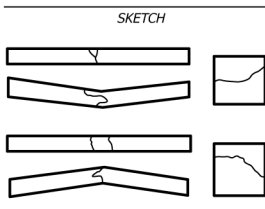
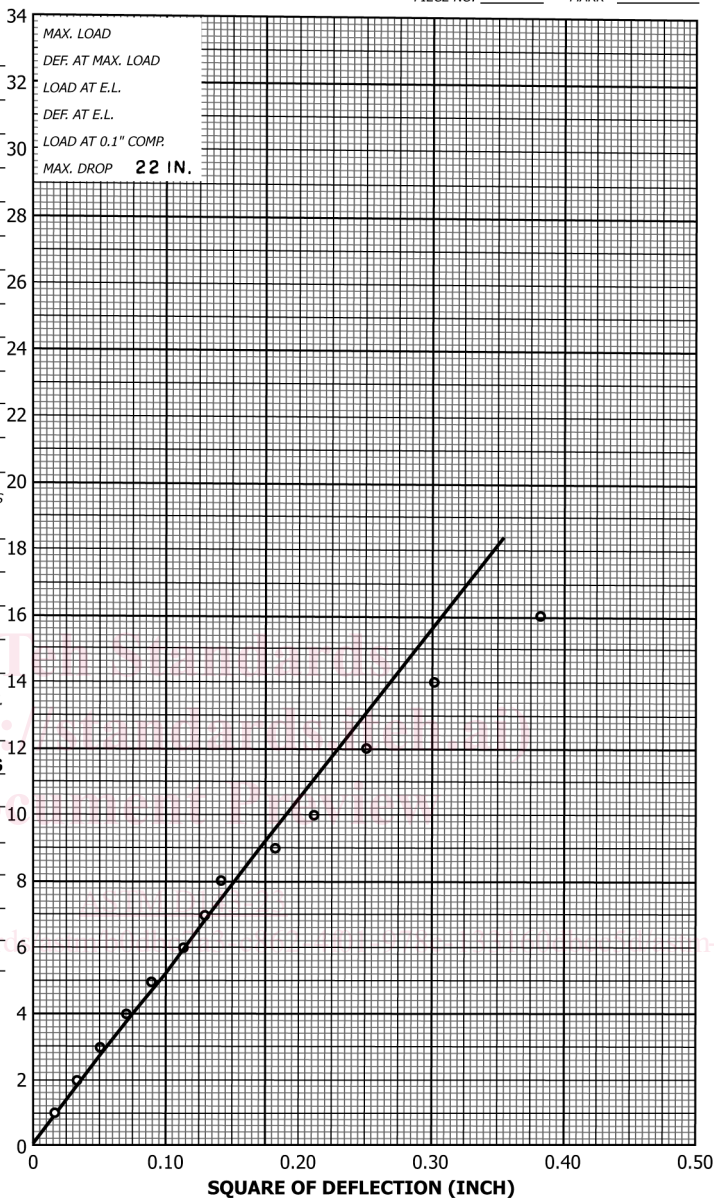


FIG. 13 Sample Data Sheet for a Manually Recorded Impact Bending Test