



Designation: D2765 – 16 (Reapproved 2024)

# Standard Test Methods for Determination of Gel Content and Swell Ratio of Crosslinked Ethylene Plastics<sup>1</sup>

This standard is issued under the fixed designation D2765; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope\*

1.1 The gel content (insoluble fraction) produced in ethylene plastics by crosslinking is determined by extracting with solvents such as decahydronaphthalene or xylenes. The methods described herein are applicable to crosslinked ethylene plastics of all densities, including those containing fillers, and all provide corrections for the inert fillers present in some of those compounds.

1.2 Test Method A, which permits most complete extraction in least time, is to be used for referee tests, but two alternative nonreferee Test Methods B and C are also described. Test Method B differs from the referee test method only in sample preparation; that is, it requires use of shavings taken at selected points in cable insulation, for example, rather than the ground sample required by the referee test method. Because the shaved particles are larger, less total surface per sample is exposed to the extractant, so this test method ordinarily yields extraction values about 1 to 2 % lower than the referee method. Test Method C requires that a specimen in one piece be extracted in xylenes at a constant temperature of 110°C. At this temperature and with a one-piece specimen, even less extraction occurs (from 3 to 9 % less than the referee test method), this method permits swell ratio (a measure of the degree of crosslinking in the gel phase) be determined.

1.3 Extraction tests are made on articles of any shape. They have been particularly useful for electrical insulations since specimens can be selected from those portions of the insulation most susceptible to insufficient crosslinking.

1.4 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system are not necessarily exact equivalents; therefore, to ensure conformance with the standard, each system shall be used independently of the other, and values from the two systems shall not be combined.

NOTE 1—This test method is equivalent to ISO 10147, Method B. It is

<sup>1</sup> These test methods are under the jurisdiction of ASTM Committee D20 on Plastics and are the direct responsibility of Subcommittee D20.15 on Thermoplastic Materials.

Current edition approved Feb. 1, 2024. Published February 2024. Originally approved in 1968. Last previous edition approved in 2016 as D2765 – 16. DOI: 10.1520/D2765-16R24.

not equivalent to ISO 10147 in any other measurement or section.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.* Specific precautionary statements are given in Sections 6, 9, and 24.

1.6 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

## 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

D297 Test Methods for Rubber Products—Chemical Analysis

D618 Practice for Conditioning Plastics for Testing

D883 Terminology Relating to Plastics

D1603 Test Method for Carbon Black Content in Olefin Plastics

D1998 Specification for Polyethylene Upright Storage Tanks

D3351 Test Method for Gel Count of Plastic Film (Withdrawn 2000)<sup>3</sup>

E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method

2.2 *ISO Standard:*

ISO 10147 Pipes and Fittings Made of Crosslinked Polyethylene (Pe-X)—Estimation of the Degree of Crosslinking by Determination of the Gel Content

## 3. Terminology

3.1 *Definitions of Terms Specific to This Standard:*

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> The last approved version of this historical standard is referenced on www.astm.org.

\*A Summary of Changes section appears at the end of this standard

3.1.1 *gel content*—the percentage by mass of polymer insoluble in a specified solvent after extraction under the specified conditions.

3.1.2 *swell ratio*—the ratio of the gel volume in the swollen state to its volume in the unswollen state.

3.2 Terms as shown in Terminology **D883** are applicable to this test method.

#### 4. Summary of Test Methods

4.1 Specimens of the crosslinked ethylene plastic are weighed and then immersed in the extracting solvent at the temperature specified by the procedure selected and for the time designated by that procedure. After extraction, the specimens are removed, dried, and reweighed as directed. The amount of material extracted is calculated and, if desired, swell ratio determined by the means described in alternative Test Method C.

#### 5. Significance and Use

5.1 Many important properties of crosslinked ethylene plastics vary with the gel content. Hence, determination of the gel content provides a means of both controlling the process and rating the quality of finished products.

5.2 Extraction tests permit verification of the proper gel content of any given crosslinked ethylene plastic and they also permit comparison between different crosslinked ethylene plastics, including those containing fillers, provided that, for the latter, the following conditions are met:

5.2.1 The filler is not soluble in either decahydronaphthalene or xylenes at the extraction temperature.

5.2.2 The amount of filler present in the compound either is known or will be determined by other means.

5.2.3 Sufficient crosslinking has been achieved to prevent migration of filler during the extraction. Usually it has been found that, at extraction levels up to 50 %, the extractant remains clear and free of filler.

5.3 A suitable antioxidant is added to the extractant to inhibit possible oxidative degradation at the extraction temperatures.

5.4 Before proceeding with this test method, reference shall be made to the specification of the material being tested. Any test specimen preparation, conditioning, dimensions, or testing parameters, or a combination thereof, covered in the materials specification shall take precedence over those mentioned in this test method. If there are no material specifications, then the default conditions apply.

#### 6. Precautions

6.1 This test method measures a much larger three – dimensional polymer network and is different than that measured by Test Method **D3351**.

6.2 It has been reported that ultra-high molecular weight polyethylene fails to completely dissolve in this procedure at times.

6.3 Atmospheric pressure affects the boiling temperature of solvents. It is possible that laboratories performing these test

methods at altitudes greater than 1500 m (5000 ft) above sea level will observe lower boiling temperatures for the solvent used. If this is observed it shall be noted in the results report.

#### TEST METHOD A (REFEREE TEST METHOD)

#### 7. Apparatus

7.1 The extraction apparatus shall be of the following general type, as illustrated in **Fig. 1**:

7.1.1 *Round-Bottom Flask*, equipped with a suitable joint that has been demonstrated to provide an essentially leak free connection. For one or two determinations at one time, a 500-mL flask is appropriate. For several determinations at one time, but not exceeding six, a 2000-mL flask is suitable.

7.1.2 *Heating Mantle* to fit the flask and with sufficient heating capacity to boil decahydronaphthalene.

7.1.3 *Reflux Condenser* with ground-glass or cork joint to fit into flask.

7.1.4 *Ring Stand and Appropriate Clamps*.

7.2 *Grinding Equipment*, suitable for reducing the sample to a fineness between 30 and 60 mesh. A bench-top laboratory mill is satisfactory, although any procedure which will produce a sample of the required fineness without generating excessive heat is acceptable.

7.2.1 *U.S. No. 30 and U.S. No. 60 Sieves*.

7.2.2 *U.S. No. 120 Stainless Steel Wire Cloth*.

7.3 *Vacuum Oven*, with vacuum source capable of creating a vacuum of at least 710 mm (28 in.) Hg and equipped with a thermometer capable of measuring to 150°C.

7.4 *Analytical Balance*, capable of weighing to 0.0001 g.

#### 8. Reagents

8.1 *Decahydronaphthalene (Decalin)*, anhydrous, boiling point 189 to 191°C.

8.2 *Xylenes*, ACS reagent grade, boiling point 138 to 141°C.

8.3 Suitable stabilizers for the solvent include:

8.3.1 *2,2'-methylene-bis (4-methyl-6-tertiary butyl phenol)* (CAS# 119-47-1)

8.3.2 *Tetrakis-(methylene-(3,5-di-(tert)-butyl-4-hydroxynamate))methane* (CAS# 6683-19-8)

8.3.3 *1,3,5-trimethyl-2,4,6-tris(3,5-di-tert-butyl-4-hydroxybenzyl)benzene* (CAS# 1709-70-2)


8.3.4 *1,3,5-tris(3,5-di-tert-butyl-4-hydroxybenzyl)-1,3,5-triazine-2,4,6(1h,3h,5h)-trione* (CAS# 27676-62-6)

#### 9. Safety Precautions

9.1 Xylenes and decahydronaphthalene are toxic and flammable solvents and shall be handled carefully. Use only in a ventilated hood. Check the effectiveness of the hood before starting the tests. Do not inhale the vapors. Excessive inhalation of the vapors has been known to cause dizziness or headache, or both. In the event of excessive inhalation, seek fresh clean air.

#### 10. Test Specimens

10.1 At least two specimens each containing  $0.300 \pm 0.015$  g of ground polymer weighed to the nearest 0.0001 g shall be tested.

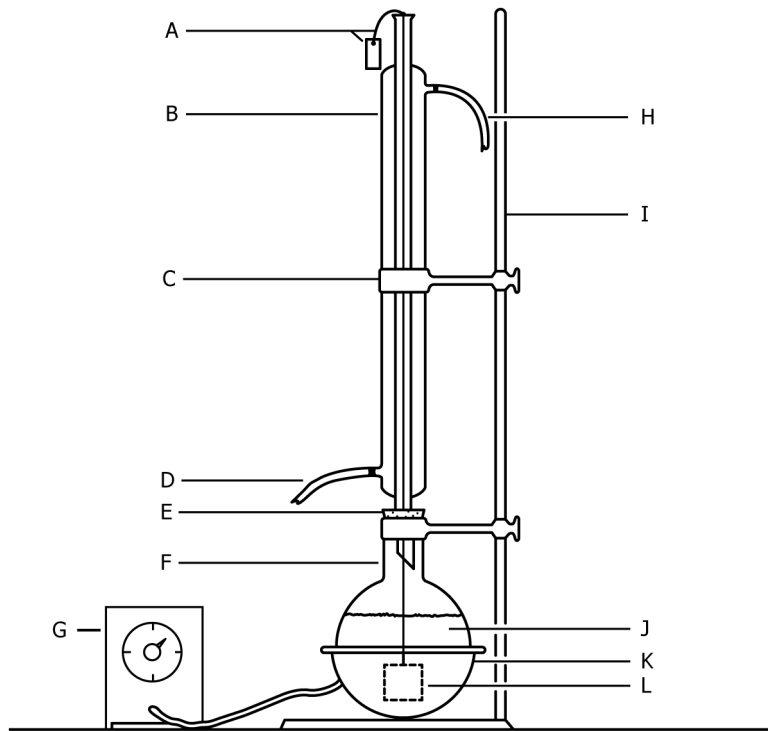

- A—Identification tag and fine wire attached to cage.
- B—Reflux condenser.
- C—Ring stand clamp.
- D—Water inlet.
- E—Joint.
- F—Large-mouth round-bottom flask.
- G—Variable transformer.
- H—Water outlet.
- I—Ring stand.
- J—Decahydronaphthalene or xylene.
- K—Heating mantle.
- L—120-mesh wire cage containing the specimen.

https://standards.iteh.ai/ (https://standards.iteh.ai) Document Preview

NOTE 1—If a slightly higher degree of accuracy is desired (about 1 to 2 %) a modified Soxhlet Extractor may be employed wherein the specimen is held in an extraction thimble. The extraction thimble, with extra-coarse fritted glass disk sealed in, will have 45-mm body diameter, 130-mm height or equivalent (height must subsequently be cut to 75 mm). The fritted disk is extra-coarse with fused edge. Glass wool 13 to 19 mm thick (½ to ¾ in.) will be placed on the bottom of the extraction thimble to support one gram 30-60 mesh ground sample which is covered with 13 to 19 mm thick layer of glass wool, a fritted glass disk and a small glass weight. The extraction thimble assembly rests upon the 55-mm portion of the thimble previously cut off, the latter inserted into the modified Soxhlet Extractor.

FIG. 1 Extraction Apparatus

10.2 The test samples shall be ground to a fineness that will pass through a 30-mesh sieve. Shake this sieved material over a 60-mesh sieve and reject any material that passes through.

10.3 Test specimens originating from insulation cut from wire shall be homogeneous and consist of an equal mixture of samples representative of insulation nearest to the conductor and samples representative of insulation nearest the outer periphery of the construction unless specific portions of the insulation are being examined for insufficient crosslinking.

**11. Procedure**

11.1 Prepare a specimen holder by cutting a piece of 120-mesh stainless steel cloth measuring approximately 80 by 40 mm (3 by 1½ in.). Fold this to form a square measuring approximately 40 mm (1½ in.). Fold two sides of this square closed by folding the cloth at the edges about 6 to 7 mm (¼ in.)

and stapling those folds. In that manner, a pouch open at the top is obtained. Weigh this pouch (W1).

11.2 Place the ground and screened sample in the weighed pouch. Weigh the pouch and specimen (W2) to the nearest 0.0001 g. Fold over the open side of the pouch and staple the edge to form a cage. Weigh the cage and sample (W3).

NOTE 2—Compaction of specimens has been observed to negatively affect the repeatability of this method. Avoid compaction of the specimens and the specimen cages.

11.3 Fill a round-bottom flask as described in 7.1.1 with enough solvent to immerse the 120-mesh cage and sample completely during extraction. Dissolve 1 % an appropriate antioxidant (8.3) in the decahydronaphthalene or xylenes.

NOTE 3—A volume of 350-mL in a 500-mL flask or 1000-mL in a 2000-mL flask has been found to be sufficient.

11.4 Boil the decahydronaphthalene or xylenes vigorously enough to ensure good agitation of the solution. Twenty to 40 drops/min from the condenser, while using 1000 g of solvent, is a satisfactory boiling rate. Suspend the cage and specimen in the solvent so that the bottom edge of the cage is almost touching the bottom of the flask. A small wire, attached to the cage and extending through the reflux condenser has been used for suspending the cage. Extract the specimen for 6 h in decahydronaphthalene or for 12 h in xylenes.

NOTE 4—Since most of the extraction occurs within less than the specified time, the period of extraction may be shortened for control tests on the basis of experience. If this is done, the time of extraction must be reported. For referee tests, extraction time is to be as specified by this test method.

11.5 After extraction, place the cage and specimen immediately in a vacuum oven preheated to 150°C. Dry the specimen to constant weight under at least 710 mm (28 in.) Hg vacuum. Cool and weigh ( $W_4$ ). If the compound absorbs moisture, cool the specimen in a desiccator before weighing.

NOTE 5—It has been reported that drying time sometimes can be materially shortened if the cage and sample are cooled for 15 min and then are placed either on a suspended screen or on lint-free absorbent material to remove excess solvent before being put into the vacuum drying oven.

11.6 If extraction tests are regularly made, it is acceptable to leave the apparatus assembled and the extracting solvent (containing inhibitor as directed) reused until it darkens. However, if there is any doubt about the values obtained with reused extractant, the test shall be repeated with fresh extractant.

NOTE 6—If the modified Soxhlet apparatus is used, the complete thimble assembly containing 1 g of sample is weighed to the nearest  $\pm 0.0001$  g before extraction and after vacuum drying.

12. Calculation

12.1 Calculate the solvent extraction in percent as follows:

$$\text{Extract, \%} = (\text{weight lost during extraction}) / \quad (1)$$

$$(\text{weight of original specimen} - \text{weight of filler})$$

$$= [(W_3 - W_4) / ((W_2 - W_1) - F(W_2 - W_1))] \times 100$$

$$= [(W_3 - W_4) / ((1 - F)(W_2 - W_1))] \times 100$$

where:

$W_1$  = weight of the pouch (sealed on three sides, one side open),

$W_2$  = weight of the specimen and the pouch (sealed on three sides, one side open),

$W_3$  = weight of the specimen and the cage, after being stapled shut,

$W_4$  = weight of the specimen and the cage after extraction and drying,

$F$  = fraction of filler (which must be insoluble in decahydronaphthalene or xylenes) in the polyethylene compound, and

gel content = 100 – percent extract.

NOTE 7—If the fraction of filler in the material is not known, the test methods described in Test Method D1603 or in Test Methods D297, may be used to determine filler content.

13. Report

13.1 Report the following information:

13.1.1 Complete identification of the compound,

13.1.2 Density of the polyethylene in the compound (usually as identified by its supplier),

13.1.3 Weight percent of polyethylene in the compound or filler content (usually as identified by its supplier or determined by the test methods identified in Note 7),

13.1.4 Percent extract; the value for each specimen and the average for the sample,

13.1.5 Solvent used, time of extraction, and any pertinent sample preparation, and

13.1.6 Any unusual or abnormal behavior observed during the test (6.3).

TEST METHOD B (NONREFEREE TEST METHOD)

14. Scope


14.1 This modification of the referee test method was developed particularly for wire and cable insulations and differs from the referee test method only in specimen preparation.

14.2 In using this alternative test method, it is recognized that the values obtained at times, are lower than those obtained by referee Test Method A for the reason given in 1.2.

15. Test Specimens

15.1 Using a wood plane, shave a strip approximately  $0.4 \pm 0.05$  mm ( $0.015 \pm 0.002$  in.) thick parallel to the axis of the insulated conductor. The test strip used for extraction shall be taken next to the conductor only when strand shielding tapes or compounds are not employed. In high-voltage cable employing strand shielding tapes or compounds, the strip shall be shaved as closely as possible along the shielded surface, being careful not to include any of the semiconducting compound (see Fig. 2).

15.2 A section approximately 6 mm ( $1/4$  in.) wide, depending on cable size, is cut longitudinally through the center portion of the strip obtained as described in 14.1. The outer sections of this strip are discarded, thus leaving only a sample

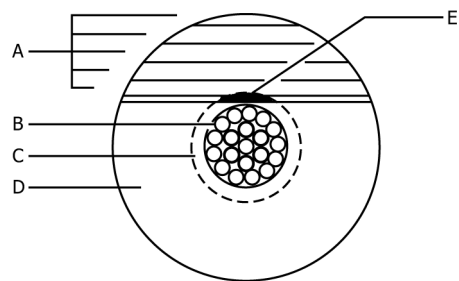

A—Shaved strips to be discarded.  
 B—Semiconducting strand shield.  
 C—Area most susceptible to insufficient crosslinking.  
 D—Crosslinked polyethylene insulation.  
 E—Specimen for solvent extraction (shaded area).

FIG. 2 Enlarged Cross-Sectional View of High-Voltage Cable Showing Sample Location