



**SLOVENSKI STANDARD**  
**SIST EN ISO 6721-1:1999**

01-maj-1999

---

Dc`ja Yfb]a Uhf]U]`E`8 c`c Yj Ub^X]bUa ] b]`a Y Ubg\_]`Ug]bcgh]`E`%`XY.  
Gd`cybUbu YUf]GC`\* +&%%% - ( žj \_`f bc`g`h^ b] b]a `dcdfUj \_ca `%% - ) Ł

Plastics - Determination of dynamic mechanical properties - Part 1: General principles  
(ISO 6721-1:1994, including Technical Corrigendum 1:1995)

Kunststoffe - Bestimmung dynamisch-mechanischer Eigenschaften - Teil 1: Allgemeine  
Grundlagen (ISO 6721-1:1994, einschließlich Technische Korrektur 1:1995)

Plastiques - Détermination des propriétés mécaniques dynamiques - Partie 1: Principes  
généraux (ISO 6721-1:1994, Rectificatif Technique 1:1995 inclus)

[https://standards.iteh.ai/catalog/standards/sist/c6aec01d-4c98-465d-b9d5-](https://standards.iteh.ai/catalog/standards/sist/c6aec01d-4c98-465d-b9d5-c59622af0315/sist-en-iso-6721-1-1999)

Ta slovenski standard je istoveten z: **EN ISO 6721-1:1996**

---

**ICS:**

83.080.01	Polimerni materiali na splošno	Plastics in general
-----------	-----------------------------------	---------------------

**SIST EN ISO 6721-1:1999** en

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST EN ISO 6721-1:1999

<https://standards.iteh.ai/catalog/standards/sist/c6aec01d-4c98-465d-b9d5-c59622af0315/sist-en-iso-6721-1-1999>

EUROPEAN STANDARD

EN ISO 6721-1

NORME EUROPÉENNE

EUROPÄISCHE NORM

February 1996

ICS 83.080

Descriptors: see ISO document

English version

Plastics - Determination of dynamic mechanical  
properties - Part 1: General principles  
(ISO 6721-1:1994, including Technical  
Corrigendum 1:1995)

Plastiques - Détermination des propriétés  
mécaniques dynamiques - Partie 1: Principes  
généraux (ISO 6721-1:1994, Rectificatif  
Technique 1:1995 inclus)

Kunststoffe - Bestimmung dynamisch-mechanischer  
Eigenschaften - Teil 1: Allgemeine Grundlagen  
(ISO 6721-1:1994, einschließlich Technische  
Korrektur 1:1995)

**STANDARD PREVIEW**  
(standards.iteh.ai)  
SIST EN ISO 6721-1:1999  
<https://standards.iteh.ai/catalog/standards/sist/c6a6c01d-4c98-465d-b9d5-c59622af0315/sist-en-iso-6721-1-1999>

This European Standard was approved by CEN on 1996-01-26. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

The European Standards exist in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

## CEN

European Committee for Standardization  
Comité Européen de Normalisation  
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

## Foreword

The text of the International Standard from Technical Committee ISO/TC 61 "Plastics" of the International Organization for Standardization (ISO) has been taken over as a European Standard by Technical Committee CEN/TC 249 "Plastics", the secretariat of which is held by IBN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 1996, and conflicting national standards shall be withdrawn at the latest by August 1996.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

## Endorsement notice

The text of the International Standard ISO 6721-1:1994 including Technical Corrigendum 1:1995 has been approved by CEN as a European Standard without any modification.

(standards.iteh.ai)

SIST EN ISO 6721-1:1999

<https://standards.iteh.ai/catalog/standards/sist/c6aec01d-4c98-465d-b9d5-c59622a10315/sist-en-iso-6721-1-1999>

INTERNATIONAL  
STANDARD

**ISO**  
**6721-1**

First edition  
1994-11-01

---

---

**Plastics — Determination of dynamic  
mechanical properties —**

**Part 1:**

**General principles  
(standards.iteh.ai)**

*Plastiques — Détermination des propriétés mécaniques dynamiques —*

*Partie 1: Principes généraux*  
<https://standards.iteh.ai/en/standards/SIST-EN-ISO-6721-1-1999>



Reference number  
ISO 6721-1:1994(E)

## ISO 6721-1:1994(E)

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 6721-1 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 2, *Mechanical properties*.

Together with ISO 6721-2 and ISO 6721-3, it cancels and replaces ISO 537:1989 and ISO 6721:1983, which have been technically revised.

ISO 6721 consists of the following parts, under the general title *Plastics — Determination of dynamic mechanical properties*:

- Part 1: *General principles*
- Part 2: *Torsion-pendulum method*
- Part 3: *Flexural vibration — Resonance-curve method*
- Part 4: *Tensile vibration — Non-resonance method*
- Part 5: *Flexural vibration — Non-resonance method*
- Part 6: *Shear vibration — Non-resonance method*
- Part 7: *Torsional vibration — Non-resonance method*

Additional parts are planned.

Annexes A, B and C of this part of ISO 6721 are for information only.

© ISO 1994

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization  
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

## Introduction

The methods specified in the various parts of ISO 6721 can be used for determining storage and loss moduli of plastics over a range of temperatures or frequencies by varying the temperature of the specimen or the frequency of oscillation. Plots of the storage or loss moduli, or both, are indicative of viscoelastic characteristics of the specimen. Regions of rapid changes in viscoelastic properties at particular temperatures or frequencies are normally referred to as transition regions. Furthermore, from the temperature and frequency dependencies of the loss moduli, the damping of sound and vibration of polymer or metal-polymer systems can be estimated.

Apparent discrepancies may arise in results obtained under different experimental conditions. Without changing the observed data, reporting in full (as described in the various parts of ISO 6721) the conditions under which the data were obtained will enable apparent differences observed in different studies to be reconciled.

The definitions of complex moduli apply exactly only to sinusoidal oscillations with constant amplitude and constant frequency during each measurement. On the other hand, measurements of small phase angles between stress and strain involve some difficulties under these conditions. Because these difficulties are not involved in some methods based on freely decaying vibrations and/or varying frequency near resonance, these methods are used frequently (see part 2 and part 3). In these cases, some of the equations that define the viscoelastic properties are only approximately valid.

**iTeh STANDARD PREVIEW**  
This page intentionally left blank  
**(standards.iteh.ai)**

[SIST EN ISO 6721-1:1999](https://standards.iteh.ai/catalog/standards/sist/c6aec01d-4c98-465d-b9d5-c59622af0315/sist-en-iso-6721-1-1999)

<https://standards.iteh.ai/catalog/standards/sist/c6aec01d-4c98-465d-b9d5-c59622af0315/sist-en-iso-6721-1-1999>



# Plastics — Determination of dynamic mechanical properties —

## Part 1: General principles

### 1 Scope

The various parts of ISO 6721 specify methods for the determination of the dynamic mechanical properties of rigid plastics within the region of linear viscoelastic behaviour. Part 1 is an introductory section which includes the definitions and all aspects that are common to the individual test methods described in the subsequent parts.

Different deformation modes may produce results that are not directly comparable. For example, tensile vibration results in a stress which is uniform across the whole thickness of the specimen, whereas flexural measurements are influenced preferentially by the properties of the surface regions of the specimen.

Values derived from flexural-test data will be comparable to those derived from tensile-test data only at strain levels where the stress-strain relationship is linear and for specimens which have a homogeneous structure.

### 2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this part of ISO 6721. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this part of ISO 6721 are encouraged to investigate the possibility of applying the most recent editions of the

standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 291:1977, *Plastics — Standard atmospheres for conditioning and testing.*

ISO 293:1986, *Plastics — Compression moulding test specimens of thermoplastic materials.*

ISO 294:<sup>1)</sup> *Plastics — Injection moulding of test specimens of thermoplastic materials.*

ISO 295:1991, *Plastics — Compression moulding of test specimens of thermosetting materials.*

ISO 1268:1974, *Plastics — Preparation of glass fibre reinforced, resin bonded, low-pressure laminated plates or panels for test purposes.*

ISO 2818:1994, *Plastics — Preparation of test specimens by machining.*

ISO 4593:1993, *Plastics — Film and sheeting — Determination of thickness by mechanical scanning.*

ISO 6721-2:1994, *Plastics — Determination of dynamic mechanical properties — Part 2: Torsion-pendulum method.*

ISO 6721-3:1994, *Plastics — Determination of dynamic mechanical properties — Part 3: Flexural vibration — Resonance-curve method.*

1) To be published. (Revision of ISO 294:1975)

### 3 Definitions

For the purposes of the various parts of this International Standard, the following definitions apply.

NOTE 1 Most of the terms defined here are also defined in ISO 472:1988, *Plastics — Vocabulary*. The definitions given here are not strictly identical with, but are equivalent to, those in ISO 472:1988.

**3.1 complex modulus,  $M^*$ :** The ratio of dynamic stress, given by  $\sigma(t) = \sigma_A \exp(i2\pi ft)$ , and dynamic strain, given by  $\varepsilon(t) = \varepsilon_A \exp[i(2\pi ft - \delta)]$ , of a viscoelastic material that is subjected to a sinusoidal vibration, where  $\sigma_A$  and  $\varepsilon_A$  are the amplitudes of the stress and strain cycles,  $f$  is the frequency,  $\delta$  is the phase angle between stress and strain (see 3.5 and figure 1) and  $t$  is time.

It is expressed in pascals (Pa).

Depending on the mode of deformation, the complex modulus may be one of several types:  $E^*$ ,  $G^*$ ,  $K^*$  or  $L^*$  (see table 3).

$$M^* = M' + iM'' \quad (\text{see 3.2 and 3.3}) \quad \dots (1)$$

where

$$i = (-1)^{1/2} = \sqrt{-1}$$

For the relationships between the different types of complex modulus, see table 1.

#### NOTES

2 For isotropic viscoelastic materials, only two of the elastic parameters  $G^*$ ,  $E^*$ ,  $K^*$ ,  $L^*$  and  $\mu^*$  are independent ( $\mu^*$  is the complex Poisson's ratio, given by  $\mu^* = \mu' + i\mu''$ ).

3 The most critical term containing Poisson's ratio  $\mu$  is the "volume term"  $1 - 2\mu$ , which has values between 0 and 0,4 for  $\mu$  between 0,5 and 0,3. The relationships in table 1 containing the "volume term"  $1 - 2\mu$  can only be used if this term is known with sufficient accuracy.

It can be seen from table 1 that the volumetric term  $1 - 2\mu$  can only be estimated with any confidence from a knowledge of the bulk modulus  $K$  or the uniaxial-strain modulus  $L$  and either  $E$  or  $G$ . This is because  $K$  and  $L$  measurements involve deformations when the volumetric strain component is relatively large.

4 Up to now, no measurements of the bulk modulus  $K$ , and only a small number of results relating to relaxation experiments measuring  $K(t)$ , have been described in the literature.

5 The uniaxial-strain modulus  $L$  is based upon a load with a high hydrostatic-stress component. Therefore values of  $L$  compensate for the lack of  $K$  values, and the "volume term"  $1 - 2\mu$  can be estimated with sufficient accuracy based upon the modulus pairs  $(G, L)$  and  $(E, L)$ . The pair  $(G, L)$  is preferred, because  $G$  is based upon loads without a hydrostatic component.

6 The relationships given in table 1 are valid for the complex moduli as well as their magnitudes (see 3.4).

7 Most of the relationships for calculating the moduli given in the other parts of this International Standard are, to some extent, approximate. They do not take into account e.g. "end effects" caused by clamping the specimens, and they include other simplifications. Using the relationships given in table 1 therefore often requires additional corrections to be made. These are given in the literature (see e.g. references [1] and [2] in the bibliography).

8 For linear-viscoelastic behaviour, the complex compliance  $C^*$  is the reciprocal of the complex modulus  $M^*$ , i.e.

$$M^* = (C^*)^{-1} \quad \dots (2)$$

Thus

$$M' + iM'' = \frac{C' - iC''}{(C')^2 + (C'')^2} \quad \dots (3)$$

**3.2 storage modulus,  $M'$ :** The real part of the complex modulus  $M^*$  [see figure 1 b)].

The storage modulus is expressed in pascals (Pa).


It is proportional to the maximum energy stored during a loading cycle and represents the stiffness of a viscoelastic material.

The different types of storage modulus, corresponding to different modes of deformation, are:  $E'_t$  tensile storage modulus,  $E'_f$  flexural storage modulus,  $G'_s$  shear storage modulus,  $G'_{t0}$  torsional storage modulus,  $K'$  bulk storage modulus,  $L'_c$  uniaxial-strain and  $L'_w$  longitudinal-wave storage modulus.

**3.3 loss modulus,  $M''$ :** The imaginary part of the complex modulus [see figure 1b)].

The loss modulus is expressed in pascals (Pa).

It is proportional to the energy dissipated (lost) during one loading cycle. As with the storage modulus (see 3.2), the mode of deformation is designated as in table 3, e.g.  $E''_t$  is the tensile loss modulus.

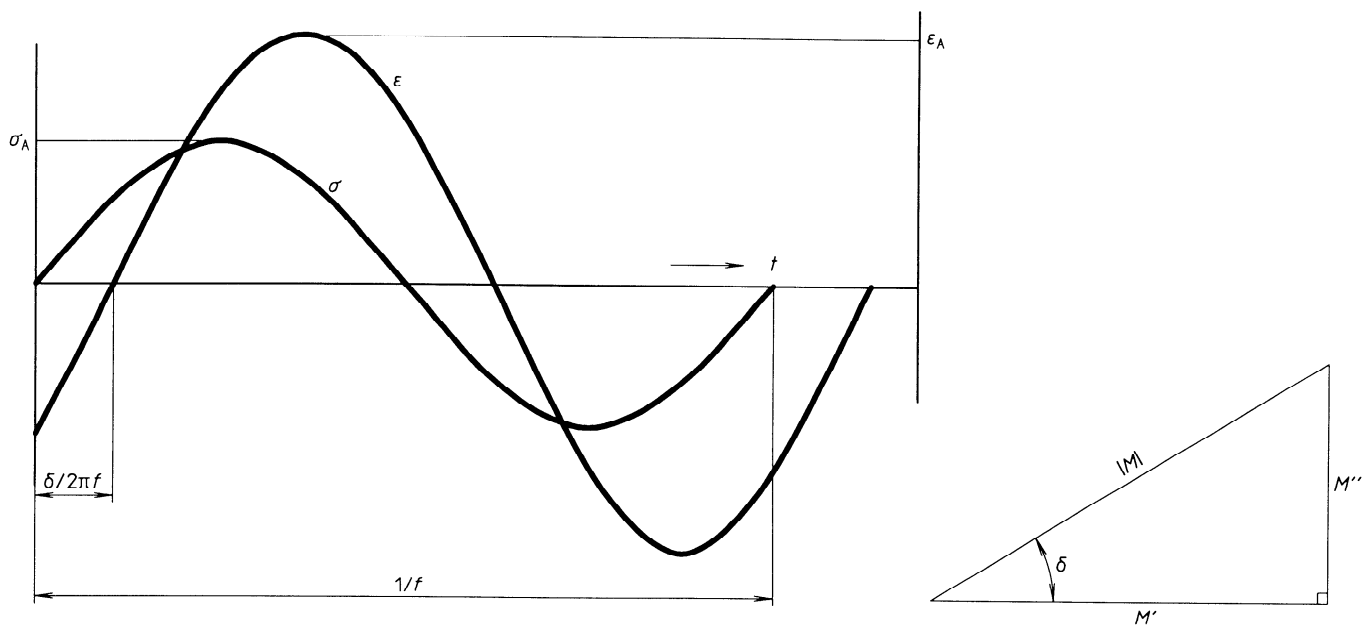

a) The phase shift  $\delta/2\pi f$  between the stress  $\sigma$  and strain  $\epsilon$  in a viscoelastic material subjected to sinusoidal oscillation ( $\sigma_A$  and  $\epsilon_A$  are the respective amplitudes,  $f$  is the frequency).

b) The relationship between the storage modulus  $M'$ , the loss modulus  $M''$ , the phase angle  $\delta$  and the magnitude  $|M|$  of the complex modulus  $M^*$ .

**iTeh STANDARD PREVIEW**  
**Figure 1 — Phase angle and complex modulus**  
**(standards.iteh.ai)**

SIST EN ISO 6721-1:1999

<https://standards.iteh.ai/catalog/standards/sist/c6aec01d-4c98-465d-b9d5-c59622af0315/sist-en-iso-6721-1-1999>

**Table 1 — Relationships between moduli for uniformly isotropic materials**

	$G$ and $\mu$	$E$ and $\mu$	$K$ and $\mu$	$G$ and $E$	$G$ and $K$	$E$ and $K$	$G$ and $L$ <sup>1)</sup>
Poisson's ratio, $\mu$ $1 - 2\mu = 2$ )				$3 - \frac{E}{G}$	$\frac{G/K}{1 + G/3K}$	$\frac{E}{3K}$	$\frac{1}{L/G - 1}$
Shear modulus, $G =$		$\frac{E}{2(1 + \mu)}$	$\frac{3K(1 - 2\mu)}{2(1 + \mu)}$			$\frac{E}{3 - E/3K}$	
Tensile modulus, $E =$	$2G(1 + \mu)$		$3K(1 - 2\mu)$		$\frac{3G}{1 + G/3K}$		$\frac{3G(1 - 4G/3L)}{1 - G/L}$
Bulk modulus, $K =$ <sup>3)</sup>	$\frac{2G(1 + \mu)}{3(1 - 2\mu)}$	$\frac{E}{3(1 - 2\mu)}$		$\frac{G}{3(3G/E - 1)}$			$L - \frac{4G}{3}$
Unaxial-strain or longitudinal-wave modulus, $L =$	$\frac{2G(1 - \mu)}{1 - 2\mu}$	$\frac{E(1 - \mu)}{(1 + \mu)(1 - 2\mu)}$	$\frac{3K(1 - \mu)}{1 + \mu}$	$\frac{G(4G/E - 1)}{3G/E - 1}$	$K + \frac{4G}{3}$	$\frac{K(1 + E/3K)}{1 - E/9K}$	

1) See note 5.  
2) See note 3.  
3) See note 4.

**3.4 magnitude  $|M|$  of the complex modulus:** The root mean square value of the storage and the loss moduli as given by the equation

$$|M|^2 = (M')^2 + (M'')^2 = (\sigma_A/\varepsilon_A)^2 \quad \dots (4)$$

where  $\sigma_A$  and  $\varepsilon_A$  are the amplitudes of the stress and the strain cycles, respectively.

The complex modulus is expressed in pascals (Pa).

The relationship between the storage modulus  $M'$ , the loss modulus  $M''$ , the phase angle  $\delta$ , and the magnitude  $|M|$  of the complex modulus is shown in figure 1 b). As with the storage modulus, the mode of deformation is designated as in table 3, e.g.  $|E_t|$  is the magnitude of the tensile complex modulus.

**3.5 phase angle,  $\delta$ :** The phase difference between the dynamic stress and the dynamic strain in a viscoelastic material subjected to a sinusoidal oscillation (see figure 1).

The phase angle is expressed in radians (rad).

As with the storage modulus (see 3.2), the mode of deformation is designated as in table 3, e.g.  $\delta_t$  is the tensile phase angle.

**3.6 loss factor ( $\tan \delta$ ):** The ratio between the loss modulus and the storage modulus, given by the equation

$$\tan \delta = M''/M' \quad \dots (5)$$

where  $\delta$  is the phase angle (see 3.5) between the stress and the strain.

The loss factor is expressed as a dimensionless number.

The loss factor  $\tan \delta$  is commonly used as a measure of the damping in a viscoelastic system. As with the storage modulus (see 3.2), the mode of deformation is designated as in table 3, e.g.  $\tan \delta_t$  is the tensile loss factor.

**3.7 stress-strain hysteresis loop:** The stress expressed as a function of the strain in a viscoelastic material subject to sinusoidal vibrations. Provided the viscoelasticity is linear in nature, this curve is an ellipse (see figure 2).

**3.8 damped vibration:** The time-dependent deformation or deformation rate  $X(t)$  of a viscoelastic sys-

tem undergoing freely decaying vibrations (see figure 3), given by the equation

$$X(t) = X_0 \exp(-\beta t) \times \sin 2\pi f_d t \quad \dots (6)$$

where

$X_0$  is the magnitude, at zero time, of the envelope of the cycle amplitudes;

$f_d$  is the frequency of the damped system;

$\beta$  is the decay constant (see 3.9).

**3.9 decay constant,  $\beta$ :** The coefficient that determines the time-dependent decay of damped free vibrations, i.e. the time dependence of the amplitude  $X_q$  of the deformation or deformation rate [see figure 3 and equation (6)].

The decay constant is expressed in reciprocal seconds ( $s^{-1}$ ).

**3.10 logarithmic decrement,  $\Lambda$ :** The natural logarithm of the ratio of two successive amplitudes, in the same direction, of damped free oscillations of a viscoelastic system (see figure 3), given by the equation

$$\Lambda = \ln(X_q/X_{q+1}) \quad \dots (7)$$

where  $X_q$  and  $X_{q+1}$  are two successive amplitudes of deformation or deformation rate in the same direction.

The logarithmic decrement is expressed as a dimensionless number.

It is used as a measure of the damping in a viscoelastic system.

Expressed in terms of the decay constant  $\beta$  and the frequency  $f_d$ , the logarithmic decrement is given by the equation

$$\Lambda = \beta/f_d \quad \dots (8)$$

The loss factor  $\tan \delta$  is related to the logarithmic decrement by the approximate equation

$$\tan \delta \approx \Lambda/\pi \quad \dots (9)$$

NOTE 9 Damped freely decaying vibrations are especially suitable for analysing the type of damping in the material under test (i.e. whether the viscoelastic behaviour is linear or non-linear) and the friction between moving and fixed components of the apparatus (see annex B).