

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 306:2000

<https://standards.iteh.ai/catalog/standards/sist/e0217153-8059-418a-b03e-40066da5177d/sist-en-iso-306-2000>

EUROPEAN STANDARD

EN ISO 306

NORME EUROPÉENNE

EUROPÄISCHE NORM

December 1996

ICS 83.080.20

Descriptors: plastics, thermoplastic resins, tests, softening tests, determination, softening point, test equipment

English version

Plastics - Thermoplastic materials - Determination
of Vicat softening temperature (VST)
(ISO 306:1994)

Plastiques - Matières thermoplastiques -
Détermination de la température de
ramollissement Vicat (VST) (ISO 306:1994)

Kunststoffe - Thermoplaste - Bestimmung der
Vicat-Erweichungstemperatur (VST)
(ISO 306:1994)

(standards.iteh.ai)

SIST EN ISO 306:2000

<https://standards.iteh.ai/catalog/standards/sist/e0217153-8059-418a-b03e-40066da5177d/sist-en-iso-306-2000>

This European Standard was approved by CEN on 1996-01-04. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

The European Standards exist in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Page 2
EN ISO 306:1996

Foreword

The text of the International Standard from Technical Committee ISO/TC 61 "Plastics" of the International Organization for Standardization (ISO) has been taken over as an European Standard by Technical Committee CEN/TC 249 "Plastics", the secretariat of which is held by IBN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 1997, and conflicting national standards shall be withdrawn at the latest by June 1997.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Endorsement notice

The text of the International Standard ISO 306:1994 has been approved by CEN as a European Standard without any modification.



iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 306:2000

<https://standards.iteh.ai/catalog/standards/sist/e0217153-8059-418a-b03e-40066da5177d/sist-en-iso-306-2000>

ANNEX 1

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION

INTERNATIONAL
STANDARD

ISO
306

Third edition
1994-08-01

**Plastics — Thermoplastic materials —
Determination of Vicat softening
temperature (VST)**

iTeh STANDARD PREVIEW

(standards.iteh.ai)
*Plastiques — Matières thermoplastiques — Détermination de la
température de ramollissement Vicat (VST)*

SIST EN ISO 306:2000

<https://standards.iteh.ai/catalog/standards/sist/e0217153-8059-418a-b03e-40066da5177d/sist-en-iso-306-2000>



Reference number
ISO 306:1994(E)

ISO 306:1994(E)**Foreword**

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 306 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 2, *Mechanical properties*.

This third edition cancels and replaces the second edition (ISO 306:1987), which has been technically revised.

© ISO 1994

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Plastics — Thermoplastic materials — Determination of Vicat softening temperature (VST)

1 Scope

1.1 This International Standard specifies four methods for the determination of the Vicat softening temperature (VST) of thermoplastic materials:

- Method A50 using a force of 10 N and a heating rate of 50 °C/h
- Method B50 using a force of 50 N and a heating rate of 50 °C/h
- Method A120 using a force of 10 N and a heating rate of 120 °C/h
- Method B120 using a force of 50 N and a heating rate of 120 °C/h

1.2 The methods specified are applicable only to thermoplastics, for which they give a measure of the temperature at which the thermoplastics start to soften rapidly.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

1) To be published. (Revision of ISO 294:1975)

2) To be published. (Revision of ISO 2818:1980)

ISO 291:1977, *Plastics — Standard atmospheres for conditioning and testing.*

ISO 293:1986, *Plastics — Compression moulding test specimens of thermoplastic materials.*

ISO 294:—¹⁾, *Plastics — Injection moulding of test specimens of thermoplastic materials.*

ISO 2818:—²⁾, *Plastics — Preparation of test specimens by machining.*

ISO 3167:1993, *Plastics — Multipurpose test specimens.*

3 Principle

Determination of the temperature at which a standard indenter penetrates 1 mm into the surface of a plastic test specimen under one of the loads given in 1.1 when the temperature is raised at a uniform rate.

The temperature at 1 mm penetration is quoted as the VST in degrees Celsius.

4 Apparatus

The apparatus consists essentially of:

4.1 Rod, provided with a **load-carrying plate** (4.4), held in a **rigid metal frame** so that it can move freely in the vertical direction, the base of the frame serving to support the test specimen under the indenting tip at the end of the rod (see figure 1).

Unless the rod and frame members have the same linear thermal expansion coefficient, the differential

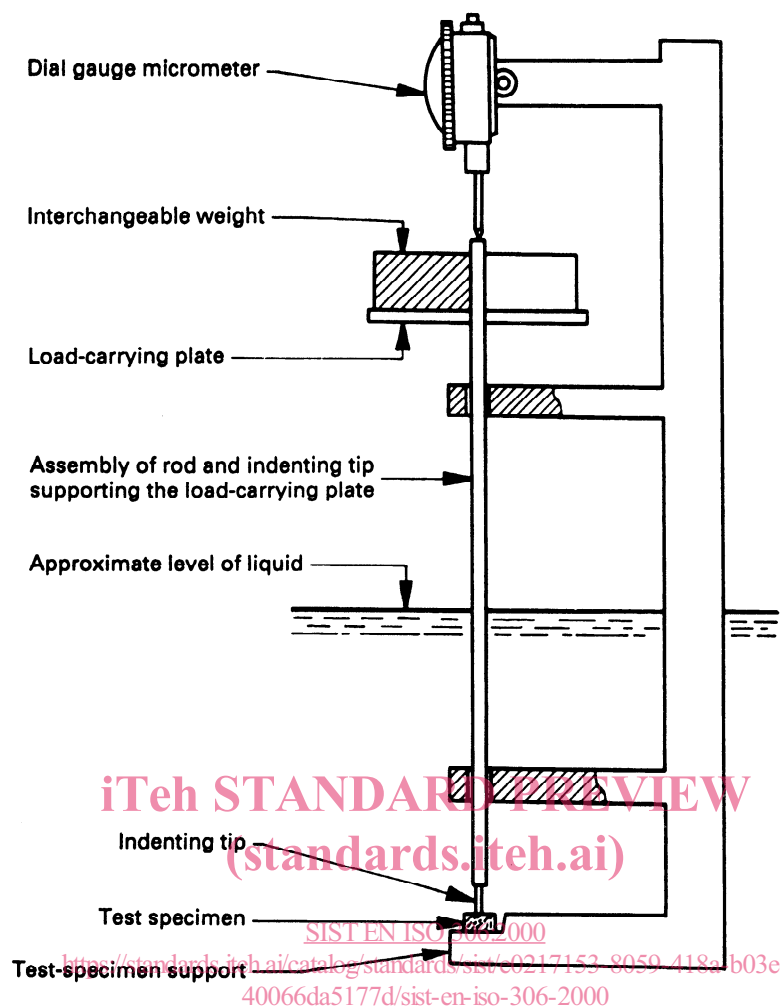


Figure 1 — Example of apparatus with a heating bath for the determination of the VST

change in the length of these parts introduces an error in the readings of the apparent deformation of the test specimen. A blank test shall be made on each apparatus using a test specimen made of rigid material having a low coefficient of expansion.³⁾ The temperature ranges to be used shall be covered and a correction term determined for each temperature. If the correction term is 0,02 mm or greater, its algebraic sign shall be noted and the term applied to each test by adding it algebraically to the reading of apparent penetration. It is recommended that the apparatus be constructed of low thermal expansion alloy.

4.2 Indenting tip, preferably of hardened steel, 3 mm long, of circular cross-section, and area $1,000 \text{ mm}^2 \pm 0,015 \text{ mm}^2$, fixed at the bottom of the rod (4.1). The lower surface of the indenting tip shall be plane and perpendicular to the axis of the rod and free from burrs.

3) Invar and borosilicate glass have been found suitable for this purpose.

4.3 Calibrated micrometer dial gauge (or other suitable measuring instrument), to measure to $\pm 0,01 \text{ mm}$ the penetration of the indenting tip into the test specimen. The thrust of the dial gauge, which contributes to the thrust on the test specimen, shall be recorded (see 4.4).

NOTES

1 In certain types of apparatus, the force of the dial gauge spring is directed upwards and is subtracted from the load; in other forms, this force acts downwards and is added to the load.

2 Since the force exerted by the spring in certain dial gauges varies considerably over the stroke, this force is measured in that part of the stroke which is to be used.

4.4 Load-carrying plate, fitted to the rod (4.1), and **suitable weights** added centrally so that the total thrust applied to the test specimen can be made up to $10 \text{ N} \pm 0,2 \text{ N}$ for methods A50 and A120 and

50 N \pm 1 N for methods B50 and B120. The combined downward thrust due to the rod, indenting tip, load-carrying plate and the force of the dial gauge spring shall not exceed 1 N.

4.5 Heating equipment, consisting of a heating bath (4.5.1) containing a liquid or an oven (4.5.2) with forced circulation of air or nitrogen.

The heating equipment shall be provided with a means of control so that the temperature can be raised at a uniform rate of either 50 °C/h \pm 5 °C/h or 120 °C/h \pm 10 °C/h, as required. The requirement for the heating rate shall be considered satisfied if, over every 6 min interval during the test, the temperature change is 5 °C \pm 0,5 °C or 12 °C \pm 1 °C, respectively.

The apparatus may be arranged to shut off the heat automatically and sound an alarm when the specified indentation has been reached (see 7.5).

4.5.1 Heating bath, containing a liquid in which the test specimen can be immersed to a depth of at least 35 mm. An efficient stirrer shall be provided. It shall be established that the liquid chosen is stable at the temperature used and does not affect the material under test, for example by swelling or cracking.

When a heating bath is used, the temperature of the liquid, measured close to the test specimen, shall be taken as the VST (see 7.5).

NOTE 3 Liquid paraffin, transformer oil, glycerol and silicone oil are suitable liquid heat-transfer media, but other liquids may be used.

4.5.2 Oven, with forced air or nitrogen circulation of about 60 times per minute, with a volume of not less than 10 litres for each apparatus and in which the air or nitrogen flow is directed perpendicular to the upper surface of the test specimen at a speed of 1,5 m/s to 2 m/s.

The result of the test will depend on the rate of transfer of heat from the circulating air or nitrogen to the surface of the test specimen. Because of the relatively small test specimen and the fact that the lower surface is in contact with the test-specimen support, the air or nitrogen temperature shall not be taken as the VST.

Take the temperature indicated by a sensor in the rod close to the indenting tip, or in the test-specimen support, as the VST.

For an initial calibration, verify by experiment that the temperature indicated by the sensor is within \pm 1 °C of the temperature that is indicated by an additional sensor embedded within a blank test specimen.

NOTE 4 Commercially available ovens are often furnished with means for suitable air or nitrogen circulation. If not, the necessary heat-transfer rate may be ensured by fitting stream plates which direct the circulating air or nitrogen perpendicular to the upper surface of the test specimen.

4.6 Temperature-measuring instrument.

4.6.1 For a heating bath

Mercury-in-glass thermometer of the partial-immersion type or other suitable temperature-measuring instrument of appropriate range and accurate to within 0,5 °C. Mercury-in-glass thermometers shall be calibrated at the depth of immersion required by 7.2.

4.6.2 For an oven with air or nitrogen circulation

Suitable temperature-measuring instrument of appropriate range and accurate to within 0,5 °C. The sensor (thermocouple or Pt 100) shall be positioned in the rod close to the indenting tip or in the test-specimen support (see 4.5.2).

5 Test specimens

5.1 At least two test specimens shall be used to test each sample. The test specimens shall be between 3 mm and 6,5 mm thick and at least 10 mm square or of 10 mm diameter. Their surfaces shall be flat and parallel and free from flash. They shall be made in accordance with the specifications, if any, for the material under test. In the absence of such specifications, any suitable procedure may be used for the preparation of test specimens.

5.2 If the samples submitted for test are in the form of moulding materials (for example, powder or granulated materials), these shall be moulded into specimens 3 mm to 6,5 mm thick, in accordance with the specifications relating to the material under test, or in accordance with ISO 293, ISO 294 or ISO 3167 if no material specification exists. If these are not applicable, any other reproducible procedure may be followed that modifies the properties of the material as little as possible.