



**SLOVENSKI STANDARD  
SIST EN ISO 604:2000**

**01-maj-2000**

---

Določa metode za določanje kompresivnih lastnosti polimernih materialov.

Plastics - Determination of compressive properties (ISO 604:1993)

Kunststoffe - Bestimmung von Druckeigenschaften (ISO 604:1993)

Plastiques - Détermination des propriétés en compression (ISO 604:1993)

**Ta slovenski standard je istoveten z: EN ISO 604:1996**

[SIST EN ISO 604:2000](https://standards.iteh.ai/catalog/standards/sist/ecfda3e0-1d36-40ac-9652-17f8d45cc92e/sist-en-iso-604-2000)

<https://standards.iteh.ai/catalog/standards/sist/ecfda3e0-1d36-40ac-9652-17f8d45cc92e/sist-en-iso-604-2000>

**ICS:**

83.080.01	Polimerni materiali na splošno	Plastics in general
-----------	--------------------------------	---------------------

**SIST EN ISO 604:2000**

**en**

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST EN ISO 604:2000

<https://standards.iteh.ai/catalog/standards/sist/ecfda3e0-1d36-40ac-9652-17f8d45cc92e/sist-en-iso-604-2000>

EUROPEAN STANDARD

EN ISO 604

NORME EUROPÉENNE

EUROPÄISCHE NORM

December 1996

ICS 83.080

Descriptors: Plastics, tests, compression tests, determination, compressibility

English version

**Plastics - Determination of compressive properties  
(ISO 604:1993)**Plastiques - Détermination des propriétés en  
compression (ISO 604:1993)Kunststoffe - Bestimmung von Druckeigenschaften  
(ISO 604:1993)**ITeH STANDARD PREVIEW**  
**(standards.iteh.ai)**SIST EN ISO 604:2000<https://standards.iteh.ai/catalog/standards/sist/ecfda3e0-1d36-40ac-9652-17f8d45cc92e/sist-en-iso-604-2000>

This European Standard was approved by CEN on 1994-12-14. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

The European Standards exist in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

**CEN**European Committee for Standardization  
Comité Européen de Normalisation  
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Page 2  
EN ISO 604:1996

### Foreword

The text of the International Standard from Technical Committee ISO/TC 61 "Plastics" of the International Organization for Standardization (ISO) has been taken over as an European Standard by Technical Committee CEN/TC 249 "Plastics", the secretariat of which is held by IBN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 1997, and conflicting national standards shall be withdrawn at the latest by June 1997.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

### Endorsement notice

The text of the International Standard ISO 604:1993 has been approved by CEN as a European Standard without any modification.



## iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST EN ISO 604:2000](https://standards.iteh.ai/catalog/standards/sist/ecf1a3e0-1d36-40ac-9652-178d45cc92e/sist-en-iso-604-2000)

<https://standards.iteh.ai/catalog/standards/sist/ecf1a3e0-1d36-40ac-9652-178d45cc92e/sist-en-iso-604-2000>

2023-08-10

AWAL/10/23

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION

# INTERNATIONAL STANDARD

**ISO  
604**

Second edition  
1993-06-15

---

---

## Plastics — Determination of compressive properties

**iTeh STANDARD PREVIEW**  
*Plastiques — Détermination des propriétés en compression*  
**(standards.iteh.ai)**

SIST EN ISO 604:2000

<https://standards.iteh.ai/catalog/standards/sist/ecfda3e0-1d36-40ac-9652-17f8d45cc92e/sist-en-iso-604-2000>



Reference number  
ISO 604:1993(E)

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 604 was prepared by Technical Committee ISO/TC 61, *Plastics*, Sub-Committee SC 2, *Mechanical properties*.

This second edition cancels and replaces the first edition (ISO 604:1973), which has been improved with respect to the following points:

- introduction of the compressive modulus;
- simplification with respect to the buckling limit;
- introduction of preferred specimen types, which relate to the multipurpose test specimen according to ISO 3167;
- introduction of three preferred testing speeds, for measuring the modulus and for testing brittle and tough materials respectively.

Annex A forms an integral part of this International Standard. Annex B is for information only.

© ISO 1993

All rights reserved. No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization  
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland



# Plastics — Determination of compressive properties

## 1 Scope

**1.1** This International Standard specifies a method for determining the compressive properties of plastics under defined conditions. A standard test specimen is defined and its length is adjusted to prevent buckling under load from affecting the results. A range of testing speeds is included.

**1.2** The method is used to investigate the compressive behaviour of the test specimens and for determining the compressive strength, compressive modulus and other aspects of the compressive stress/strain relationship under the conditions defined.

**1.3** The method applies to the following range of materials:

- rigid and semirigid thermoplastics moulding and extrusion materials, including compounds filled and reinforced by e.g. short fibres, small rods, plates or granules in addition to unfilled types; rigid and semirigid thermoplastic sheet;
- rigid and semirigid thermoset moulding materials, including filled and reinforced compounds; rigid and semirigid thermoset sheet;
- thermotropic liquid crystal polymers.

The method is not normally suitable for use with materials reinforced by textile fibres, rigid cellular materials and sandwich structures containing cellular material.

**1.4** The method is performed using specimens which may be either moulded to the chosen dimensions, machined from the central portion of the standard multipurpose test specimen (see ISO 3167) or machined from finished and semifinished products such as mouldings, laminates and extruded or cast sheet.

**1.5** The method specifies preferred dimensions for the test specimen. Tests which are carried out on specimens of different dimensions, or on specimens which are prepared under different conditions, may produce results which are not comparable. Other factors, such as the speed of testing and the conditioning of the specimens, can also influence the results. Consequently, when comparative data are required, these factors should be carefully controlled and recorded.

## 2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 291:1977, *Plastics — Standard atmospheres for conditioning and testing.*

ISO 293:1986, *Plastics — Compression moulding test specimens of thermoplastic materials.*

ISO 294:—<sup>1)</sup>, *Plastics — Injection moulding of test specimens of thermoplastic materials.*

ISO 295:1991, *Plastics — Compression moulding of test specimens of thermosetting materials.*

ISO 472:1988, *Plastics — Vocabulary.*

ISO 1268:1974, *Plastics — Preparation of glass fibre reinforced, resin bonded, low-pressure laminated plates or panels for test purposes.*

1) To be published. (Revision of ISO 294:1975)

ISO 2602:1980, *Statistical interpretation of test results — Estimation of the mean — Confidence interval*.

ISO 2818:—<sup>2)</sup>, *Plastics — Preparation of test specimens by machining*.

ISO 3167:1993, *Plastics — Multipurpose test specimens*.

ISO 5893:1985, *Rubber and plastics test equipment — Tensile, flexural and compression types (constant rate of traverse) — Description*.

### 3 Principle

The test specimen is compressed along its major axis at constant speed until the specimen fractures or until the load or the decrease in length reaches a predetermined value. The load sustained by the specimen is measured during this procedure.

### 4 Definitions

For the purposes of this International Standard, the following definitions apply (see also figure 1):

**4.1 gauge length,  $L_0$ :** Initial distance between the gauge marks on the test specimen.

It is expressed in millimetres (mm).

**4.2 speed of testing,  $v$ :** Rate of approach of the plates of the testing machine during the test.

It is expressed in millimetres per minute (mm/min).

**4.3 compressive stress,  $\sigma$  (engineering):** Compressive load, per unit area of original cross-section, carried by the test specimen (see note 3).

It is expressed in megapascals (MPa).

**4.3.1 compressive stress at yield,  $\sigma_y$ :** First stress at which an increase in strain (see 4.4) occurs without an increase in stress; may be less than the maximum attainable stress (see figure 1, curve a, and note 3).

**4.3.2 compressive strength,  $\sigma_M$ :** Maximum compressive stress sustained by the test specimen during a compressive test (see figure 1 and note 3).

**4.3.3 compressive stress at break (rupture),  $\sigma_B$ :** Compressive stress at break of the test specimen (see figure 1 and note 3).

**4.3.4 compressive stress at  $x$  % strain,  $\sigma_x$ :** Stress at which the strain reaches a specified value of  $x$  % (see 4.5).

The compressive stress at  $x$  % strain may be measured, e.g., if the stress/strain curve does not exhibit a yield point (see figure 1, curve b, and note 3). In this case,  $x$  shall be taken from the relevant product standard or agreed upon by the interested parties. However, in any case,  $x$  must be lower than the strain at compressive strength.

**4.4 compressive strain,  $\varepsilon$ :** Decrease in length per unit original length of the gauge  $L_0$  [see 8.2, equation (3) and note 3].

It is expressed as a dimensionless ratio or percentage (%).

**4.5 nominal compressive strain,  $\varepsilon_c$ :** Decrease in length per unit original length  $l$  of the test specimen [see 8.2, equation (4)].

It is expressed as a dimensionless ratio and may be specified directly or as a percentage of the initial length.

**4.5.1 nominal compressive yield strain,  $\varepsilon_{cy}$ :** Strain corresponding to the compressive yield stress  $\sigma_y$  (see 4.3.1).

**4.5.2 nominal compressive strain at compressive strength,  $\varepsilon_{cM}$ :** Strain corresponding to the compressive strength  $\sigma_M$  (see 4.3.2).

**4.5.3 nominal compressive strain at break,  $\varepsilon_{cB}$ :** Strain at break of the test specimen.

**4.6 compressive modulus,  $E_c$ :** Ratio of the stress difference ( $\sigma_2 - \sigma_1$ ) to the corresponding strain difference values ( $\varepsilon_2 = 0,002\ 5$  minus  $\varepsilon_1 = 0,000\ 5$ ) [see 8.3, equation (7)].

It is expressed in megapascals, MPa.

#### NOTES

1 The compression modulus is calculated on the basis of the compressive strain  $\varepsilon$  only (see 4.4).

2 With computer-aided equipment, the determination of the modulus  $E_c$  using two distinct stress/strain points may be replaced by a linear regression procedure applied on the part of the curve between these mentioned points.

3 In compression tests the stresses  $\sigma$  and strains  $\varepsilon$  are negative. The negative sign, however, is generally omitted. If this generates confusion, e.g. in comparing tensile and compressive properties, the negative sign may be added for the latter. This unnecessary for the nominal compressive strains  $\varepsilon_c$ .

2) To be published. (Revision of ISO 2818:1980)



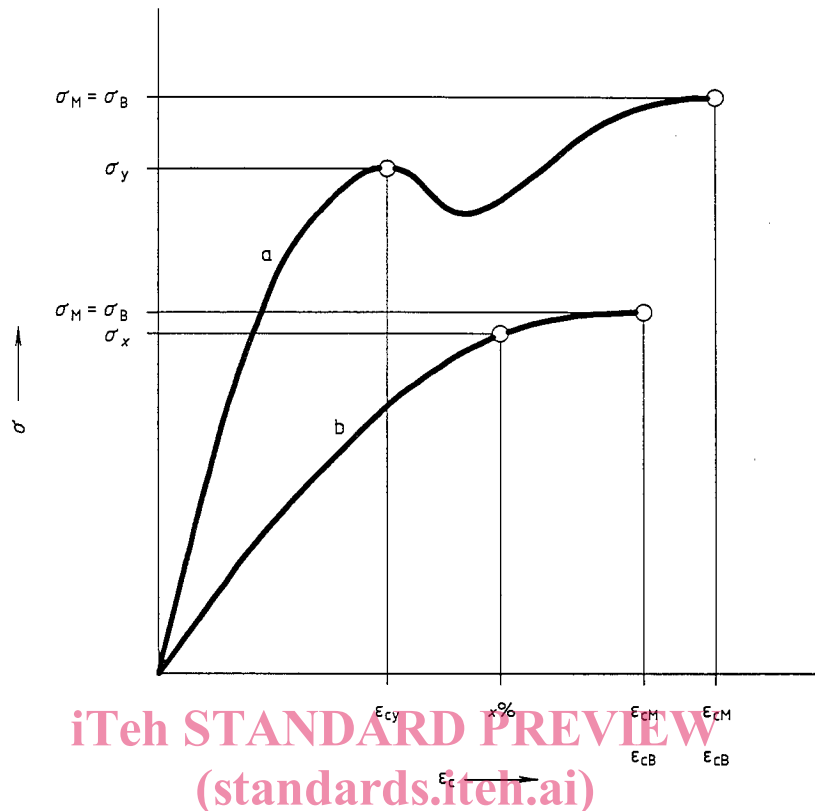


Figure 1 — Typical stress/strain curves

SIST EN ISO 604:2000

[https://standards.iteh.ai/catalog/standards/sist/ecfda3e0-1d36-40ac-9652-](https://standards.iteh.ai/catalog/standards/sist/ecfda3e0-1d36-40ac-9652-178d45cc92e/sist-en-iso-604-2000)

[178d45cc92e/sist-en-iso-604-2000](https://standards.iteh.ai/catalog/standards/sist/ecfda3e0-1d36-40ac-9652-178d45cc92e/sist-en-iso-604-2000)

value with an accuracy of  $\pm 1\%$  or better of the relevant value.

## 5 Apparatus

### 5.1 Testing machine

The testing machine shall be power-driven and capable of maintaining the appropriate speed of testing as specified in 7.5. The machine shall satisfy the conditions given in ISO 5893. The testing machine shall be equipped with the devices described in 5.1.1 to 5.1.3.

**5.1.1 Compression tool**, of hardened steel compression plates, for applying the deformation to the test specimen, so constructed that the load carried by the specimen is axial within 1:1 000 and transmitted through polished surfaces which are flat within 0,025 mm and parallel to each other in a plane normal to the loading axis.

NOTE 4 A self-aligning device may be used where required.

**5.1.2 Load indicator**, capable of showing the total compressive load carried by the test specimen. The mechanism shall be essentially free of inertia lag at the specified testing speed and shall indicate the load

**5.1.3 Deformation indicator**, suitable for determining the change in length of the appropriate part of the test specimen. If compressive strain  $\epsilon$  is to be measured (preferred), then this length is the gauge length; otherwise, for nominal compressive strain  $\epsilon_c$ , it is the distance between the contact surfaces of the compression tool. It is desirable, but not essential, that this instrument automatically records this distance. This instrument shall be essentially free of inertia lag at the specified testing speed and shall be accurate to  $\pm 1\%$  or better of the relevant value.

When a deformation indicator is attached to the test specimen, care shall be taken to ensure that any distortion of or damage to the test specimen is minimal. It is also essential that there is no slippage between the deformation indicator and the test specimen.

### 5.2 Devices for measuring the dimensions of the test specimens

**5.2.1** For rigid materials, use a micrometer or equivalent, reading to at least 0,01 mm, for measuring the thickness, width and length.

5.2.2 For semirigid materials, use a micrometer or equivalent, reading to at least 0,01 mm and provided with a flat circular foot which applies a pressure of 20 kPa  $\pm$  3 kPa, for measuring thickness.

## 6 Test specimens

### 6.1 Preparation

Prepare test specimens in accordance with the requirements of the International Standard for the material concerned. In the absence of such requirements, the most appropriate method taken from the list of International Standards in clause 2 shall be used, unless otherwise agreed by the interested parties.

All surfaces of the test specimens shall be free from visible flaws, scratches and other imperfections that are likely to influence the results.

### 6.2 Shape

The test specimen shall be in the shape of a right prism, cylinder or tube. All machining operations shall be carried out carefully so that smooth surfaces result. Great care shall be taken in machining the ends so that smooth, flat, parallel surfaces and sharp, clean edges, to within 0,025 mm perpendicular to the longest axis of the specimen, result.

It is recommended to machine the end surfaces of the test specimen with a lathe or a milling machine.

The dimensions of the test specimens shall meet the conditions in equation (1) (see annex B).

$$\varepsilon_c^* \leq 0,4 \left( \frac{x}{l} \right)^2 \quad \dots (1)$$

where

- $\varepsilon_c^*$  is the maximum nominal compressive strain, expressed as a dimensionless ratio, which occurs during the test;
- $l$  is the length of the specimen, measured parallel to the axis of the compressive force;
- $x$  is the diameter of the cylinder, the outer diameter of the tube or the thickness (the smaller side of the cross-section) of the prism, depending on the shape of the test specimen.

#### NOTES

5 For measurement of the compressive modulus  $E_c$  according to 4.6, the dimension ratio  $x/l \geq 0,08$  is recommended.

6 When carrying out compression tests in general, the dimension ratio  $x/l \geq 0,4$  is recommended. This corresponds to a maximum compressive strain of about 6 %.

7 Equation (1) is based upon the linear stress/strain behaviour of the material under test. Values of  $\varepsilon_c^*$  two to three times higher than the maximum strain used in the test should be chosen with increasing compressive strain and ductility of the material.

### 6.3 Preferred test specimens

The preferred dimensions for test specimens are given in table 1.

**Table 1 — Dimensions of preferred specimen types**

Dimensions in millimetres

Type	Measurement	Length, $l$	Width, $b$	Thickness, $h$
A	modulus	$50 \pm 2$	$10 \pm 0,2$	$4,0 \pm 0,2$
B	strength	$10 \begin{smallmatrix} +0 \\ -2 \end{smallmatrix}$		

Preferably the specimens are to be cut from a multi-purpose test specimen (see ISO 3167).

NOTE 8 Annex A details two types of small test specimen for use when, for reasons of lack of material or geometric constraints for a product, the preferred specimens cannot be used.

### 6.4 Gauge marks

If optical deformation indicators are used, it is necessary to put gauge marks on the specimen to define the gauge length. These shall be approximately equidistant from the midpoint of the test specimen, and the distance between the marks shall be measured to an accuracy of 1 % or better.

Gauge marks shall not be scratched, punched or impressed upon the test specimen in any way which causes damage to the material being tested. It must be ensured that the marking medium has no detrimental effect on the material being tested and that, in the case of two pairs of parallel lines, they are as narrow as possible.

### 6.5 Anisotropic materials

6.5.1 In the case of anisotropic materials, the test specimens shall be chosen so that the compressive stress in the test procedure will be applied in the same or similar direction to that experienced by the products (moulded articles, sheet, tubes, etc.) during their application in service, if known.

The relationship between the dimensions of the test specimen and the size of the product will determine the possibility of using preferred test specimens. If the use of the preferred test specimen is impossible, the size of the product will govern the choice of dimensions of the test specimens in accordance with

6.2 as well. It should be noted that the orientation and the dimensions of the test specimens sometimes have a very significant influence on the test results. This is particularly true of laminates.

**6.5.2** When the material shows a significant difference in compressive properties in two principal directions, it shall be tested in these two directions. If, because of its destined application, this material will be subjected to compressive stress at some specific orientation to the principal direction, it is desirable to test the material in that orientation.

The orientation of the test specimens relative to the principal directions shall be recorded.

## 6.6 Number of test specimens

**6.6.1** Test at least five specimens for each sample in the case of isotropic materials.

**6.6.2** Test at least ten specimens, five normal to, and five parallel to the principal axis of anisotropy for each sample, in the case of anisotropic materials.

**6.6.3** Specimens that break at some obvious flaw shall be discarded and replacement specimens shall be tested.

## 6.7 Conditioning of test specimens

The test specimens shall be conditioned in accordance with the requirements of the International Standard for the material. In the absence of such requirements, use shall be made of the most appropriate conditions given in ISO 291, unless otherwise agreed by the interested parties.

The preferred condition is atmosphere 23/50, except when the compressive properties of the material are known to be insensitive to moisture, in which case humidity control is unnecessary.

## 7 Test procedure

**7.1** Perform the test in one of the standard atmospheres specified in ISO 291, preferably the same atmosphere as used for conditioning.

**7.2** Measure the width and thickness, or the diameter(s), of the test specimen at three points along its length and calculate the mean value of the cross-sectional area.

Measure the length of each test specimen, to 1 % accuracy.

**7.3** Place the test specimen between the surfaces of the compression plates and align the centreline of the compression plate surfaces. Ensure that the end surfaces of the specimen are parallel to the surfaces

of the compression plates and adjust the machine so that the surfaces of the ends of the test specimen and compression plate are just touching.

NOTE 9 During compression, the end surfaces of the test specimen may slip along the compression plates to varying extents, depending upon the surface textures of the specimen and plates. This will lead to varying degrees of barrel distortion, which in turn may influence the properties to be measured. The less rigid the material, the more pronounced the effect.

For the most precise measurements, it is recommended that either the end surfaces be treated with an appropriate lubricant to promote slip or that discs of fine abrasive paper be used between specimen and plates to inhibit slip. If either method is used, it shall be noted in the test report.

**7.4** Attach the deformation indicator, if required.

**7.5** Set the speed of testing  $v$  in millimetres per minute (see 4.2) in accordance with the material specification or, in the absence of this, to that of the following value:

$$1 \pm 0,2$$

$$2 \pm 0,4$$

$$5 \pm 1$$

$$10 \pm 2$$

$$20 \pm 2$$

which is the closest approximation to

$v = 0,02l$  ( $l$  in millimetres) for modulus measurements;

$v = 0,1l$  ( $l$  in millimetres) for strength measurements with brittle materials, which break prior to yielding;

$v = 0,5l$  ( $l$  in millimetres) for strength measurements with ductile materials, which yield.

For the preferred test specimens (see 6.3) the testing speeds are

1 mm/min for modulus measurements ( $l = 50$  mm);

1 mm/min for strength measurements with brittle materials ( $l = 10$  mm);

5 mm/min for strength measurements with ductile materials ( $l = 10$  mm).