

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 12086-2:2000

<https://standards.iteh.ai/catalog/standards/sist/9824a892-b3cb-418c-8ed6-9903eca334c2/sist-en-iso-12086-2-2000>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN ISO 12086-2

May 1999

ICS 83.080.20

English version

Plastics - Fluoropolymer dispersions and moulding and extrusion materials - Part 2: Preparation of test specimens and determination of properties (ISO 12086-2:1995)

Plastiques - Polymères fluorés: dispersions et matériaux pour moulage et extrusion - Partie 2: Préparation des éprouvettes et détermination des propriétés (ISO 12086-2:1995)

This European Standard was approved by CEN on 16 April 1999.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Page 2
EN ISO 12086-2:1999

Foreword

The text of the International Standard from Technical Committee ISO/TC 61 "Plastics" of the International Organization for Standardization (ISO) has been taken over as an European Standard by Technical Committee CEN/TC 249 "Plastics", the secretariat of which is held by IBN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by November 1999, and conflicting national standards shall be withdrawn at the latest by November 1999.


According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

NOTE FROM CEN/CS: The foreword is susceptible to be amended on reception of the German language version. The confirmed or amended foreword, and when appropriate, the normative annex ZA for the references to international publications with their relevant European publications will be circulated with the German version.

(standards.iteh.ai)

Endorsement notice

The text of the International Standard ISO 12086-2:1995 has been approved by CEN as a European Standard without any modification.

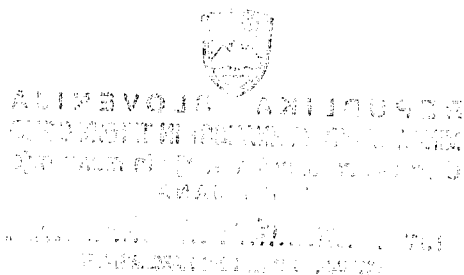

INTERNATIONAL
STANDARD

ISO
12086-2

First edition
1995-12-15

**Plastics — Fluoropolymer dispersions and
moulding and extrusion materials —**

Part 2:

**Preparation of test specimens and
determination of properties**

<https://standards.iteh.ai/catalog/standards/sist/en-iso-12086-2-2000>
*Plastiques — Polymères fluorés: dispersions et matériaux pour moulage
et extrusion —*

Partie 2: Préparation des éprouvettes et détermination des propriétés



Reference number
ISO 12086-2:1995(E)

Contents

	Page
1 Scope	1
2 Normative references	1
3 Definitions	3
4 Symbols and abbreviations	3
5 Sampling	4
6 Preparation of test specimens	4
7 Conditioning and test conditions	4
8 General testing of fluoropolymers	4
8.1 Electrical properties	4
8.2 Mechanical properties	5
8.3 Thermal-transition temperatures	6
8.4 Density	8
8.5 Flammability by oxygen index	8
8.6 Particle size and size distribution	8
9 Testing of fluoropolymer dispersions	13
9.1 General	13
9.2 Preparation of test samples	13
9.3 Isolation of PTFE from dispersion	14
9.4 Coagulum in dispersions	14
9.5 Percentage polymer and surfactant in aqueous dispersions	15
9.6 PTFE solids content by hydrometer	15
9.7 pH of dispersions	16
10 Testing of PTFE and closely related materials	16
10.1 General	16
10.2 Preparation of test specimens by moulding	16

© ISO 1995

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

10.3	Bulk density	18
10.4	Extrusion pressure	23
10.5	Powder-flow time	27
10.6	Standard specific gravity (SSG), extended specific gravity (ESG), and thermal-instability index (TII)	27
10.7	Stretching-void index (SVI)	30
11	Testing of conventionally melt-processible fluoropolymers ..	32
11.1	Preparation of test specimens by moulding	32
11.2	Melt mass-flow rate (MFR) and melt volume-flow rate (MVR) ..	33
12	Other test methods used with fluoropolymers	35
12.1	Brittleness temperature of plastics and elastomers by impact ..	35
12.2	Coefficients of static and kinetic friction	35
12.3	Zero-strength time	35

iTeh STANDARD PREVIEW

Annexes

A	Listing of test methods (alphabetical order)	36
B	Designatory properties for common fluoropolymer types with cross-reference listing to the tables for codes in ISO 12086-1 and the test methods in ISO 12086-2	37
C	Bibliography	40

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 12086-2 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 9, *Thermoplastic materials*.

ISO 12086 consists of the following parts, under the general title *Plastics — Fluoropolymer dispersions and moulding and extrusion materials*:

- Part 1: *Designation system and basis for specifications*
- Part 2: *Preparation of test specimens and determination of properties*

Annexes A, B and C of this part of ISO 12086 are for information only.

Plastics — Fluoropolymer dispersions and moulding and extrusion materials —

Part 2:

Preparation of test specimens and determination of properties

WARNING — This part of ISO 12086 may involve hazardous materials, operations and equipment. It does not purport to address all of the safety problems associated with its use. It is the responsibility of the user of this part of ISO 12086 to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use. The warnings in subclauses 8.6.1.1, 9.7 and 10.6.1.3 point out specific hazards.

1 Scope

1.1 This part of ISO 12086 describes the preparation of test specimens and provides test methods to define characteristics of thermoplastic fluoropolymer resins. Results from the testing may be used as the basis for designation, material specifications, or both. This part of ISO 12086 describes the conditions of test for determining both designatory and other properties of the homopolymers and various copolymers of fluoromonomers, as dispersions or powders for moulding, extrusion, and other uses. The test procedures included are appropriate for, but are not restricted to, the fluoropolymers listed in clause 4 and for which designatory properties are specified in ISO 12086-1.

1.2 The properties of semi-finished and finished products made from fluoropolymer resins depend on the material used, the shape of the product, the physical and morphological state of the material resulting from the processing operations, and on the test conditions. Therefore, to obtain reproducible test results, the defined methods of preparation of test specimens and defined test conditions given in this part of ISO 12086 must be applied.

1.3 Agreements between vendor and purchaser should preferably be based on properties measured using the specimens and test conditions described in this part of ISO 12086.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this part of ISO 12086. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this part of ISO 12086 are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 75-2:1993, *Plastics — Determination of temperature of deflection under load — Part 2: Plastics and ebonite.*

ISO 178:1993, *Plastics — Determination of flexural properties.*

ISO 179:1993, *Plastics — Determination of Charpy impact strength.*

ISO 180:1993, *Plastics — Determination of Izod impact strength.*

ISO 291:1977, *Plastics — Standard atmospheres for conditioning and testing.*

ISO 293:1986, *Plastics — Compression moulding test specimens of thermoplastic materials.*

ISO 472:1988, *Plastics — Vocabulary.*

ISO 527-1:1993, *Plastics — Determination of tensile properties — Part 1: General principles.*

ISO 527-2:1993, *Plastics — Determination of tensile properties — Part 2: Test conditions for moulding and extrusion plastics.*

ISO 527-3:1995, *Plastics — Determination of tensile properties — Part 3: Test conditions for films and sheets.*

ISO 565:1990, *Test sieves — Metal wire cloth, perforated metal plate and electroformed sheet — Nominal sizes of openings.*

ISO 842:1984, *Raw materials for paints and varnishes — Sampling.*

ISO 1043-1:1987, *Plastics — Symbols — Part 1: Basic polymers and their special characteristics.*

ISO 1043-2:1988, *Plastics — Symbols — Part 2: Fillers and reinforcing materials.*

ISO 1133:1991, *Plastics — Determination of the melt mass-flow rate (MFR) and the melt volume-flow rate (MVR) of thermoplastics.*

ISO 1148:1980, *Plastics — Aqueous dispersions of polymers and copolymers — Determination of pH.*

ISO 1183:1987, *Plastics — Methods for determining the density and relative density of non-cellular plastics.*

ISO 4589:1984, *Plastics — Determination of flammability by oxygen index.*

ISO 8962:1987, *Plastics — Polymer dispersions — Determination of density.*

ISO 12000:—¹⁾, *Plastics/rubber — Polymer dispersions and rubber latices (natural and synthetic) — Definitions and review of test methods.*

ISO 12086-1:1995, *Plastics — Fluoropolymer dispersions and moulding and extrusion materials — Part 1: Designation system and basis for specifications.*

IEC 93:1980, *Methods of test for volume resistivity and surface resistivity of solid electrical insulating materials.*

IEC 243-1:1988, *Methods of test for electric strength of solid insulating materials — Part 1: Tests at power frequencies.*

IEC 250:1969, *Recommended methods for the determination of the permittivity and dielectric dissipation factor of electrical insulating materials at power, audio and radio frequencies including metre wavelengths.*

ASTM D 746-79(1987), *Test method for brittleness temperature of plastics and elastomers by impact.*

ASTM D 1430-91a, *Specification for polychlorotrifluoroethylene (PCTFE) plastics.*

ASTM D 1457-91a, *Specification for PTFE molding and extrusion materials.*

ASTM D 1894-93, *Test method for static and kinetic coefficients of friction of plastic film and sheeting.*

ASTM D 3418-83(1988), *Test method for transition temperatures of polymers by thermal analysis.*

ASTM D 4052-91, *Test method for density and relative density of liquids by digital density meter.*

ASTM D 4591-93a, *Test method for determining temperatures and heats of transitions of fluoropolymers by differential scanning calorimetry.*

ASTM D 4894-91a, *Specification for polytetrafluoroethylene (PTFE) granular molding and ram extrusion materials.*

ASTM D 4895-91a, *Specification for polytetrafluoroethylene (PTFE) resins produced from dispersion.*

BS 3406:Part 5:1983, *Methods for determination of particle size distribution — Part 5: Recommendations for electrical sensing zone method (the Coulter principle).*

BS 4641:1986, *Method for specifying electroplated coatings of chromium for engineering purposes.*

1) To be published.

3 Definitions

3.1 The terminology given in ISO 472 is applicable to this part of ISO 12086, except for terms defined in 3.2. The terms listed in 3.1.1 to 3.1.3 are repeated from ISO 472 to be sure there is no misunderstanding.

3.1.1 dispersion: A heterogeneous system in which a finely divided material is distributed in another material.

3.1.2 fluoroplastic: A plastic based on polymers made with monomers containing one or more atoms of fluorine, or copolymers of such monomers with other monomers, the fluoromonomer(s) being in the greatest amount by mass.

3.1.3 latex: A colloidal aqueous dispersion of a polymeric material.

3.2 For the purposes of this part of ISO 12086, the following additional definitions apply.

3.2.1 amorphous: Noncrystalline, or devoid of regular structure.

3.2.2 bulk density: The mass (in grams) per litre of material, measured under the conditions of the test.

3.2.3 copolymer: A polymer formed from two or more types of monomer.

3.2.4 emulsion polymer (as it applies to fluoropolymer materials): Material isolated from its polymerization medium as a colloidal aqueous dispersion of the polymer solids.

NOTE 1 This definition, used in the fluoropolymer industry, is similar to that for "latex" in ISO 472 and is quite different from the definition for "emulsion" in ISO 472.

3.2.5 fluorocarbon plastic: A plastic based on polymers made from perfluoromonomers only.

3.2.6 fluoropolymer: Synonymous with *fluoroplastic* (see 3.1.2).

3.2.7 melt-processible: Capable of being processed by, for example, injection moulding, screw extrusion, and other operations typically used with thermoplastics.

3.2.8 preforming: Compacting powdered PTFE material under pressure in a mould to produce a solid object, called a preform, that is capable of being handled.

NOTE 2 With PTFE, "moulding" and "compaction" are terms used interchangeably with "preforming".

3.2.9 sintering (as it applies to PTFE): A thermal treatment during which the material is melted and recrystallized by cooling, with coalescence occurring during the treatment.

3.2.10 standard specific gravity (SSG): The specific gravity of a specimen of PTFE material preformed, sintered, and cooled through the crystallization point at a rate of 1 °C per minute in accordance with the appropriate sintering schedule as described in this part of ISO 12086.

NOTE 3 The SSG of unmodified PTFE is inversely related to its molecular mass.

3.2.11 suspension polymer: A polymer isolated from its liquid polymerization medium as a solid having a particle size well above colloidal dimensions.

3.2.12 zero-strength time (ZST): A measure of the relative molecular mass of PCTFE.

STANDARD PREVIEW
(standards.iteh.org)

4 Symbols and abbreviations

4.1 The abbreviated terms given in ISO 1043-1 and ISO 1043-2 are applicable to this part of ISO 12086.

4.2 This part of ISO 12086 is particularly concerned with, but is not limited to, test methods for the materials listed below:

PTFE	polytetrafluoroethylene
PFA	perfluoro(alkoxy alkane)
FEP	perfluoro(ethylene-propene) copolymer
EFEP	ethylene-tetrafluoroethylene-hexafluoropropene copolymer
TFE/PDD	tetrafluoroethylene-perfluoro(dioxole) copolymer
VDF/HFP	vinylidene fluoride-hexafluoropropene copolymer
VDF/TFE	vinylidene fluoride-tetrafluoroethylene copolymer
VDF/TFE/HFP	vinylidene fluoride-tetrafluoroethylene-hexafluoropropene copolymer

ETFE	ethylene-tetrafluoroethylene copolymer
PVDF	poly(vinylidene fluoride)
VDF/CTFE	vinylidene fluoride-chlorotrifluoroethylene copolymer
PCTFE	polychlorotrifluoroethylene
PVF	poly(vinyl fluoride)
ECTFE	ethylene-chlorotrifluoroethylene copolymer

4.3 For the purposes of this part of ISO 12086, the following abbreviated terms apply in addition to those given in 3.2 and 4.2.

AF	amorphous fluoropolymer
ESG	extended specific gravity (see 10.6)
MFR	melt mass-flow rate (see 11.2)
MVR	melt volume-flow rate (see 11.2)
SSG	standard specific gravity (see 10.6)
SVI	stretching-void index (see 10.7)
TII	thermal-instability index (see 10.6)
ZST	zero-strength time (see 12.3)

5 Sampling

The materials should preferably be sampled in accordance with ISO 842. Adequate statistical sampling shall be considered an acceptable alternative. Special considerations are included in the pertinent clause.

6 Preparation of test specimens

Where applicable, ISO standards shall be followed for the preparation of test specimens. In some instances, special procedures are required that are described either in the general discussion or in the method.

7 Conditioning and test conditions

7.1 For tests of specific gravity, tensile properties, and electrical properties, condition the moulded test specimens in atmosphere 23 of ISO 291 for a period of at least 4 h prior to testing. The other tests require no conditioning.

NOTE 4 For PVDF, some producers recommend waiting one week after moulding before testing in order to minimize the effects of post crystallization.

7.2 Conduct tests at a laboratory temperature of $23\text{ °C} \pm 2\text{ °C}$ for determining specific gravity, tensile properties, and electrical properties only. (See note 5 for comments related to PTFE.) Since the fluoropolymer resins do not absorb water, the maintenance of constant humidity during testing is not necessary. Conduct tests for melt flow rate and melting-peak temperature under ordinary laboratory conditions.

NOTE 5 A minimum temperature of 22 °C should preferably be maintained with PTFE due to its first-order transition just below 22 °C that affects properties determined at slightly lower temperatures. This effect of temperature is especially important during the determination of density/specific gravity.

8 General testing of fluoropolymers

Properties required for designation or specification, or both, shall be determined in accordance with the international or national standards listed in clause 2 or the procedures given in this part of ISO 12086. Tables of values of the designatory properties and corresponding codes are included in ISO 12086-1. Tables of values and codes are also included in this part of ISO 12086 for many of the other properties that are needed to supplement the designatory properties for specification and other purposes.

8.1 Electrical properties

8.1.1 Dielectric constant and dissipation factor

Determine these properties on three specimens, each 100 mm in diameter, in accordance with IEC 250. Typical frequencies used for testing are 100 Hz, 1 kHz, 1 MHz and 100 MHz. For some applications, it is important to know the values at subambient and elevated temperatures. Codes for test frequencies and values of the properties are given in tables 1 and 2.

NOTE 6 Electrical properties, like many other properties, vary with temperature.

Table 1 — Codes for test frequencies

Code	Test frequency
2	100 Hz
3	1 kHz
6	1 MHz
8	100 MHz

Table 2 — Codes and ranges for dielectric constant and dissipation factor

Code	Dielectric constant	Code	Dissipation factor
A	< 1,6	A	< 0,000 1
B	1,6 to < 1,8	B	0,000 1 to < 0,000 2
C	1,8 to < 2,0	C	0,000 2 to < 0,000 4
D	2,0 to < 2,2	D	0,000 4 to < 0,000 6
E	2,2 to < 2,4	E	0,000 6 to < 0,000 8
F	2,4 to < 2,6	F	0,000 8 to < 0,001 0
G	2,6 to < 2,8	G	0,001 0 to < 0,001 2
H	2,8 to < 3,0	H	0,001 2 to < 0,001 4
I	3,0 to < 3,2	I	0,001 4 to < 0,001 6
J	3,2 to < 3,4	J	0,001 6 to < 0,001 8
K	3,4 to < 3,6	K	0,001 8 to < 0,002 0
L	3,6 to < 4,0	L	0,002 0 to < 0,002 2
M	4,0 to < 4,5	M	0,002 2 to < 0,002 4
N	4,5 to < 5,0	N	0,002 4 to < 0,002 6
O	5,0 to < 5,5	O	0,002 6 to < 0,002 8
P	5,5 to < 6,0	P	0,002 8 to < 0,003 0
Q	6,0 to < 6,5	R	0,003 0 to < 0,003 5
S	6,5 to < 7,0	S	0,003 5 to < 0,004 0
T	7,0 to < 8,0	T	0,004 0 to < 0,006 0
U	8,0 to < 9,0	U	0,006 0 to < 0,008 0
V	9,0 to < 10,0	V	0,008 0 to < 0,010
W	10,0 to < 11,0	W	0,010 to < 0,030
X	11,0 to < 12,0	X	0,030 to < 0,10
Y	12,0 to < 14,0	Y	≥ 0,1
Z	≥ 14,0		

Table 3 — Codes and ranges for dielectric strength

Code	Dielectric strength (kV/mm)
A	< 5
B	5 to < 10
C	10 to < 15
D	15 to < 20
E	20 to < 25
F	25 to < 30
G	30 to < 35
H	35 to < 40
I	40 to < 45
J	45 to < 50
K	50 to < 55
L	55 to < 60
M	60 to < 65
N	65 to < 70
O	70 to < 75
P	75 to < 80
Q	80 to < 85
R	85 to < 90
S	90 to < 95
T	95 to < 100
U	≥ 100

8.1.3 Surface resistivity

Determine this property in accordance with IEC 93. Codes and ranges are listed in table 4.

Table 4 — Codes and ranges for surface resistivity

Code	Surface resistivity (Ω)
A	< 10^3
B	10^3 to 10^{12}
C	> 10^{12}

8.1.2 Dielectric strength (electric strength)

Determine this property in accordance with the procedures of IEC 243-1. Codes for values of the property are given in table 3.

NOTE 7 Dielectric strength, which is expressed in kilovolts per millimetre, varies with the thickness of the test specimen.

8.2 Mechanical properties

8.2.1 Impact properties

Determine impact properties using the procedures of ISO 180 for Izod impact strength and ISO 179 for Charpy impact strength. Codes and ranges are given in table 5. The test used, the size of the test specimen, and the type of notch shall be reported in addition to the code for impact strength.