



# SLOVENSKI STANDARD

## SIST EN ISO 9771:1999

01-maj-1999

---

### Polimerni materiali – Fenolne smole - Določevanje psevdoadiabatskega porasta temperature tekočih rezolov (ISO 9771:1995)

Plastics - Phenolic resins - Determination of the pseudo-adiabatic temperature rise of liquid resols when cured under acid conditions (ISO 9771:1995)

Kunststoffe - Phenolharze - Bestimmung des pseudo-adiabatischen Temperaturanstiegs flüssiger Resole bei Aushärtung unter sauren Bedingungen (ISO 9771:1995)

Plastiques - Résines phénoliques - Détermination de l'élévation de température pseudoadiabatique des résols liquides thermodurcis en conditions acides (ISO 9771:1995)

<https://standards.iteh.ai/catalog/standards/sist/7a95be6e-6315-4d0a-8cee-8afbe30776ba/sist-en-iso-9771-1999>

Ta slovenski standard je istoveten z: **EN ISO 9771:1997**

---

#### **ICS:**

83.080.10      Duromeri      Thermosetting materials

**SIST EN ISO 9771:1999**      en

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST EN ISO 9771:1999

<https://standards.iteh.ai/catalog/standards/sist/7a95be6e-6315-4d0a-8cee-8afbe30776ba/sist-en-iso-9771-1999>

EUROPEAN STANDARD

EN ISO 9771

NORME EUROPÉENNE

EUROPÄISCHE NORM

February 1997

ICS 83.080.10

Descriptors: see ISO document

English version

**Plastics - Phenolic resins - Determination of the  
pseudo-adiabatic temperature rise of liquid resols  
when cured under acid conditions  
(ISO 9771:1995)**

Plastiques - Résines phénoliques - Kunststoffe - Phenolharze - Bestimmung des  
Détermination de l'élévation de température pseudo-adiabatischen Temperaturanstiegs  
pseudoadiabatique des résols liquides flüssiger Resole bei Aushärtung unter sauren  
thermodurcis en conditions acides Bedingungen (ISO 9771:1995)

SIST EN ISO 9771:1999

<https://standards.iteh.ai/catalog/standards/sist/7a95be6e-6315-4d0a-8cee-8afbe30776ba/sist-en-iso-9771-1999>

This European Standard was approved by CEN on 1997-01-05. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

The European Standards exist in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

## CEN

European Committee for Standardization  
Comité Européen de Normalisation  
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Page 2  
EN ISO 9771:1997

## Foreword

The text of the International Standard from Technical Committee ISO/TC 61 "Plastics" of the International Organization for Standardization (ISO) has been taken over as an European Standard by Technical Committee CEN/TC 249 "Plastics", the secretariat of which is held by IBN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 1997, and conflicting national standards shall be withdrawn at the latest by August 1997.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

## Endorsement notice

The text of the International Standard ISO 9771:1995 has been approved by CEN as a European Standard without any modification.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[SIST EN ISO 9771:1999](https://standards.iteh.ai/catalog/standards/sist/7a95be6e-6315-4d0a-8cee-8afbe30776ba/sist-en-iso-9771-1999)

<https://standards.iteh.ai/catalog/standards/sist/7a95be6e-6315-4d0a-8cee-8afbe30776ba/sist-en-iso-9771-1999>

INTERNATIONAL  
STANDARD

**ISO**  
**9771**

Second edition  
1995-05-01

---

---

**Plastics — Phenolic resins —  
Determination of the pseudo-adiabatic  
temperature rise of liquid resols when  
cured under acid conditions**  
**(standards.iteh.ai)**

*Plastiques — Résines phénoliques — Détermination de l'élévation de  
température pseudoadiabatique des résols liquides thermodurcis en  
conditions acides*  
<https://standards.iteh.ai/catalog/standards/sist/7a95be6e-6315-4d0a-8cee-8afbe30776ba/sist-en-iso-9771-1999>



Reference number  
ISO 9771:1995(E)

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 9771 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 12, *Thermosetting materials*.

This second edition cancels and replaces the first edition (ISO 9771:1989), of which it constitutes a minor revision.

© ISO 1995

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization  
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

# Plastics — Phenolic resins — Determination of the pseudo-adiabatic temperature rise of liquid resols when cured under acid conditions

## 1 Scope

This International Standard specifies a method for determining the exothermic reactivity of thermo-setting liquid phenolic resins when mixed with an acid hardener under specified conditions. The results of the determination are used as a means of assessing the behaviour of the resin during processing.

## 2 Principle

A phenolic resin is mixed with an acid hardener and allowed to harden. The highest temperature reached is measured, as well as the time taken to reach this temperature.

## 3 Reagent

**3.1 Suitable acid hardener**, depending on the composition of the resin, e.g. *p*-phenol sulfonic acid, technical grade, 65 % (*m/m*) ± 1 % (*m/m*) in water.

## 4 Apparatus (see figure 1)

**4.1 Reaction vessel**: paper cup impregnated with polyethylene, with the following dimensions:

- diameter at base: about 60 mm
- diameter at rim: about 70 mm
- height: about 60 mm

**4.2 Hollow foam block**, made of phenolic-resin or polyurethane-resin foam with an apparent density of 30 kg/m<sup>3</sup> to 50 kg/m<sup>3</sup> and with a cavity to accommodate the reaction vessel (4.1).

The cavity shall be arranged so that the surface of the reaction mixture lies about 30 mm below the top edge of the foam block and so that the reaction vessel sits firmly in the foam material.

The thickness of the thermal-insulation layer between the reaction vessel and its surroundings shall be at least 60 mm.

NOTE 1 It is good practice to change the foam block periodically since wear of the block can affect the test result.

**4.3 Non-metallic cover plate**, for the foam block (4.2).

**4.4 Thermocouple**, with its hot junction immersed in glycol or other suitable liquid at the bottom of a test tube (4.7).

**4.5 Temperature recorder**.

**4.6 Pipette**, nominal capacity 10 ml.

**4.7 Test tube**, 60 mm × Ø 16 mm, containing 2 ml of glycol or other suitable liquid.

**4.8 Stirring device**: mechanical or hand stirrer.

**4.9 Balance**, accurate to 0,2 g.

Dimensions in millimetres

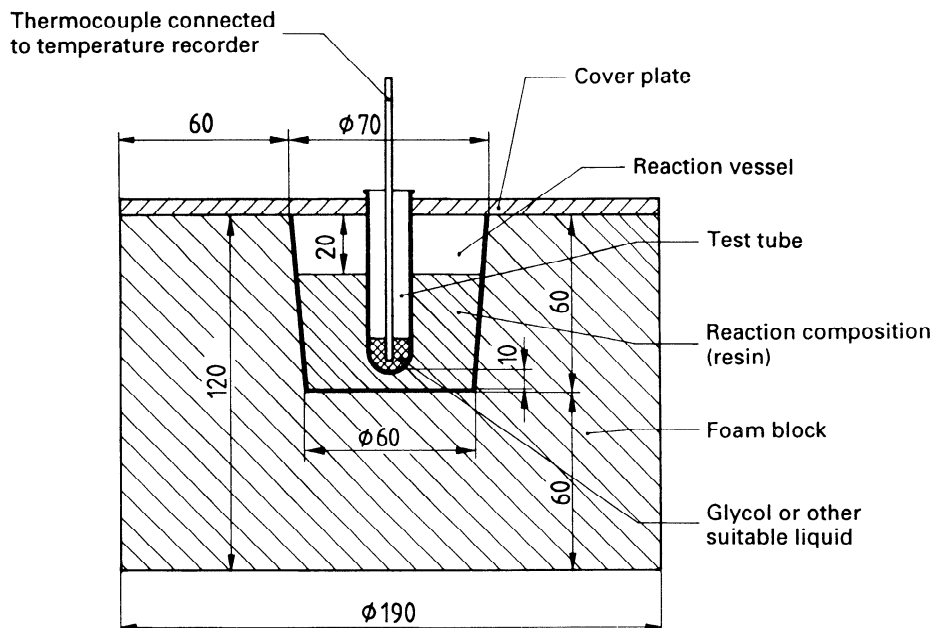


Figure 1 — Schematic diagram of apparatus

(standards.iteh.ai)

## 5 Procedure

Weigh  $100 \text{ g} \pm 0,5 \text{ g}$  of the resin sample, kept at a temperature of  $23 \text{ }^\circ\text{C} \pm 0,2 \text{ }^\circ\text{C}$ , into the reaction vessel (4.1). Condition the reaction vessel containing the test portion at  $23 \text{ }^\circ\text{C} \pm 0,2 \text{ }^\circ\text{C}$ , and place it in the foam block (4.2). Add 10 ml of hardener, also kept at  $23 \text{ }^\circ\text{C} \pm 0,2 \text{ }^\circ\text{C}$ , in one portion, using the pipette (4.6). Immediately after adding the hardener, start the temperature recorder (4.5) and mix resin and hardener thoroughly by stirring for 35 s. Other mixing times may be used if necessary, but they shall be mentioned in the test report. After mixing thoroughly, remove the stirrer and replace it by the test tube (4.7) containing the thermocouple (4.4). Lower the test tube with the thermocouple through the cover plate (4.3) so that it dips into the reaction mixture with the bottom of the test tube located in the middle of the foam block, 1 cm above the bottom of the beaker.

If a starting temperature of  $23 \text{ }^\circ\text{C}$  does not produce a distinct temperature peak, use a higher temperature for both the resin and the hardener.

If the resin is too reactive, use a smaller amount of catalyst.

By means of the temperature recorder, record

a) the maximum temperature reached;

b) the time to reach the maximum temperature.

Carry out the procedure twice.

## 6 Expression of results

### 6.1 Calculation

Calculate the mean of the measurements of maximum temperature, in degrees Celsius, and the mean of the measurements of the time, in minutes, taken to reach each maximum temperature, and report these means as the results.

If variations greater than 5 % occur, repeat the test.

### 6.2 Precision (test error)

Maximum temperature:

Repeatability:  $\pm 3 \%$

Reproducibility:  $\pm 5 \%$

Time to reach maximum temperature:

Repeatability:  $\pm 5 \%$

Reproducibility:  $\pm 5 \%$